




500 X

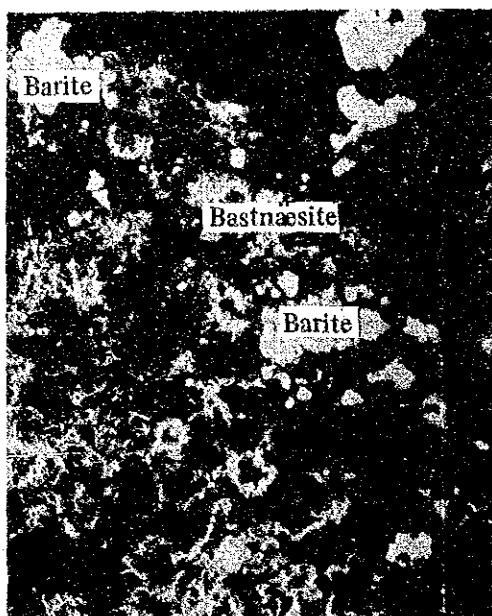

Ba-L α 700X

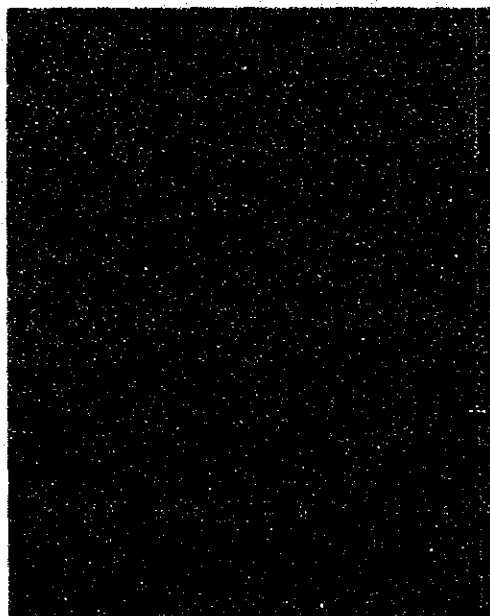

S-K α 700X

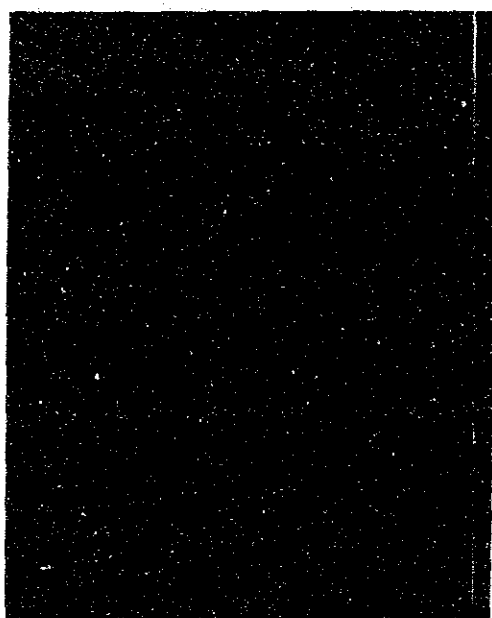

La-L α 700X



Sample No ; BR-1-E
Depth ; 38.20m
Rock type ; Carbonatite
Mineral name ; Barite, Bastnaesite

Apx. 11 X-ray Images of Minerals (EPMA Test)

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (m)	ROCK TYPE	ppm														P %	Sr ppm	BaY (GRF) ppm	Nb-YRF ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA				
KA-04	50	200	ALV	1660	29.0	782	0.9	584	96.1	7.5	55	<1	5.3	0.066	767	1480	120	1050		
KA-05	50	250	ALV	1425	23.0	656	1.0	496	81.9	5.1	55	<1	6.1	0.083	776	4010	125	810		
KA-06	50	300	ALV	2340	37.5	1220	1.7	792	131.0	11.2	95	<1	10.7	0.322	1390	6670	190	4050		
KA-07	50	350	ALV	1535	29.9	708	1.5	571	99.5	6.7	74	<1	8.2	0.253	1475	4970	160	1500		
KA-08	50	400	FCB	2250	36.4	1260	3.9	999	138.0	12.7	1245	5	25.7	0.598	2910	13280	470	375		
KB-02	100	100	ALV	1370	25.3	655	1.1	515	84.1	5.5	60	2	9.6	0.087	1160	4740	185	465		
KB-03	100	150	ALV	3170	34.7	2380	1.4	715	99.3	6.1	134	4	9.1	0.046	1390	4930	220	762		
KB-04	100	200	ALV	5660	36.3	4000	1.8	1380	161.5	13.4	88	2	6.6	0.348	1470	5600	210	105		
KB-05	100	250	ALV	1940	33.8	947	0.8	684	116.0	7.9	48	<1	4.1	0.086	2900	6490	130	1130		
KB-06	100	300	ALV	2810	41.3	1535	1.9	829	155.5	11.5	77	<1	11.0	1.430	4150	7990	240	1200		
KB-07	100	350	ALV	651	13.8	420	1.0	224	44.5	3.1	75	5	6.4	0.508	1325	2720	120	320		
KB-08	100	400	ALV	1465	27.3	704	1.0	510	94.8	6.8	134	<1	7.2	0.369	1705	5800	160	250		
KB-09	100	450	FCB	7830	63.2	6830	4.4	1650	189.0	17.7	1716	80	25.0	1.060	2910	11150	670	370		
KB-10	100	500	FCB	7860	56.7	4390	1.7	1560	145.5	6.8	779	<5	9.4	0.182	1155	6940	210	700		
KB-11	100	550	ALV	8070	31.8	7230	2.2	1110	110.0	7.8	341	18	13.1	0.157	1280	8230	220	70		
KC-02	150	100	FCB	6150	48.9	3250	2.7	2270	172.0	7.7	607	<1	13.1	0.089	793	7890	300	600		
KC-03	150	150	ALV	1905	30.1	1155	1.5	678	93.9	8.1	81	3	7.4	0.122	2120	6790	180	2300		
KC-04	150	200	ALV	2610	38.9	1320	1.2	968	120.0	7.4	125	<1	7.9	0.045	1380	5830	230	1050		
KC-05	150	250	ALV	2240	32.6	1115	0.5	899	129.0	5.9	32	2	4.7	0.861	2950	5800	140	3450		
KC-06	150	300	ALV	2720	43.6	1360	1.4	1050	160.0	9.1	37	<1	7.0	0.833	3450	5960	210	2050		
KC-07	150	350	ALV	3180	45.1	1690	1.3	1250	176.0	10.2	81	<1	10.9	0.134	2670	5290	240	1650		
KC-08	150	400	ALV	1830	41.4	896	0.9	801	132.0	8.7	166	3	6.2	0.279	2220	3950	200	610		
KC-09	150	450	ALV	3330	16.7	2800	3.0	567	59.3	5.8	265	3	12.1	0.066	834	8440	260	570		
KC-10	150	500	ALV	4680	39.8	3850	5.6	813	88.2	15.3	181	<1	23.2	0.103	1085	10690	650	200		
KD-02	200	100	FCB	6460	45.6	3240	1.8	2100	183.5	7.2	640	<1	9.0	0.068	704	24000	190	550		
KD-03	200	150	ALV	2310	40.2	1375	2.4	893	136.0	12.0	67	4	14.5	0.136	935	4420	360	750		
KD-04	200	200	ALV	1080	16.4	542	0.5	427	57.3	3.6	70	<1	2.6	0.047	3770	4260	81	72		
KD-05	200	250	ALV	3360	41.0	2020	2.5	1180	152.0	12.9	64	6	11.3	0.056	713	6880	260	780		
KD-06	200	300	ALV	3990	46.7	1950	0.3	1630	205	11.8	76	<1	5.4	0.061	716	7530	160	70		
KD-07	200	350	ALV	1390	24.0	662	0.5	441	83.4	5.4	39	2	4.1	0.085	3750	3750	115	810		
KE-08	200	400	ALV	1175	19.7	544	0.6	353	67.9	5.4	34	<1	3.4	0.032	1325	2110	87	1450		
KE-09	200	450	ALV	872	15.6	398	1.2	215	52.9	4.2	67	16	5.5	5.64	6790	6340	100	1450		
KD-10	200	500	ALV	1145	22.2	491	0.7	331	77.0	7.6	29	<1	3.8	0.080	2610	1250	115	740		
KE-01	250	50	FCB	3490	44.0	1140	1.5	1445	187.0	7.9	1741	1	6.0	0.353	1160	14990	160	1050		
KE-02	250	100	FCB	7590	37.0	5260	1.9	1195	137.0	7.5	328	<7	8.8	0.077	929	8800	180	1000		
KE-03	250	150	ALV	1600	29.0	738	1.5	523	102.5	6.6	232	<1	7.3	0.139	1510	4030	150	215		
KE-04	250	200	ALV	991	15.5	528	0.5	227	48.6	3.2	36	<1	2.4	0.040	3660	2830	65	110		
KE-05	250	250	ALV	2760	39.5	1210	0.6	744	136.5	9.7	77	5	3.8	0.070	1760	3000	145	245		
KE-06	250	300	ALV	3450	51.2	1870	0.7	907	173.0	10.0	67	<2	3.7	0.039	483	4500	130	300		
KE-07	250	350	ALV	2120	28.7	1240	1.1	549	105.0	7.4	49	6	6.2	0.037	2090	1860	170	1100		

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (m)	ROCK TYPE	ppm														P %	Sr ppm	BaY (XRF) ppm	Nb-YRF ppm
			NAA	Ba	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA	Th				
KE-06	250	400	ALV	1460	21.6	872	1.6	280	59.5	6.7	123	15	12.2	0.924	4350	6070	180	290		
KE-09	250	450	ALV	1420	24.6	715	1.2	402	86.5	5.4	64	2	6.2	0.263	2020	4840	150	300		
KE-10	250	500	FCB	96	83.2	159	1.6	485	274	13.9	3383	21	9.3	0.402	2200	9850	280	2050		
KF-01	300	50	FCB	5240	40.4	1700	1.5	2060	172.0	5.6	1142	3	9.0	0.141	1505	16280	175	570		
KF-02	300	100	FCB	1330	26.0	594	1.4	560	89.8	4.4	207	3	9.9	0.093	454	6510	135	235		
KF-03	300	150	ALV	1715	32.6	709	0.8	696	103.0	8.1	138	2	4.6	0.062	1320	6350	125	65		
KF-04	300	200	ALV	1225	25.2	550	1.0	510	83.8	8.3	45	<1	8.2	0.069	913	1560	150	260		
KF-05	300	250	ALV	1045	20.9	458	0.7	422	68.5	5.0	34	<1	4.6	0.077	4690	2650	91	380		
KF-06	300	300	ALV	1165	22.7	567	0.8	446	72.9	6.7	40	8	5.4	0.073	3320	4210	125	700		
KF-07	300	350	MTBT	202	4.9	92	0.3	90	13.9	1.3	20	<1	2.3	0.034	673	1300	34	79		
KF-08	300	400	ALV	817	24.0	422	2.9	362	63.1	12.3	159	5	20.8	0.041	3340	3610	300	710		
KF-09	300	450	ALV	1660	35.1	762	1.3	615	104.5	10.4	102	<1	9.8	0.083	2080	3970	220	31		
KF-10	300	500	FCB	1750	30.7	281	1.2	1000	107.5	9.5	744	<2	9.6	0.103	785	13140	250	29		
KG-01	350	50	FCB	8540	47.5	4440	2.1	2290	178.5	11.5	725	5	16.4	0.102	2000	17860	360	465		
KG-02	350	100	ALV	1305	26.2	578	1.2	540	81.1	6.3	89	2	7.8	0.077	1260	4930	140	99		
KG-03	350	150	ALV	2970	38.9	1410	1.0	1035	133.5	9.7	106	1	7.8	0.089	718	7420	170	2350		
KG-04	350	200	ALV	1655	30.2	795	1.0	568	94.7	8.0	54	<1	8.2	0.065	1865	6070	153	920		
KG-05	350	250	ALV	993	20.6	480	0.8	359	62.0	5.3	19	<1	6.2	1.600	4150	2420	125	320		
KG-06	350	300	ALV	4080	28.9	2770	1.1	1300	110.0	7.2	48	<4	6.6	0.290	1800	3950	135	740		
KG-07	350	350	MTBT	243	2.8	139	0.4	83	10.8	0.6	9	<1	2.2	0.100	358	790	31	57		
KG-08	350	400	ALV	1300	23.9	763	2.0	531	74.8	7.5	97	6	11.7	0.040	2260	3750	210	1500		
KG-09	350	450	ALV	620	14.5	303	0.8	302	47.3	5.1	41	<1	4.3	0.037	3960	3790	110	2350		
KG-10	350	500	ALV	1385	33.6	741	0.7	778	113.5	8.7	48	<1	6.2	0.297	1810	4620	130	2150		
KH-01	400	50	FCB	>10000	39.7	6250	3.3	1925	137.5	15.2	387	4	26.4	0.291	1275	9560	440	285		
KH-02	400	100	ALV	>10000	26.5	9840	1.8	1710	105.5	7.9	238	<3	9.8	0.052	1225	5620	290	170		
KH-03	400	150	ALV	3010	49.6	1760	1.5	1150	156.0	13.5	93	1	7.5	0.110	952	7210	240	410		
KH-04	400	200	ALV	1475	26.1	899	0.7	635	87.8	7.3	75	<1	3.7	0.188	1420	4400	120	1800		
KH-05	400	250	MTBT	337	4.5	201	0.5	98	14.1	0.9	10	<1	2.9	0.040	211	1290	34	71		
KH-06	400	300	MTBT	50	0.8	35	0.3	22	3.1	0.7	4	<1	1.4	0.024	150	1150	18	23		
KH-07	400	350	ALV	1005	19.7	485	0.5	424	64.7	4.0	35	5	3.5	0.030	1860	1610	105	790		
KH-08	400	400	ALV	1215	25.6	570	0.8	617	89.6	8.2	15	<1	4.6	0.054	3520	5060	150	170		
KH-09	400	450	ALV	773	26.2	402	1.7	378	70.7	7.5	84	4	12.8	0.068	1575	2080	230	485		
KH-10	400	500	ALV	4790	22.2	2130	1.8	1180	86.5	3.5	586	7	11.5	0.065	795	15510	240	130		
KI-02	450	100	ALV	1510	38.0	683	3.1	719	112.5	13.6	301	<1	20.6	0.102	700	3590	390	385		
KI-03	450	150	ALV	943	13.0	412	0.8	408	51.6	4.2	62	<1	4.9	0.055	1970	5830	110	170		
KI-04	450	200	ALV	1035	24.2	476	0.8	477	74.0	5.5	68	<1	5.0	0.054	802	1760	115	345		
KI-05	450	250	ALV	2420	35.5	1125	1.4	894	125.0	7.0	79	<1	7.7	0.078	1730	8470	200	780		
KI-06	450	300	ALV	1750	27.0	747	0.6	739	101.5	5.8	26	<1	4.8	0.229	3740	3610	120	25		
KI-07	450	350	ALV	1075	20.1	495	1.0	487	68.5	5.0	44	6	5.3	0.092	3180	1660	140	1350		
KI-08	450	400	ALV	1220	20.5	564	1.1	515	78.3	7.5	25	<1	5.7	0.363	3320	2080	150	465		

Apex. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (N)	ROCK TYPE	X Y		Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sr	NAA	Tb	NAA	Tb	NAA	Th	NAA	U	NAA	Yb	NAA	P	Sr	Ba	Y	(XRF)	Mo	(XRF)
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
KI-09	450	450	ALV	2990	48.2	1335	1.8	1205	150.5	11.5	262	<1	12.5	0.073	1275	5400	300	105															
KI-10	450	500	ALV	1535	44.7	147	1.0	1610	154.0	7.9	1311	6	11.8	0.047	958	21400	250	13															
KJ-02	500	100	FCB	4650	34.9	1180	1.8	1970	124.5	4.5	849	5	9.5	0.106	2890	12210	190	2150															
KJ-03	500	150	ALV	926	21.7	442	1.0	377	73.9	6.8	60	2	6.9	0.062	784	3520	135	420															
KJ-04	500	200	ALV	3310	64.6	1425	0.9	1420	237	15.1	61	2	8.9	0.060	1285	5400	220	86															
KJ-05	500	250	MTBT	1113	2.6	39	0.3	40	7.2	1.2	8	<1	2.1	0.026	185	1290	18	22															
KJ-06	500	300	ALV	1240	24.9	644	0.6	296	81.2	6.5	30	3	1.7	0.229	3550	4890	97	1700															
KJ-07	500	350	ALV	2060	36.1	1140	1.2	742	124.0	8.6	87	1	7.4	0.129	2560	4890	170	240															
KJ-08	500	400	ALV	1175	22.7	616	0.8	477	79.9	6.3	43	<1	5.9	0.070	2500	1870	150	900															
KJ-09	500	450	ALV	6820	38.3	6360	3.1	1245	316	12.7	238	<74	21.5	0.852	3710	7660	380	115															
KJ-10	500	500	ALV	2100	34.8	416	1.1	1150	153.5	6.4	1005	4	7.6	0.0874	1005	12380	185	45															
KK-02	550	100	FCB	1590	69.2	140	2.6	1350	241	15.8	2196	2	16.9	0.168	1840	14390	390	425															
KK-03	550	150	ALV	603	12.1	270	0.4	249	41.2	3.6	53	27	2.5	0.066	1150	5260	61	1400															
KK-04	550	200	ALV	2500	38.7	1285	0.7	904	140.5	7.2	222	<2	5.4	0.552	1450	5730	150	670															
KK-05	550	250	ALV	3220	54.3	1470	0.5	1355	209	10.9	41	2	5.3	0.060	1165	3570	165	550															
KK-06	550	300	ALV	1120	20.9	595	0.7	422	71.0	4.8	40	<1	4.8	1.240	4730	4810	120	700															
KK-07	550	350	ALV	1295	23.0	688	0.7	462	81.1	6.6	14	<1	4.8	1.300	6070	5050	130	1250															
KK-08	550	400	ALV	1015	22.7	478	1.0	436	81.3	7.4	83	<1	7.0	0.141	3500	1910	160	78															
KK-09	550	450	ALV	790	16.7	365	0.7	319	52.9	4.1	36	<1	5.2	0.072	4350	2930	105	120															
KK-10	550	500	ALV	2310	30.6	1285	2.1	687	91.2	10.8	330	<1	13.9	0.063	1920	6440	300	1200															
KK-02	550	100	FCB	1310	53.4	161	1.5	1690	218	10.2	1499	4	9.6	0.260	827	12610	230	450															
KK-03	550	150	ALV	1140	27.2	552	1.2	587	108.0	6.1	1482	4	5.9	0.422	1365	19740	110	385															
KK-04	550	200	ALV	2270	40.0	1060	1.3	878	129.0	10.8	75	4	10.8	0.071	769	3240	230	1900															
KK-05	550	250	ALV	1375	24.9	665	1.1	529	84.4	6.6	95	2	6.4	0.751	3090	2110	130	1000															
KK-06	550	300	ALV	1375	24.5	666	1.2	540	85.2	6.2	95	1	6.6	0.640	4180	2220	115	560															
KL-07	600	350	ALV	823	17.4	375	0.8	347	59.4	5.2	49	5	4.6	0.835	4530	3680	160	1500															
KL-06	600	400	ALV	1640	28.1	805	1.0	619	97.2	8.0	60	6	6.8	1.845	3890	3350	140	1200															
KL-09	600	450	ALV	1165	25.1	511	1.1	549	81.0	6.7	45	4	5.3	0.189	2200	6080	175	255															
KL-10	600	500	ALV	2640	38.7	1965	1.1	921	135.5	10.1	55	6	5.9	0.112	2500	6590	250	1150															
KM-02	650	100	FCB	2310	43.2	321	1.5	1750	206	8.4	1566	6	6.1	0.308	1030	19900	175	500															
KM-03	650	150	ALV	8300	26.4	6840	2.5	1135	102.5	7.2	204	2	14.0	0.214	1585	8920	240	40															
KM-04	650	200	ALV	992	17.9	508	0.7	364	60.7	5.4	42	2	4.4	0.096	1210	2460	97	340															
KM-05	650	250	FCB	3430	46.6	1645	1.3	1060	158.5	11.3	55	<1	7.2	0.104	1040	9360	230	240															
KM-06	650	300	ALV	2630	23.7	1965	1.3	579	83.9	5.8	70	<1	4.2	0.524	2410	4810	135	465															
KM-07	650	350	ALV	1065	20.6	499	0.5	383	68.9	5.6	34	<1	2.3	0.480	4990	2220	100	270															
KM-08	650	400	ALV	1415	24.0	707	0.7	498	86.6	7.4	71	<1	5.2	0.072	2030	5130	150	720															
KM-09	650	450	ALV	8890	30.4	7830	1.1	1325	100.5	9.2	161	14	10.9	0.468	2510	6310	220	130															
KM-10	650	500	ALV	911	15.7	454	0.5	300	54.1	3.0	49	<1	2.1	2.19	4420	4160	89	2700															
KN-03	700	150	FCB	585	31.3	129	1.0	728	134.5	6.7	755	1	6.8	0.404	2260	16340	170	205															
KN-04	700	200	FCB	>10000	20.1	8700	1.4	1685	90.6	2.2	360	5	9.0	0.184	1965	8530	135	145															

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDI- NATES (M)	ROCK TYPE	ppm														P %	Sr ppm	BaY (ORF) ppm	Nb-YRF ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sm	NAA	Tb	NAA				
KN-05	700	250	ALV	3420	13.1	2730	0.8	506	55.0	3.8	66	<1	3.3	0.167	770	6890	98	385		
KN-06	700	300	ALV	1815	48.4	349	1.5	1445	218	9.9	1122	1	9.8	0.135	1830	10840	240	195		
KN-07	700	350	ALV	1235	33.4	590	1.0	471	98.3	9.3	186	<1	7.0	0.116	1375	4460	210	465		
KN-08	700	400	ALV	1745	31.5	766	0.9	671	118.5	9.3	139	<1	5.0	0.085	3200	5550	185	120		
KN-09	700	450	ALV	756	13.8	379	0.5	253	43.6	3.7	34	10	2.8	0.338	3700	4410	84	700		
KO-04	750	200	FCB	3540	36.1	569	0.9	1455	163.0	5.8	534	2	7.2	0.117	1605	15670	115	1700		
LD-02	200	100	MTBT	266	4.0	115	0.3	101	15.1	1.2	19	<1	1.1	0.350	1755	2060	41	145		
LD-03	200	150	CBB	577	4.7	219	0.3	207	19.8	0.8	67	4	0.8	0.109	763	2610	42	340		
LD-04	200	200	ALV	1570	4.2	1055	0.7	306	25.4	2.1	75	41	1.5	0.212	4540	2550	82	53		
LD-05	200	250	FCB	2840	32.7	1485	2.1	745	105.0	9.0	263	8	7.9	0.312	1650	4450	230	590		
LD-06	200	300	ALV	429	4.3	293	0.3	93	10.4	0.6	11	4	0.4	0.085	3760	1820	20	105		
LD-07	200	350	ALV	759	3.2	491	0.4	179	18.4	1.2	33	15	1.0	0.253	5110	2660	42	205		
LE-01	250	50	PHN	168	<4.1	87	0.1	74	10.4	0.8	34	2	1.5	0.350	1235	670	29	380		
LE-02	250	100	PHN	155	<3.4	84	<0.1	70	9.7	0.9	37	7	1.0	0.371	1260	630	31	385		
LE-04	250	200	PHN	186	1.8	102	0.2	66	9.7	0.8	31	7	2.8	0.383	1360	770	31	380		
LE-05	250	250	FCB	2320	27.2	1280	3.2	654	91.2	8.0	268	9	14.9	0.228	935	6680	240	500		
LE-06	250	300	PHN	175	2.2	85	0.1	63	10.1	0.7	32	7	2.3	0.401	1100	4670	37	385		
LE-07	250	350	PHN	174	4.0	82	0.1	66	9.3	0.9	31	4	0.7	0.346	2300	1390	35	375		
LE-08	250	400	PHN	141	<4.5	73	0.3	56	9.2	1.0	29	1	0.8	0.362	942	1860	38	390		
LE-09	250	450	PHN	149	3.9	73	0.1	60	9.7	0.9	27	1	1.0	0.368	820	1470	33	400		
LE-10	250	500	PHN	117	0.7	70	0.2	59	8.6	0.9	31	10	1.3	0.348	991	710	25	375		
LE-12	250	600	MTBT	27	0.4	11	0.3	<11	2.5	<0.7	1	1	2.2	0.037	149	260	20	13		
LE-13	250	650	MTBT	22	<0.5	8	0.2	5	2.6	0.6	<1	<1	0.8	0.034	113	450	29	8		
LF-03	300	150	PHN	113	2.6	67	<0.1	45	8.7	0.6	30	3	0.6	0.354	725	19250	33	380		
LF-04	300	200	PHN	136	1.9	70	<0.1	60	9.0	1.0	33	8	2.7	0.345	1310	1040	34	390		
LF-05	300	250	PHN	140	1.3	66	0.3	55	8.4	0.6	31	7	0.5	0.347	1215	2280	39	385		
LF-06	300	300	PHN	136	3.0	72	0.2	56	9.4	1.0	29	5	0.9	0.362	1200	1680	34	380		
LF-07	300	350	PHN	128	2.7	68	<0.1	61	8.5	0.8	28	9	<	0.6	0.380	905	890	31	380	
LF-08	300	400	PHN	119	2.5	67	0.2	60	8.3	0.9	29	8	0.8	0.403	1635	2760	33	375		
LF-09	300	450	PHN	123	2.5	66	<0.1	73	9.3	0.9	33	5	0.9	0.391	862	890	29	385		
LF-10	300	500	FCB	89	3.6	53	1.4	30	8.4	1.5	31	<1	7.2	0.144	502	1790	92	185		
LF-11	300	550	MTBT	20	<0.5	6	0.3	14	2.3	1.0	<1	<1	1.9	0.036	134	430	20	12		
LF-12	300	600	MTBT	15	0.5	6	0.3	6	2.4	0.5	<1	<1	1.9	0.031	130	850	23	8		
LF-13	300	650	MTBT	7	0.7	9	0.3	9	2.9	0.3	<1	<1	0.6	0.036	169	270	20	10		
LG-01	350	50	PHN	104	4.3	70	0.2	56	9.8	1.2	7	<1	1.4	0.305	1760	1330	30	80		
LG-03	350	150	PHN	153	2.7	66	0.2	52	8.3	0.8	29	6	0.9	0.344	1800	870	32	375		
LG-04	350	200	PHN	178	3.3	72	0.2	56	9.8	1.1	7	<1	1.6	0.299	1365	980	30	86		
LG-05	350	250	PHN	151	2.8	69	0.1	51	8.7	1.0	28	6	1.1	0.384	1660	2040	34	370		
LG-06	350	300	PHN	153	2.9	70	0.3	56	9.2	0.8	28	6	1.1	0.401	915	730	30	385		
LG-07	350	350	PHN	161	2.8	68	0.1	57	9.6	1.0	29	7	1.7	0.373	1055	870	28	380		

Apx. 12 Results of Geochemical Analysis

SAMPLE COORDI- ROCK

NUMBER NATES(M) TYPE

X Y

LG-10 350 500 MTBT
 LG-11 350 550 FCB
 LG-12 350 600 ALV
 LG-13 350 650 ALV

Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sr	NAA	Sr	NAA	Tb	NAA	Th	NAA	U	NAA	Yb	NAA	P	%	Sr	ppm	BaY (ORF)	No-XRF	ppm	ppm
11	0.7	5	0.4	9	2.1	1.1	2	<	1	1.8	0.039	157	670	25	28														
252	10.3	125	2.0	70	20.4	6.0	130	1	11.6	0.055	569	3590	170	390															
247	3.5	121	1.2	76	12.8	2.4	56	2	6.6	0.049	305	1100	98	535															
397	9.2	207	2.2	129	22.6	3.9	100	1	12.5	0.348	514	1030	170	395															

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDI-NATES (度)	ROCK TYPE	X	Y	Ce	NAA	Eu	NAA	La	NAA	Nd	NAA	Sm	NAA	Tb	NAA	Th	NAA	U	NAA	Yb	NAA	P	Sr	BaY (ORF)	Nb-XRF
					ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
LK-13	550	650	FCB	36	10.0	26	1.4	28	20.6	5.0	52	1	10.6	0.039	211	4270	230	185								
LL-01	600	50	CBB	118	4.9	88	2.4	65	9.2	3.0	73	64	15.3	0.461	701	2010	195	520								
LL-02	600	100	ALV	688	12.1	460	3.1	194	33.9	5.6	266	13	18.8	0.708	1975	4360	240	340								
LL-03	600	150	ALV	402	8.7	322	1.8	124	21.6	3.4	119	8	12.4	0.163	983	4360	155	210								
LL-04	600	200	FCB	455	16.3	311	16.1	181	39.3	10.3	432	13	35.1	3.38	2230	6180	640	530								
LL-05	600	250	FCB	312	43.2	111	1.9	395	124.5	11.7	295	2	12.6	0.088	595	7430	290	1200								
LL-06	600	300	FCB	1535	50.0	272	1.7	1435	213	7.7	862	5	8.1	0.084	952	9030	195	235								
LL-07	600	350	FCB	3590	63.2	364	1.2	2150	247	11.7	938	20	10.6	0.164	384	15870	280	275								
LL-08	600	400	FCB	6850	23.4	6160	2.5	1390	86.6	6.1	112	22	13.9	0.831	2710	8720	430	1450								
LL-09	600	450	FCB	1580	63.7	279	2.3	1935	279	10.8	1540	9	11.4	0.175	484	16040	290	78								
LL-10	600	500	FCB	2400	17.3	769	0.6	993	74.6	2.1	334	19	2.8	0.108	1400	12500	63	46								
LL-11	600	550	FCB	20	14.8	107	0.8	128	45.7	2.8	436	8	3.6	0.114	233	13460	100	41								
LL-12	600	600	FCB	644	53.7	213	0.9	347	168.0	10.4	1926	5	6.1	0.054	245	8340	210	280								
LL-13	600	650	FCB	952	48.6	127	0.8	1540	180.5	6.7	1526	6	5.4	0.116	862	12960	185	15								
LM-02	650	100	CBB	353	21.9	192	2.1	239	62.7	7.3	209	2	14.3	0.047	1835	10460	380	830								
LM-04	650	200	FCB	246	7.3	124	1.2	95	18.6	2.6	179	4	7.0	0.030	443	6390	125	630								
LM-05	650	250	FCB	379	24.5	209	1.9	222	70.6	8.4	193	5	13.1	0.041	1155	6740	280	1250								
LM-06	650	300	FCB	1475	29.2	363	2.2	541	85.3	8.9	134	17	10.2	1.460	1320	22900	430	4550								
LM-07	650	350	FCB	245	4.3	197	0.7	86	10.6	1.7	9	14	3.0	0.217	418	6620	84	1090								
LM-08	650	400	FCB	1270	19.6	238	1.3	878	84.0	3.6	541	11	7.1	0.168	4790	13280	230	53								
LN-01	700	50	CBB	412	19.0	224	2.2	168	43.5	8.0	581	4	14.1	0.154	573	5870	360	600								
LN-02	700	100	FCB	118	3.3	59	0.9	41	7.5	1.4	68	11	5.7	0.226	511	1710	74	670								
LN-03	700	150	FCB	371	58.7	137	2.7	496	147.0	17.9	748	3	17.1	0.054	1330	5650	430	1150								
LN-04	700	200	FCB	860	44.5	104	6.3	915	131.5	14.4	306	7	38.2	0.031	3330	9360	640	530								
LN-06	700	300	FCB	2220	35.8	517	1.5	1550	136.5	4.7	560	9	8.7	0.048	385	9060	135	56								
LN-07	700	350	FCB	2820	44.2	625	1.7	1635	155.5	8.1	564	12	11.7	0.036	909	10610	310	115								
LN-08	700	400	FCB	2610	57.8	977	1.8	2680	236	8.3	1415	5	11.7	0.030	3030	17670	230	110								
LO-02	750	100	FCB	3200	40.8	1770	1.9	1195	143.5	8.8	466	<	2	12.5	0.030	932	8430	310	460							
LO-03	750	150	FCB	345	24.0	229	3.9	253	57.0	10.9	212	6	27.8	0.108	5160	6710	550	345								
LO-04	750	200	FCB	364	52.7	195	4.9	638	169.0	12.3	710	5	28.3	0.043	1050	6860	540	355								
LO-06	750	300	CBB	110	14.9	81	2.4	143	34.2	7.5	57	2	16.5	0.036	6300	8390	410	440								
LO-07	750	350	FCB	426	62.1	88	1.4	777	201	13.9	351	7	9.4	0.041	358	7430	250	380								
LO-09	750	450	FCB	749	89.3	145	0.8	974	372	6.3	2927	2	3.2	0.116	639	11440	125	140								
LP-02	800	100	FCB	783	99.2	128	2.5	1225	350	22.3	1913	3	21.5	0.192	858	8780	410	210								
LP-03	800	150	FCB	600	24.3	332	2.2	284	69.8	8.8	366	7	17.1	0.075	4770	8320	330	600								
LP-04	800	200	CBB	455	16.7	192	1.9	225	52.2	5.3	170	9	14.3	0.038	635	6300	440	1450								
LP-05	800	250	ALV	299	14.2	187	2.1	182	43.5	4.7	127	6	12.0	0.037	1055	8400	300	790								
LP-07	800	350	ALV	350	17.3	217	2.0	117	39.2	8.3	386	4	14.6	0.101	773	3680	290	600								
LP-08	800	400	FCB	1360	28.1	635	1.7	577	95.1	6.8	506	5	11.8	0.048	2410	8290	270	195								

Apex. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (M)	ROCK TYPE	X		Ce ppm	NAA ppm	La ppm	NAA ppm	Lu ppm	NAA ppm	Nd ppm	NAA ppm	Sm ppm	NAA ppm	Tb ppm	NAA ppm	Th ppm	NAA ppm	U ppm	NAA ppm	Yb ppm	NAA ppm	P %	Sr ppm	Ba ppm	Y (ORP) ppm	Nb ppm	Rb ppm
LH-01	400	50	ALV		995	3.7	867	0.4	172	12.9	1.1	30	10	1.0	0.275	4660	2410	28	38									
LH-02	400	100	ALV		292	6.9	203	2.5	132	20.5	2.7	85	4	12.6	0.101	636	5450	160	380									
LH-03	400	150	PHN		136	3.4	83	0.4	77	9.0	0.8	29	6	1.6	0.372	1035	4100	36	370									
LH-07	400	350	ALV		899	12.6	643	1.9	275	46.7	4.1	258	3	10.7	0.040	733	3960	145	530									
LH-08	400	400	CB8		1360	15.0	913	2.1	409	59.8	4.3	100	8	12.3	0.091	727	3740	155	195									
LH-09	400	450	ALV		223	9.8	142	2.7	87	23.4	4.6	131	6	14.3	0.063	641	1020	210	590									
LH-10	400	500	MTBT		33	1.8	21	0.3	<5	2.6	0.9	4	<1	1.4	0.027	117	610	23	25									
LH-11	400	550	MTBT		29	1.6	19	0.3	13	3.2	0.3	7	<1	1.7	0.029	116	750	23	21									
LH-12	400	600	MTBT		13	1.5	9	0.3	6	2.1	0.2	1	<1	1.5	0.033	178	580	22	8									
LH-13	400	650	FCB		67	3.9	50	1.1	31	8.1	1.9	59	2	5.8	0.075	280	900	86	240									
LI-01	450	50	ALV		982	12.2	659	1.3	248	44.1	3.4	56	4	6.4	0.754	1920	1570	150	135									
LI-02	450	100	ALV		361	4.6	329	1.2	87	12.4	1.2	34	3	6.4	0.374	2500	1840	87	110									
LI-03	450	150	ALV		592	11.1	392	1.6	191	31.7	3.5	168	3	7.5	0.057	701	5110	135	620									
LI-04	450	200	FCB		647	48.5	112	0.7	615	202	6.9	1206	6	2.7	0.166	1020	15080	125	140									
LI-06	450	300	FCB		748	13.7	558	1.5	183	40.5	5.9	200	6	8.7	0.038	633	4340	210	670									
LI-07	450	350	FCB		815	10.3	509	2.2	266	40.1	2.6	129	7	10.7	0.070	491	2670	105	560									
LI-08	450	400	FCB		414	9.1	242	1.0	153	23.3	2.7	86	6	6.2	0.277	505	1750	105	325									
LI-10	450	500	FCB		208	10.7	131	2.6	87	23.5	5.3	214	13	16.0	0.241	730	2070	230	570									
LJ-01	500	50	ALV		877	10.4	522	1.5	270	38.7	3.6	142	11	6.9	0.183	558	1080	105	400									
LJ-02	500	100	ALV		251	14.9	165	1.9	114	33.9	5.9	48	5	12.0	0.048	1840	8090	280	510									
LJ-03	500	150	FCB		566	4.8	482	2.0	128	7.7	1.2	52	122	11.2	2.06	3800	3510	100	100									
LJ-04	500	200	FCB		1235	11.0	870	1.2	300	37.4	2.5	47	5	5.8	0.123	849	1730	90	92									
LJ-06	500	300	ALV		387	7.5	212	1.8	143	23.1	2.9	64	3	10.0	0.214	4500	3580	96	69									
LJ-07	500	350	FCB		363	19.8	246	3.3	152	47.7	8.6	263	3	20.3	0.076	623	7490	360	1300									
LJ-08	500	400	FCB		100	80.0	38	1.1	1155	337	10.9	1922	4	8.0	0.067	268	8200	175	79									
LJ-09	500	450	FCB		4340	55.4	844	1.5	2530	282	7.9	1473	<2	7.3	0.161	376	22900	210	92									
LJ-10	500	500	FCB		1340	72.1	286	1.0	1545	295	9.8	2079	12	11.8	0.061	300	11800	155	39									
LJ-13	500	650	FCB		158	16.2	39	1.7	118	35.8	7.2	109	3	12.9	0.031	666	3970	260	120									
LK-01	550	50	ALV		1295	7.4	943	0.7	317	38.7	1.4	192	12	1.6	0.549	2770	3050	50	93									
LK-02	550	100	ALV		763	21.3	498	1.0	234	52.0	6.0	205	7	6.5	0.260	1010	4650	155	460									
LK-03	550	150	CB8		1310	16.4	890	1.8	359	53.6	3.6	207	10	11.4	0.070	1065	5410	200	800									
LK-04	550	200	FCB		348	16.9	180	1.8	223	53.8	5.7	305	7	12.0	0.120	520	2500	310	590									
LK-05	550	250	CB8		1280	16.1	875	2.2	372	52.8	3.7	237	9	11.9	0.114	996	5470	150	660									
LK-06	550	300	FCB		605	6.8	396	2.7	172	26.8	2.6	118	9	14.5	0.169	553	3950	145	710									
LK-07	550	350	FCB		1120	49.4	130	0.9	1340	226	5.7	1283	7	6.8	0.050	290	12250	145	37									
LK-08	550	400	FCB		1370	47.2	160	1.2	655	205	6.9	1632	4	9.0	0.055	257	13080	160	72									
LK-09	550	450	ALV		1110	15.4	699	1.7	240	61.0	4.9	350	8	9.1	0.051	1055	6670	135	670									
LK-10	550	500	FCB		1355	20.5	706	1.2	464	72.3	4.9	145	10	6.6	0.866	931	9630	165	2700									
LK-11	550	550	FCB		1430	93.0	573	1.3	1455	339	11.5	2330	12	11.0	0.076	638	6790	440	160									
LK-12	550	600	FCB		1115	27.8	671	2.9	365	71.2	9.7	283	56	21.6	0.064	470	4580	410	1050									

Apex 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (M)	ROCK TYPE	ppm														P %	Sr ppm	Ba Y (ORF) ppm	Nb-ZRF ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA				
LP-09	800 450	FCB	222	48.5	190	1.3	179	150.0	9.6	1692	2	8.1	0.081	303	5680	175	120			
LQ-01	850 50	FCB	2120	64.0	363	0.8	1625	260	8.9	1729	8	5.5	0.079	675	15640	175	86			
LQ-02	850 100	FCB	1335	59.5	130	1.7	1340	297	12.4	1694	10	9.6	0.242	1235	13220	330	20			
LQ-03	850 150	FCB	2120	51.8	365	1.4	1140	177.0	10.3	838	8	7.3	0.061	2340	11230	280	510			
LQ-04	850 200	FCB	2750	47.8	974	1.5	1110	177.5	11.2	901	2	7.9	0.056	1430	6460	360	265			
LQ-05	850 250	FCB	5190	38.2	1875	1.2	1515	158.5	8.2	511	6	9.1	0.050	823	10100	290	35			
LQ-06	850 300	FCB	1525	36.3	491	2.2	898	164.0	8.3	848	3	17.0	0.049	1975	14800	370	10			
LQ-07	850 350	FCB	6110	55.2	3590	4.6	1165	221	15.5	595	131	35.4	0.062	1565	6340	590	210			
LQ-08	850 400	FCB	2430	55.5	356	2.1	723	199.5	11.8	1691	4	12.2	0.053	2090	7010	370	700			
LQ-09	850 450	FCB	>10000	78.1	6990	1.9	2990	278	10.0	1858	8	5.3	0.077	1360	8130	240	1450			
LQ-10	850 500	FCB	256	34.4	148	0.7	580	150.0	4.3	1024	6	4.9	0.110	362	8780	105	25			
LR-01	900 50	ALV	870	8.0	452	0.8	1270	26.3	2.5	86	9	4.3	0.799	2830	3760	85	190			
LR-02	900 100	FCB	945	85.4	135	0.8	959	353	13.3	2281	11	18.8	0.384	2290	13690	175	36			
LR-03	900 150	FCB	1080	38.1	238	0.6	962	127.0	8.5	494	10	4.3	0.080	1735	9570	240	26			
LR-04	900 200	FCB	1895	58.2	546	2.3	1085	220	14.4	965	11	15.5	0.090	2830	12040	540	420			
LR-05	900 250	FCB	473	25.5	217	1.5	244	86.1	6.6	280	8	9.8	0.039	1850	5260	300	555			
LR-06	900 300	FCB	6890	47.5	3330	3.6	1425	211	12.8	599	105	22.0	0.073	3100	14360	550	325			
LR-07	900 350	FCB	440	5.4	247	1.3	110	19.1	2.3	82	4	7.3	0.056	470	4040	120	570			
LR-08	900 400	FCB	4910	83.4	1110	1.2	1840	200	13.8	2070	91	5.8	0.110	1150	7780	220	79			
LR-09	900 450	FCB	177	3.2	87	0.5	49	10.7	13.6	26	<1	2.9	0.201	556	2270	67	190			
LR-10	900 500	FCB	165	37.2	166	1.3	223	117.0	7.9	889	<1	8.6	0.039	292	7540	175	100			
LR-11	900 550	FCB	1305	71.1	173	0.5	1245	288	9.5	1620	4	4.8	0.055	515	18720	165	20			
NA-01	100 50	ALV	2440	34.4	1230	0.9	810	132.0	7.1	88	13	4.0	0.039	3330	3380	170	2000			
NA-02	100 100	MTBT	2140	31.4	1170	0.8	654	116.5	8.1	128	6	5.7	0.030	2470	3560	175	670			
NA-03	100 150	ALV	926	12.1	420	0.5	273	46.3	3.6	15	11	2.9	0.038	3590	1030	76	200			
NA-04	100 200	ALV	543	8.0	286	0.8	191	28.2	2.9	18	29	3.1	0.342	4390	1170	80	520			
NA-05	100 250	ALV	102	1.7	58	0.2	35	6.1	0.8	9	2	1.3	0.228	448	4720	52	150			
NA-06	100 300	ALV	119	2.5	61	0.5	27	5.9	0.6	32	18	3.4	0.147	671	1460	63	465			
NA-07	100 350	ALV	83	1.7	44	0.3	29	5.9	0.6	10	3	1.5	0.217	338	1460	49	165			
NA-08	100 400	ALV	1360	8.8	878	1.1	296	34.0	2.8	91	<1	7.2	0.075	901	4610	145	115			
NA-09	100 450	ALV	1995	24.8	1235	1.7	521	82.8	7.3	93	4	11.8	0.178	3310	5250	250	155			
NB-01	200 50	ALV	1410	22.0	753	0.6	472	30.5	4.2	43	<1	3.2	0.048	2210	2290	72	35			
NB-02	200 100	ALV	94	1.3	54	<0.1	35	4.7	0.6	6	4	0.7	0.036	875	1740	13	45			
NB-03	200 150	ALV	892	14.4	422	0.5	251	46.5	4.4	36	5	3.4	0.332	4060	840	89	54			
NB-04	200 200	ALV	1090	13.4	470	0.4	214	51.6	2.9	39	42	1.7	0.049	3360	650	43	410			
NB-05	200 250	ALV	142	3.2	85	0.4	55	9.5	0.9	16	3	1.9	0.445	1020	1870	53	195			
NB-06	200 300	ALV	1950	36.7	1070	2.1	498	120.0	10.7	233	3	14.3	0.926	4960	2340	300	225			
NB-07	200 350	FCB	84	1.8	57	0.2	25	5.5	0.6	10	<1	1.4	0.142	292	2450	47	170			
NB-08	200 400	ALV	1010	17.3	598	0.8	279	63.1	5.9	83	15	4.9	1.510	5910	1990	145	390			
NB-09	200 450	ALV	3420	30.9	2710	1.7	509	112.0	9.9	82	11	9.2	0.346	2800	5880	270	435			

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDI- NATES (M)	ROCK TYPE	ppm														%		ppm		ppm			
			Co	NAA	Es	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA	Th	NAA	U	NAA	Yb	NAA	P	Sr
NB-10	200	500	FCB	6820	160.0	3670	13.4	2740	466	46.9	2426	14	78.7	0.132	984	18580	1700	1250						
NC-01	300	50	ALV	1010	13.8	550	0.6	208	49.1	3.9	29	42	3.2	0.082	2750	610	77	970						
NC-02	300	100	SOV	382	6.2	220	0.3	90	22.6	1.9	30	3	3.0	0.247	7020	960	49	31						
NC-03	300	150	ALV	893	24.8	697	3.5	249	59.3	15.4	148	35	30.9	1.845	4870	3750	710	280						
NC-04	300	200	ALV	1455	28.5	852	1.3	475	93.4	8.6	122	36	9.6	0.340	3370	4810	220	670						
NC-05	300	250	ALV	1315	22.0	387	1.1	370	74.2	7.1	20	18	7.3	0.302	2660	3600	175	540						
NC-06	300	300	ALV	1890	28.3	1070	1.1	606	108.0	8.1	23	13	8.3	0.312	3550	2260	175	315						
NC-07	300	350	ALV	9160	80.2	7780	11.8	1695	262	31.9	999	13	76.0	2.86	6540	17170	1300	890						
NC-08	300	400	FCB	6670	94.1	2800	8.2	1740	314	26.7	854	12	55.5	0.305	952	17970	1250	680						
NC-09	300	450	FCB	10830	152.5	6130	16.0	4640	451	43.5	2259	22	113.0	0.268	1140	18800	2000	1500						
NC-10	300	500	FCB	5240	233	1245	8.6	5500	769	45.7	2601	1	49.8	0.071	414	21800	1050	800						
ND-01	400	50	ALV	1305	24.9	614	1.3	551	80.1	6.6	89	5	8.9	0.695	3460	1960	180	62						
ND-02	400	100	ALV	719	17.6	228	0.7	358	60.6	4.0	99	2	4.3	0.112	3740	1080	92	44						
ND-03	400	150	ALV	1140	20.0	531	0.8	475	65.2	5.4	32	1	5.9	0.239	3940	2240	140	11						
ND-04	400	200	ALV	1985	32.4	986	0.7	851	104.0	7.8	49	6	5.3	0.057	2390	2800	150	510						
ND-05	400	250	ALV	1760	17.3	1080	1.1	561	54.7	5.0	37	6	5.4	0.273	1540	4920	125	230						
ND-06	400	300	ALV	2240	28.1	1180	1.3	540	84.1	6.8	55	11	7.7	0.797	2790	7750	190	215						
ND-07	400	350	FCB	4680	136.0	1045	2.4	4920	503	21.7	1613	<1	15.8	0.101	934	12400	450	415						
ND-08	400	400	FCB	474	31.9	162	3.3	344	75.8	11.3	510	22	23.5	0.396	1205	9520	630	700						
ND-09	400	450	FCB	513	15.2	337	1.7	259	36.0	7.1	166	<1	12.0	0.111	687	3430	330	690						
ND-10	400	500	FCB	1600	86.4	613	4.8	1255	309	21.8	1095	2	45.1	0.076	2680	8100	760	630						
NE-01	500	50	ALV	1295	17.1	584	0.4	476	57.2	4.0	24	5	2.3	0.793	3290	930	77	520						
NE-02	500	100	ALV	375	11.8	356	0.6	322	38.0	3.0	26	1	4.9	0.071	3400	430	79	8						
NE-03	500	150	CBB	1565	18.9	958	1.8	404	57.0	5.8	125	5	11.6	0.210	1365	3550	175	120						
NE-04	500	200	FCB	5830	52.4	1795	1.8	2240	203	7.1	524	5	10.2	0.079	2000	36100	180	135						
NE-05	500	250	FCB	923	11.1	483	0.7	195	34.4	2.9	22	4	4.7	0.773	1745	4250	73	345						
NE-06	500	300	FCB	15560	212	5540	10.9	5110	826	60.2	1606	<2	73.1	0.119	2080	24600	2300	1200						
NE-07	500	350	FCB	3170	41.5	2000	3.1	3740	100.5	15.5	330	51	25.2	0.057	773	18420	1400	490						
NE-08	500	400	CBB	813	23.2	324	2.6	259	64.0	8.9	290	5	17.8	0.350	871	4240	320	730						
NE-09	500	450	FCB	8530	175.0	2090	5.1	4310	540	30.0	1806	44	30.4	0.334	951	24600	800	34						
NE-10	500	500	FCB	7640	106.0	2700	3.2	2940	349	19.8	748	22	24.5	0.076	845	20100	560	70						
NF-01	600	50	ALV	1300	19.8	526	0.5	380	72.1	5.4	51	4	2.8	0.318	3810	1560	94	10						
NF-02	600	100	ALV	19470	64.9	14330	4.6	2840	234	15.3	362	44	38.0	1.040	4040	11820	520	37						
NF-03	600	150	FCB	6510	70.3	1230	1.4	3060	299	6.6	641	11	6.9	0.055	859	25000	185	49						
NF-04	600	200	FCB	535	15.2	312	4.3	97	29.5	8.9	477	37	34.0	1.510	2280	4070	640	225						
NF-05	600	250	FCB	223	6.3	80	1.3	78	16.0	3.4	22	7	8.5	0.722	2160	1580	105	150						
NF-06	600	300	FCB	3450	24.6	2240	2.4	577	73.4	9.3	222	12	19.8	0.804	3640	6030	290	960						
NF-07	600	350	FCB	3160	39.9	1860	3.0	691	115.0	15.3	339	6	21.5	0.203	4080	5210	470	33						
NF-08	600	400	CBB	165	2.6	113	0.5	52	8.9	1.3	28	1	4.7	0.080	758	1960	69	360						
NF-09	600	450	CBB	462	18.6	254	3.7	161	43.1	10.4	347	4	26.4	0.181	1330	4730	510	470						

Apex 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (N)	ROCK TYPE	X		Ce	Naa	Eu	Naa	La	Naa	Nd	Naa	Sm	Naa	Tb	Naa	Tb	Naa	U	Naa	Yb	Naa	P	Sr	Ba	Y	Nb	XRF
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
NG-01	700	50	ALV	262	4.8	190	1.3	45	12.3	1.8	11	6	7.0	0.731	2380	1630	76	250										
NG-02	700	100	ALV	1640	23.0	790	1.1	530	88.4	5.2	38	<1	5.8	0.211	4120	4380	140	1150										
NG-03	700	150	ALV	1495	26.4	709	1.2	422	72.4	7.7	43	10	7.7	0.960	3360	4050	185	360										
NG-04	700	200	ALV	823	13.2	491	4.4	200	34.8	5.9	216	11	31.7	2.20	2210	6000	430	220										
NG-05	700	250	ALV	2010	24.6	1050	0.9	562	85.6	7.2	34	10	4.1	0.057	2900	2760	150	305										
NG-06	700	300	SOV	527	11.1	240	0.3	124	23.0	3.0	5	<1	2.4	0.521	3820	510	62	18										
NG-07	700	350	ALV	189	3.6	90	0.6	58	9.6	1.0	34	10	4.2	0.096	829	820	71	263										
NG-08	700	400	ALV	101	2.5	64	0.3	34	5.1	0.6	43	11	2.7	0.088	931	1600	57	305										
NH-01	800	50	CB8	1965	29.6	949	1.1	598	96.1	7.1	33	<1	5.4	0.337	3810	4710	135	700										
NH-02	800	100	CB8	1300	15.5	776	1.0	349	57.4	6.4	79	4	6.6	0.339	1840	2940	170	260										
NH-03	800	150	ALV	734	15.0	350	0.7	236	39.9	5.1	10	49	2.9	0.849	2820	2570	110	430										
NH-04	800	200	ALV	910	12.6	450	0.6	272	40.2	3.9	7	38	3.4	0.728	1915	4330	77	220										
NH-05	800	250	ALV	1580	23.0	815	1.4	463	76.0	8.0	36	<1	7.8	0.447	3990	4960	180	1050										
NH-06	800	300	ALV	801	13.4	397	0.6	259	46.2	2.9	6	4	3.1	0.776	3070	4290	80	35										
NH-07	800	350	ALV	1505	18.7	703	0.9	412	66.7	3.6	55	1	5.4	0.123	3330	4790	110	990										
NH-08	800	400	ALV	1495	18.9	660	0.5	235	51.4	3.1	23	4	2.9	0.044	3480	4040	75	2650										
NI-01	900	50	ALV	803	11.2	384	1.0	172	38.6	2.8	24	<1	6.7	0.325	4380	2210	83	175										
NI-02	900	100	ALV	3540	20.8	2110	1.6	481	81.3	3.3	95	<2	7.9	0.035	1330	4010	140	265										
NI-03	900	150	ALV	694	11.4	322	0.7	147	33.7	2.5	37	42	4.8	0.520	3320	3690	87	425										
NI-04	900	200	ALV	1145	17.7	562	2.0	178	52.8	6.1	86	1	11.6	0.061	1245	5460	220	64										
NI-05	900	250	ALV	306	10.0	230	0.7	83	26.1	4.6	16	1	4.2	0.070	1205	4480	78	125										
NI-06	900	300	ALV	2170	25.4	1015	0.6	408	86.6	5.4	17	4	2.4	0.037	2460	2900	96	190										
NI-07	900	350	ALV	1390	26.7	635	1.3	296	82.2	8.3	99	2	6.7	0.046	1860	3910	195	41										
RA-01	100	50	MTBT	172	4.6	95	0.3	43	11.6	1.7	18	<1	1.8	0.227	266	790	80	235										
RA-02	100	100	MTBT	214	3.3	125	0.6	36	11.2	1.6	36	<1	2.9	0.014	776	900	44	215										
RA-03	100	150	ALV	1025	13.6	601	1.4	183	41.6	4.0	86	7	7.8	0.158	2990	2530	140	255										
RA-04	100	200	MTBT	20	1.3	11	0.5	7	3.5	0.6	10	<1	3.4	0.019	534	620	46	100										
RA-05	100	250	ALV	1005	12.6	502	1.2	185	43.8	2.9	39	11	5.8	0.305	3670	1600	82	385										
RA-06	100	300	MTBT	12	1.1	8	0.3	7	2.4	<0.8	<1	<1	1.7	0.030	214	480	21	7										
RA-07	100	350	FCB	3030	30.8	1910	2.5	608	95.5	9.9	223	10	16.4	0.228	4790	2710	380	240										
RA-08	100	400	FCB	2240	17.5	1390	1.3	368	54.5	5.9	99	7	10.2	0.118	1875	5240	260	150										
RA-09	100	450	ALV	5030	40.1	3400	2.5	903	133.5	13.2	339	3	17.2	0.111	2850	7840	490	59										
RA-10	100	500	ALV	4320	30.3	2940	1.5	760	100.5	7.9	240	8	10.8	0.055	3590	4000	280	160										
RA-11	100	550	ALV	603	16.2	356	1.8	135	28.3	8.8	106	21	13.9	1.115	1925	2560	300	845										
RA-12	100	600	FCB	8980	86.3	6130	5.8	1770	280	29.9	501	4	51.7	0.173	3790	12660	1100	90										
RA-13	100	650	FCB	7190	68.4	4960	4.5	1525	213	24.7	557	14	34.7	0.224	2810	11960	860	150										
RB-01	200	50	ALV	190	1.9	128	0.4	40	6.6	0.6	12	2	2.3	0.025	384	850	51	54										
RB-02	200	100	FCB	2670	26.7	1715	1.2	626	95.5	6.8	140	9	7.2	0.165	895	5150	175	395										
RB-03	200	150	FCB	5540	50.8	3740	2.2	798	125.0	15.0	941	4	24.1	0.094	2960	5950	520	170										
RB-04	200	200	FCB	>10000	102.0	7200	6.0	1865	341	35.6	668	15	48.2	0.161	4080	9770	1000	125										

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDI-NATES (M)	ROCK TYPE	ppm														P %	Sr ppm	BaY (ORF) ppm	Nb-YRF ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sm	NAA	Tb	NAA				
RB-05	200 250	FCB	300	4.2	166	0.4	68	12.3	1.2	23	6	1.7	0.413	680	830	51	200			
RB-06	200 300	ALV	4110	32.9	3070	2.0	794	106.0	10.6	302	10	15.3	0.069	4030	300	460	65			
RB-07	200 350	FCB	6170	53.8	3810	4.1	1100	164.5	16.7	318	6	30.8	0.162	3010	4440	830	97			
RB-08	200 400	FCB	5340	44.9	4080	3.8	1280	163.0	12.8	282	6	19.2	0.114	4470	7180	580	110			
RB-09	200 450	FCB	3870	35.2	2380	2.3	745	110.5	11.4	280	12	15.9	0.214	3050	3230	460	315			
RB-10	200 500	FCB	6270	55.9	4550	2.9	1575	196.5	15.1	345	8	18.2	0.099	3010	12480	560	165			
RB-11	200 550	FCB	5340	64.0	3540	4.5	1345	214	17.7	364	3	29.0	0.078	2060	10250	660	135			
RB-12	200 600	FCB	4780	45.8	3190	2.7	1050	164.0	14.3	597	13	12.8	0.064	3000	24000	400	82			
RB-13	200 650	ALV	>10000	39.5	7960	1.9	2030	177.0	6.1	501	47	8.4	0.185	2120	11180	185	420			
RB-14	200 700	ALV	>10000	54.2	>10000	3.0	1760	147.0	5.3	544	63	19.0	0.896	2750	10810	430	155			
RC-02	300 100	ALV	1520	18.3	784	2.0	340	32.6	6.2	51	247	22.5	2.69	3910	5020	270	1850			
RC-03	300 150	FCB	532	2.8	333	0.4	96	7.7	1.2	16	16	3.2	0.043	3450	4520	47	810			
RC-04	300 200	FCB	8320	88.5	5560	2.7	1740	293	29.5	475	5	21.7	0.448	5450	5950	770	6			
RC-05	300 250	FCB	8400	77.6	5740	2.2	870	125.5	21.1	441	8	26.3	0.126	3590	10470	780	87			
RC-06	300 300	FCB	5310	51.9	3830	2.4	1055	153.0	11.9	293	4	14.9	0.106	2860	5860	480	135			
RC-07	300 350	FCB	6150	47.4	4140	2.1	1375	176.0	14.3	411	3	13.7	0.082	2680	4800	440	105			
RC-08	300 400	ALV	509	9.2	263	0.6	164	27.4	3.2	41	15	4.1	0.351	10070	5060	63	650			
RC-09	300 450	ALV	1075	13.6	633	0.7	283	46.6	3.8	41	3	5.3	0.184	2100	2180	105	60			
RC-10	300 500	ALV	1425	11.6	870	0.3	358	36.6	3.1	59	31	3.5	0.342	2110	4440	95	1800			
RC-11	300 550	FCB	4260	47.8	2860	2.7	1190	176.5	13.8	346	11	20.2	0.060	3160	5410	420	285			
RC-12	300 600	ALV	1040	18.4	496	1.3	224	36.7	9.1	165	29	14.6	0.104	3470	4290	260	195			
RC-13	300 650	ALV	1020	20.3	492	1.1	220	33.5	7.7	113	26	12.3	0.643	3830	4050	230	225			
RC-14	300 700	FCB	8640	53.7	5140	3.5	1980	182.0	14.0	355	3	22.3	1.855	6970	14020	360	63			
RC-15	300 750	FCB	3000	27.6	2100	1.8	752	98.4	8.7	230	9	10.9	0.094	1905	9000	310	120			
RD-01	400 50	ALV	1055	14.3	564	0.8	274	29.5	3.2	29	80	4.5	0.449	3940	1750	84	1450			
RD-02	400 100	ALV	2820	26.0	1915	0.6	535	47.4	8.8	231	3	6.7	0.038	3710	2940	175	91			
RD-03	400 150	ALV	4560	35.3	3190	0.7	1040	111.5	6.0	357	13	5.2	0.074	3130	2520	140	81			
RD-04	400 200	ALV	752	25.4	341	2.1	205	57.4	11.4	231	10	17.7	3.12	7110	4150	290	73			
RD-05	400 250	ALV	838	11.7	403	0.2	244	31.8	3.1	14	14	2.3	0.585	3040	1710	63	170			
RD-06	400 300	ALV	1035	10.6	571	1.0	122	19.7	4.8	277	2	12.8	0.681	5640	3550	270	< 5			
RD-07	400 350	ALV	517	6.2	228	0.3	138	19.3	2.3	32	3	2.8	0.287	2330	940	78	42			
RD-08	400 400	ALV	389	5.6	183	0.1	125	17.8	1.7	5	2	1.7	0.161	2120	870	40	31			
RD-09	400 450	ALV	627	7.2	480	0.7	168	25.8	3.1	59	< 1	5.2	0.226	3780	3680	230	6			
RD-10	400 500	ALV	1115	30.5	572	2.9	350	50.1	14.2	350	22	18.6	0.463	2170	5440	400	365			
RD-11	400 550	ALV	963	12.7	584	0.8	293	46.0	3.1	40	16	6.0	0.556	3850	3050	105	340			
RD-12	400 600	ALV	363	4.4	268	0.9	82	13.0	1.2	14	1	4.9	0.256	4000	4590	70	130			
RD-13	400 650	ALV	2030	20.8	1310	1.2	534	74.6	5.0	91	23	6.9	0.224	3140	1440	140	830			
RD-14	400 700	FCB	4890	52.6	3870	1.4	1005	170.0	15.9	372	3	11.7	0.156	5600	4510	440	72			
RD-15	400 750	FCB	769	4.6	616	1.3	172	21.0	2.3	32	3	7.1	0.650	4630	4310	105	49			
RD-16	400 800	ALV	1445	21.1	805	0.2	496	74.5	3.3	40	2	1.8	0.082	2060	1410	75	215			

Apex 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (N, E)	ROCK TYPE	ELEMENTS (ppm)														Sr ppm	BaY (XRF) No-XRF ppm				
			Ce	Nb	Eu	Nb	La	La	Ni	Nb	Sm	Nb	Tb	Nb	Th	Nb		U	Nb	Yb	Nb	P %
RE-01	500 50	ALV	1780	25.0	1000	1.2	410	68.7	7.3	64	1	10.3	0.330	4680	4140	190	55					
RE-02	500 100	ALV	550	7.8	287	0.6	165	26.1	2.1	92	11	3.3	0.068	2930	2050	83	145					
RE-03	500 150	ALV	470	7.7	283	0.4	169	27.3	2.2	31	6	2.8	0.316	2250	2340	80	90					
RE-04	500 200	ALV	948	11.6	503	0.3	296	43.5	3.0	11	5	2.6	0.430	2510	1060	63	110					
RE-05	500 250	ALV	501	6.6	306	0.1	153	26.0	1.9	15	14	1.6	0.319	3250	4450	55	175					
RE-06	500 300	ALV	648	7.7	292	0.3	178	28.6	2.2	15	<1	2.0	0.100	2600	3710	60	12					
RE-07	500 350	ALV	618	10.4	323	0.3	216	32.3	1.9	4	12	1.3	0.153	3590	3720	64	390					
RE-08	500 400	ALV	857	10.3	374	0.3	241	37.2	2.6	11	3	2.3	0.182	2450	1760	59	270					
RE-09	500 450	ALV	599	7.7	341	0.8	203	28.2	1.7	22	10	4.3	0.364	693	670	62	321					
RE-10	500 500	ALV	263	4.9	191	0.3	116	17.0	1.2	8	11	2.7	0.159	1380	760	42	145					
RE-11	500 550	ALV	>10000	43.5	>10000	4.4	2320	171.0	12.4	172	16	27.7	0.843	2110	10280	450	48					
RE-12	500 600	FCB	>10000	32.1	>10000	3.0	2740	145.5	5.2	183	27	16.7	1.770	2840	8750	270	165					
RE-13	500 650	ALV	943	8.3	639	0.4	228	30.5	2.0	6	10	1.8	0.271	3070	2120	58	145					
RE-14	500 700	ALV	798	9.3	546	1.2	216	33.7	2.3	44	1	6.3	0.391	1530	2610	155	335					
RE-15	500 750	ALV	928	15.9	461	0.7	314	52.4	4.4	52	54	4.7	0.946	2890	910	120	870					
RE-16	500 800	ALV	1150	50.7	655	1.2	361	114.5	17.0	17	17	9.5	0.953	4080	4210	250	680					
RE-17	500 850	ALV	1140	18.5	571	0.6	427	66.1	5.1	19	2	3.2	0.160	4080	1330	110	370					
RF-01	600 50	SOV	416	5.8	229	0.9	124	19.9	1.6	6	25	5.2	1.150	7310	2410	54	98					
RF-02	600 100	ALV	762	11.3	397	0.5	250	36.6	3.2	62	17	3.6	0.052	3310	1830	61	205					
RF-03	600 150	FCB	1665	17.0	1225	2.1	458	59.1	5.4	135	2	13.1	0.176	2670	5330	220	125					
RF-04	600 200	ALV	679	10.3	404	0.8	277	38.6	3.4	62	1	8.6	0.042	3470	920	130	29					
RF-05	600 250	ALV	1030	8.1	522	0.5	327	33.7	1.8	182	1	3.7	0.232	2300	470	56	31					
RF-06	600 300	ALV	764	9.3	444	0.3	282	36.5	2.2	54	1	2.3	0.087	5260	830	72	43					
RF-07	600 350	ALV	694	7.6	392	0.4	247	29.5	1.7	27	1	3.1	0.052	3770	2610	63	84					
RF-08	600 400	ALV	613	6.1	403	1.4	239	27.5	1.8	102	<1	8.6	0.058	3900	850	85	32					
RF-09	600 450	ALV	379	5.1	211	0.3	151	19.9	1.0	22	2	1.8	0.344	3950	1020	39	31					
RF-10	600 500	ALV	436	8.9	235	0.5	194	29.9	3.2	25	1	4.2	0.161	2260	730	99	20					
RF-11	600 550	ALV	662	9.2	368	0.5	254	34.0	2.1	28	7	2.3	0.248	854	550	80	600					
RF-12	600 600	ALV	1960	22.4	1690	1.4	636	79.8	5.7	239	1	10.4	0.109	1365	7180	210	81					
RF-13	600 650	FCB	451	5.9	260	0.3	186	24.5	1.7	20	8	1.9	0.310	922	540	45	73					
RF-14	600 700	ALV	1295	16.8	688	0.8	490	65.0	3.5	10	1	5.5	0.166	2340	3190	86	36					
RF-15	600 750	ALV	1355	26.1	699	1.1	671	96.2	8.3	22	4	8.5	0.556	2030	3710	210	20					
RF-16	600 800	FCB	5870	46.7	4310	1.8	1475	162.0	12.4	281	6	10.9	0.040	3220	7190	290	10					
RF-17	600 850	CBB	2360	18.5	1845	1.6	646	65.1	4.8	78	8	9.6	0.195	4880	3230	175	425					
RF-18	600 900	CBB	291	3.6	239	0.3	83	13.3	1.2	23	1	1.7	0.102	545	4830	38	100					
RG-01	700 50	ALV	3250	17.6	2450	1.7	519	61.0	5.4	239	2	12.2	0.042	2450	5610	320	96					
RG-02	700 100	ALV	513	7.7	221	0.8	136	22.7	2.6	54	3	5.1	0.251	3320	580	98	98					
RG-03	700 150	ALV	352	9.2	273	0.7	203	30.9	2.8	68	5	5.1	0.290	3760	570	83	49					
RG-04	700 200	ALV	593	8.1	200	0.6	151	25.3	2.7	57	3	4.0	0.385	3130	540	71	325					
RG-05	700 250	SOV	432	5.4	210	0.6	114	16.7	1.5	10	1	3.7	0.467	8020	850	57	21					

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (N)	ROCK TYPE	X		Y		Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sm	NAA	Tb	NAA	Th	NAA	U	NAA	Yb	NAA	P	Sr	Ba	Y	(XRF)	Nb	(XRF)
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
RG-06	700 300	MTBT	152	4.6	115	0.8	57	11.3	1.8	1.8	1.8	18	1	4.2	0.094	477	1380	67	28														
RG-07	700 350	ALV	984	16.9	468	0.8	287	47.9	5.6	4.4	44	1	5.3	0.067	2920	1230	130	175															
RG-08	700 400	ALV	1495	15.7	526	1.0	313	46.7	4.9	4.2	42	2	6.9	0.311	3410	1090	110	440															
RG-09	700 450	ALV	1190	19.9	465	0.4	328	57.7	6.2	6.2	62	1	3.0	0.174	3800	970	110	690															
RG-10	700 500	ALV	758	10.3	408	0.4	239	34.2	2.4	2.4	51	1	1.8	0.076	2930	700	61	143															
RG-11	700 550	SOV	376	9.0	240	0.5	167	27.7	2.7	2.7	8	3	4.6	0.899	4160	410	71	60															
RG-12	700 600	ALV	1085	13.3	382	0.7	283	44.9	4.4	16	16	3	4.5	0.442	2920	660	100	44															
RG-13	700 650	ALV	1185	16.7	492	1.8	338	46.8	6.0	6.2	62	68	13.1	1.380	2090	220	1400																
RG-14	700 700	ALV	3230	33.6	1840	1.4	671	98.3	7.5	264	6	6	6.7	0.371	1525	2420	155	260															
RG-15	700 750	ALV	907	20.2	408	0.8	341	68.6	5.7	64	7	7	6.0	0.474	2400	500	125	26															
RG-16	700 800	ALV	1175	21.8	568	1.0	405	69.9	6.5	27	11	11	6.1	0.463	4660	850	130	255															
RG-17	700 850	ALV	1400	23.3	649	1.1	507	78.3	6.7	36	45	45	6.9	0.160	2590	5070	155	600															
RG-18	700 900	ALV	4760	41.4	3250	1.0	1085	152.5	8.4	341	2	2	6.6	0.079	840	4650	185	44															
RG-19	700 950	ALV	1500	15.6	880	1.1	386	55.9	4.0	73	17	17	5.8	0.370	5150	3660	135	400															
RH-01	800 50	ALV	627	9.1	316	0.5	188	31.6	3.3	3.3	20	3.4	0.422	2950	760	85	310																
RH-02	800 100	ALV	406	5.7	179	0.3	124	21.4	1.5	25	4	4	2.0	0.198	2680	510	48	46															
RH-03	800 150	ALV	1780	18.8	1020	1.4	432	73.1	6.4	172	10	10	7.9	0.307	2370	2000	185	465															
RH-04	800 200	ALV	631	10.6	305	0.5	197	37.8	3.4	9	2	2	3.0	0.460	3030	980	80	48															
RH-05	800 250	ALV	1110	18.0	528	1.0	351	59.8	5.5	79	2	2	6.5	0.337	3140	990	135	720															
RH-06	800 300	ALV	636	12.7	307	0.7	212	40.9	4.0	24	5	5	4.5	0.104	3570	1450	105	210															
RH-07	800 350	ALV	918	13.9	429	0.8	289	51.5	4.4	5	5	5	6.5	0.634	2560	950	110	81															
RH-08	800 400	ALV	889	14.4	539	0.5	299	53.0	5.0	11	11	11	3.7	0.176	3690	1080	96	690															
RH-09	800 450	ALV	347	5.7	159	0.3	107	20.5	1.7	2	2	2	1.8	0.240	1840	310	43	35															
RH-10	800 500	ALV	826	10.0	338	0.4	220	36.3	2.6	35	35	35	2.8	0.121	4120	690	83	96															
RH-11	800 550	SOV	362	5.3	185	0.6	110	19.1	1.6	5	5	5	3.4	0.246	7080	660	46	10															
RH-12	800 600	SOV	467	6.7	242	0.6	139	24.7	1.8	5	5	5	2.8	0.814	7720	1340	53	63															
RH-13	800 650	ALV	2380	15.2	1995	1.5	335	51.5	3.8	97	1	1	10.2	1.930	2650	3330	170	14															
RH-14	800 700	ALV	1575	24.7	735	0.6	551	94.7	5.6	17	6	6	4.9	0.261	2960	4960	105	450															
RH-15	800 750	ALV	2270	34.6	1155	0.9	680	132.5	5.1	41	15	15	3.8	0.069	2180	5270	95	222															
RH-16	800 800	ALV	2610	38.7	1245	0.9	893	142.0	9.1	84	5	5	8.1	0.114	2350	5260	130	1490															
RH-17	800 850	ALV	2890	31.3	1650	1.5	525	107.5	7.7	80	26	26	9.4	0.222	2840	5470	240	780															
RH-18	800 900	ALV	>10000	65.3	8720	2.5	3910	269	8.9	394	19	19	5.6	0.108	11540	12530	270	462															
RH-19	800 950	ALV	9680	32.8	8400	6.2	1255	101.0	11.2	243	7	7	29.1	0.806	12180	7910	500	145															
RH-20	800 1000	ALV	1765	20.6	1120	6.0	341	79.9	9.3	249	16	16	40.8	3.08	5380	8630	600	305															
RI-01	900 50	ALV	512	5.9	323	0.6	144	21.3	1.9	17	17	17	3.4	0.372	3700	770	61	14															
RI-02	900 100	ALV	469	6.2	237	0.4	134	23.0	2.2	14	4	4	2.1	0.305	4350	940	46	33															
RI-03	900 150	FCB	381	7.3	304	0.8	71	22.3	2.9	38	3	3	5.0	0.034	1680	6510	76	71															
RI-05	900 250	ALV	2360	31.7	1290	1.3	731	118.5	8.6	36	10	10	8.9	0.503	3280	3470	180	16															
RI-07	900 350	ALV	490	7.3	267	0.7	133	26.1	2.3	67	67	67	4.8	0.443	5920	880	76	58															
RI-08	900 400	ALV	1145	16.3	605	1.2	336	57.7	4.9	19	19	19	6.8	0.492	2130	980	135	120															

Apx. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (M)		ROCK TYPE	ELEMENTS (ppm)														P %	Sr ppm	BaY (ORF) Nb-YRF ppm	
	X	Y		Ce	NAA	Eu	NAA	La	NAA	Li	NAA	Mg	NAA	Sn	NAA	Tb	NAA			Th	NAA
RI-09	900	450	ALV	587	8.4	310	0.4	184	30.2	3.2	9	6	2.8	0.243	3220	1080	67	300			
RI-10	900	500	ALV	507	8.1	294	1.1	166	26.6	2.8	26	2	6.1	0.304	2950	810	88	100			
RI-11	900	550	ALV	384	5.4	204	0.9	128	20.4	1.5	29	<1	6.5	0.177	2900	500	75	29			
RI-12	900	600	ALV	624	11.3	385	0.3	213	37.4	3.3	15	<1	2.0	0.120	2530	830	67	22			
RI-13	900	650	ALV	1190	13.2	714	0.7	333	49.2	3.4	36	<1	4.6	0.601	2380	1610	110	6			
RI-14	900	700	ALV	240	6.2	136	1.6	78	16.2	2.6	25	3	9.6	0.077	2830	2570	105	510			
RI-15	900	750	ALV	1040	20.6	466	0.8	422	68.4	5.2	22	15	3.5	0.455	3180	490	105	1300			
RI-16	900	800	ALV	1650	19.6	911	0.9	532	72.2	3.9	67	13	5.0	0.284	2950	1190	110	550			
RI-17	900	850	ALV	1400	22.9	665	0.7	490	82.6	6.3	52	6	2.7	0.248	3090	940	125	395			
RI-18	900	900	ALV	1155	14.3	601	0.5	353	54.8	3.3	31	9	2.4	0.151	3070	2310	79	365			
RI-19	900	950	ALV	1555	28.2	749	1.1	542	90.1	9.1	69	15	5.8	0.445	3610	3420	170	1550			
RI-20	900	1000	ALV	1330	18.0	848	1.1	395	62.1	5.8	95	19	6.4	0.258	3550	2660	160	465			
RI-21	900	1050	ALV	1115	16.6	684	0.5	317	47.2	4.8	24	54	3.0	0.258	3040	4010	105	620			

Apex. 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDI-NATES (M)	ROCK TYPE	ppm														P %	Sr ppm	Ba Y (XRF) ppm	Nb-Zr (XRF) ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA				
SA-01	100	50	FCB	1150	30.2	360	3.0	465	92.9	10.6	146	5	21.4	0.038	184	8030	310	55		
SA-02	100	100	FCB	3510	50.7	913	1.2	1645	197.0	9.3	696	12	11.9	0.041	732	6840	260	34		
SA-03	100	150	FCB	5120	54.2	1915	1.1	1530	196.5	7.2	646	9	8.0	0.044	487	7060	250	52		
SA-04	100	200	FCB	5910	47.5	1740	0.7	2110	221	3.6	436	10	2.6	0.258	751	8270	97	8		
SA-05	100	250	FCB	7710	70.4	5500	6.2	1540	230	22.0	456	13	41.1	0.215	2280	9440	700	115		
SA-06	100	300	ALV	2120	26.2	945	0.6	593	93.4	6.4	42	3	3.6	1.520	4400	5620	125	2750		
SA-07	100	350	ALV	1700	18.6	857	0.2	510	70.8	3.6	25	2	1.7	0.209	3150	1950	75	87		
SA-08	100	400	FCB	1925	7.3	922	0.7	484	37.8	1.8	84	2	4.6	0.029	355	9450	43	26		
SA-09	100	450	FCB	5830	56.4	4150	3.3	1175	158.0	14.0	691	3	20.6	0.140	2450	9230	640	46		
SA-10	100	500	MTBT	121	1.3	57	0.3	33	4.9	0.4	9	2	1.9	0.031	202	1070	22	17		
SB-01	200	50	FCB	5600	99.5	1320	2.8	2860	337	16.6	1813	6	18.8	0.022	403	10510	520	< 5		
SB-02	200	100	FCB	1585	59.8	219	1.2	1565	230	9.5	685	3	11.2	0.022	439	7070	250	< 5		
SB-03	200	150	FCB	251	159.5	100	0.6	1830	523	20.0	2088	<	2	5.3	0.172	794	6850	320	7	
SB-04	200	200	FCB	1925	28.0	603	1.2	804	108.0	4.2	283	5	5.4	0.029	268	10000	98	11		
SB-05	200	250	FCB	4730	75.0	2070	1.2	1275	201	10.4	1029	<	5	4.9	0.028	962	5550	135	8	
SB-06	200	300	ALV	2230	28.7	985	0.3	701	101.5	6.9	23	9	2.3	0.426	4390	5560	110	730		
SB-07	200	350	CBF	253	4.6	118	0.4	99	14.5	1.2	45	<	1	2.2	0.039	200	2200	45	200	
SB-08	200	400	CBF	382	7.0	203	1.2	112	19.0	2.9	67	5	7.2	0.715	855	3130	110	200		
SB-09	200	450	FCB	1545	20.6	800	0.4	498	79.8	2.8	205	4	1.3	0.039	470	5880	40	145		
SB-10	200	500	ALV	1415	50.0	811	1.3	414	112.5	19.4	759	10	8.6	0.773	964	5060	340	580		
SB-10	200	500	ALV	1570	49.3	868	1.6	590	114.0	18.5	661	19	10.3	0.880	1150	4020	310	600		
SC-01	300	50	FCB	924	77.4	159	0.5	1935	319	7.1	1452	4	4.1	0.034	379	5940	100	125		
SC-02	300	100	ALV	1220	18.9	639	0.9	401	54.9	5.2	219	15	3.3	0.376	1015	6370	125	1000		
SC-03	300	150	FCB	686	20.9	302	2.5	246	49.8	10.2	90	9	15.9	0.470	773	4700	310	780		
SC-04	300	200	FCB	6480	32.4	2560	0.2	1695	154.0	4.3	264	11	<	1.5	0.043	413	16660	80	29	
SC-05	300	250	FCB	223	8.1	86	0.4	132	25.0	1.7	74	5	2.2	0.045	390	6590	46	17		
SC-06	300	300	FCB	5190	46.8	3530	2.6	1220	151.0	10.2	341	3	11.3	0.273	1365	9720	340	73		
SC-07	300	350	FCB	1835	63.8	388	1.0	1435	259	7.6	620	3	6.7	0.023	549	7400	160	51		
SC-08	300	400	FCB	2740	39.9	645	1.4	1355	147.0	9.2	371	2	8.2	0.094	1315	9860	190	115		
SC-09	300	450	FCB	7450	52.8	4130	1.5	1730	105.5	12.9	786	22	7.1	0.027	657	10180	240	180		
SC-10	300	500	FCB	11890	87.0	7960	2.6	2200	236	22.3	850	13	25.2	0.102	2020	10890	610	20		
SD-01	400	50	MTBT	340	17.8	170	1.5	109	37.9	8.3	71	2	8.1	0.064	707	8230	210	79		
SD-02	400	100	FCB	237	2.9	136	0.5	60	9.8	0.5	17	<	1	0.030	143	1100	29	6		
SD-03	400	150	MTBT	12250	56.6	5540	0.7	2410	269	7.1	483	14	2.0	0.071	451	16440	130	10		
SD-03	400	150	MTBT	152	1.8	64	0.4	32	5.0	0.9	7	<	1	1.4	0.032	114	620	19	5	
SD-04	400	200	FCB	3090	45.0	816	0.7	1395	165.0	5.2	665	6	2.7	0.022	383	15830	135	< 5		
SD-05	400	250	ALV	2270	30.9	1035	0.5	680	104.0	7.2	25	3	4.0	0.426	5580	6440	135	275		
SD-06	400	300	ALV	1610	19.5	728	0.5	479	66.4	5.5	27	1	5.0	0.666	4520	4650	120	210		
SD-07	400	350	FCB	642	85.2	54	1.1	1695	311	9.3	1386	2	8.1	0.086	349	9280	220	12		
SD-08	400	400	FCB	4150	38.9	1505	1.1	1155	125.0	8.4	704	1	6.2	0.596	677	8510	210	135		

Apex 12 Results of Geochemical Analysis

SAMPLE NUMBER	COORDINATES (N, E)	ROCK TYPE	ppm														P %	Sr ppm		BaY (XRF) ppm		Nb-Ta (XRF) ppm				
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Ni	NAA	Sm	NAA	Tb	NAA		Th	NAA	U	NAA	Yb	NAA	P	Sr	BaY (XRF)
SD-09	400	450	FCB	5160	45.4	4050	2.6	1105	173.0	12.9	599	8	19.3	0.307	2400	6720	460	115								
SD-10	400	500	FCB	3900	52.5	2790	2.5	880	180.0	13.2	421	<1	13.0	0.467	3620	4920	370	205								
SD-11	400	550	FCB	5280	59.4	4090	3.1	912	203	17.7	628	13	20.5	0.216	1940	4920	520	170								
SE-01	500	50	MTBT	83	1.4	56	0.5	17	5.4	0.3	9	<1	2.2	0.032	142	840	24	6								
SE-02	500	100	MTBT	94	1.6	68	0.4	22	5.5	0.7	11	<1	1.7	0.029	116	510	24	8								
SE-03	500	150	MTBT	20	0.8	12	0.4	8	2.9	<0.7	2	<1	1.3	0.027	104	200	19	6								
SE-04	500	200	MTBT	12	1.0	7	0.3	10	2.2	<0.3	2	<1	1.5	0.028	119	460	19	6								
SE-09	500	450	FCB	6430	42.1	5550	2.3	936	161.0	11.8	327	2	15.7	0.312	1645	6080	360	120								
SE-10	500	500	FCB	5070	44.6	3830	2.1	911	175.0	10.8	370	<1	12.0	0.139	1280	4460	330	210								
SE-11	500	550	FCB	3640	30.6	2840	2.2	696	122.0	8.1	190	<1	13.9	0.340	1850	6840	270	110								
SE-12	500	600	FCB	4380	47.7	3030	2.6	943	185.0	13.5	540	4	15.9	0.277	1920	5590	370	185								
SE-13	500	650	FCB	3100	43.3	3820	1.4	880	175.0	9.2	325	7	7.1	0.133	1545	4800	240	56								
SF-01	600	50	ALV	3310	47.9	2120	2.2	498	185.0	11.3	854	2	11.4	0.318	609	4600	260	125								
SF-02	600	100	MTBT	81	1.5	61	0.4	22	4.2	0.8	6	<1	2.0	0.030	118	370	26	6								
SF-03	600	150	MTBT	57	1.3	37	0.4	16	4.6	<1.0	10	<1	1.6	0.027	155	270	19	5								
SF-04	600	200	MTBT	16	0.6	10	0.3	5	2.2	0.9	1	<1	2.2	0.026	92	230	20	6								
SF-05	600	250	MTBT	17	0.7	9	0.3	9	2.5	0.4	1	<1	1.4	0.026	103	250	18	5								
SF-10	600	500	MTBT	15	0.7	7	0.3	<5	2.0	0.7	1	<1	1.7	0.025	112	280	17	5								
SF-11	600	550	MTBT	13	0.7	7	0.4	<5	2.2	<0.4	1	<1	1.6	0.029	98	200	18	5								
SF-12	600	600	ALV	4980	39.5	3590	2.2	776	119.5	9.0	315	2	14.8	0.308	1685	4200	370	100								
SF-13	600	650	ALV	4820	44.1	3110	1.8	1000	142.5	7.1	335	13	10.8	0.076	643	5230	230	61								
SF-14	600	700	ALV	33	1.1	23	1.2	6	2.9	0.5	7	<1	6.4	0.014	553	410	39	14								
SG-01	700	50	MTBT	108	1.3	68	0.4	26	5.3	0.6	7	<1	1.9	0.022	122	230	22	5								
SG-02	700	100	MTBT	11	0.7	8	0.4	<5	2.1	0.4	1	<1	1.9	0.022	111	170	17	5								
SG-03	700	150	MTBT	19	0.7	10	0.3	6	2.2	0.3	1	<1	1.7	0.022	108	190	17	5								
SG-04	700	200	ALV	373	8.6	219	1.2	64	24.9	2.9	58	18	6.1	0.982	635	360	95	230								
SG-05	700	250	MTBT	15	0.8	8	0.3	6	2.1	0.2	1	<1	1.4	0.019	112	460	19	<5								
SG-06	700	300	MTBT	10	0.6	5	0.3	5	1.8	<0.2	<1	<1	1.5	0.021	99	330	17	8								
SG-07	700	350	MTBT	11	0.7	5	0.4	5	2.1	0.3	<1	<1	1.7	0.018	137	260	18	<5								
SG-11	700	550	MTBT	9	0.6	6	0.3	7	2.4	0.3	<1	<1	1.8	0.021	106	290	17	6								
SG-12	700	600	FCB	5690	48.9	5020	3.6	1460	196.0	13.5	489	12	18.3	0.113	1210	6150	380	99								
SG-13	700	650	FCB	6290	46.3	5830	2.1	1460	181.5	11.4	409	19	14.2	0.128	1120	7960	300	98								
SG-14	700	700	MTBT	1420	16.7	1965	1.1	20	43.5	5.3	116	2	4.3	0.024	120	210	19	<5								
SH-01	800	50	MTBT	65	1.4	57	0.5	27	4.7	0.4	5	<1	1.5	0.020	134	340	20	6								
SH-02	800	100	MTBT	13	0.9	13	0.5	8	3.0	0.2	1	<1	2.0	0.018	183	200	20	<5								
SH-03	800	150	ALV	2180	23.3	1690	1.7	642	94.3	6.8	168	17	9.8	0.198	1860	1960	195	215								
SH-04	800	200	MTBT	16	0.8	13	0.4	10	2.5	0.4	1	<1	1.8	0.018	107	290	17	<5								
SH-05	800	250	MTBT	27	0.9	19	0.2	9	2.9	0.2	2	<1	1.7	0.015	136	210	16	5								
SH-06	800	300	ALV	1205	14.7	840	1.0	401	64.5	3.2	82	7	4.6	0.080	615	1200	83	345								
SH-07	800	350	MTBT	242	5.7	282	0.6	10	13.9	1.3	20	2	3.6	0.018	132	440	18	<5								

Apx. 12 Results of Geochemical Analysis

SAMPLE COORDI- ROCK
NUMBER NATES(井) TYPE

SAMPLE NUMBER	COORDI- NATES(井)	ROCK TYPE	ppm														P %	Sr ppm	BaY (XRF) ppm	BaY (XRF) No-XRF ppm
			Ce	NAA	Eu	NAA	La	NAA	Lu	NAA	Nd	NAA	Sm	NAA	Tb	NAA				
SH-11	800	550 MTBT	0.7	12	0.3	10	2.8	0.3	1	<1	1.8	0.029	127	210	21	7				
SH-12	800	600 ALV	11.1	692	0.8	368	52.6	1.8	131	14	2.4	0.037	231	3180	53	175				
SH-13	800	650 MTBT	0.9	9	0.4	13	3.0	0.4	1	<1	2.0	0.022	156	210	21	5				
SH-14	800	700 MTBT	0.9	14	0.4	11	2.7	<0.4	2	<1	2.1	0.019	108	240	19	6				
SI-01	900	50 MTBT	0.6	3	0.3	7	1.5	<0.5	<1	<1	1.7	0.017	138	190	17	5				
SI-02	900	100 MTBT	0.6	3	0.3	6	1.5	1.1	<1	<1	1.2	0.018	129	190	18	<5				
SI-03	900	150 MTBT	0.7	3	0.4	5	1.8	<0.5	<1	<1	1.4	0.023	105	280	20	5				
SI-04	900	200 MTBT	0.7	3	0.4	6	1.8	1.5	<1	<1	1.8	0.018	105	190	19	<5				
SI-05	900	250 MTBT	0.8	4	0.3	4	1.9	<0.6	<1	1	1.9	0.020	108	220	20	<5				
SI-06	900	300 MTBT	0.5	3	0.4	5	1.7	0.3	<1	1	1.7	0.021	110	270	20	5				
SI-07	900	350 MTBT	0.7	3	0.5	3	1.9	1.4	<1	1	1.9	0.022	132	310	19	<5				
SI-12	900	600 MTBT	0.7	4	0.5	<5	1.7	<0.8	<1	2	1.4	0.018	137	380	20	<5				
SI-13	900	650 MTBT	0.7	4	0.3	6	1.8	<0.5	<1	1	1.9	0.018	122	190	19	5				
SI-14	900	700 MTBT	0.9	3	0.4	7	1.9	1.6	<1	1	1.6	0.017	140	310	20	<5				

Apex 13 Results of Chemical Analysis of Drill Core Samples - Trace Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Au s/tonne	Ba ppm	Sr ppm	Nb ppm	Zr ppm	Ce ppm	La ppm	Eu ppm	Gd ppm	Pr ppm	Nd ppm	Sm ppm	Eu ppm	Tb ppm	Dy ppm	Ho ppm	Er ppm	Tm ppm	Yb ppm	Lu ppm		
																								U ppm	Th ppm
BRL-1-01	0.00	1.40	1.40	WETH MAT	< 0.07	>10000	950	3650	520	2460	54.9	1380	4.7	753	177.0	23.5	805	57	28.2						
BRL-1-02	1.80	4.80	3.00	WETH MAT	< 0.07	>10000	800	2350	850	5730	67.2	3120	8.1	1285	235	27.8	982	73	51.0						
BRL-1-03	4.80	8.70	3.00	OX-MI GN	< 0.07	>10000	2100	2400	790	9300	69.5	7090	8.4	1525	274	26.1	723	255	46.8						
BRL-1-04	8.70	10.00	1.50	OX-MI GN	< 0.07	>10000	1250	1100	680	>10000	106.0	>10000	5.7	1985	354	32.8	1438	347	32.3						
BRL-1-05	10.00	12.05	2.05	OX-MI GN	< 0.07	>10000	1950	1900	560	>10000	79.2	>10000	5.0	1985	308	21.2	895	382	21.3						
BRL-1-06	12.05	15.00	2.05	OX-MI GN	< 0.07	>10000	1400	690	590	8570	84.8	6700	3.9	1445	327	25.6	1315	201	18.7						
BRL-1-07	15.00	16.50	1.50	OX-MI GN	< 0.07	>10000	1800	320	510	8270	79.4	6430	3.9	1585	320	21.8	1375	265	25.1						
BRL-1-08	16.50	16.80	0.30	ORE	< 0.07	>10000	1500	900	740	>10000	88.4	>10000	6.0	1805	345	31.9	1278	381	32.9						
BRL-1-09	16.80	20.80	4.00	OX-MI GN	< 0.07	>10000	2250	890	720	>10000	92.7	>10000	6.1	2000	337	30.3	1338	429	36.3						
BRL-1-10	20.80	22.45	1.65	OX-MI GN	< 0.07	>10000	1800	390	830	>10000	113.0	>10000	5.2	2100	422	38.2	2025	357	32.0						
BRL-1-11	22.45	26.75	4.30	OX-MI GN	< 0.07	>10000	2100	670	1100	>10000	101.0	>10000	8.7	1935	363	36.2	1677	362	47.3						
BRL-1-12	26.75	29.50	2.75	OX-MI GN	< 0.07	>10000	1000	240	560	8820	101.5	7970	5.7	1565	420	27.6	1628	246	31.8						
BRL-1-13	29.50	32.30	2.80	OX-MI GN	< 0.07	>10000	1500	1300	810	7080	78.1	6150	6.5	1210	279	25.8	1212	220	34.6						
BRL-1-14	32.80	36.00	3.20	ORE	< 0.07	>10000	1500	1200	800	7560	91.1	6170	7.6	1415	337	32.9	1016	133	45.0						
BRL-1-15	36.00	38.40	2.40	OX-MI GN	< 0.07	>10000	3000	1900	1000	6670	100.5	4120	9.1	1440	351	35.7	965	123	48.7						
BRL-1-16	38.40	41.40	3.00	OX-MI GN	< 0.07	>10000	1450	480	800	9240	88.1	6420	7.9	1660	309	32.5	890	99	38.4						
BRL-1-17	41.40	44.40	3.00	SI ORE	< 0.07	>10000	3000	73	880	8360	62.9	5410	6.8	1590	242	23.2	628	62	42.7						
BRL-1-18	46.10	49.20	3.10	SI ORE	< 0.07	>10000	400	285	350	2860	67.4	1330	4.1	1045	265	18.1	1071	15	21.1						
BRL-1-19	49.20	54.00	4.80	OX-MI GN	< 0.07	>10000	1250	730	730	8720	72.1	4880	5.9	1450	246	26.2	1081	4	33.1						
BRL-1-20	54.00	60.10	6.10	GOSSAN	< 0.07	>10000	2100	1400	860	7540	112.0	4540	4.5	1785	380	35.4	1457	6	29.6						
BRL-1-21	60.10	65.65	5.55	GOSSAN	< 0.07	>10000	1300	1050	880	7150	123.5	5030	5.5	1725	445	41.2	1452	9	41.2						
BRL-1-22	65.65	67.40	1.75	CB	< 0.07	>10000	1150	910	750	5640	110.5	3870	3.9	1255	360	39.4	982	7	34.1						
BRL-1-23	67.40	68.60	1.20	MN-FE ORE	< 0.07	>10000	700	540	420	3660	88.6	1595	2.7	1280	369	24.4	1021	5	22.7						
BRL-1-24	68.60	71.80	3.20	CB	< 0.07	>10000	1350	1650	780	5020	137.5	3250	4.9	1385	494	41.0	1209	7	38.2						
BRL-1-25	71.80	72.75	0.95	ORE	< 0.07	>10000	950	460	840	3090	98.2	1570	4.0	1390	382	32.1	1026	6	35.1						
BRL-1-26	72.75	74.85	2.10	CB	< 0.07	>10000	1750	660	580	9050	101.0	4600	4.4	2260	407	31.1	1054	8	38.8						
BRL-1-27	75.00	77.60	2.60	CB	< 0.07	>10000	2200	295	590	>10000	65.3	>10000	3.4	1795	238	22.9	672	6	27.3						
BRL-1-28	77.60	80.40	2.80	CB FRESH	< 0.07	>10000	1500	420	660	7010	110.0	3790	4.6	1750	397	32.9	913	3	38.0						
BRL-1-29	85.40	85.40		CB FRESH	< 0.07	4500	2900	370	340	1680	23.5	963	3.5	330	83.3	11.3	259	2	22.2						
BRL-1-30	107.30			CB FRESH	< 0.07	7000	3600	640	270	3000	24.9	2100	3.4	470	94.0	10.3	267	1	21.6						
BRL-1-31	113.90			CB FRESH	< 0.07	7000	2050	670	260	4250	42.3	2790	1.6	737	157.5	13.0	336	1	13.8						
BRL-1-32	121.70			CB FRESH	< 0.07	>10000	2050	630	260	5160	34.4	3610	2.9	821	137.5	10.4	354	<	1	18.8					
BRL-1-33	131.30			CB-BRC	< 0.07	5700	2700	1000	370	3320	66.2	1755	2.4	731	230	18.1	534	8	15.0						
BRL-1-34	142.80			CB FRESH	< 0.07	>10000	1200	1200	670	>10000	97.7	3740	4.8	2750	466	20.4	1015	3	25.1						
BRL-1-35	152.50			CB FRESH	< 0.07	>10000	2250	1250	720	3240	57.3	476	3.8	1545	466	17.4	762	1	34.4						
BRL-1-36	163.80			CB-SHEARD	< 0.07	>10000	2050	870	370	5970	28.6	4590	3.6	785	113.5	11.2	407	2	26.3						
BRL-1-37	166.50			NEPHELINE	< 0.07	>10000	>10000	375	62	312	5.6	132	0.7	85	20.8	2.7	64	<	1	4.6					
BRL-1-38	180.00			NEPHELINE	< 0.07	>10000	>10000	475	115	361	8.1	183	1.5	84	25.9	4.2	123	<	1	9.7					
BRL-1-39	197.95	200.10	2.15	CB FRESH	< 0.07	>10000	>10000	355	270	>10000	31.3	9740	2.5	989	181.5	8.8	242	<	2	18.7					
BR-1-01	4.45	9.90	5.45	CB	< 0.07	8600	2500	940	540	1960	45.5	892	3.8	578	151.0	17.7	437	1	23.2						

Apex 13 Results of Chemical Analysis of Drill Core Samples - Trace Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (M)	WIDTH (M)	ROCK TYPE	Au g/tonne	Ba ppm	Sr ppm	Nb ppm	Zr ppm	Ce ppm	Eu ppm	La ppm	Lu ppm	Nd ppm	Sm ppm	Tb ppm	Th ppm	U ppm	Yb ppm	Y ppm
BR-1-02	9.90	14.05	4.15	CB-ORE	< 0.07	> 10000	1450	1650	500	3420	71.8	1345	3.4	989	268	25.0	568	12	25.1
BR-1-03	14.05	17.40	3.35	CB-ORE	< 0.07	> 10000	1350	1700	380	4300	55.8	1805	3.0	1075	226	15.9	374	9	18.0
BR-1-04	17.40	17.55	0.15	CB-ORE	< 0.07	> 10000	850	790	730	6640	95.1	3490	5.0	1340	370	30.1	1353	4	34.8
BR-1-05	19.80	24.10	4.30	CB	< 0.07	> 10000	1750	620	410	9960	49.0	7530	3.3	1310	202	15.6	351	3	25.7
BR-1-06	26.80	27.70	0.90	CB	< 0.07	> 10000	2250	1300	880	3080	78.4	1520	5.6	768	249	34.3	661	6	34.4
BR-1-07	27.80	31.20	3.50	CB	0.14	> 10000	2250	1500	630	> 10000	65.8	7610	5.2	1595	260	25.0	747	9	24.1
BR-1-08	31.20	31.50	0.30	ORE	< 0.07	> 10000	1000	200	350	4390	60.2	1675	2.6	1265	647	18.1	647	5	11.9
BR-1-09	35.60	40.30	4.70	CB	0.07	> 10000	2200	245	490	> 10000	52.5	> 10000	4.6	1680	214	12.8	578	124	18.5
BR-1-10	40.30	40.60	0.30	ORE	< 0.07	> 10000	1400	195	640	> 10000	79.9	8630	4.9	1585	302	18.3	1112	43	25.1
BR-1-11	41.90	44.40	2.50	ORE	< 0.07	> 10000	850	250	440	7240	77.3	3370	3.3	1500	316	17.8	751	23	14.5
BR-1-12	47.10	50.40	3.30	CB-ORE	< 0.07	> 10000	2050	1350	470	7520	59.6	5190	4.1	1185	226	17.7	573	12	21.1
BR-2-01	0.00	6.40	6.40	WETH MAT	< 0.07	> 10000	1900	1550	850	> 10000	96.9	8070	7.7	1500	328	33.3	981	5	43.0
BR-2-02	6.40	7.10	0.70	GOSSAN	0.07	> 10000	3100	1050	830	7660	85.5	5340	6.7	1100	283	28.1	759	7	37.6
BR-2-03	7.10	10.50	3.40	OX-MI GN	< 0.07	> 9800	375	990	220	2560	27.0	1525	1.7	415	104.0	8.4	333	18	8.2
BR-2-04	10.50	13.40	2.90	GOSSAN	< 0.07	> 10000	2650	1100	690	9760	83.2	6610	5.1	1435	276	27.9	932	24	28.0
BR-2-05	15.05	18.30	3.25	SI ORE	< 0.07	> 10000	2850	690	790	9930	85.2	7040	5.3	1450	306	28.6	1018	86	29.9
BR-2-06	18.30	22.50	4.20	SAND	< 0.07	> 10000	1900	1000	870	6640	91.6	4560	6.7	1150	287	36.2	1025	98	44.2
BR-2-07	22.50	26.20	3.70	OX-MI GN	< 0.07	> 10000	2850	500	740	6220	91.7	4260	6.1	1245	284	35.8	864	79	36.7
BR-2-08	26.20	30.00	3.80	SAND	< 0.07	> 10000	1550	780	690	5390	73.8	3470	5.7	863	220	33.1	750	97	34.4
BR-2-09	30.00	33.00	3.00	ORE	< 0.07	> 10000	2050	1450	810	8120	133.0	6420	5.5	1580	443	43.7	1453	186	31.9
BR-2-10	35.00	35.80	2.80	ORE	< 0.07	> 10000	2850	1850	840	7980	121.5	6170	6.2	1360	376	42.3	1283	72	35.1
BR-2-11	35.80	41.60	5.80	OX-MI GN	< 0.07	> 10000	2150	1250	850	8310	126.0	7140	6.2	1380	386	44.1	1133	126	36.3
BR-2-12	41.60	44.80	3.20	GOSSAN	< 0.07	> 10000	3850	640	630	7760	77.1	6820	4.6	1180	251	26.8	718	57	25.4
BR-2-13	44.80	50.10	5.30	GOSSAN	< 0.07	> 10000	4150	750	580	7590	81.2	6500	3.8	1205	257	27.1	796	41	19.8
BR-3-01	3.90	8.40	4.50	OX-MI GN	0.07	> 10000	1350	980	680	4840	71.0	2070	4.8	1405	260	25.9	1093	5	33.3
BR-3-02	8.40	14.80	6.40	OX-MI GN	< 0.07	> 10000	500	990	600	5810	73.5	2190	4.3	1520	278	26.1	1199	3	30.0
BR-3-03	14.80	20.40	5.60	OX-MI GN	< 0.07	> 10000	1400	1400	900	9760	74.5	6010	6.9	1690	258	30.9	1099	15	42.5
BR-3-04	20.40	20.85	0.45	ORE	< 0.07	> 10000	1000	255	370	3830	48.3	1410	2.3	958	190.0	16.8	775	6	15.3
BR-3-05	20.85	30.20	9.45	OX-MI GN	< 0.07	> 10000	1250	1100	860	7050	84.9	4120	5.8	1515	272	36.9	1068	3	40.3
BR-3-06	30.20	36.25	6.05	OX-MI GN	< 0.07	> 10000	1300	610	820	6730	78.7	3890	6.3	979	317	34.6	1051	4	44.3
BR-3-07	36.25	41.45	5.20	OX-MI GN	< 0.07	> 10000	1050	980	1150	8660	108.0	4930	7.0	1095	375	52.3	1291	9	52.3
BR-3-08	41.45	46.00	4.55	OX-MI GN	0.07	> 10000	1150	1750	740	9170	105.5	6100	5.7	1305	389	40.2	1349	6	36.3
BR-3-09	46.00	50.40	4.40	OX-MI GN	< 0.07	> 10000	2000	1150	1250	> 10000	97.4	6440	9.0	1190	339	49.7	1415	8	58.6
BR-4-01	0.70	2.00	1.30	SI ORE	< 0.07	> 10000	2100	275	370	2460	19.6	2230	2.0	230	71.6	8.9	220	3	15.9
BR-4-02	2.00	3.60	1.60	SI ORE	0.07	> 10000	1050	1150	500	6990	43.8	4100	3.4	1005	199.0	15.8	466	3	23.5
BR-4-03	3.60	5.40	1.80	GOSSAN	< 0.07	> 10000	2800	1250	700	7110	58.0	5250	4.7	1060	266	21.9	757	3	35.0
BR-4-04	5.40	9.60	4.20	SI ORE	< 0.07	> 10000	550	205	330	4390	37.8	1865	2.4	1085	212	10.9	451	2	16.2
BR-4-05	11.30	15.00	3.70	OX-MI GN	< 0.07	> 10000	4050	1500	1200	8360	77.1	5340	7.1	1165	320	31.8	839	3	51.9
BR-4-06	15.00	18.80	3.80	SI ORE	< 0.07	> 10000	850	1250	600	5570	69.6	4380	3.5	851	271	24.3	767	3	23.8
BR-4-07	18.80	23.50	4.70	SI ORE	< 0.07	> 10000	1000	420	420	5470	61.6	3420	3.2	992	277	19.9	868	2	18.6

Apex 13 Results of Chemical Analysis of Drill Core Samples - Trace Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Au s/tonne	Ba ppm	Sr ppm	Nb ppm	XRF ppm	Ce ppm	Eu ppm	La ppm	Lu ppm	Ni ppm	Sn ppm	Tb ppm	Ta ppm	U ppm	Vb ppm	Yb ppm	Zn ppm
BR-4-08	23.50	27.00	3.50	GOSSAN	< 0.07	>10000	1050	840	610	9690	72.2	4620	3.7	1525	306	21.9	779	< 17	28.1	
BR-4-09	27.00	35.10	6.10	ORE	< 0.07	>10000	1650	700	1050	7270	81.6	3940	5.8	1250	309	26.4	945	< 2	40.5	
BR-4-10	42.20	46.00	3.20	CB	< 0.07	>10000	3200	530	730	6660	59.5	3500	5.7	859	182.5	25.9	568	3	42.2	
BR-4-11	46.00	50.50	4.50	CB	< 0.07	>10000	3100	390	430	>10000	50.0	9590	3.1	1630	172.0	16.6	496	3	15.6	
BR-5-01	0.00	3.80	3.80	WETH MAT	< 0.07	>10000	1600	770	660	8420	83.0	3090	3.3	1910	286	31.3	902	2	26.6	
BR-5-02	4.70	8.80	4.10	OX-MI GN	< 0.07	>10000	2450	405	860	>10000	92.0	4420	5.1	1900	307	33.0	1219	3	35.2	
BR-5-03	8.80	15.80	7.00	ORE	< 0.07	>10000	1900	1100	1350	>10000	142.5	8730	8.1	1850	409	57.5	1614	24	59.4	
BR-5-04	15.80	21.90	6.10	OX-MI GN	< 0.07	>10000	750	1350	1050	9030	98.2	4210	6.3	1625	322	44.9	1378	< 4	45.7	
BR-5-05	21.90	26.60	4.70	OX-MI GN	< 0.07	>10000	500	950	420	6730	67.0	2510	3.7	1485	256	24.3	1212	< 4	23.5	
BR-5-06	27.80	35.30	7.50	SI ORE	< 0.07	>10000	1100	1100	510	9030	72.9	4710	4.4	1515	256	25.5	857	< 3	26.7	
BR-5-07	35.30	39.20	3.90	OX-MI GN	< 0.07	>10000	1550	580	710	>10000	81.1	5510	4.3	1735	271	30.2	1001	14	26.3	
BR-5-08	39.20	46.60	7.40	OX-MI GN	< 0.07	>10000	1650	1600	790	>10000	84.2	5950	4.9	1680	277	35.2	922	24	31.7	
BR-5-09	46.60	49.90	3.30	OX-MI GN	< 0.07	>10000	1850	1400	450	>10000	55.2	5900	2.8	1400	187.0	19.8	629	2	15.9	
BR-5-10	49.90	50.40	0.50	SI ORE	< 0.07	>10000	1900	700	540	>10000	62.3	5810	3.4	1405	191.5	25.0	746	4	20.8	
BR-6-01	0.00	2.90	2.90	WETH MAT	< 0.07	>10000	1450	930	810	7490	79.3	5100	4.9	1150	233	36.2	551	8	40.0	
BR-6-02	5.60	8.60	3.00	OX-MI GN	< 0.07	>10000	500	840	530	4250	64.3	2400	2.3	847	207	26.5	520	19	21.2	
BR-6-03	8.60	13.20	4.60	CA-FE ORE	< 0.07	>10000	1700	305	700	>10000	53.7	4630	3.6	2110	231	19.4	690	26	17.9	
BR-6-04	16.30	17.30	1.00	ORE	< 0.07	>10000	2200	270	860	4420	72.8	2390	4.6	1160	237	30.0	781	81	32.6	
BR-6-05	23.90	25.50	1.40	GOSSAN	< 0.07	>10000	2500	475	740	>10000	60.0	>10000	4.7	2380	233	20.6	581	143	26.3	
BR-6-06	25.30	29.20	3.90	SI ORE	< 0.07	>10000	2400	1250	670	>10000	54.9	9770	4.3	2190	244	17.2	655	114	28.6	
BR-6-07	29.20	31.60	2.40	CA-FE ORE	< 0.07	>10000	2800	630	570	>10000	49.5	7450	4.2	1865	203	21.0	487	99	27.5	
BR-6-08	32.50	37.50	5.00	SI ORE	< 0.07	>10000	1950	810	650	>10000	80.6	7280	4.9	2640	347	22.5	995	49	27.7	
BR-6-09	39.50	43.10	3.60	ORE	< 0.07	>10000	2000	310	730	>10000	61.7	6590	5.9	2790	294	14.1	719	20	38.4	
BR-6-10	43.10	46.50	3.20	SI ORE	< 0.07	>10000	1900	140	550	8350	51.0	3750	4.2	1785	221	15.6	538	38	28.4	
BR-6-11	47.40	49.30	1.90	SI ORE	< 0.07	>10000	2650	265	910	>10000	69.3	5910	6.4	2440	290	23.2	707	50	45.8	
BR-7-01	0.00	6.00	6.00	WETH MAT	< 0.07	>10000	1800	1000	780	6350	64.1	4020	5.3	1280	220	30.2	428	24	40.9	
BR-7-02	6.00	11.30	5.30	WETH MAT	< 0.07	>10000	950	870	670	5860	57.1	3590	3.9	1005	187.0	25.5	370	14	28.0	
BR-7-03	11.30	13.00	1.70	WETH MAT	< 0.07	>10000	1450	950	880	>10000	70.5	5460	5.7	1450	249	32.2	798	20	35.0	
BR-7-04	13.00	18.50	5.50	WETH MAT	< 0.07	>10000	1150	650	770	>10000	83.4	8990	7.2	1990	307	34.5	708	88	45.7	
BR-7-05	18.30	18.50	0.20	SI ORE	< 0.07	>10000	500	195	370	2960	112.5	1040	3.5	1400	446	30.9	889	33	22.1	
BR-7-06	19.10	19.80	0.70	SAND	< 0.07	>10000	1400	1050	650	3570	51.9	2960	6.5	431	171.0	25.9	455	71	46.7	
BR-7-07	31.60	39.10	7.50	OX-MI GN	< 0.07	>10000	1500	470	880	6880	69.3	7760	5.1	880	270	26.5	861	8	35.9	
BR-7-08	41.20	41.70	0.50	ORE	< 0.07	>10000	1550	860	400	2420	30.3	1885	2.9	503	134.5	12.0	392	4	21.2	
BR-7-09	44.50	45.90	1.40	OX-MI GN	< 0.07	>10000	700	1500	640	4660	66.4	4010	4.3	583	242	24.4	790	14	33.7	
BR-7-10	45.90	50.40	4.50	OX-MI GN	< 0.07	>10000	1100	1700	410	5020	62.4	4570	2.7	673	194.0	19.0	653	9	18.6	
BR-8-01	0.00	6.00	6.00	WETH MAT	< 0.07	>10000	1450	620	720	7200	79.3	8500	5.9	890	308	28.0	936	132	28.8	
BR-8-02	6.00	7.70	1.70	WETH MAT	< 0.07	>10000	1000	1100	570	7090	90.6	7100	3.8	1045	349	30.5	977	134	22.4	
BR-8-03	7.70	9.20	1.50	OX-MI GN	< 0.07	>10000	950	445	480	4400	68.3	4550	3.8	744	260	20.2	730	78	19.4	
BR-8-04	9.20	12.00	2.80	SAND	< 0.07	>10000	850	1650	690	6840	51.6	7460	4.5	923	301	30.3	744	132	27.5	
BR-8-05	12.00	19.40	7.40	OX-MI GN	< 0.07	>10000	2250	405	700	4410	83.1	3790	5.2	832	323	24.8	899	32	31.5	

Apex 13 Results of Chemical Analysis of Drill Core Samples - Trace Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (ft)	WIDTH (in)	ROCK TYPE	Au s/tonne	Ba ppm	Sr ppm	Nb ppm	XRF ppm	Ce ppm	Eu ppm	La ppm	NAA Lu ppm	NAA Nd ppm	NAA Sm ppm	NAA Tb ppm	NAA Tl ppm	NAA U ppm	NAA Yb ppm	NAA ppm
BR-8-06	19.40	25.65	6.25	OX-MI GN	< 0.07	>10000	2350	630	1000	3570	80.4	9950	5.8	1015	284	32.3	930	20	38.3
BR-8-07	25.65	26.20	0.55	CB	< 0.07	>10000	2250	240	730	2390	41.6	2730	5.0	335	132.5	23.0	470	3	34.0
BR-8-08	26.20	34.05	7.15	OX-MI GN	< 0.07	>10000	1900	570	680	6490	65.1	8340	5.0	847	220	21.4	702	26	33.8
BR-8-09	34.05	37.10	3.05	CB	< 0.07	>10000	1500	610	350	8910	43.7	>10000	2.8	1840	211	13.7	377	21	18.6
BR-8-10	37.10	39.55	2.45	OX-MI GN	< 0.07	>10000	1750	3100	540	2060	43.3	2050	5.9	718	167.5	19.2	583	12	31.1
BR-8-11	39.55	42.35	2.80	CB	< 0.07	>10000	1550	720	640	4440	70.8	4740	5.1	1310	278	25.9	802	21	28.8
BR-8-12	42.35	47.10	4.75	CB	< 0.07	>10000	2050	700	600	4510	62.8	5270	5.4	1145	237	24.4	800	13	34.0
BR-8-13	47.10	50.40	3.50	CB FRESH	< 0.07	>10000	1750	380	440	5260	58.7	5430	3.5	1530	262	19.7	770	9	19.7
BR-9-01	8.45	9.45	1.00	OX-MI GN	0.27	>10000	300	290	460	1430	50.0	983	4.5	794	195.0	15.8	684	< 2	23.5
BR-9-02	14.50	15.25	0.75	OX-MI GN	< 0.07	>10000	350	335	760	6810	70.3	6080	7.6	2240	340	21.7	915	7	39.8
BR-9-03	25.20	27.70	2.50	OX-MI GN	< 0.07	>10000	2750	3800	640	2860	72.9	2160	5.5	1220	276	28.4	439	22	32.7
BR-9-04	27.70	29.00	1.50	CB	< 0.07	>10000	1850	2700	620	1975	58.3	1370	5.9	962	234	23.8	539	18	33.8
BR-9-05	29.00	31.40	2.40	CB	< 0.07	>10000	1750	1350	380	1035	29.5	783	2.9	409	116.0	14.7	341	8	16.5
BR-9-06	31.40	32.70	1.30	ORE	< 0.07	>10000	1100	235	750	3970	70.1	3360	5.0	1455	286	27.9	998	9	31.3
BR-9-07	32.70	34.80	2.10	OX-MI GN	< 0.07	>10000	1200	235	320	5120	54.1	4060	3.6	1635	254	16.3	747	18	18.6
BR-9-08	34.80	38.40	3.60	FE-CB	< 0.07	>10000	2550	485	500	7720	58.5	8940	5.1	1700	260	20.3	716	17	30.8
BR-9-09	38.40	39.10	0.70	CB	< 0.07	>10000	2100	760	360	2670	39.0	3200	3.2	708	149.5	14.8	367	4	19.4
BR-9-10	39.10	40.70	1.60	OX-MI GN	< 0.07	>10000	1450	340	220	2120	21.6	3470	2.0	617	103.0	8.1	239	3	11.6
BR-9-11	46.40	50.40	4.00	CB FRESH	< 0.07	>10000	2600	2700	230	2720	32.7	1405	2.5	462	107.5	10.4	225	5	16.6
BR-10-01	6.30	10.50	4.20	WETH MAT	< 0.07	>10000	1650	1350	990	>10000	121.5	>10000	8.6	1810	415	35.8	1187	17	47.6
BR-10-02	10.50	14.90	4.40	OX-MI GN	< 0.07	>10000	1500	720	560	6490	62.8	4620	5.6	1080	228	18.3	770	4	29.8
BR-10-03	14.90	15.90	1.00	GOSSAN	< 0.07	>10000	1250	465	550	7710	78.3	5790	5.1	1550	301	18.5	893	< 5	28.5
BR-10-04	17.30	22.50	5.20	WETH MAT	< 0.07	>10000	1300	940	640	>10000	72.8	9600	6.5	1670	274	19.4	925	30	35.5
BR-10-05	22.50	25.60	3.10	OX-MI GN	< 0.07	>10000	1250	650	350	3360	47.4	2270	3.3	766	188.0	9.7	528	13	16.8
BR-10-06	25.60	28.20	2.60	CB	< 0.07	>10000	1800	700	720	>10000	66.7	>10000	6.2	1950	277	21.3	723	21	35.4
BR-10-07	28.20	32.80	4.60	FE-CB	< 0.07	>10000	2100	550	660	>10000	69.8	9660	5.8	1570	288	16.3	736	21	36.6
BR-10-08	32.80	36.30	3.50	FE-CB	< 0.07	>10000	1750	450	530	9710	49.7	7930	5.3	1165	200	13.8	554	12	29.6
BR-10-09	37.00	43.40	6.40	CB	< 0.07	>10000	1400	1050	420	3810	39.3	2590	4.7	581	144.0	11.7	420	11	28.2
BR-10-10	43.40	46.10	2.70	CB	< 0.07	>10000	1250	640	360	1545	23.4	961	3.7	343	73.1	8.8	290	5	21.0
BR-10-11	46.10	48.20	2.10	CB	< 0.07	>10000	2000	2000	920	>10000	65.6	8130	7.7	1490	198.5	21.7	829	25	49.3
BR-10-12	48.20	50.40	2.20	FE-CB	< 0.07	>10000	2300	650	960	>10000	85.6	>10000	8.1	1565	225	26.6	904	51	46.9
BR-11-01	0.50	4.50	4.50	WETH MAT	< 0.07	>10000	350	520	780	>10000	96.1	7550	6.2	1740	340	32.6	983	16	41.8
BR-11-02	4.50	11.20	6.70	WETH MAT	< 0.07	>10000	450	1100	1300	>10000	103.5	9970	10.8	1935	343	40.8	894	30	72.3
BR-11-03	11.20	17.90	6.70	WETH MAT	< 0.07	>10000	600	1250	1400	>10000	114.5	9200	10.7	1260	333	48.6	1547	9	68.9
BR-11-04	17.90	22.50	4.60	GOSSAN	< 0.07	>10000	550	3250	590	2180	42.2	1270	5.6	510	131.5	18.1	605	9	38.3
BR-11-05	22.50	24.10	1.60	CB	< 0.07	>10000	2650	1250	430	2960	34.9	1670	4.3	629	124.0	14.2	244	8	27.1
BR-11-06	24.10	30.15	6.05	GOSSAN	< 0.07	>10000	1550	1800	690	>10000	54.4	9680	5.8	1320	159.0	16.8	426	13	37.2
BR-11-07	30.15	35.45	5.30	CB	< 0.07	>10000	2850	960	380	3660	32.6	2640	3.5	602	114.5	12.3	327	7	20.8
BR-11-08	35.45	35.80	0.35	FE-CB	< 0.07	>10000	1150	520	900	5730	94.0	2900	3.5	1460	305	30.4	1490	9	27.7
BR-11-09	35.80	36.00	0.20	FE-CB	< 0.07	>10000	1450	520	490	4340	60.7	2260	3.8	953	214	20.5	759	3	25.3

Apx. 13 Results of Chemical Analysis of Drill Core Samples — Trace Level Analysis —

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Au s/tonne	Ba ppm	Sr ppm	Nb ppm	XRF ppm	Ce ppm	Eu ppm	La ppm	NAA ppm	Lu ppm	Ni ppm	NAA ppm	Sn ppm	NAA ppm	Tb ppm	NAA ppm	Th ppm	NAA ppm	U ppm	NAA ppm	Yb ppm	NAA ppm
BR-15-03	17.00	18.35	1.35	ORE	< 0.07	>10000	750	450	195	3330	45.4	1380	1.0	1145	226	7.8	703	7	7.7						
BR-15-04	23.40	25.00	1.60	GOSSAN	< 0.07	>10000	1150	600	740	>10000	73.2	9470	5.2	1885	196.0	25.8	1080	33	29.4						
BR-15-05	25.00	25.90	0.90	CB	< 0.07	>10000	2000	79	450	9910	57.5	6130	2.9	1715	219	16.2	910	69	13.5						
BR-15-06	25.90	29.90	4.00	ORE	< 0.07	>10000	1250	175	420	4580	37.5	1745	1.5	1210	131.0	9.5	638	13	9.9						
BR-15-07	37.70	39.25	1.55	MN-Fe ORE	< 0.07	>10000	550	63	270	5470	72.2	1835	2.1	1615	237	16.0	1039	34	14.4						
BR-15-08	42.00	43.20	1.20	MN-Fe ORE	< 0.07	>10000	600	110	260	4050	44.1	995	1.5	1805	170.0	9.2	755	15	10.9						
BR-15-09	43.20	43.90	0.70	CB	< 0.07	>10000	700	245	500	10000	58.7	4590	3.1	2270	225	14.8	860	16	23.0						
BR-16-01	12.90	13.30	0.40	ORE	< 0.07	>10000	1150	365	490	9960	62.7	7030	5.1	1935	225	16.5	1026	6	37.5						
BR-16-02	14.90	16.00	1.10	OX-MI GN	< 0.07	>10000	450	830	480	2450	69.6	1460	3.4	1055	224	17.0	1081	4	27.1						
BR-16-03	16.40	16.90	0.50	SI ORE	< 0.07	>10000	750	385	480	3580	61.3	2800	3.6	757	151.0	17.4	1441	16	29.1						

Apx. 14 Results of Chemical Analysis of Drill Core Samples - Ore Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF		Ce XRF		La XRF		Nd XRF	
				%	%	%	%	%	%	%	%
BRL-1-01	0.00	1.40	1.40	WETH MAT	1.67	0.34	0.190	0.13			
BRL-1-02	1.80	4.80	3.00	WETH MAT	2.43	0.75	0.420	0.23			
BRL-1-03	4.80	8.70	3.90	OX-MI GN	4.46	1.28	0.970	0.32			
BRL-1-04	8.70	10.00	1.30	OX-MI GN	10.20	2.11	2.12	0.50			
BRL-1-05	10.00	12.05	2.05	OX-MI GN	7.57	2.15	1.920	0.48			
BRL-1-06	12.05	15.00	2.05	OX-MI GN	3.86	1.18	0.960	0.31			
BRL-1-07	15.00	16.50	1.50	OX-MI GN	4.66	1.17	0.920	0.34			
BRL-1-08	16.50	16.80	0.30	ORE	4.80	1.63	1.420	0.38			
BRL-1-09	16.80	20.80	4.00	OX-MI GN	6.25	2.06	1.910	0.45			
BRL-1-10	20.80	22.45	1.65	OX-MI GN	6.38	2.44	2.31	0.54			
BRL-1-11	22.45	26.75	4.30	OX-MI GN	5.77	1.93	1.800	0.41			
BRL-1-12	26.75	29.50	2.75	OX-MI GN	3.77	1.24	1.170	0.35			
BRL-1-13	29.50	32.30	2.80	OX-MI GN	6.05	1.02	0.930	0.26			
BRL-1-14	32.30	36.00	3.20	ORE	2.73	1.07	0.880	0.30			
BRL-1-15	36.00	38.40	2.40	OX-MI GN	4.51	0.98	0.580	0.32			
BRL-1-16	38.40	41.40	3.00	OX-MI GN	3.87	1.09	0.840	0.26			
BRL-1-17	41.40	44.40	3.00	SI ORE	1.83	0.92	0.650	0.23			
BRL-1-18	46.10	49.20	3.10	SI ORE	1.67	0.35	0.170	0.16			
BRL-1-19	49.20	54.00	4.80	OX-MI GN	3.83	1.06	0.670	0.25			
BRL-1-20	54.00	60.10	6.10	GOSSAN	3.19	0.94	0.630	0.30			
BRL-1-21	60.10	65.65	5.55	GOSSAN	4.24	0.93	0.760	0.35			
BRL-1-22	65.65	67.40	1.75	CB	3.47	0.75	0.580	0.25			
BRL-1-23	67.40	68.60	1.20	MN-FE ORE	2.07	0.51	0.240	0.24			
BRL-1-24	68.60	71.80	3.20	CB	3.35	0.68	0.480	0.27			
BRL-1-25	71.80	72.75	0.95	ORE	3.48	0.45	0.230	0.27			
BRL-1-26	72.75	74.85	2.10	CB	4.79	1.17	0.680	0.43			
BRL-1-27	75.00	77.60	2.60	CB	4.93	1.50	1.500	0.31			
BRL-1-28	77.60	80.40	2.80	CB FRESH	2.68	0.85	0.500	0.29			
BRL-1-29	80.40	98.85	10.95	CB FRESH	0.48	0.19	0.110	0.05			
BRL-1-30	98.85	110.60	11.75	CB FRESH	0.79	0.33	0.270	0.08			
BRL-1-31	110.60	114.50	3.90	CB FRESH	0.90	0.46	0.350	0.12			
BRL-1-32	121.70	130.00	15.50	CB FRESH	1.36	0.56	0.450	0.13			
BRL-1-33	130.00	142.30	12.30	CB-BRC	1.26	0.38	0.230	0.12			
BRL-1-34	142.30	147.55	5.25	CB FRESH	7.58	1.33	0.530	0.62			
BRL-1-35	147.55	158.05	10.50	CB FRESH	4.72	0.42	0.069	0.31			
BRL-1-36	158.05	164.90	6.85	CB-SHEARD	9.06	0.69	0.670	0.18			
BRL-1-37	164.90	174.00	9.10	NEPHELINE	2.90	0.05	0.005	0.02			
BRL-1-38	174.00	196.85	22.85	NEPHELINE	2.15	0.05	0.014	0.02			
BRL-1-39	197.95	200.10	2.15	CB FRESH	2.87	1.14	1.260	0.17			
BR-1-01	4.45	9.90	5.45	CB	1.10	0.28	0.130	0.11			

Apx. 14 Results of Chemical Analysis of Drill Core Samples — Ore Level Analysis —

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF		Ce XRF		La XRF		Nd XRF	
				%	%	%	%	%	%	%	%
BR-1-02	9.90 - 14.05	4.15	CB-ORE	1.32	0.40	0.170	0.17				
BR-1-03	14.05 - 17.40	3.35	CB-ORE	1.48	0.46	0.220	0.17				
BR-1-04	17.40 - 17.55	0.15	CB-ORE	1.53	0.72	0.460	0.25				
BR-1-05	19.80 - 24.10	4.30	CB	2.65	1.10	1.010	0.24				
BR-1-06	26.80 - 27.70	0.90	CB	0.97	0.36	0.190	0.13				
BR-1-07	27.70 - 31.20	3.50	CB	4.82	1.32	1.050	0.31				
BR-1-08	31.20 - 31.50	0.30	ORE	2.25	0.50	0.220	0.24				
BR-1-09	35.60 - 40.30	4.70	CB	5.46	1.75	1.740	0.34				
BR-1-10	40.30 - 40.60	0.30	ORE	3.85	1.33	1.240	0.32				
BR-1-11	41.90 - 44.40	2.50	ORE	3.96	0.81	0.480	0.30				
BR-1-12	47.10 - 50.40	3.30	CB-ORE	2.56	0.86	0.710	0.22				
BR-2-01	0.00 - 6.40	6.40	WETH MAT	3.35	1.21	1.110	0.32				
BR-2-02	6.40 - 7.10	0.70	GOSSAN	4.32	0.81	0.690	0.20				
BR-2-03	7.10 - 10.50	3.40	OX-MI GN	1.04	0.30	0.210	0.08				
BR-2-04	10.50 - 13.40	2.90	GOSSAN	3.65	1.07	0.870	0.26				
BR-2-05	15.05 - 18.30	3.25	SI ORE	2.68	1.06	0.910	0.25				
BR-2-06	18.30 - 22.50	4.20	SAND	4.20	0.75	0.640	0.18				
BR-2-07	22.50 - 26.20	3.70	OX-MI GN	3.36	0.75	0.600	0.20				
BR-2-08	26.20 - 30.00	3.80	SAND	5.74	0.68	0.530	0.15				
BR-2-09	30.00 - 33.00	3.00	ORE	4.30	1.01	0.990	0.27				
BR-2-10	33.00 - 35.80	2.80	ORE	3.55	0.96	0.900	0.23				
BR-2-11	35.80 - 41.60	5.80	OX-MI GN	4.36	1.07	1.090	0.25				
BR-2-12	41.60 - 44.80	3.20	GOSSAN	4.20	0.90	0.910	0.18				
BR-2-13	44.80 - 50.10	5.30	GOSSAN	2.77	0.87	0.860	0.18				
BR-3-01	3.90 - 8.40	4.50	OX-MI GN	5.59	0.62	0.310	0.25				
BR-3-02	8.40 - 14.80	6.40	OX-MI GN	7.57	0.78	0.370	0.34				
BR-3-03	14.80 - 20.40	5.60	OX-MI GN	6.44	1.32	0.980	0.35				
BR-3-04	20.40 - 20.85	0.45	ORE	2.99	0.47	0.180	0.17				
BR-3-05	20.85 - 30.20	9.45	OX-MI GN	5.90	0.84	0.580	0.24				
BR-3-06	30.20 - 36.25	6.05	OX-MI GN	5.23	0.77	0.530	0.25				
BR-3-07	36.25 - 41.45	5.20	OX-MI GN	9.44	1.06	0.750	0.35				
BR-3-08	41.45 - 46.00	4.55	OX-MI GN	5.27	1.01	0.820	0.28				
BR-3-09	46.00 - 50.40	4.40	OX-MI GN	8.57	1.30	0.990	0.34				
BR-4-01	0.70 - 2.00	1.30	SI ORE	12.60	0.33	0.320	0.09				
BR-4-02	2.00 - 3.60	1.60	SI ORE	4.90	0.82	0.550	0.24				
BR-4-03	3.60 - 5.40	1.80	GOSSAN	5.21	0.80	0.680	0.25				
BR-4-04	5.40 - 9.60	4.20	SI ORE	1.79	0.47	0.210	0.21				
BR-4-05	11.30 - 15.00	3.70	OX-MI GN	2.71	0.89	0.650	0.24				
BR-4-06	15.00 - 18.80	3.80	SI ORE	2.29	0.70	0.620	0.19				
BR-4-07	18.80 - 23.50	4.70	SI ORE	1.65	0.59	0.410	0.19				

Apx. 14 Results of Chemical Analysis of Drill Core Samples - Ore Level Analysis -

SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF		Ce XRF		La XRF		Nd XRF	
				%	%	%	%	%	%	%	%
BR-4-08	23.50	27.00	3.50	GOSSAN	4.83	1.12	0.610	0.37			
BR-4-09	27.00	33.10	6.10	ORE	2.78	0.89	0.520	0.29			
BR-4-10	42.20	46.00	3.20	CB	2.74	0.89	0.470	0.15			
BR-4-11	46.00	50.50	4.50	CB	3.56	1.22	1.240	0.23			
BR-5-01	0.00	3.80	3.80	WETH MAT	3.21	0.77	0.410	0.29			
BR-5-02	4.70	8.80	4.10	OX-MI GN	5.83	1.06	0.650	0.32			
BR-5-03	8.80	15.80	7.00	ORE	5.12	1.43	1.360	0.35			
BR-5-04	15.80	21.90	6.10	OX-MI GN	2.04	0.91	0.620	0.28			
BR-5-05	21.90	26.60	4.70	OX-MI GN	0.71	0.57	0.300	0.21			
BR-5-06	27.80	35.30	7.50	SI ORE	2.49	0.82	0.610	0.23			
BR-5-07	35.30	39.20	3.90	OX-MI GN	3.19	1.14	0.850	0.30			
BR-5-08	39.20	46.60	7.40	OX-MI GN	5.40	1.19	0.930	0.31			
BR-5-09	46.60	49.90	3.30	OX-MI GN	4.98	0.95	0.790	0.23			
BR-5-10	49.90	50.40	0.50	SI ORE	7.09	1.05	0.800	0.27			
BR-6-01	0.00	2.90	2.90	WETH MAT	3.90	0.72	0.700	0.18			
BR-6-02	5.60	8.60	3.00	OX-MI GN	4.19	0.45	0.350	0.15			
BR-6-03	8.60	13.20	4.60	CA-FE ORE	2.18	1.15	0.670	0.33			
BR-6-04	16.30	17.30	1.00	ORE	7.38	0.52	0.350	0.21			
BR-6-05	23.90	25.30	1.40	GOSSAN	12.00	1.98	2.12	0.41			
BR-6-06	25.30	29.20	3.90	SI ORE	5.11	1.63	1.390	0.35			
BR-6-07	29.20	31.60	2.40	CA-FE ORE	5.19	1.31	1.080	0.30			
BR-6-08	32.50	37.50	5.00	SI ORE	6.35	1.36	1.110	0.46			
BR-6-09	39.50	43.10	3.60	ORE	4.58	1.52	0.960	0.44			
BR-6-10	43.10	46.30	3.20	SI ORE	6.43	1.00	0.580	0.31			
BR-6-11	47.40	49.30	1.90	SI ORE	5.49	1.40	0.850	0.42			
BR-7-01	0.00	6.00	6.00	WETH MAT	2.81	0.77	0.610	0.21			
BR-7-02	6.00	11.30	5.30	WETH MAT	4.66	0.70	0.560	0.18			
BR-7-03	11.30	13.00	1.70	WETH MAT	4.96	1.20	0.870	0.25			
BR-7-04	13.00	18.30	5.30	WETH MAT	4.69	1.46	1.480	0.35			
BR-7-05	18.30	18.50	0.20	SI ORE	3.15	0.37	0.150	0.24			
BR-7-06	19.10	19.80	0.70	SAND	4.21	0.63	0.410	0.13			
BR-7-07	31.60	39.10	7.50	OX-MI GN	6.67	1.26	1.170	0.32			
BR-7-08	41.20	41.70	0.50	ORE	5.94	0.48	0.270	0.17			
BR-7-09	44.50	45.90	1.40	OX-MI GN	4.90	0.89	0.600	0.24			
BR-7-10	45.90	50.40	4.50	OX-MI GN	2.77	0.90	0.640	0.19			
BR-8-01	0.00	6.00	6.00	WETH MAT	6.80	1.28	1.190	0.29			
BR-8-02	6.00	7.70	1.70	WETH MAT	4.98	1.33	1.130	0.36			
BR-8-03	7.70	9.20	1.50	OX-MI GN	3.63	0.81	0.630	0.22			
BR-8-04	9.20	12.00	2.80	SAND	7.21	1.28	1.170	0.31			
BR-8-05	12.00	19.40	7.40	OX-MI GN	6.01	0.78	0.510	0.26			

Apex 14 Results of Chemical Analysis of Drill Core Samples — Ore Level Analysis —







SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF		Ce XRF		La XRF		Nd XRF	
				%	%	%	%	%	%	%	%
BR-8-06	19.40	25.65	6.25	OX-MI	GN	6.08	1.58	1.480	0.35		
BR-8-07	25.65	26.20	0.55	CB		1.53	0.47	0.390	0.11		
BR-8-08	26.20	34.05	7.15	OX-MI	GN	1.26	1.26	1.330	0.29		
BR-8-09	34.05	37.10	3.05	CB		3.51	1.50	1.520	0.28		
BR-8-10	37.10	39.55	2.45	OX-MI	GN	2.31	0.38	0.270	0.11		
BR-8-11	39.55	42.35	2.80	CB		3.29	0.80	0.650	0.21		
BR-8-12	42.35	47.10	4.75	CB		2.08	0.76	0.660	0.18		
BR-8-13	47.10	50.40	3.30	CB	FRESH	3.63	0.94	0.760	0.24		
BR-9-01	8.45	9.45	1.00	OX-MI	GN	4.22	0.30	0.140	0.13		
BR-9-02	14.50	15.25	0.75	OX-MI	GN	2.81	1.25	0.880	0.37		
BR-9-03	25.20	27.70	2.50	OX-MI	GN	2.43	0.55	0.300	0.21		
BR-9-04	27.70	29.00	1.30	CB		1.78	0.37	0.180	0.15		
BR-9-05	29.00	31.40	2.40	CB		0.57	0.21	0.097	0.07		
BR-9-06	31.40	32.70	1.30	ORE		3.69	0.73	0.490	0.25		
BR-9-07	32.70	34.80	2.10	OX-MI	GN	6.71	0.94	0.610	0.30		
BR-9-08	34.80	38.40	3.60	FE-CB		5.91	1.36	1.280	0.29		
BR-9-09	38.40	39.10	0.70	CB		2.55	0.49	0.430	0.12		
BR-9-10	39.10	40.70	1.60	OX-MI	GN	1.69	0.49	0.500	0.10		
BR-9-11	46.40	50.40	4.00	CB	FRESH	0.63	0.26	0.150	0.09		
BR-10-01	6.30	10.50	4.20	WETH	MAT	4.18	1.82	1.870	0.39		
BR-10-02	10.50	14.90	4.40	OX-MI	GN	2.54	0.82	0.600	0.23		
BR-10-03	14.90	15.90	1.00	GOSSAN		3.76	0.97	0.760	0.31		
BR-10-04	17.30	22.50	5.20	WETH	MAT	5.88	1.43	1.260	0.36		
BR-10-05	22.50	25.60	3.10	OX-MI	GN	3.32	0.43	0.290	0.17		
BR-10-06	25.60	28.20	2.60	CB		4.10	1.87	1.660	0.42		
BR-10-07	28.20	32.80	4.60	FE-CB		3.86	1.39	1.220	0.33		
BR-10-08	32.80	36.30	3.50	FE-CB		3.02	1.15	0.970	0.23		
BR-10-09	37.00	43.40	6.40	CB		1.84	0.47	0.310	0.13		
BR-10-10	43.40	46.10	2.70	CB		1.44	0.21	0.120	0.06		
BR-10-11	46.10	48.20	2.10	CB		2.96	1.36	1.050	0.29		
BR-10-12	48.20	50.40	2.20	FE-CB		5.35	1.70	1.560	0.37		
BR-11-01	0.50	4.50	4.00	WETH	MAT	4.77	1.15	1.070	0.35		
BR-11-02	4.50	11.20	6.70	WETH	MAT	3.87	1.42	1.440	0.37		
BR-11-03	11.20	17.90	6.70	WETH	MAT	3.76	1.26	1.400	0.28		
BR-11-04	17.90	22.50	4.60	GOSSAN		1.85	0.26	0.150	0.09		
BR-11-05	22.50	24.10	1.60	CB		1.49	0.36	0.220	0.12		
BR-11-06	24.10	30.15	6.05	GOSSAN		8.09	1.29	1.450	0.28		
BR-11-07	30.15	35.45	5.30	CB		1.57	0.42	0.330	0.11		
BR-11-08	35.45	39.80	4.35	FE-CB		1.47	0.70	0.400	0.27		
BR-11-09	39.80	46.00	6.20	FF-CB		5.43	0.58	0.330	0.22		

Apx. 14 Results of Chemical Analysis of Drill Core Samples — Ore Level Analysis —







SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF		Ce XRF		La XRF		Nd XRF	
				%	%	%	%	%	%	%	%
BR-11-10	36.00	38.10	2.10	CB	2.94	1.02	0.980	0.21			
BR-11-11	38.10	38.65	0.55	MN-FE ORE	1.72	0.27	0.988	0.23			
BR-11-12	38.65	41.95	3.30	CB	2.88	0.73	0.580	0.21			
BR-11-13	43.30	45.00	1.70	CB FRESH	5.78	1.34	1.020	0.42			
BR-11-14	45.00	50.30	5.30	CB FRESH	2.30	0.83	0.880	0.15			
BR-12-01	9.00	13.60	4.60	OX-MI GN	9.17	0.72	0.400	0.31			
BR-12-02	13.60	13.90	0.30	ORE	0.82	0.20	0.084	0.06			
BR-12-03	16.50	17.10	0.60	ORE	1.59	0.48	0.250	0.18			
BR-12-04	17.80	18.70	0.90	ORE	1.53	0.28	0.076	0.17			
BR-12-05	26.70	31.70	5.00	OX-MI GN	3.42	0.70	0.350	0.26			
BR-12-06	31.70	34.90	3.20	OX-MI GN	4.50	0.88	0.620	0.28			
BR-12-07	34.90	41.35	6.45	GOSSAN	4.49	1.50	1.610	0.31			
BR-12-08	41.35	44.70	3.35	CB	3.52	0.59	0.450	0.17			
BR-12-09	44.90	48.20	3.30	CB	5.45	0.69	0.550	0.18			
BR-12-10	48.20	49.70	1.50	FE-CB	5.78	1.68	1.390	0.42			
BR-12-11	50.10	50.40	0.30	FE-CB	4.59	1.31	1.260	0.25			
BR-13-01	0.50	3.40	2.90	GOSSAN	4.59	0.91	0.780	0.24			
BR-13-02	3.40	7.70	4.30	WETH MAT	3.73	0.80	0.670	0.21			
BR-13-03	21.30	23.30	2.00	OX-MI GN	5.43	0.39	0.210	0.22			
BR-13-04	23.30	26.35	3.05	CB	4.04	0.32	0.130	0.21			
BR-13-05	26.35	27.75	1.40	MN-FE ORE	5.69	0.32	0.110	0.30			
BR-13-06	27.75	29.15	1.40	MN-FE ORE	5.94	0.59	0.190	0.45			
BR-13-07	29.15	30.80	1.65	FE-CB	5.60	0.70	0.370	0.37			
BR-13-08	30.80	31.55	0.75	MN-FE ORE	5.73	0.54	0.160	0.43			
BR-13-09	31.55	34.80	3.25	MN-FE ORE	7.08	0.65	0.290	0.36			
BR-13-10	34.80	39.80	5.00	CB FRESH	7.34	1.56	1.200	0.44			
BR-13-11	40.40	42.20	1.80	CB FRESH	7.44	1.69	1.720	0.33			
BR-13-12	42.50	46.10	3.60	CB FRESH	2.13	0.44	0.300	0.15			
BR-13-13	46.10	48.10	2.00	CB FRESH	7.60	0.95	0.840	0.31			
BR-13-14	48.10	50.40	2.30	CB FRESH	4.58	1.38	1.200	0.35			
BR-14-01	0.00	1.40	1.40	WETH MAT	3.13	0.52	0.320	0.22			
BR-14-02	1.40	4.15	2.75	WETH MAT	1.93	0.48	0.430	0.12			
BR-14-03	4.15	4.90	0.75	ORE	0.96	0.23	0.039	0.21			
BR-14-04	8.05	8.25	0.20	ORE	1.48	1.05	0.420	0.41			
BR-14-05	8.60	10.65	2.05	CB	4.17	1.02	1.030	0.19			
BR-14-06	11.50	12.15	0.65	CB	4.16	1.80	0.790	0.73			
BR-14-07	12.15	13.30	1.15	ORE	2.43	0.94	0.750	0.25			
BR-14-08	38.00	40.90	2.90	SIL GN	0.69	0.60	0.430	0.18			
BR-15-01	11.70	12.10	0.40	ORE	3.83	0.30	0.061	0.28			
BR-15-02	15.70	16.45	0.25	ORE	4.57	0.67	0.300	0.27			

Apx. 14 Results of Chemical Analysis of Drill Core Samples - Ore Level Analysis -







SAMPLE NUMBER	DEPTH OF SAMPLE (m)	WIDTH (m)	ROCK TYPE	Ba XRF %	Ce XRF %	La XRF %	Nd XRF %
BR-15-03	17.00 - 18.35	1.35	ORE	7.57	0.44	0.190	0.24
BR-15-04	23.40 - 25.00	1.60	GOSSAN	7.97	1.65	1.440	0.38
BR-15-05	25.00 - 25.90	0.90	CB	6.04	1.21	0.840	0.30
BR-15-06	25.90 - 29.90	4.00	ORE	8.26	0.88	0.390	0.36
BR-15-07	37.70 - 39.25	1.55	MN-FE ORE	5.86	0.46	0.160	0.26
BR-15-08	42.00 - 43.20	1.20	MN-FE ORE	5.02	0.55	0.150	0.28
BR-15-09	43.20 - 43.90	0.70	CB	6.59	1.10	0.610	0.35
BR-16-01	12.90 - 13.50	0.40	ORE	3.81	1.07	0.950	0.28
BR-16-02	14.90 - 16.00	1.10	OX-MI GN	6.99	0.36	0.220	0.20
BR-16-03	16.40 - 16.90	0.50	SI ORE	13.50	0.54	0.480	0.19

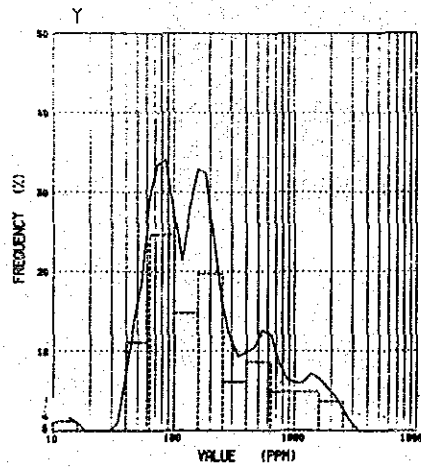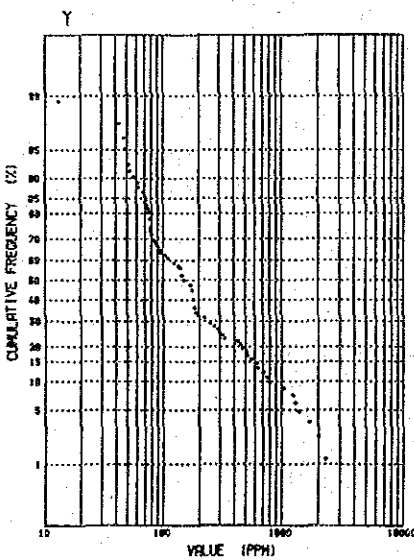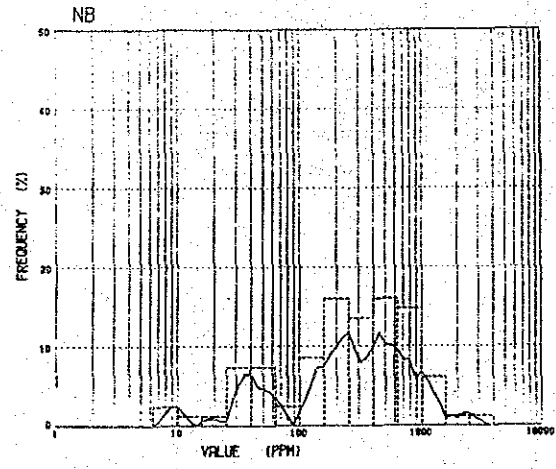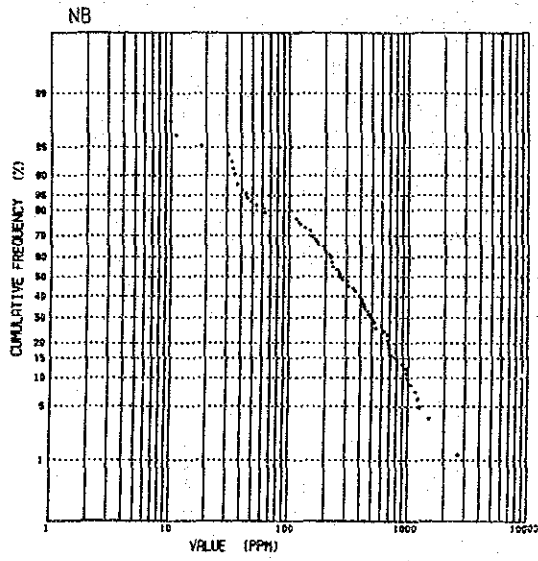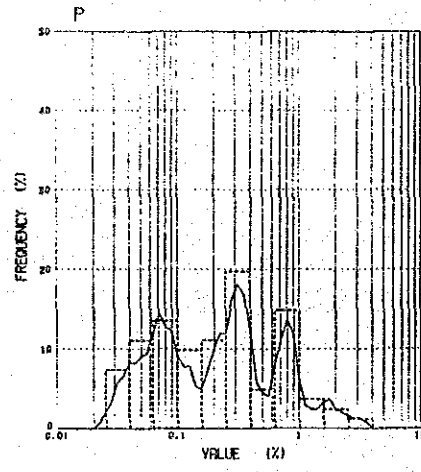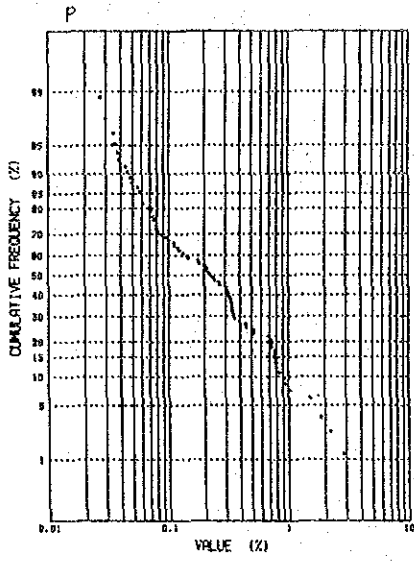

Apx. 15 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill North Sector –

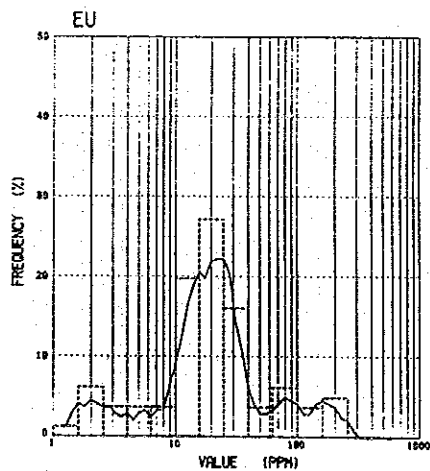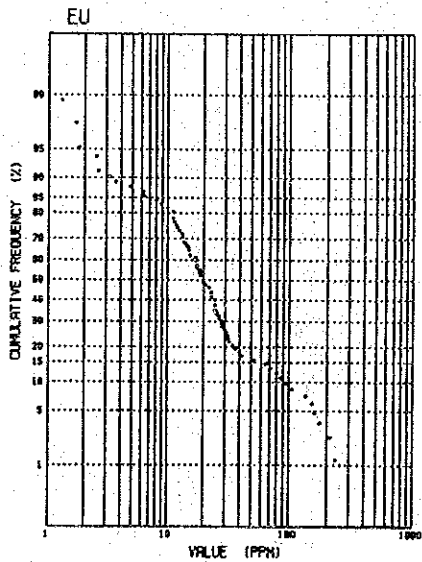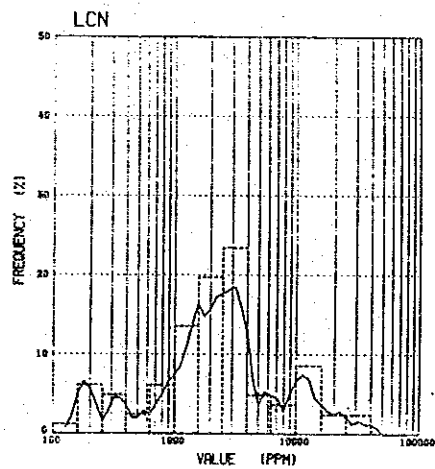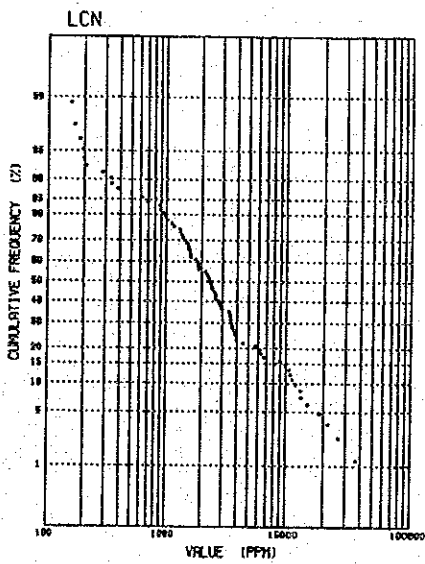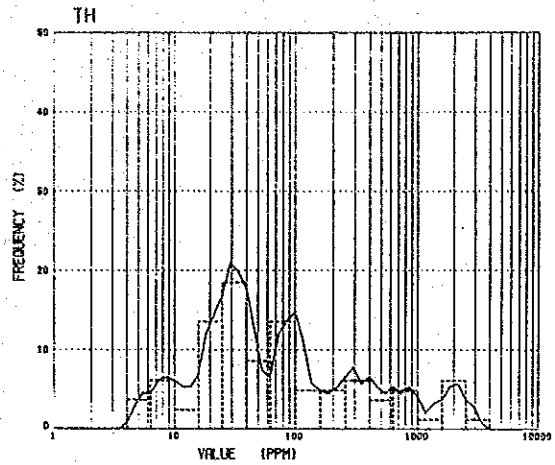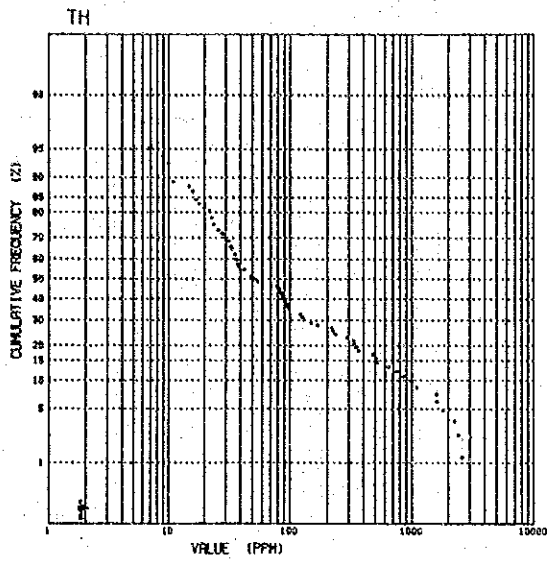


Apx. 15 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill North Sector –

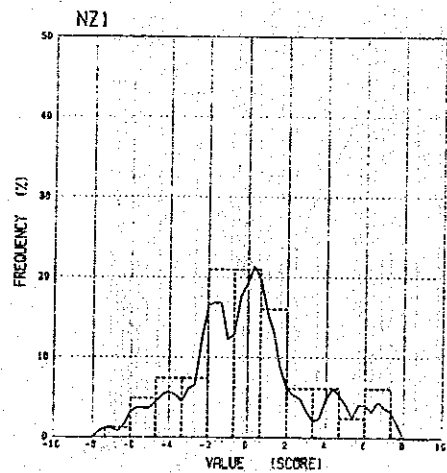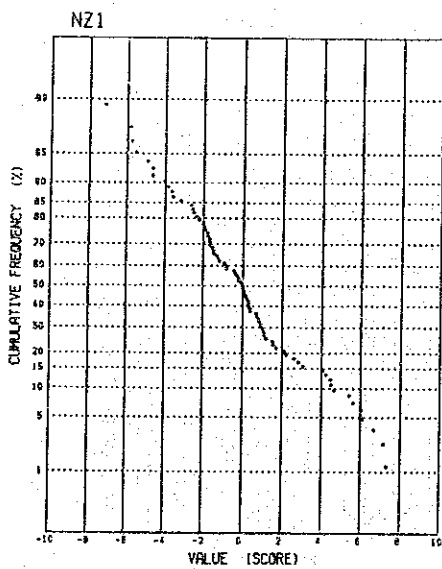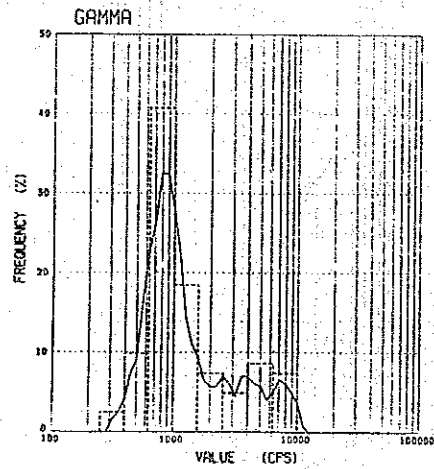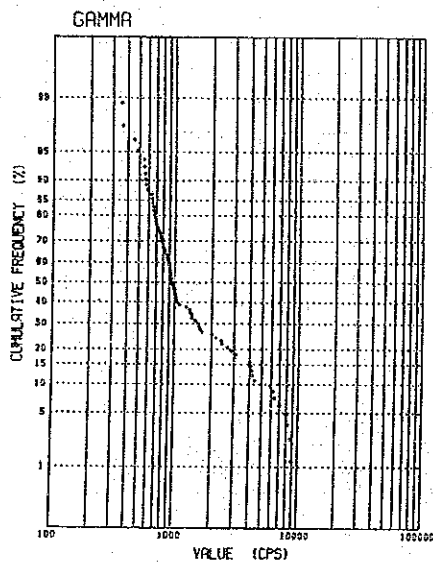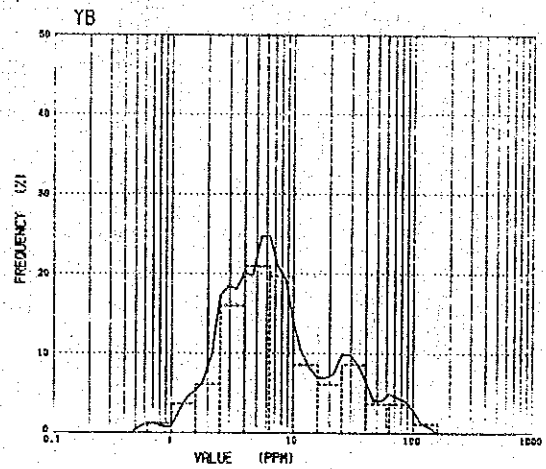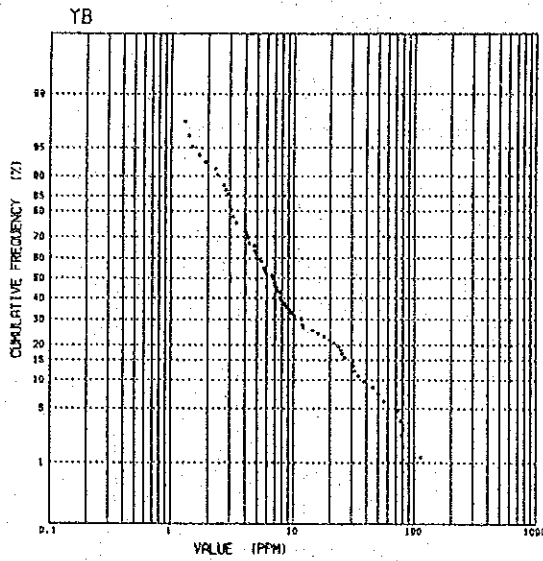





Apx. 15 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill North Sector –


NRHN AREA

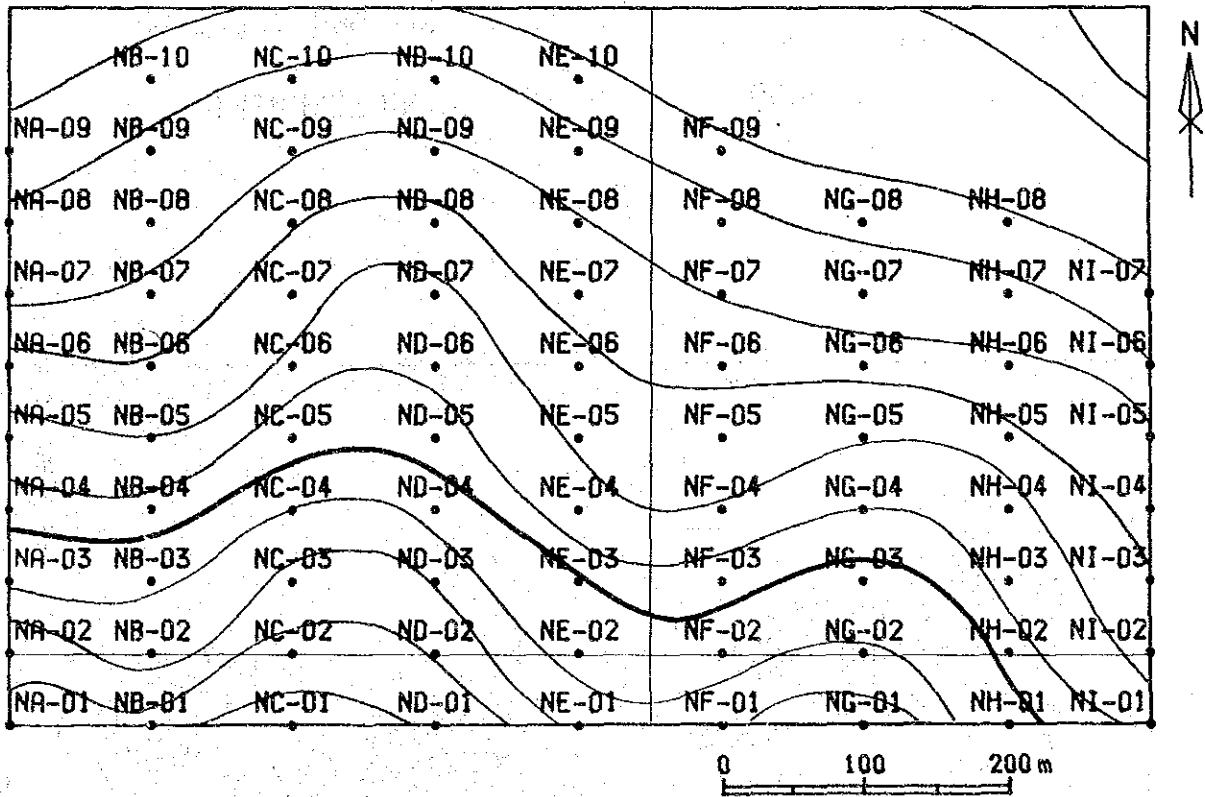

Apx. 16 Location Map of Geochemical Samples -- North Ruri Hill North Sector --

AREA NAME = NRHN
 FILE NAME = P
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 2.5
 MINIMUM = .2
 THRESHOLD = .56
 MAP SCALE = 1:5000


LEGEND
 ANOMALY ZONE
 THRESHOLD CONTOUR LINE
 CONTOUR LINE AND
 CONTOUR VALUE (%)
 SAMPLE POINT

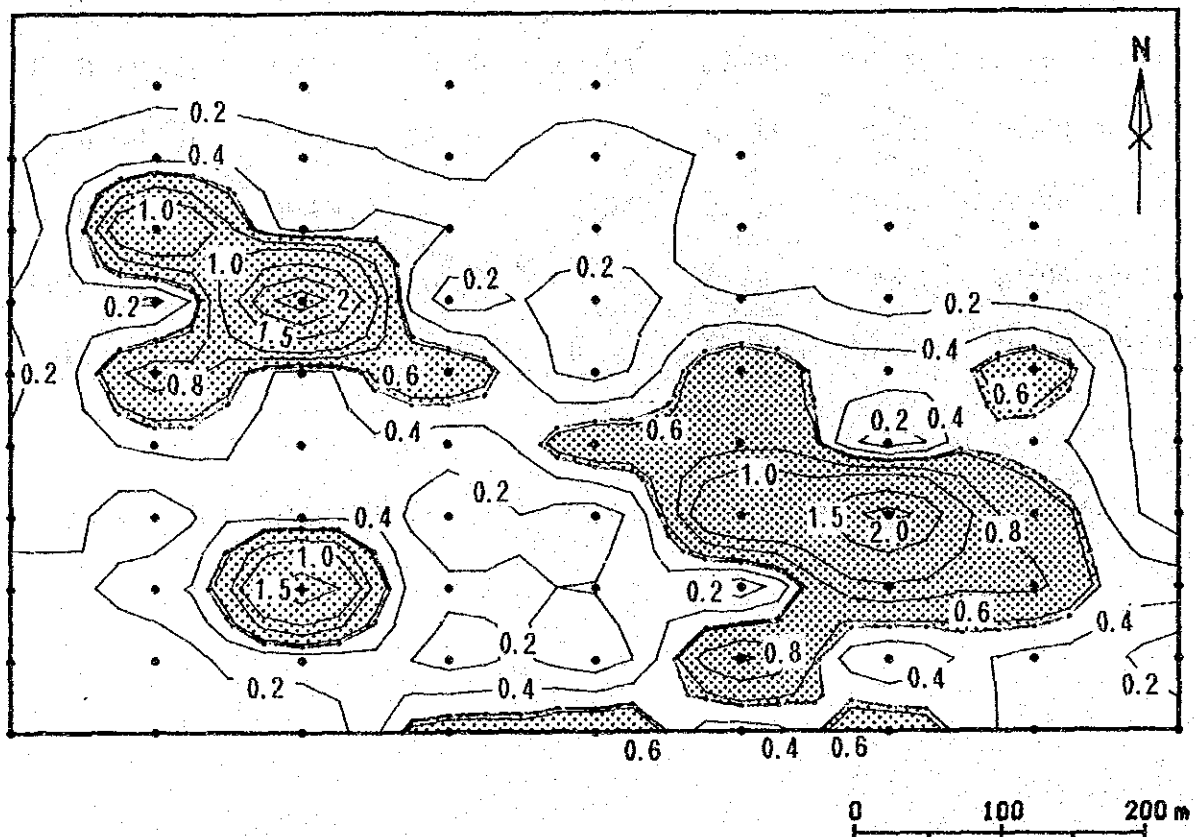

Apx. 17 Geochemical Density and Anomaly Map of P – North Ruri Hill North Sector –


AREA NAME = NRHN
 FILE NAME = NB
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 3000
 MINIMUM = 200
 THRESHOLD = 880
 MAP SCALE = 1:5000

LEGEND



ANOMALY ZONE

THRESHOLD CONTOUR LINE




CONTOUR LINE AND

CONTOUR VALUE (ppm)





SAMPLE POINT

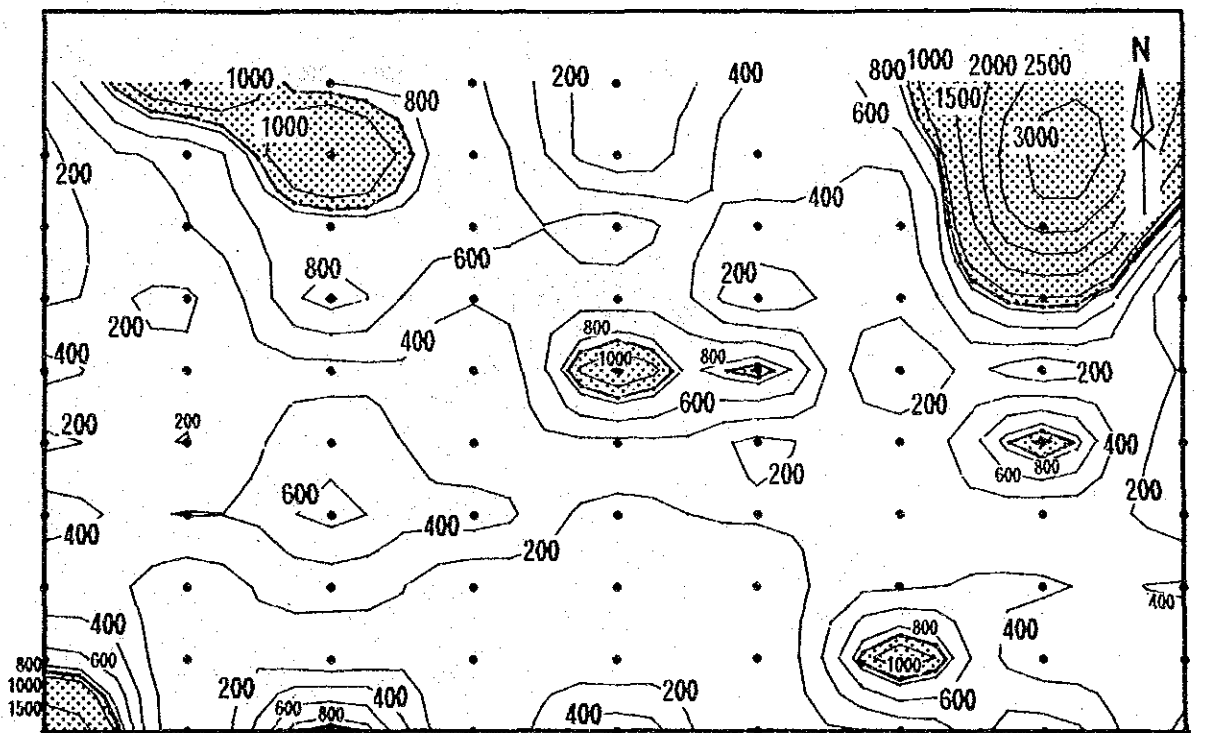

Apx. 18 Geochemical Density and Anomaly Map of Nb - North Ruri Hill North Sector -

AREA NAME = NRHN
 FILE NAME = Y
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 2000
 MINIMUM = 200
 THRESHOLD = 1000
 MAP SCALE = 1:5000

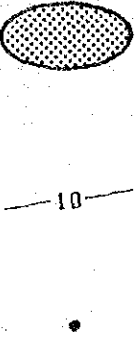LEGEND

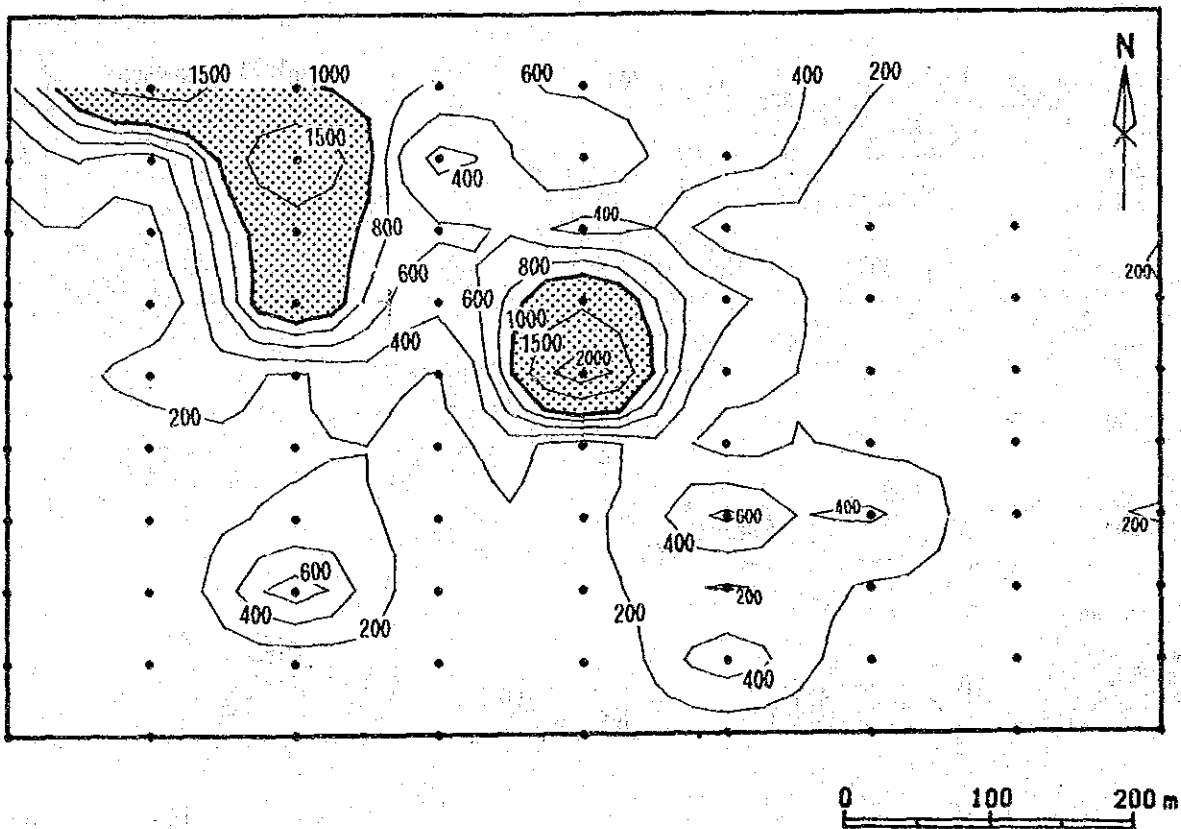 ANOMALY ZONE
 THRESHOLD CONTOUR LINE
 CONTOUR LINE AND
 CONTOUR VALUE (ppm)
 SAMPLE POINT



Apx. 19 Geochemical Density and Anomaly Map of Y - North Ruri Hill North Sector -

AREA NAME = NRHN

FILE NAME = TH

NO. OF SAMPLE = 81

CONTOUR VALUE

MAXIMUM = 2500

MINIMUM = 50

THRESHOLD = 1200


MAP SCALE = 1:5000

LEGEND



ANOMALY ZONE

THRESHOLD CONTOUR LINE





CONTOUR LINE AND

CONTOUR VALUE (ppm)




SAMPLE POINT

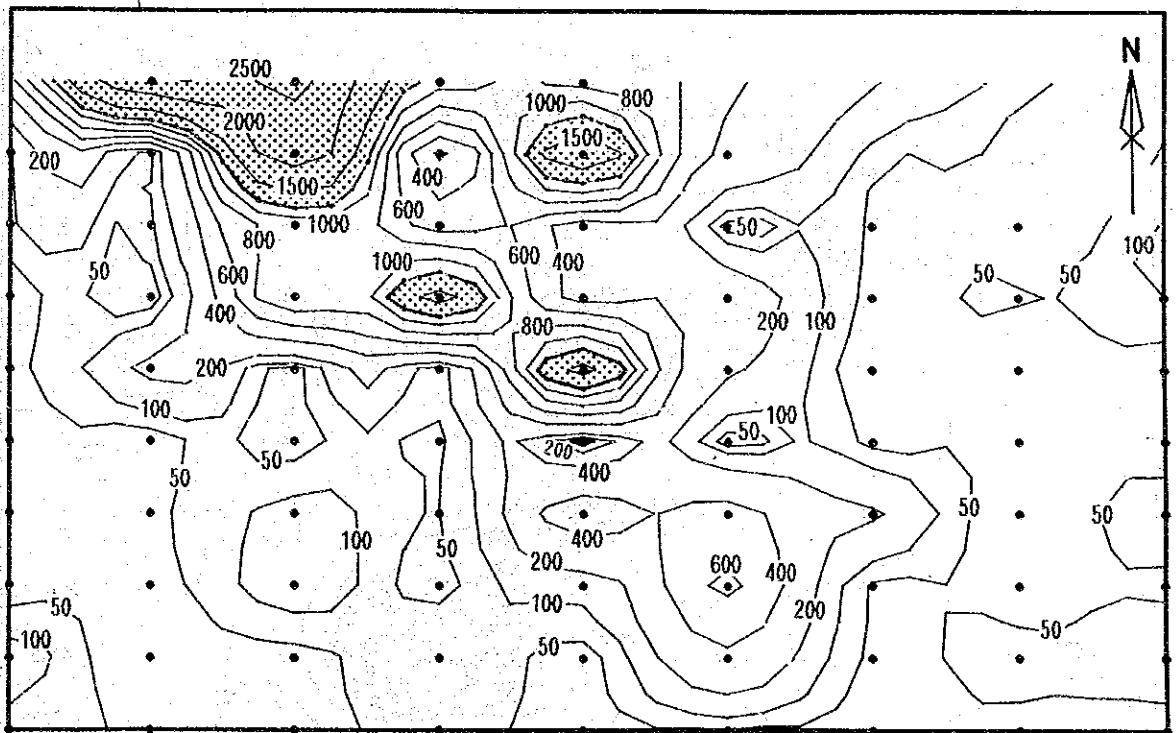

Apx. 20 Geochemical Density and Anomaly Map of Th - North Ruri Hill North Sector -


AREA NAME = NRHN
 FILE NAME = LCN
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 35000
 MINIMUM = 2000
 THRESHOLD = 8000
 MAP SCALE = 1:5000

LEGEND




ANOMALY ZONE

THRESHOLD CONTOUR LINE



CONTOUR LINE AND
CONTOUR VALUE (ppm)


• SAMPLE POINT

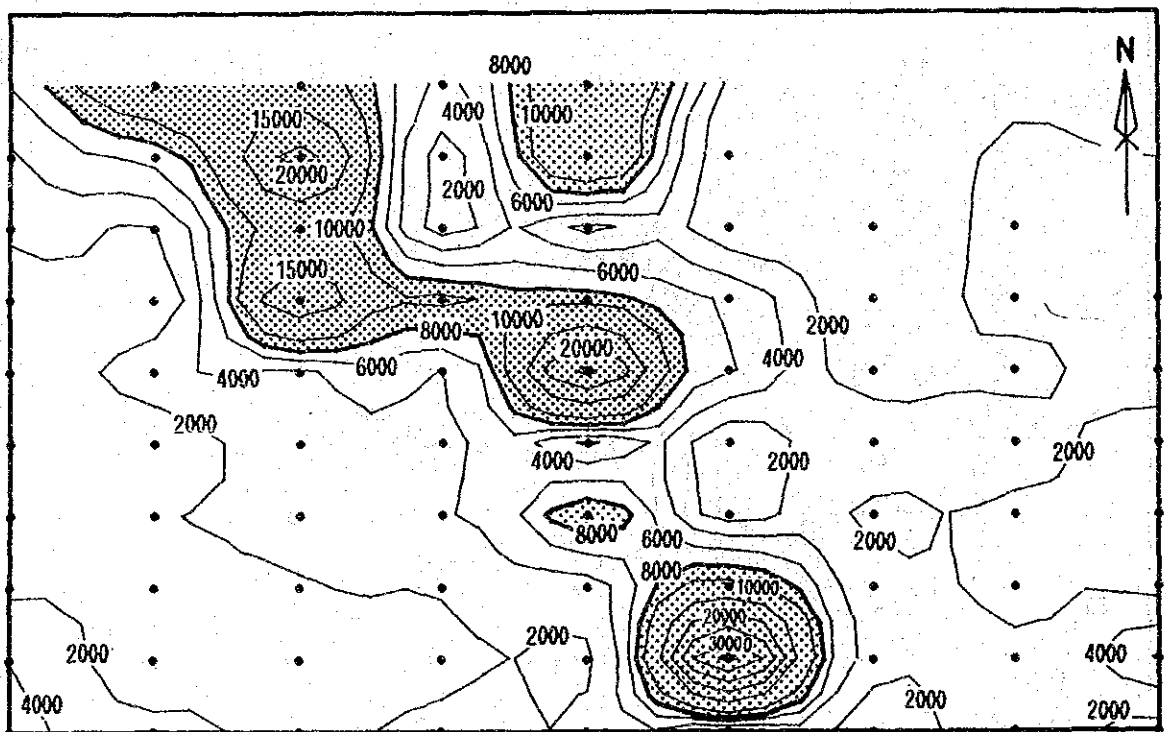

Apx. 21 Geochemical Density and Anomaly Map of La+Ce+Nd - North Ruri Hill North Sector -


AREA NAME = NRHN
 FILE NAME = EU
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 200
 MINIMUM = 20
 THRESHOLD = 50
 MAP SCALE = 1:5000

LEGEND



ANOMALY ZONE

THRESHOLD CONTOUR LINE




CONTOUR LINE AND

CONTOUR VALUE (ppm)






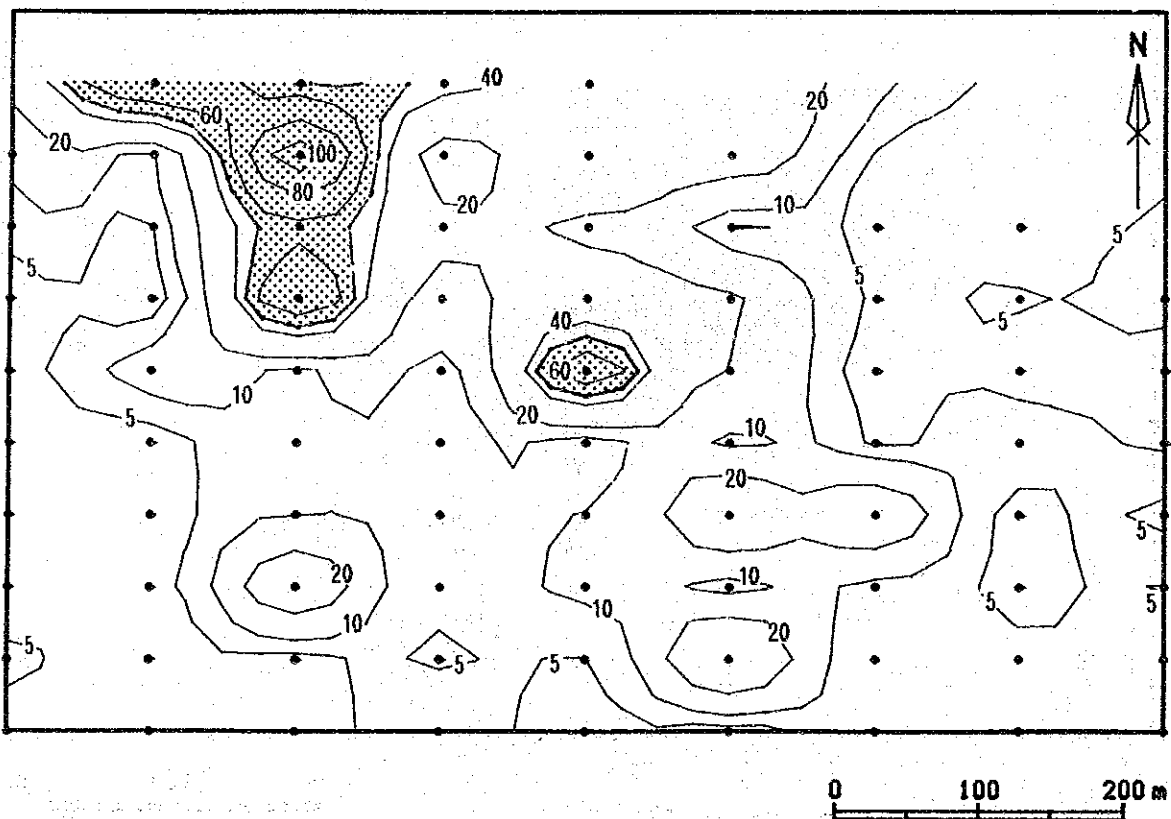
SAMPLE POINT

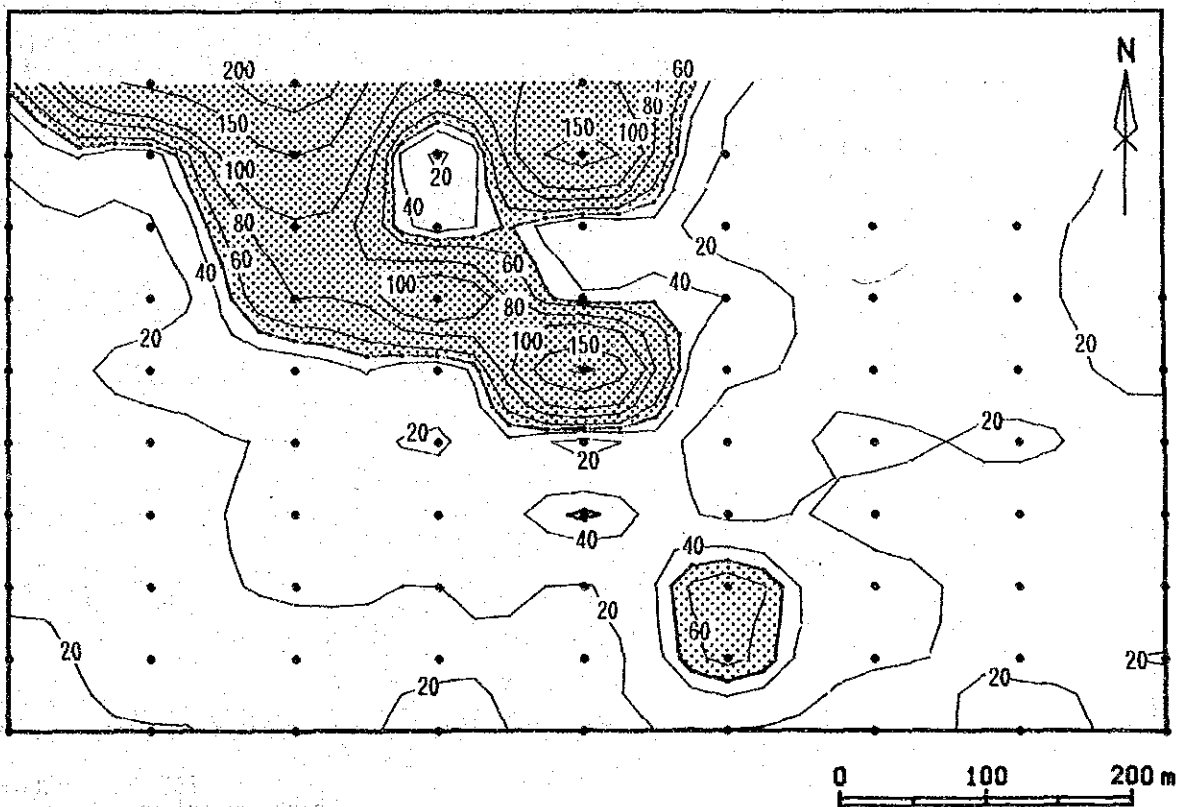

Apx. 22 Geochemical Density and Anomaly Map of Eu -North Ruri Hill North Sector --

AREA NAME = NRHN
 FILE NAME = YB
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 100
 MINIMUM = 5
 THRESHOLD = 49
 MAP SCALE = 1:5000





LEGEND
 ANOMALY ZONE
 THRESHOLD CONTOUR LINE
 CONTOUR LINE AND
 CONTOUR VALUE (ppm)
 SAMPLE POINT




Apx. 23 Geochemical Density and Anomaly Map of Yb - North Ruri Hill North Sector -

AREA NAME = NRHN
 FILE NAME = GAMMA
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 8000
 MINIMUM = 1000
 INTERVAL = 1000
 THRESHOLD = 3200
 MAP SCALE = 1:5000



LEGEND

-  ANOMALY ZONE
-  THRESHOLD CONTOUR LINE
-  CONTOUR LINE AND CONTOUR VALUE (cpe)
-  SAMPLE POINT






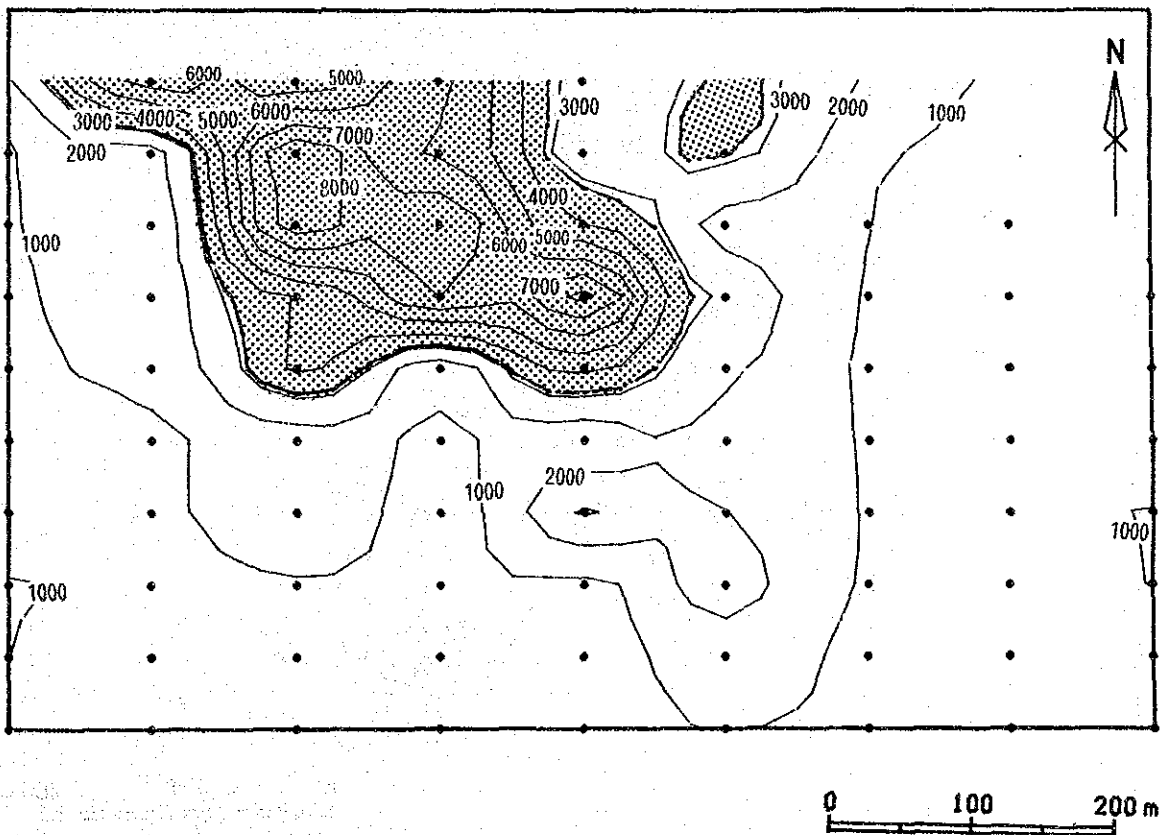


Apx. 24 Geochemical Density and Anomaly Map of γ -Ray — North Ruri Hill North Sector —







AREA NAME = NRHN
 FILE NAME = NZ1
 NO. OF SAMPLE = 81
 CONTOUR VALUE
 MAXIMUM = 7
 MINIMUM = 0
 INTERVAL = 1
 THRESHOLD = 3.3
 MAP SCALE = 1:5000

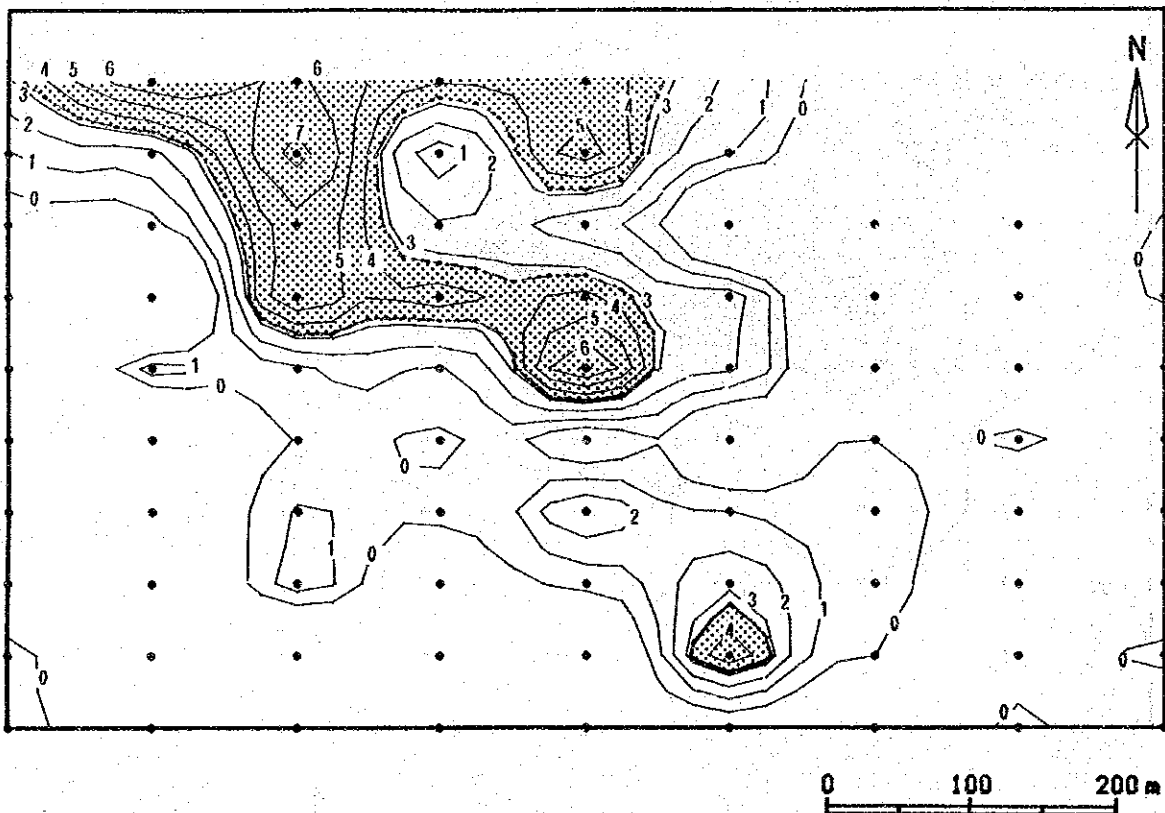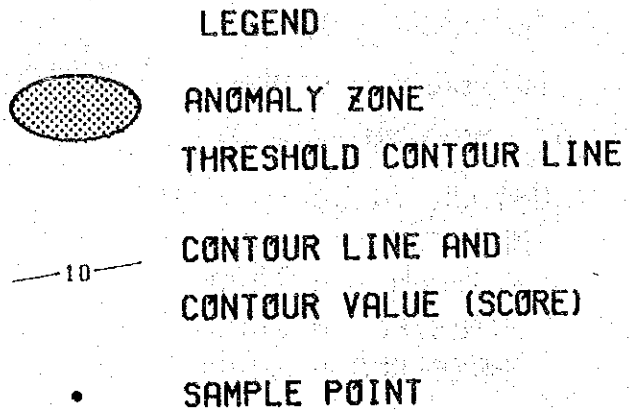







Apx. 25 Geochemical Density and Anomaly Map of Z1 Component -- North Ruri Hill
 North Sector --

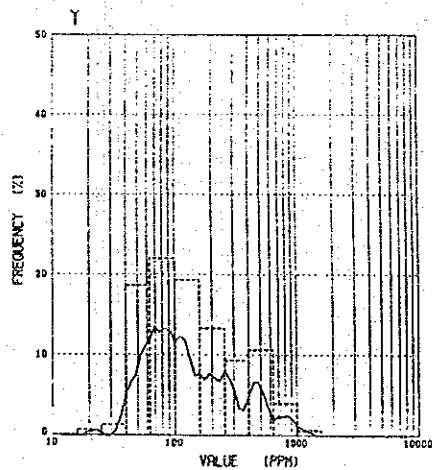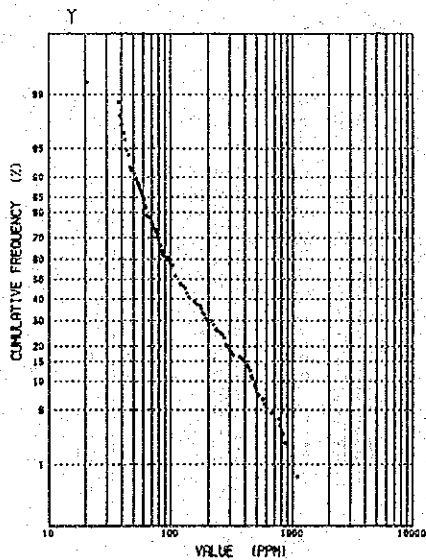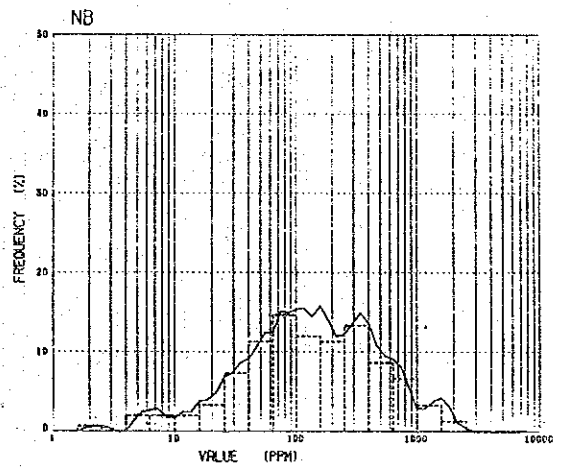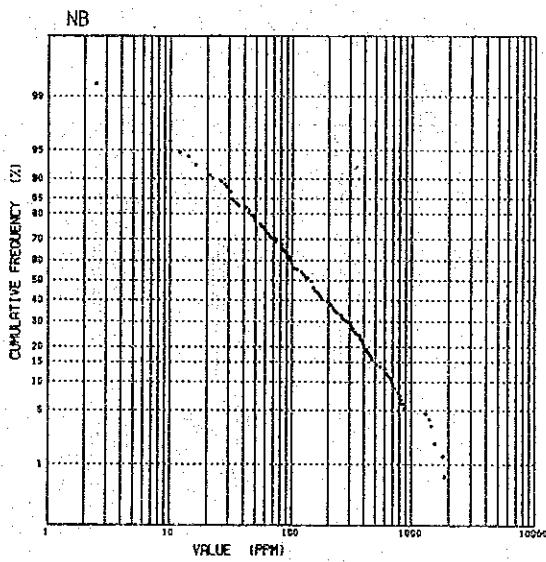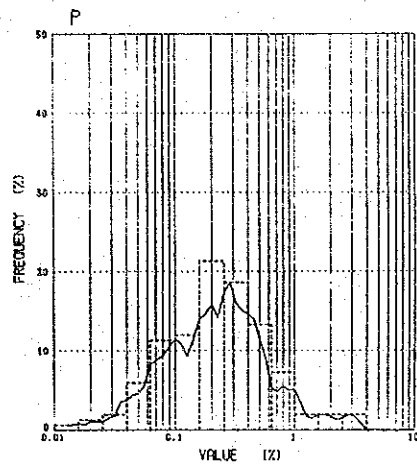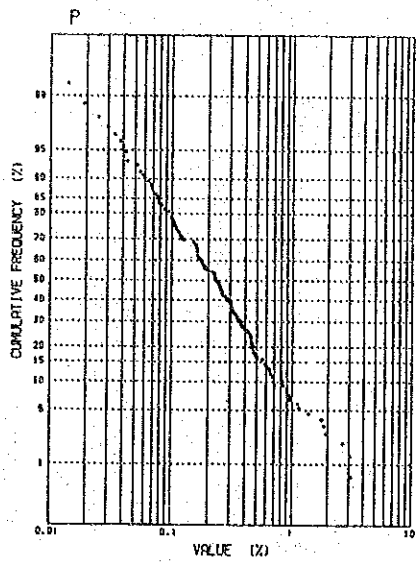


Apx. 26 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill South Sector –

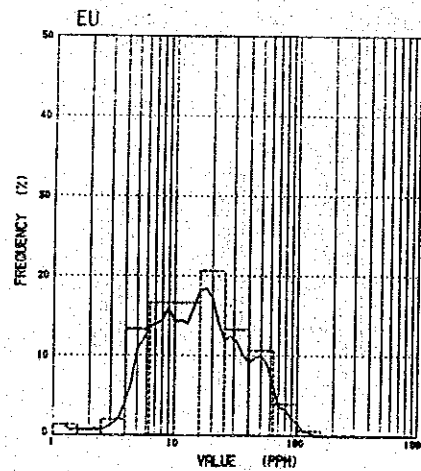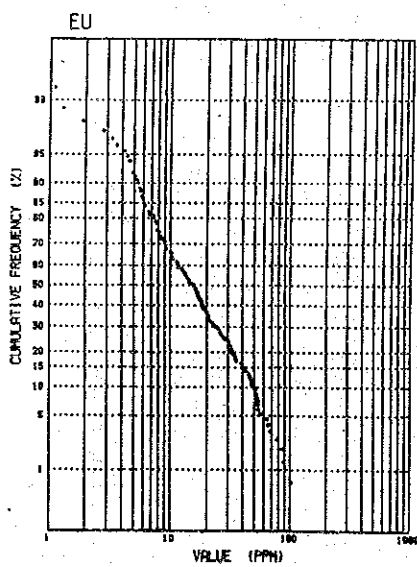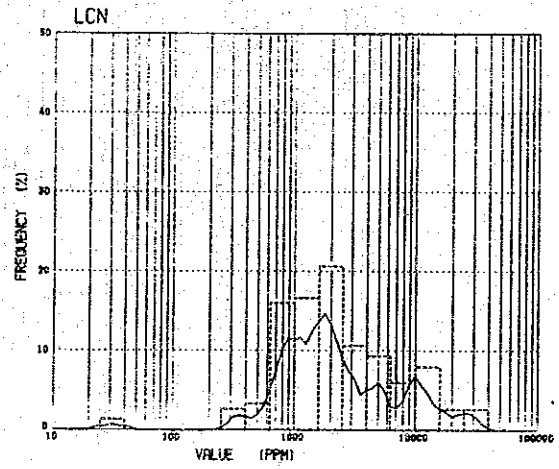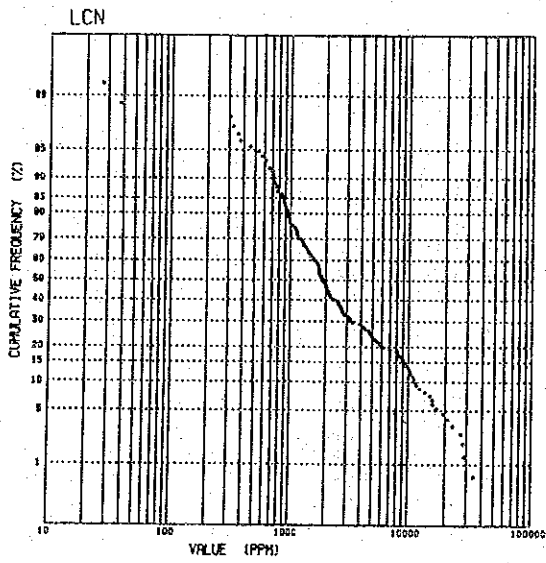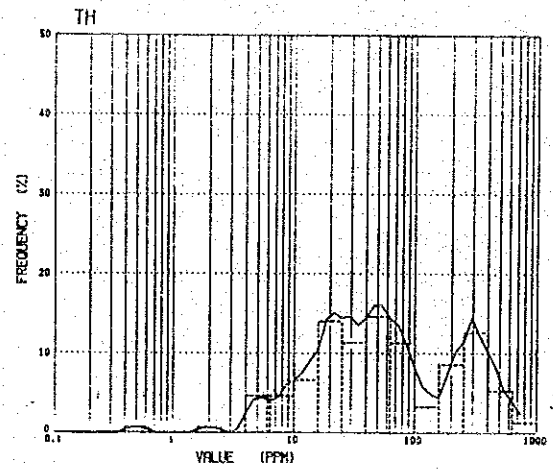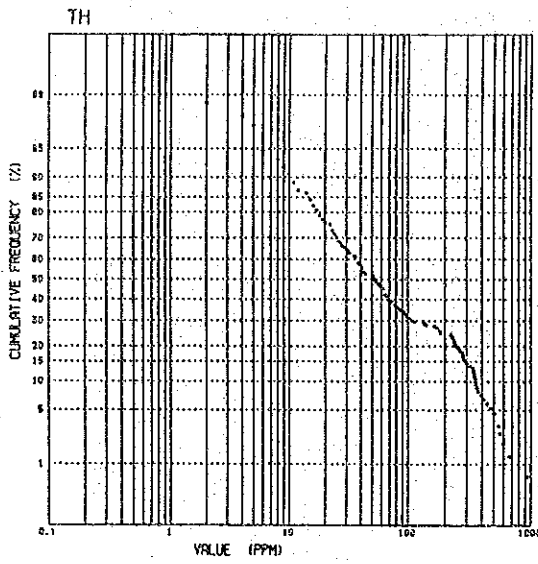

Apx. 26 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill South Sector –

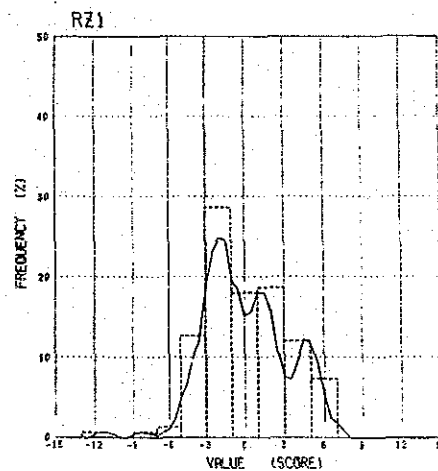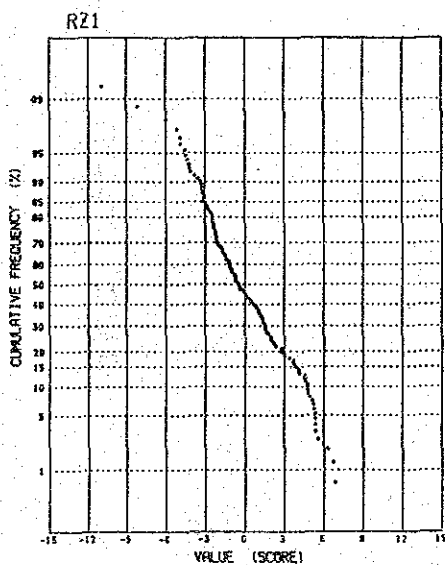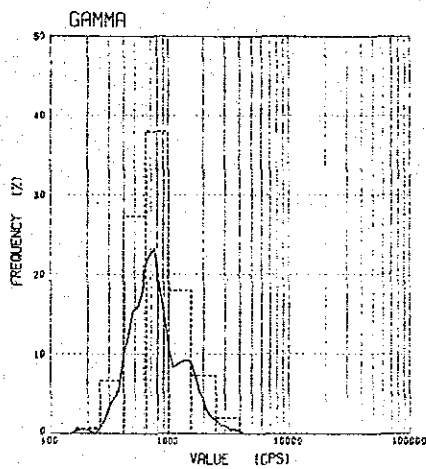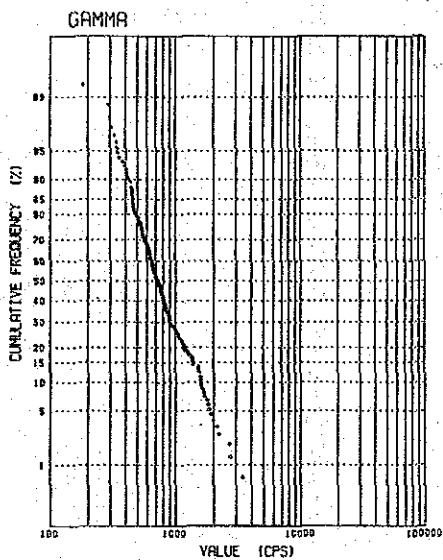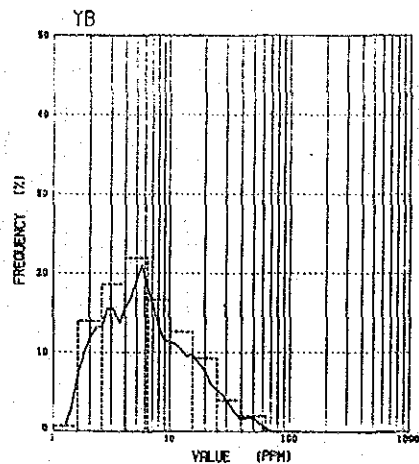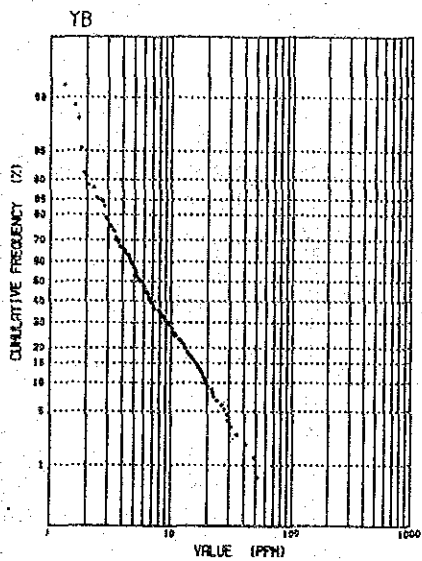


Apx. 26 Cumulative Frequency Distributions and Histograms of Elements – North Ruri Hill South Sector –

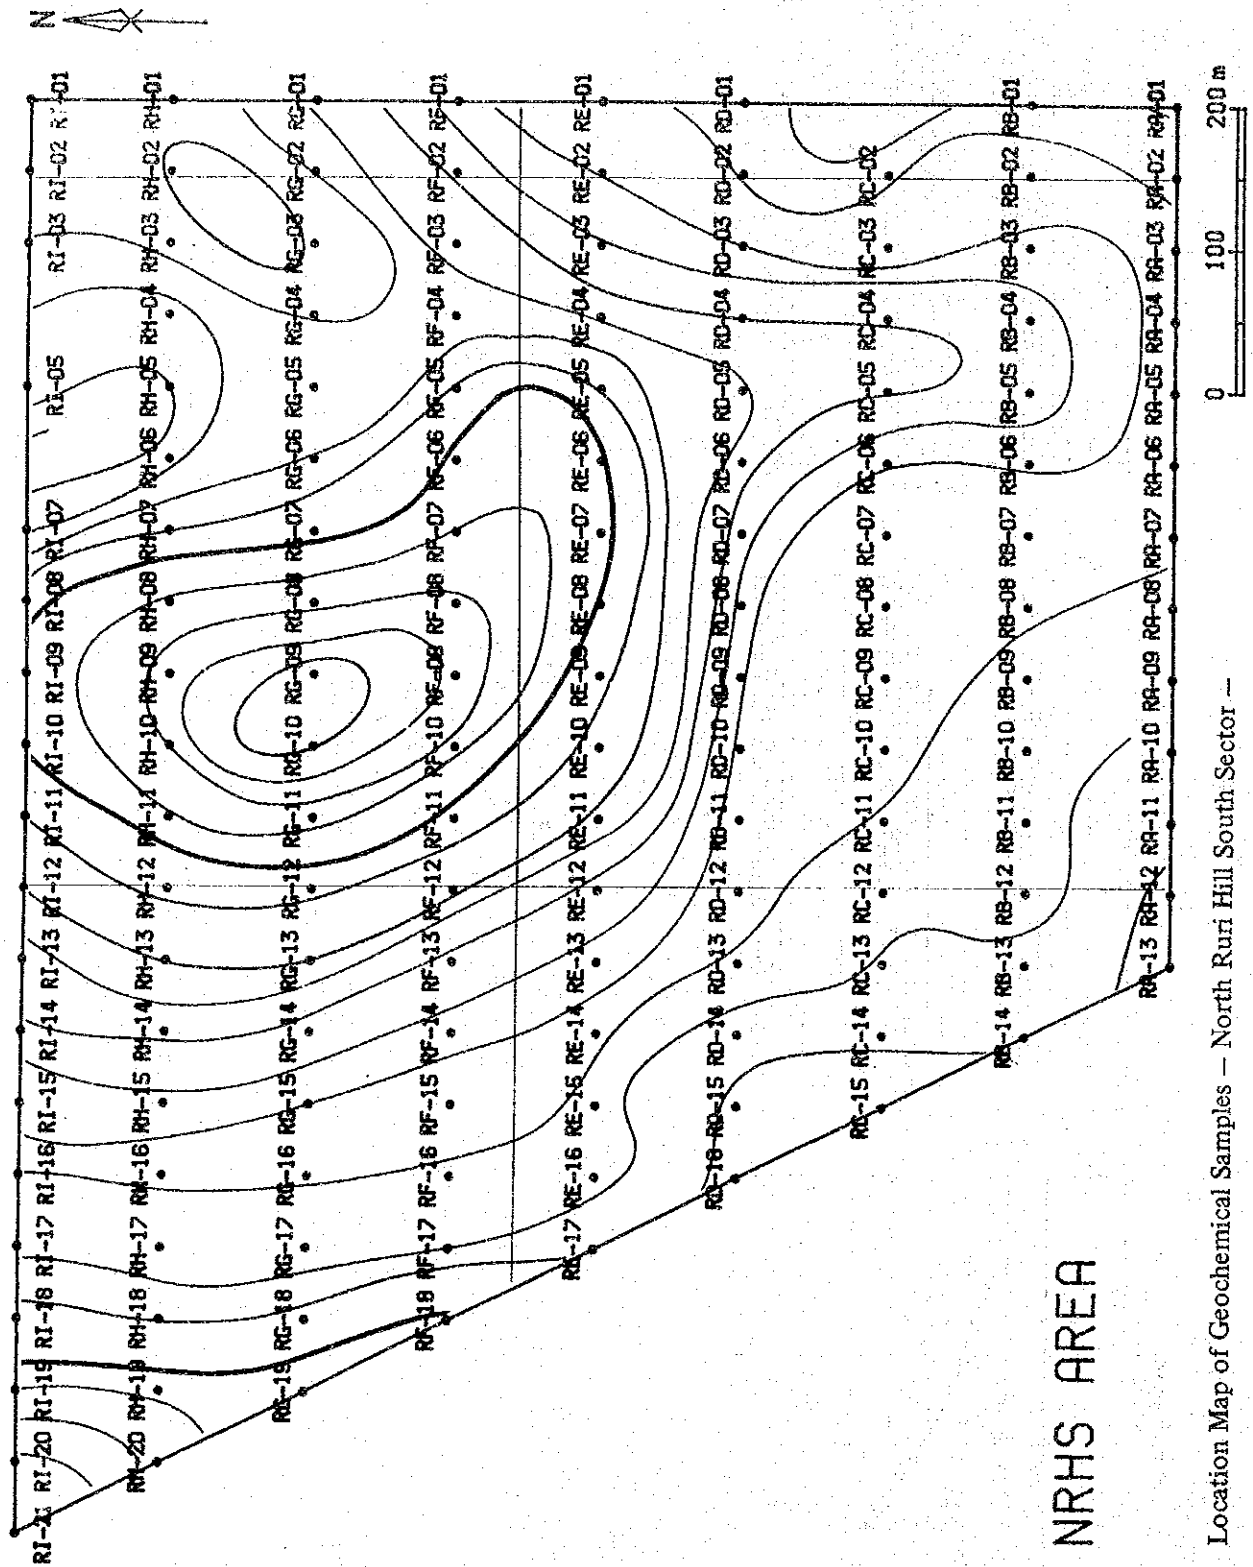


NRHS AREA

Apx. 27 Location Map of Geochemical Samples - North Ruri Hill South Sector -

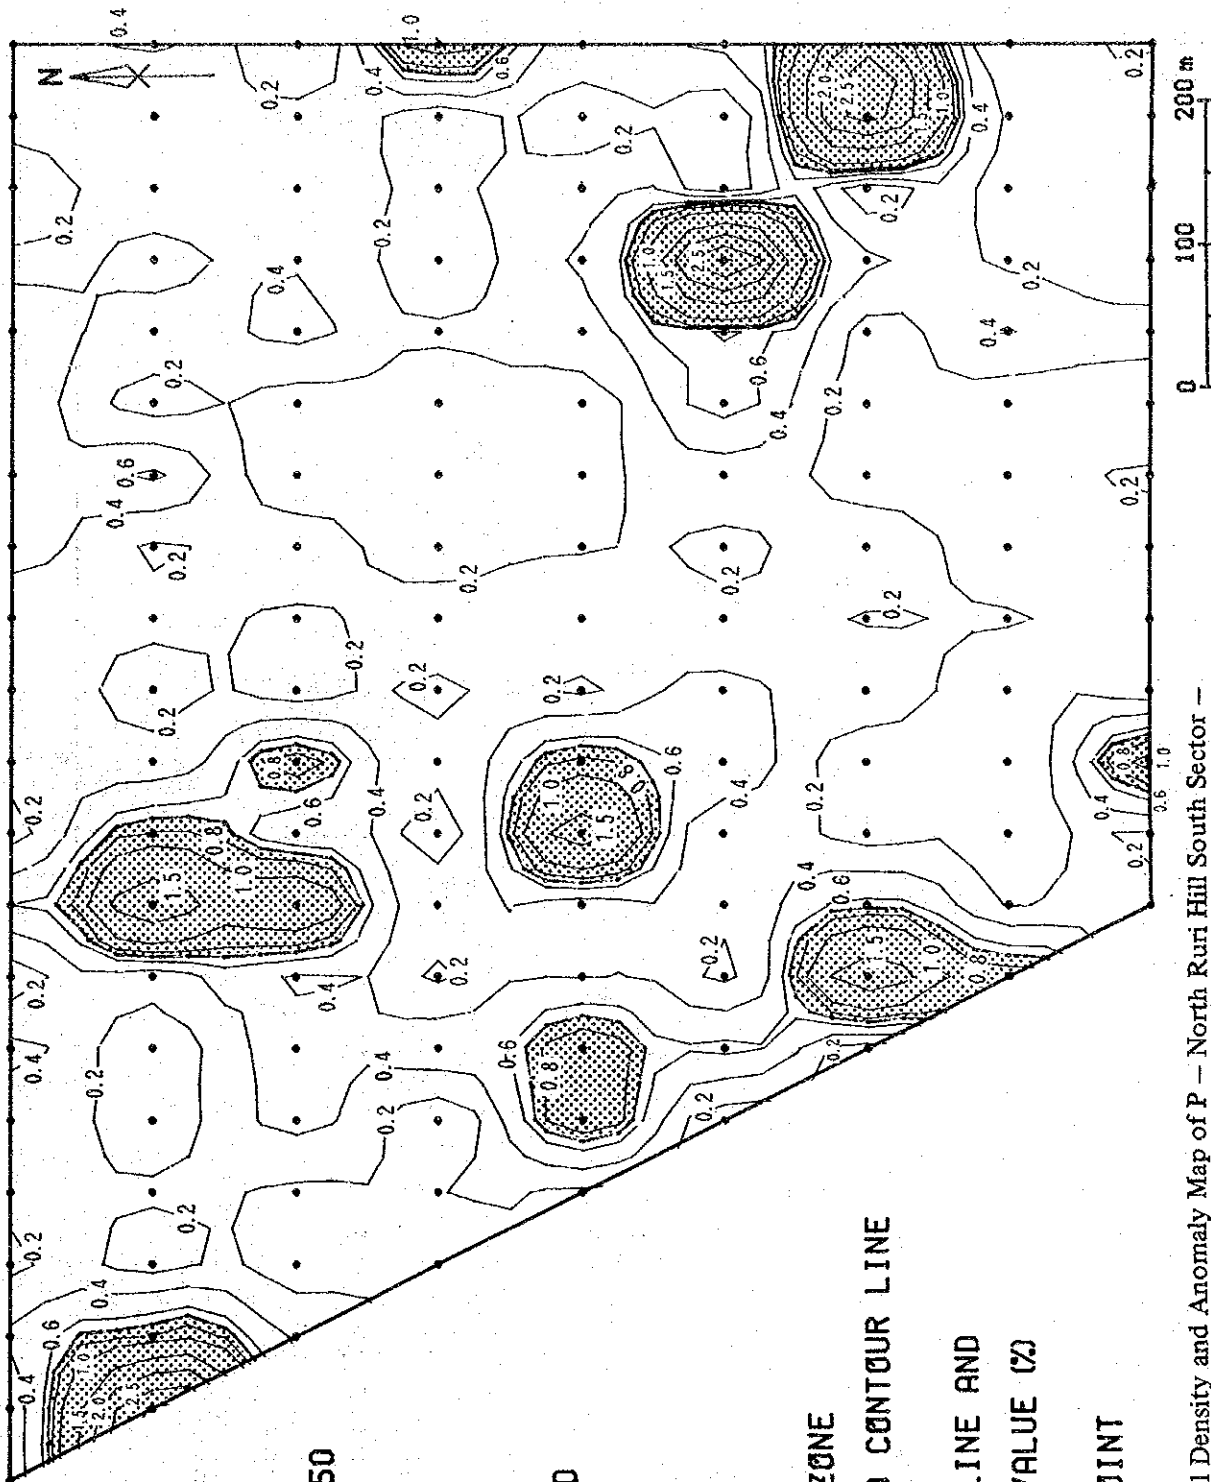


AREA NAME = NRHS
 FILE NAME = P
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 3
 MINIMUM = .2
 THRESHOLD = .7
 MAP SCALE = 1:5000

LEGEND





-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- CONTOUR LINE AND CONTOUR VALUE (%)
- SAMPLE POINT

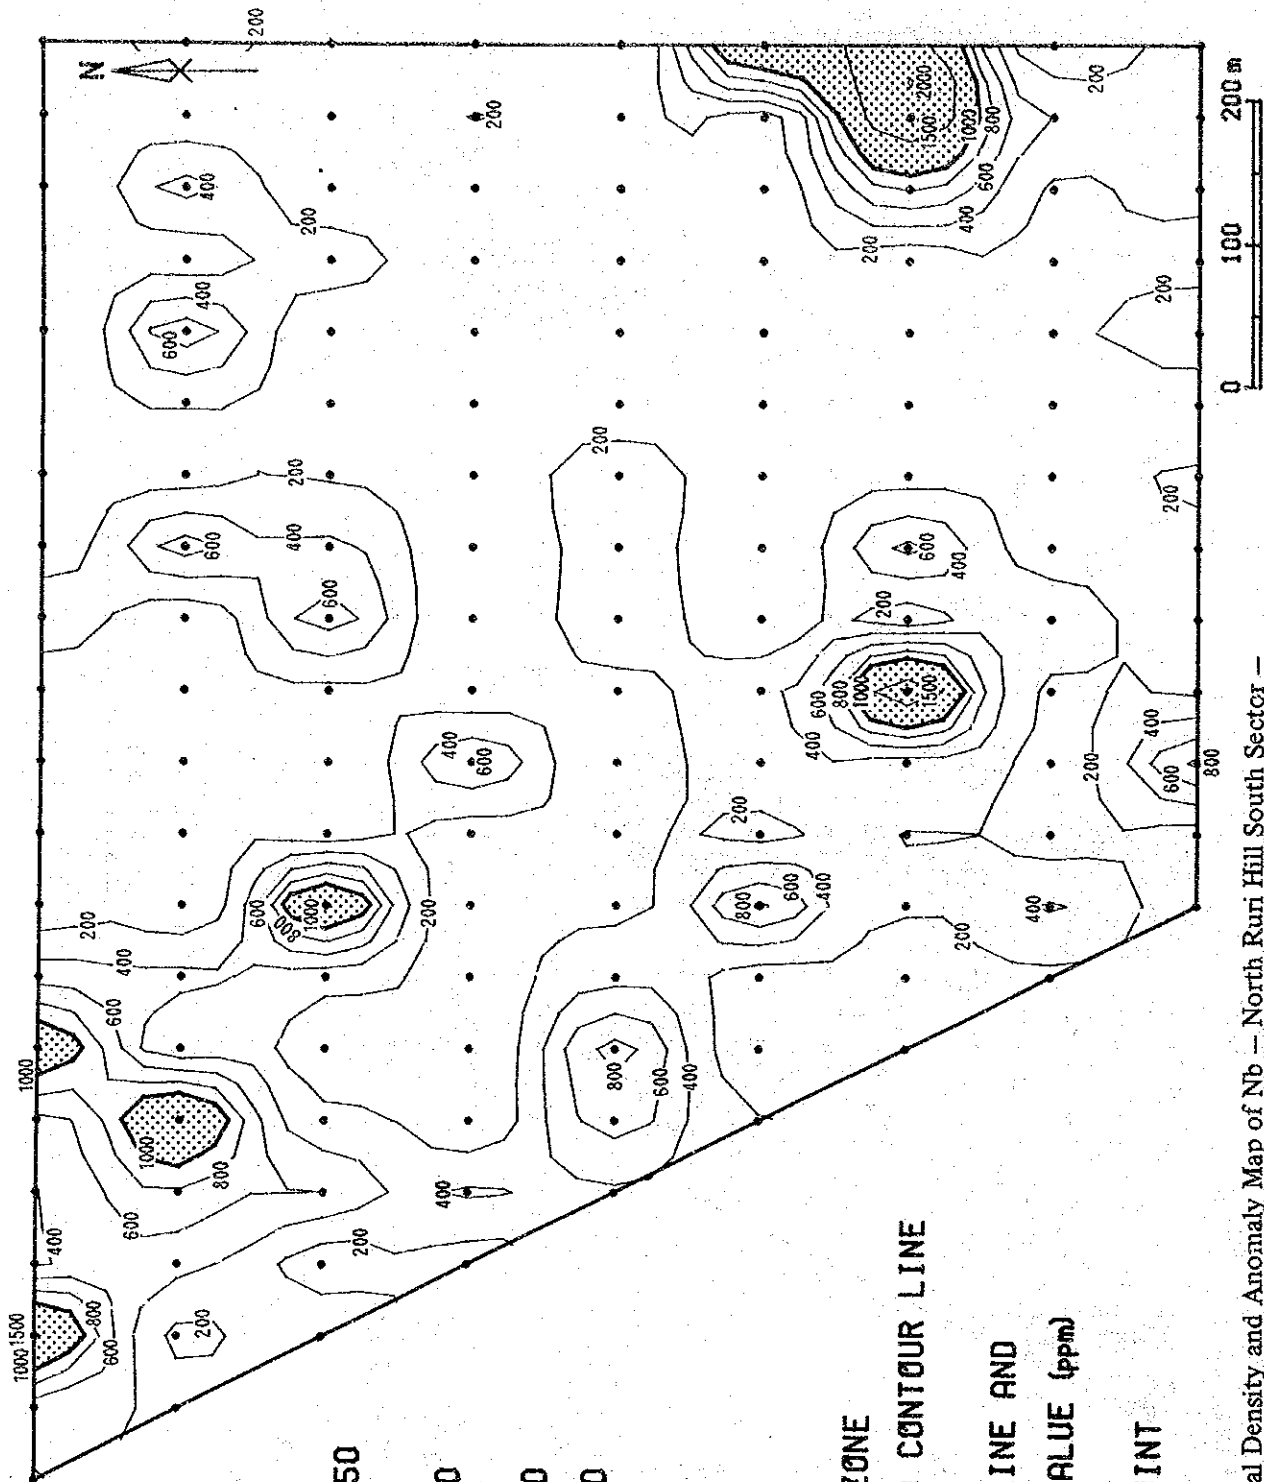
Apx. 28 Geochemical Density and Anomaly Map of P — North Ruri Hill South Sector —



AREA NAME = NRHS
 FILE NAME = NB
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 2000
 MINIMUM = 200
 THRESHOLD = 1000
 MAP SCALE = 1:5000





LEGEND

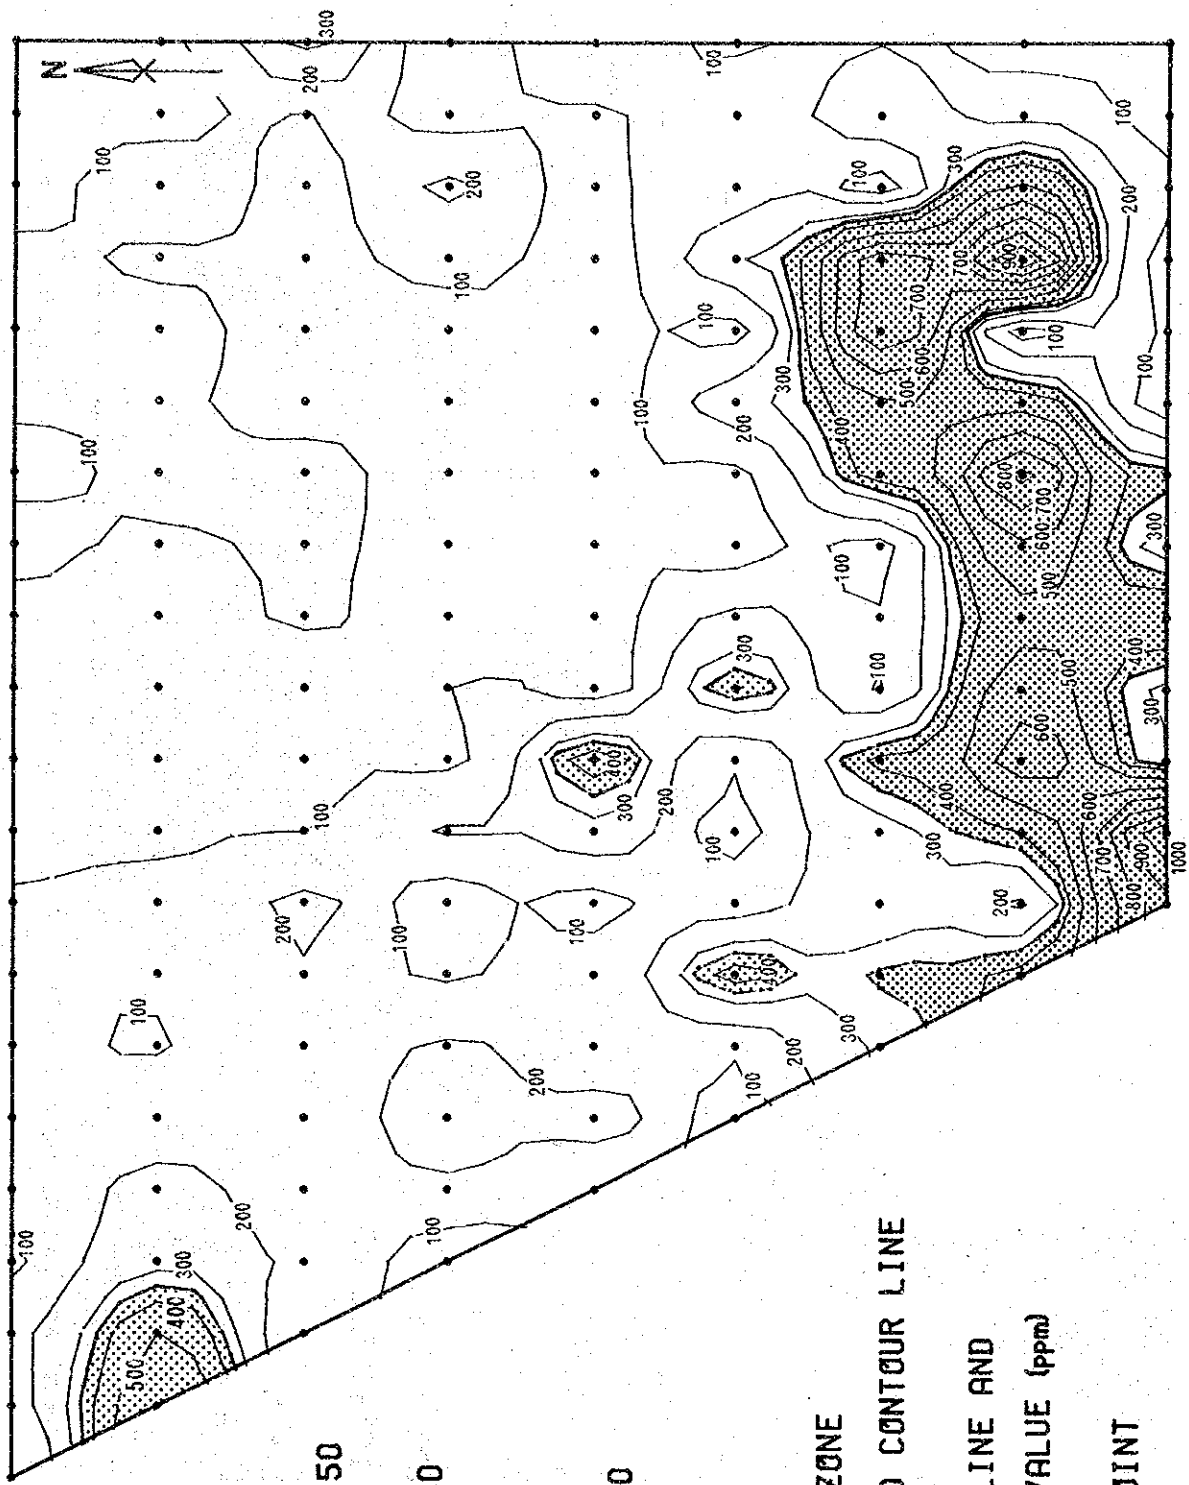- 
 ANOMALY ZONE
- 
 THRESHOLD CONTOUR LINE
- 
 CONTOUR LINE AND
 CONTOUR VALUE (ppm)
- 
 SAMPLE POINT




AREA NAME = NRHS
 FILE NAME = Y
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 1000
 MINIMUM = 100
 INTERVAL = 100
 THRESHOLD = 350
 MAP SCALE = 1:5000

LEGEND


-  ANOMALY ZONE
-  THRESHOLD CONTOUR LINE
-  CONTOUR LINE AND CONTOUR VALUE (ppm)
-  SAMPLE POINT

Apx. 30 Geochemical Density and Anomaly Map of Y - North Ruri Hill South Sector -

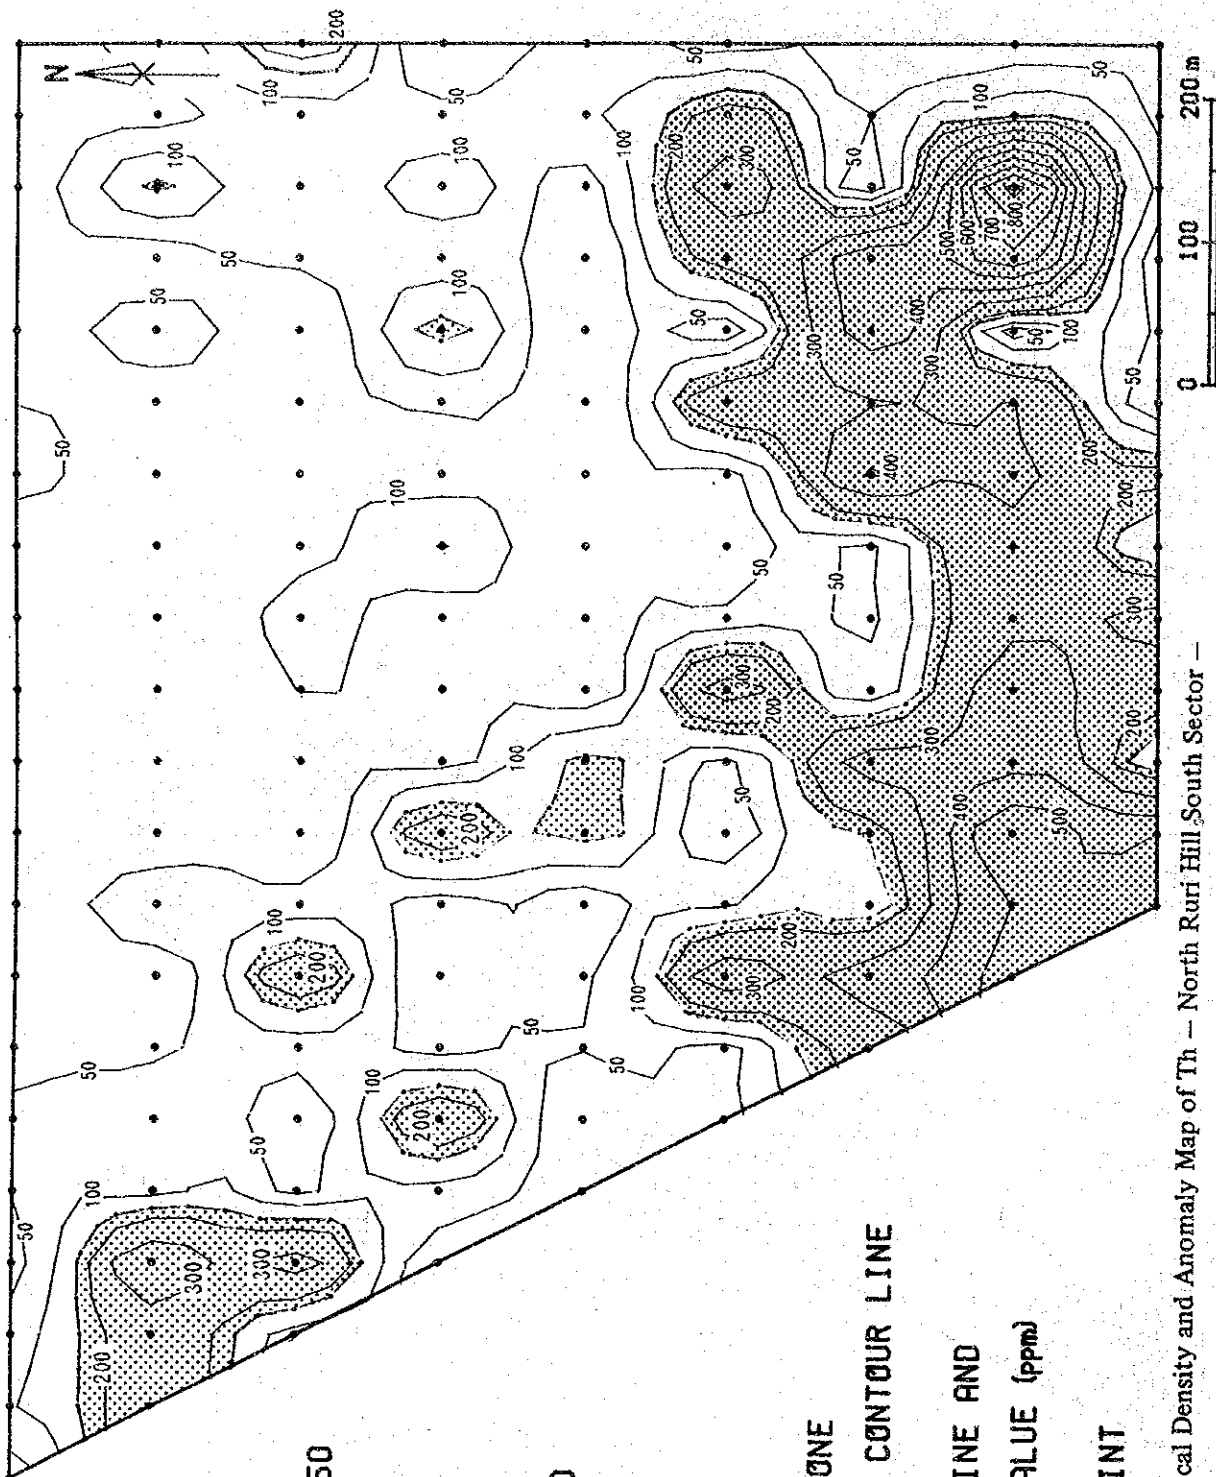


AREA NAME = NRHS
 FILE NAME = TH
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 900
 MINIMUM = 50
 THRESHOLD = 160
 MAP SCALE = 1:5000

LEGEND


-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- 100 — CONTOUR LINE AND CONTOUR VALUE (ppm)
- SAMPLE POINT

Apx. 31 Geochemical Density and Anomaly Map of Th — North Ruri Hill South Sector —

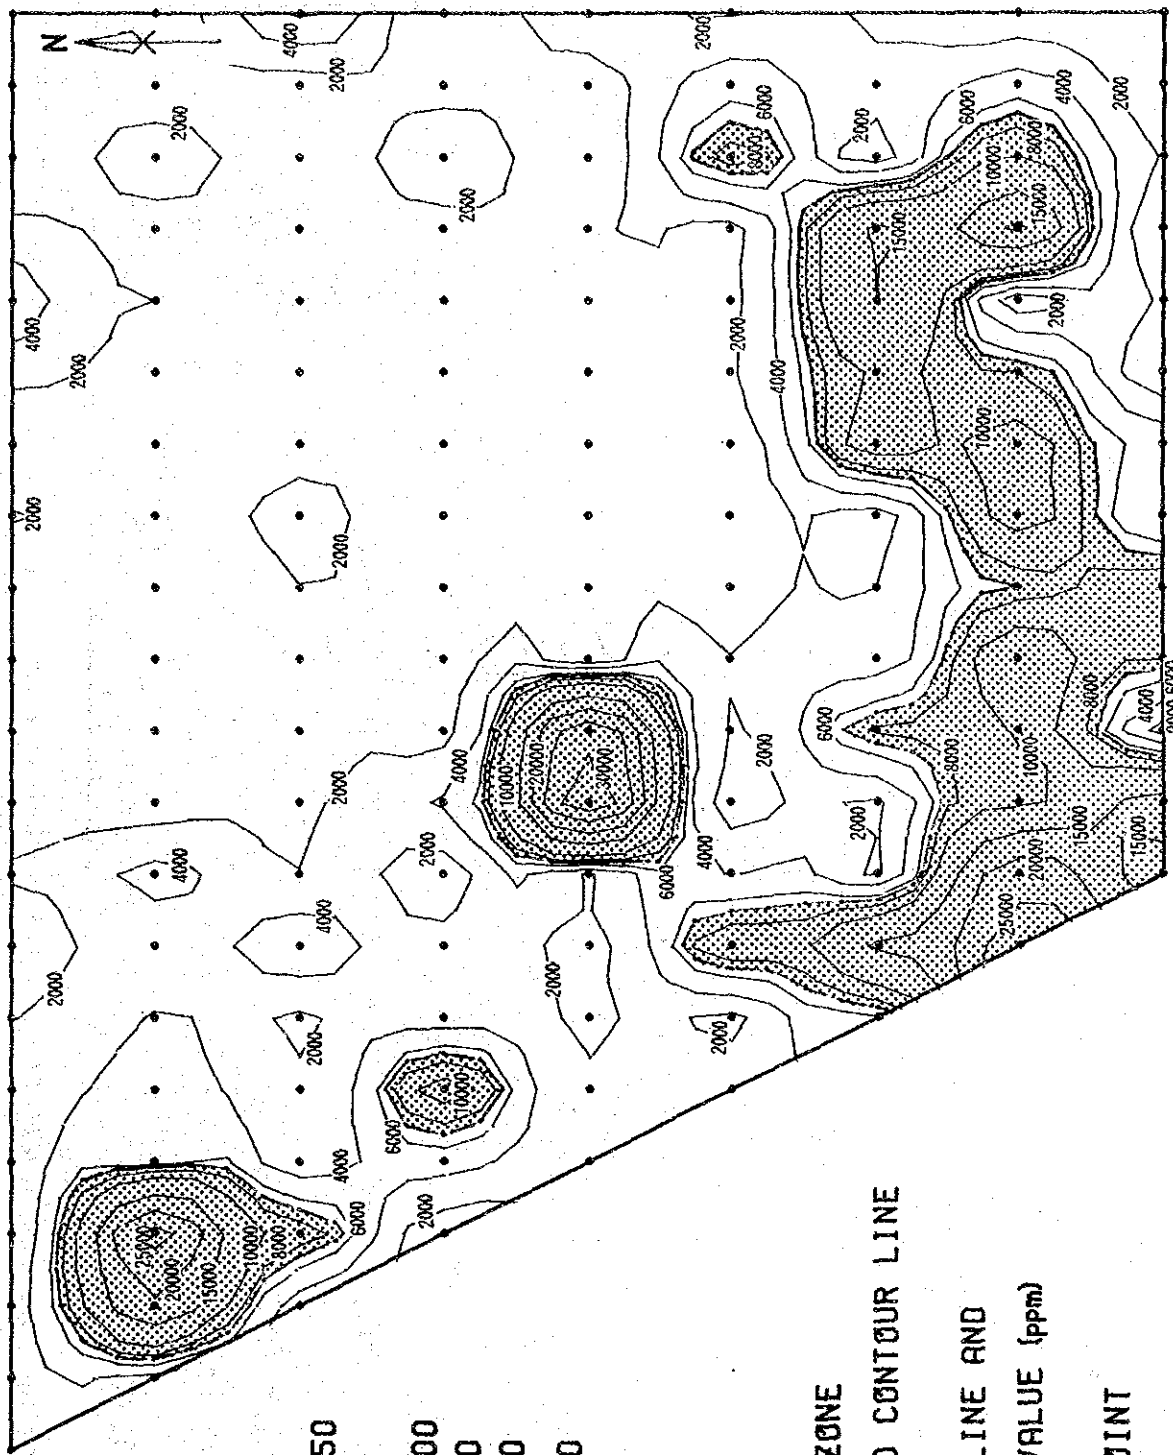


AREA NAME = NRHS
 FILE NAME = LCN
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 30000
 MINIMUM = 2000
 THRESHOLD = 7000
 MAP SCALE = 1:5000

LEGEND


-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- 10 — CONTOUR LINE AND CONTOUR VALUE (ppm)
- SAMPLE POINT

Apx. 32 Geochemical Density and Anomaly Map of La+Ce+Nd - North Ruri Hill South Sector -

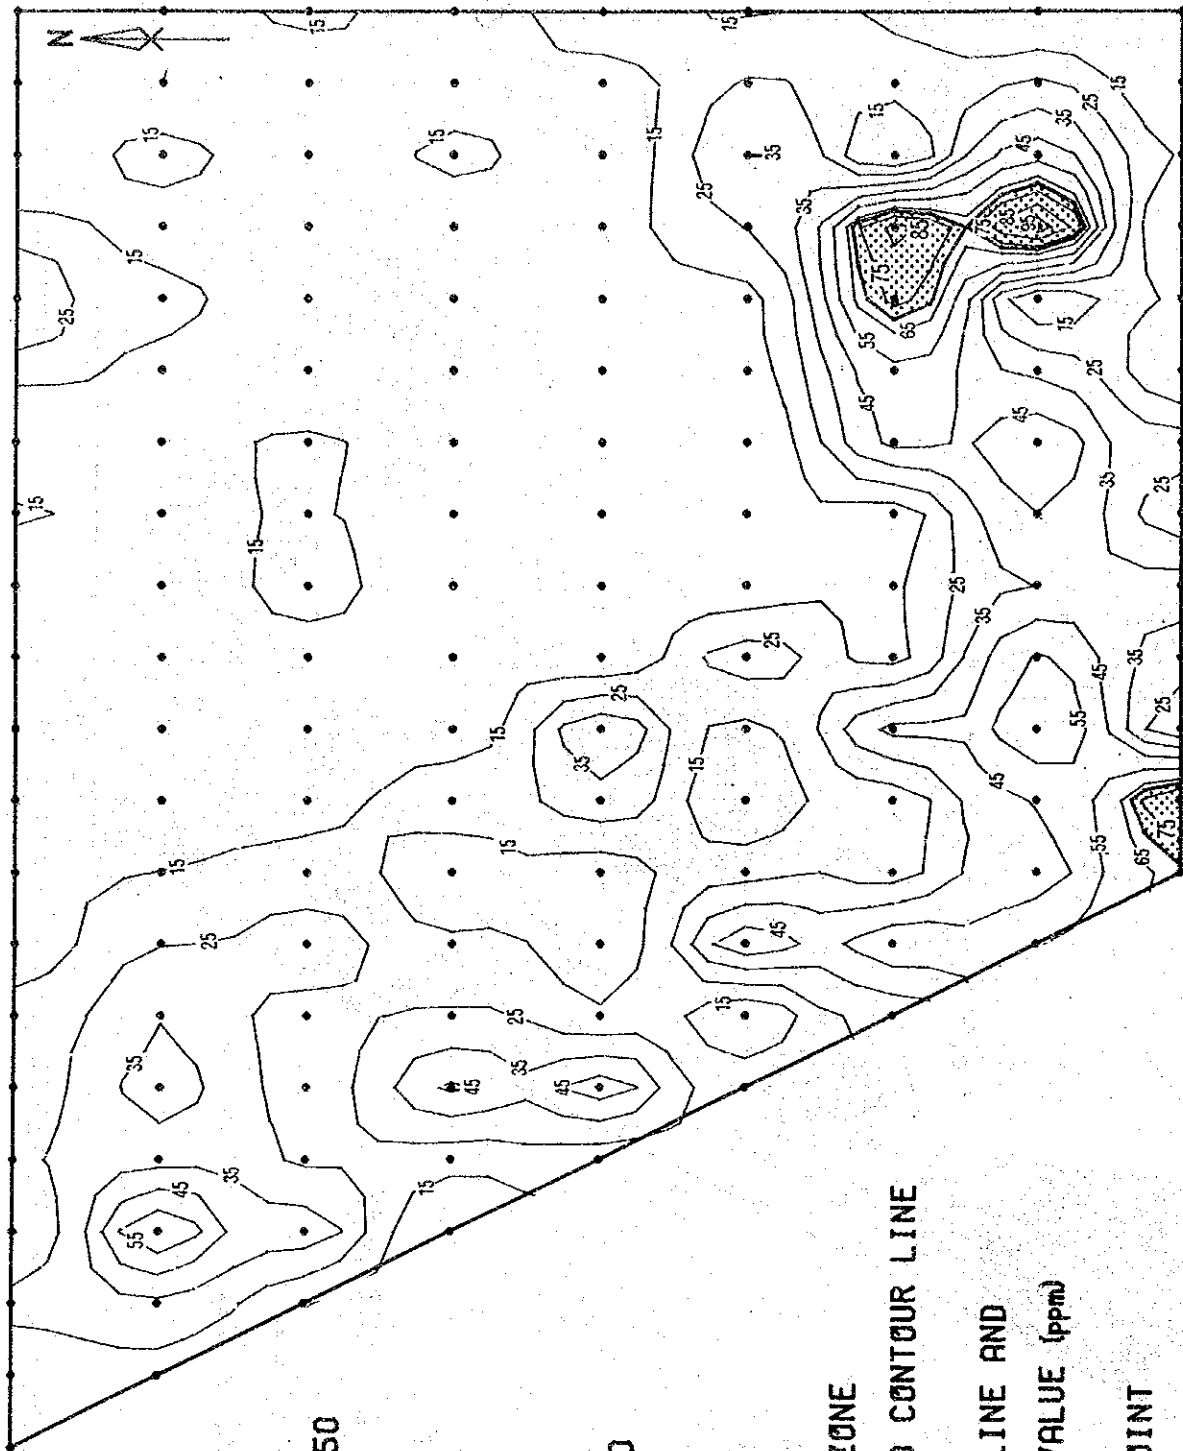


AREA NAME = NRHS
 FILE NAME = EU
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 95
 MINIMUM = 15
 INTERVAL = 10
 THRESHOLD = 70
 MAP SCALE = 1:5000

LEGEND

-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- 10 — CONTOUR LINE AND CONTOUR VALUE (ppm)
- SAMPLE POINT

Apx. 33 Geochemical Density and Anomaly Map of Eu — North Ruri Hill South Sector —

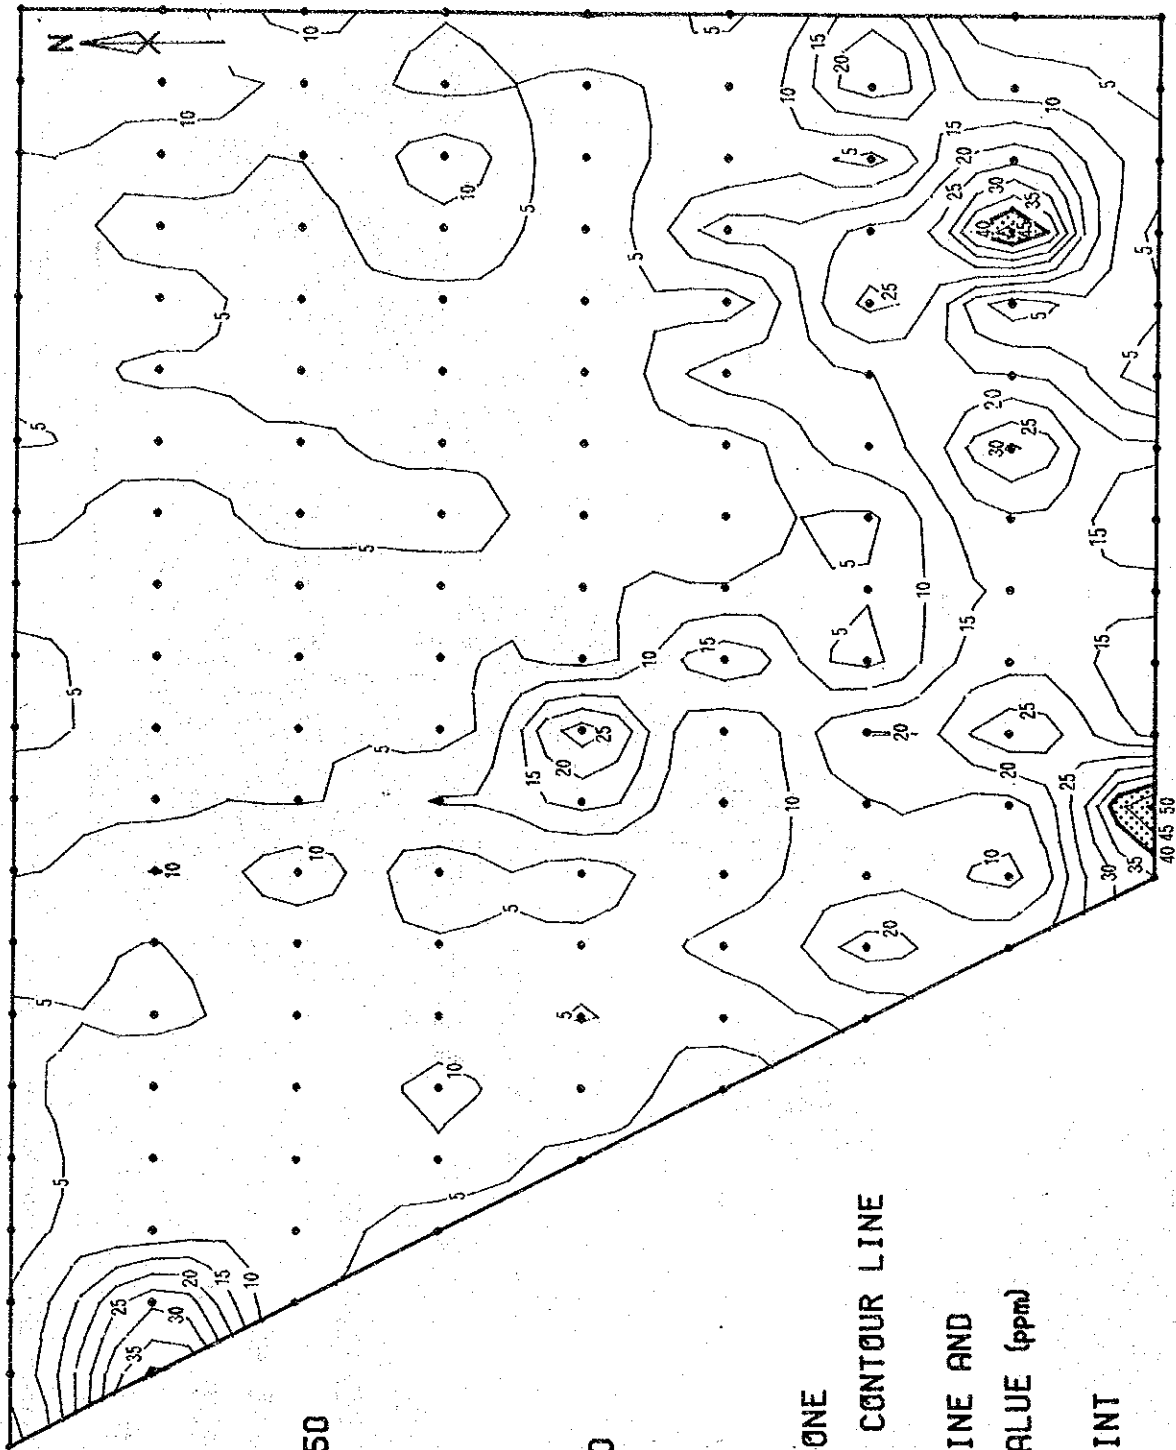

AREA NAME = NRHS

FILE NAME = YB

NO. OF SAMPLE = 150

CONTOUR VALUE

MAXIMUM = 50


MINIMUM = 5


INTERVAL = 5

THRESHOLD = 40

MAP SCALE = 1:5000


LEGEND

-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- 10 — CONTOUR LINE AND CONTOUR VALUE (ppm)
- SAMPLE POINT

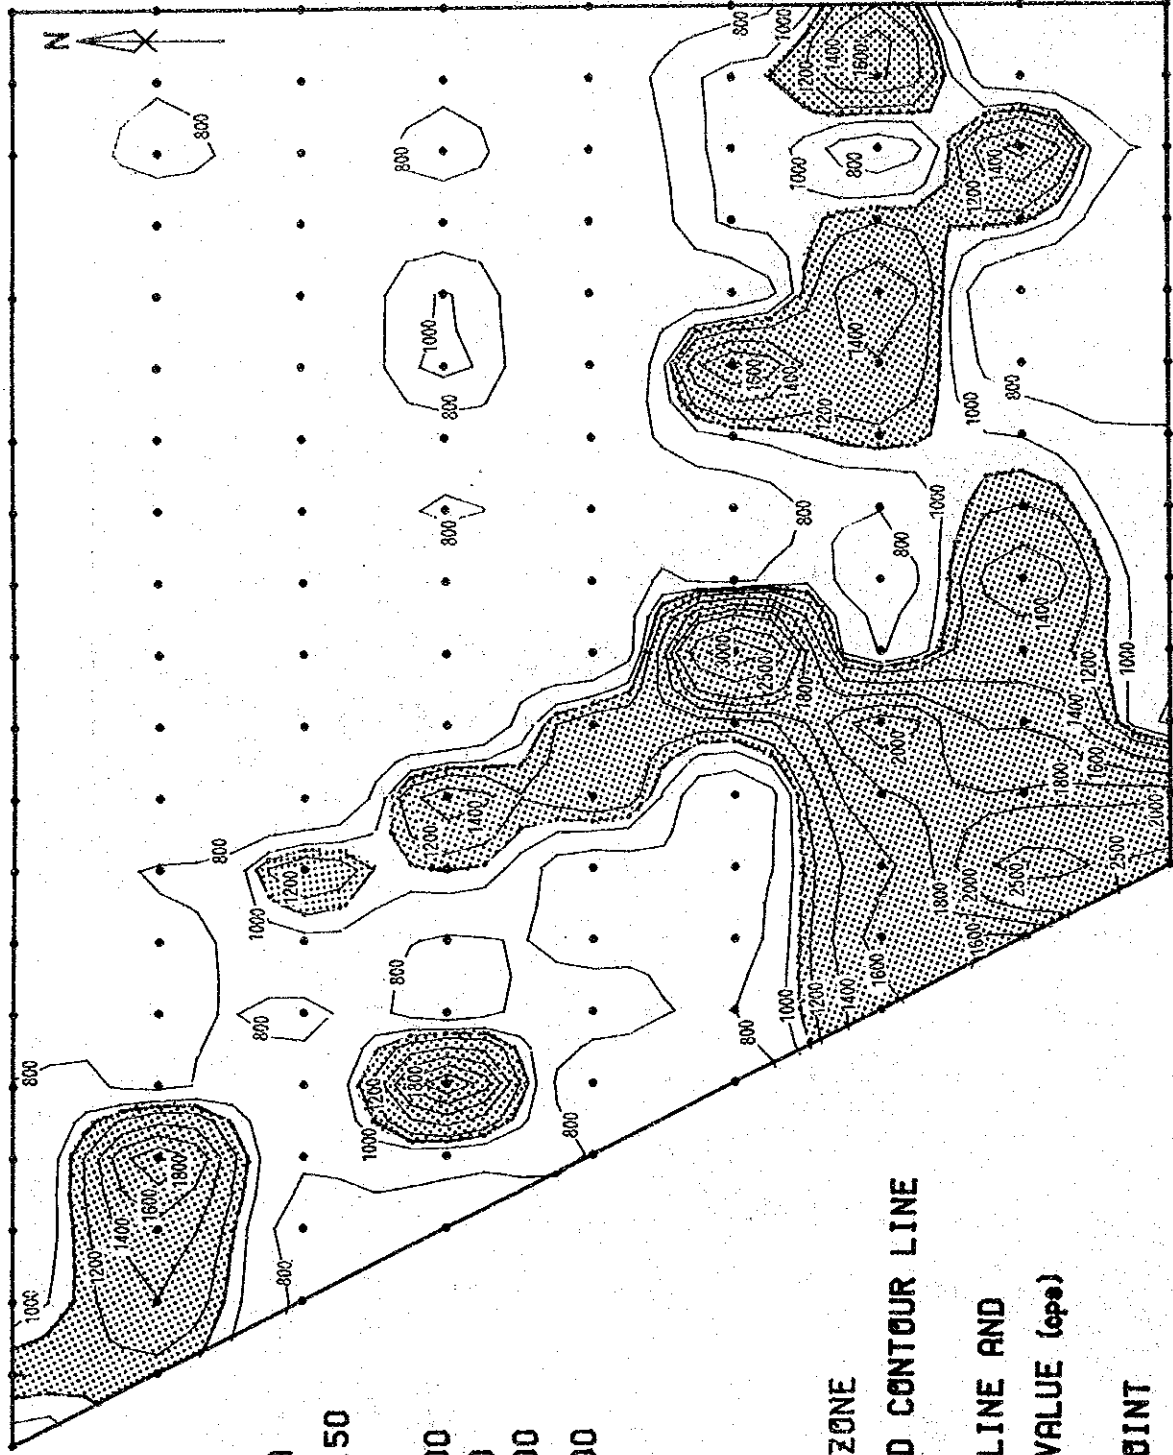


AREA NAME = NRHS
 FILE NAME = GAMMA
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 3000
 MINIMUM = 800
 THRESHOLD = 1100
 MAP SCALE = 1:5000

LEGEND


-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- 10 — CONTOUR LINE AND CONTOUR VALUE (cpa)
- SAMPLE POINT

Apx. 35 Geochemical Density and Anomaly Map of γ -Ray - North Ruri Hill South Sector -






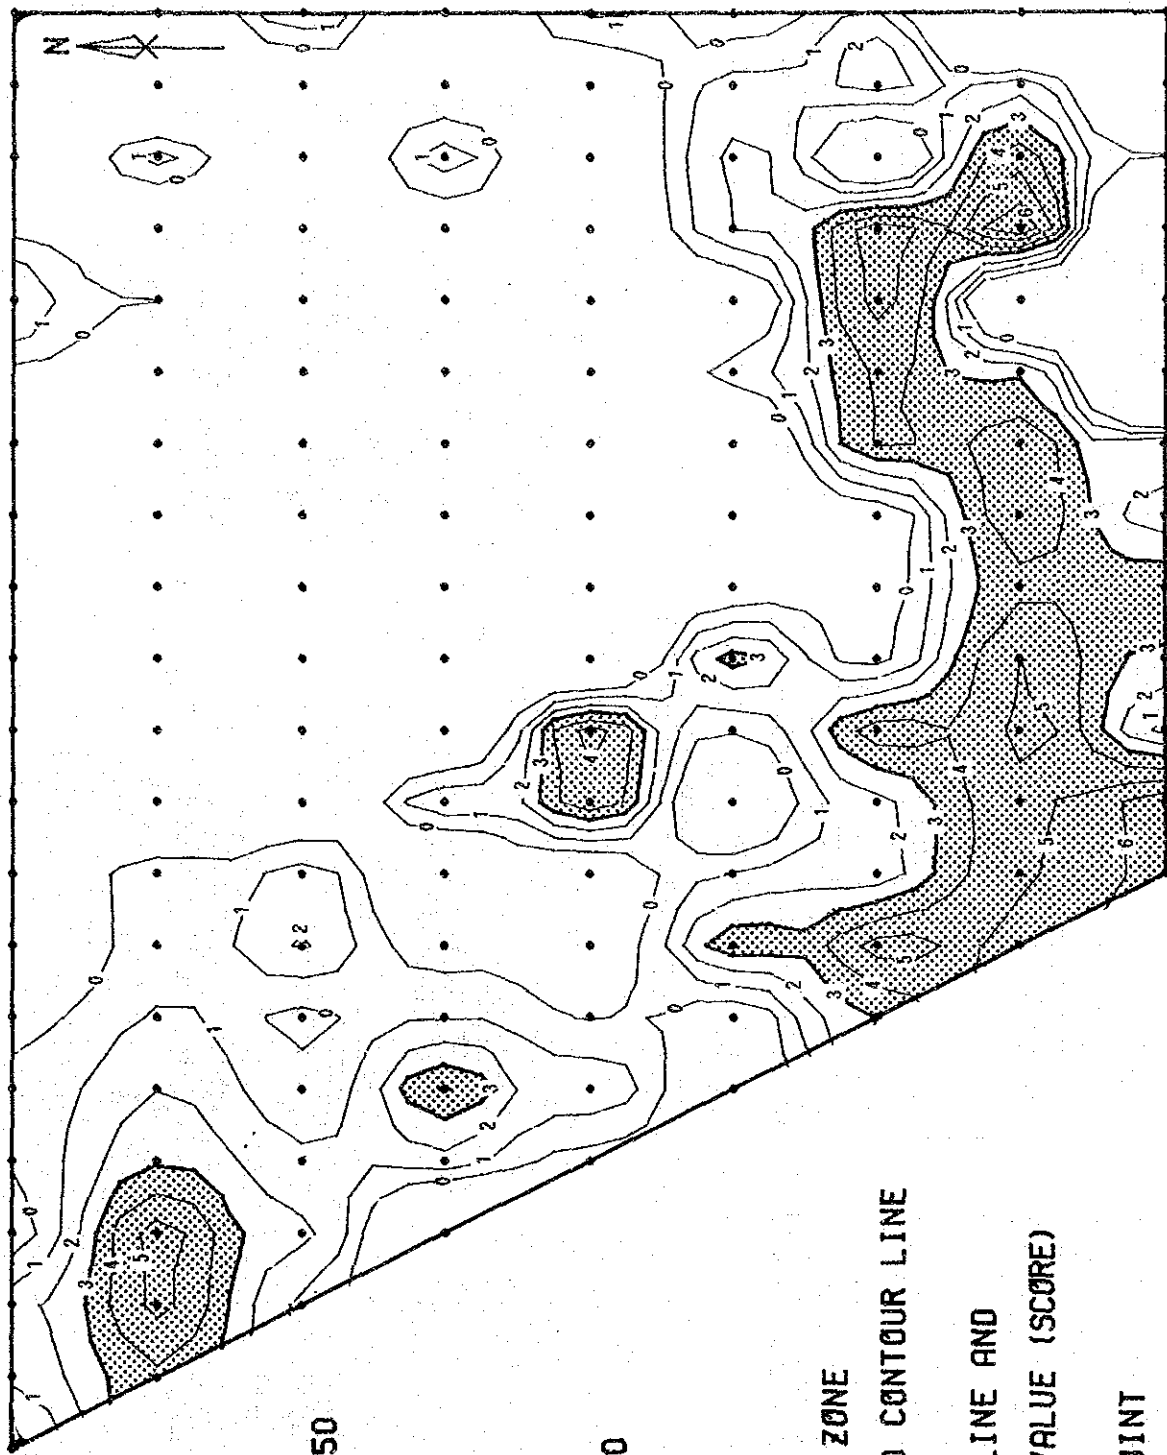


AREA NAME = NRHS
 FILE NAME = RZ1
 NO. OF SAMPLE = 150
 CONTOUR VALUE
 MAXIMUM = 7
 MINIMUM = 0
 INTERVAL = 1
 THRESHOLD = 3
 MAP SCALE = 1:5000







LEGEND

-  ANOMALY ZONE
- 10 — THRESHOLD CONTOUR LINE
- CONTOUR LINE AND CONTOUR VALUE (SCORE)
- SAMPLE POINT







Ap. 36 Geochemical Density and Anomaly Map of Z1 Component - North Ruri Hill South Sector -

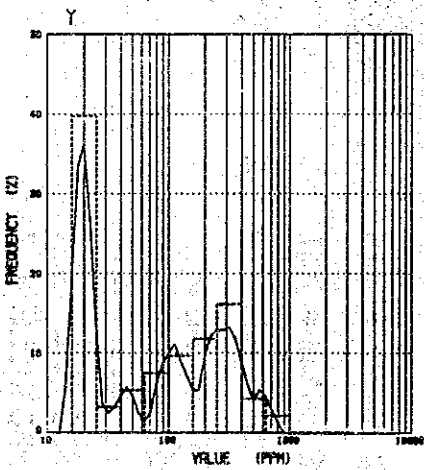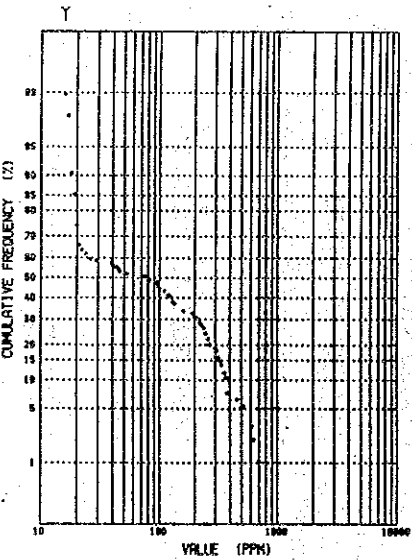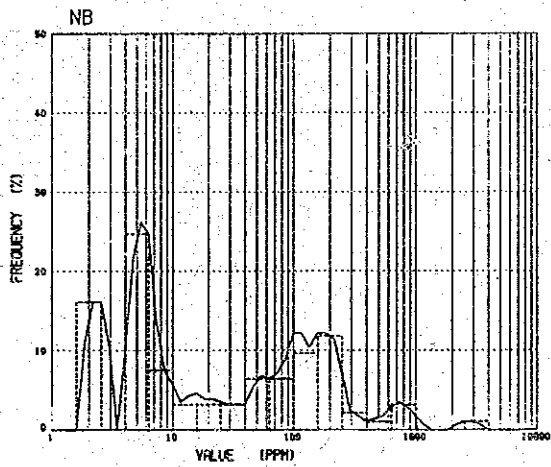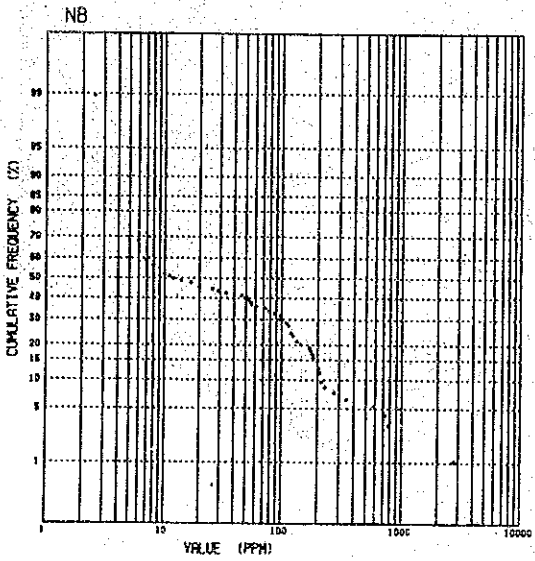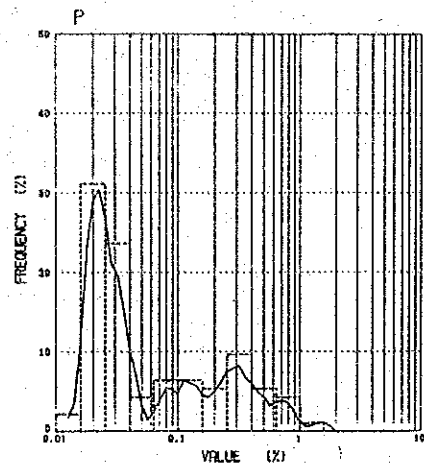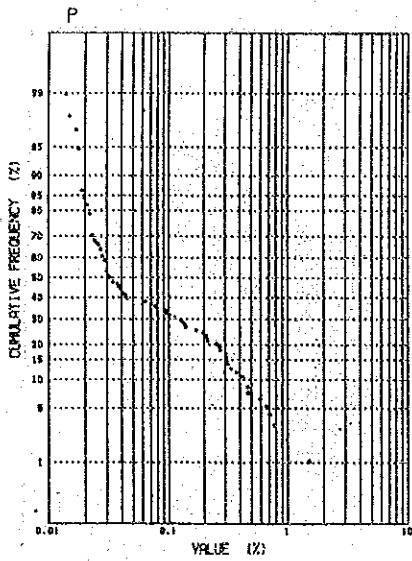

Apx. 37 Cumulative Frequency Distributions and Histograms of Elements – South Ruri Hill Sector –

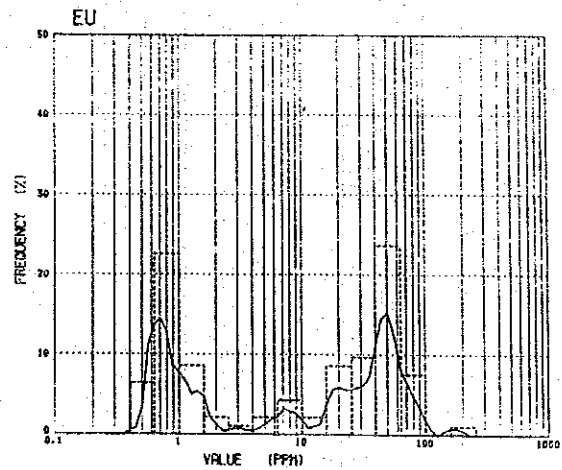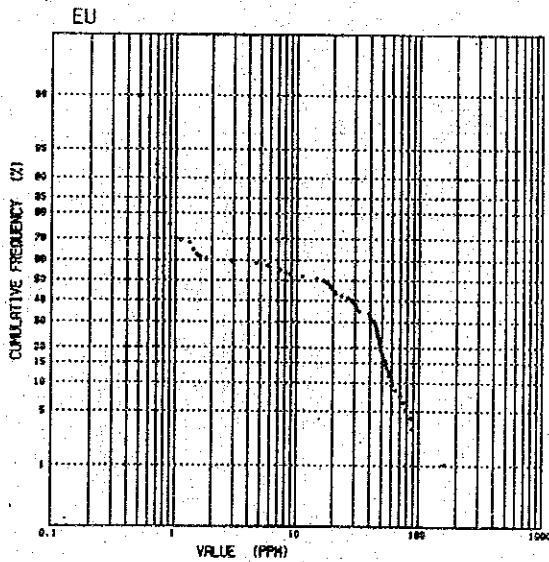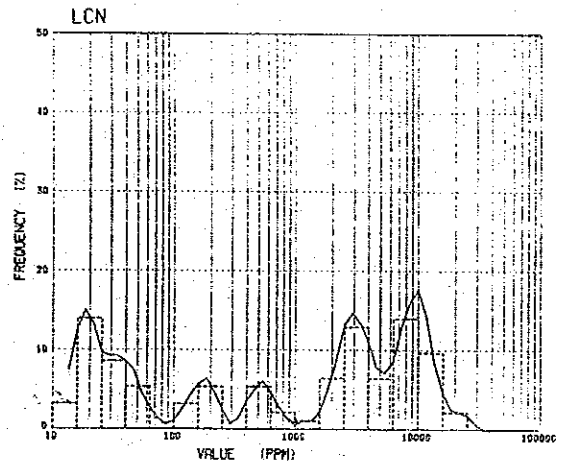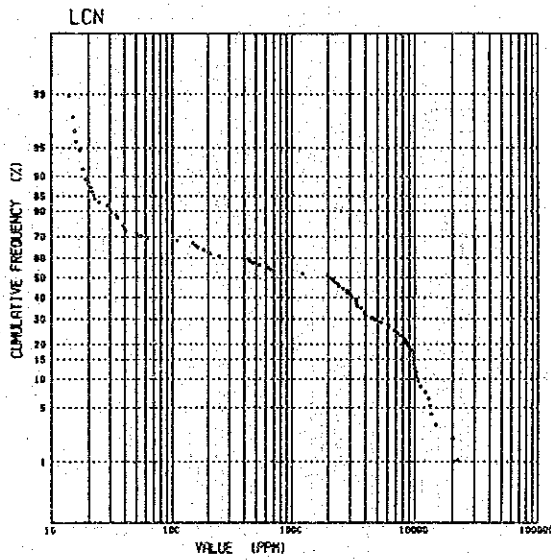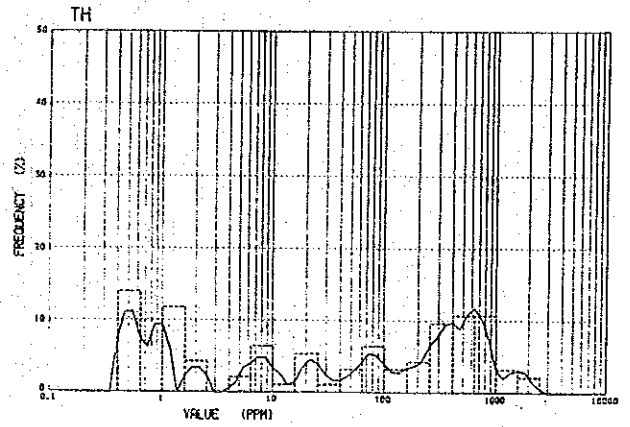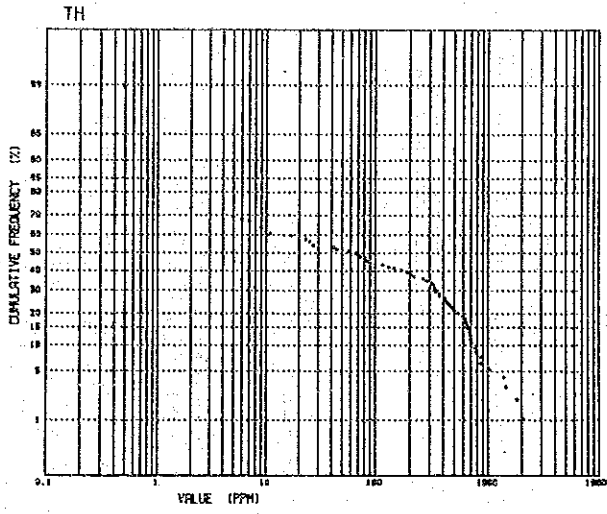


Apx. 37 Cumulative Frequency Distributions and Histograms of Elements – South Ruri Hill Sector –

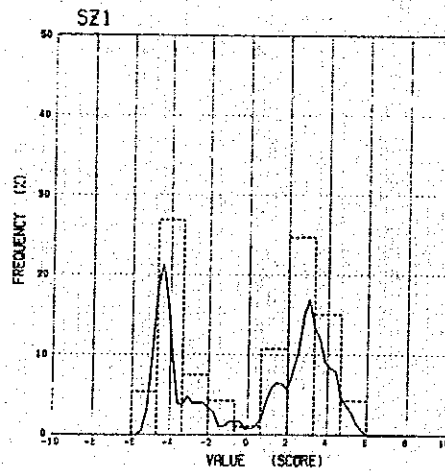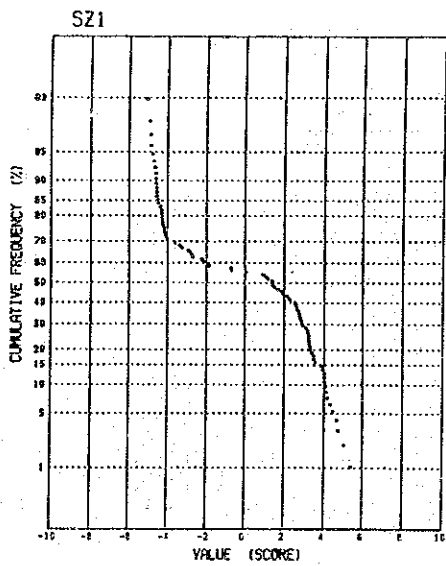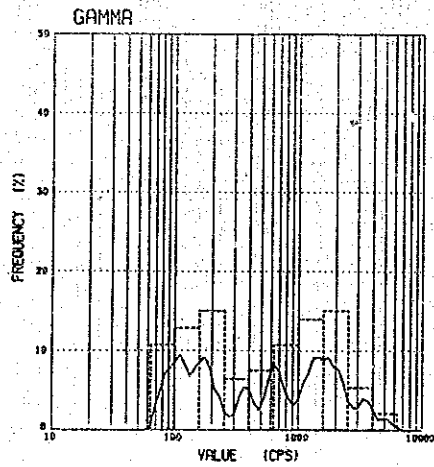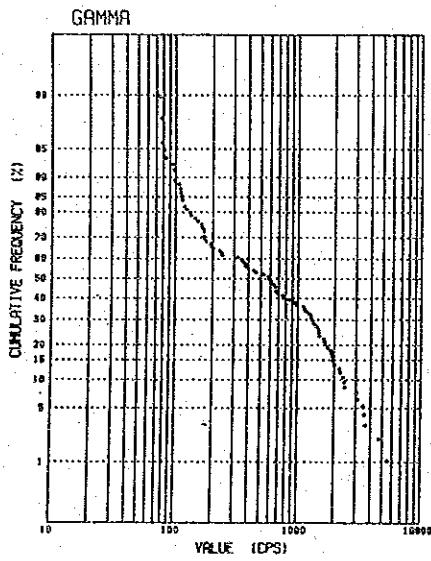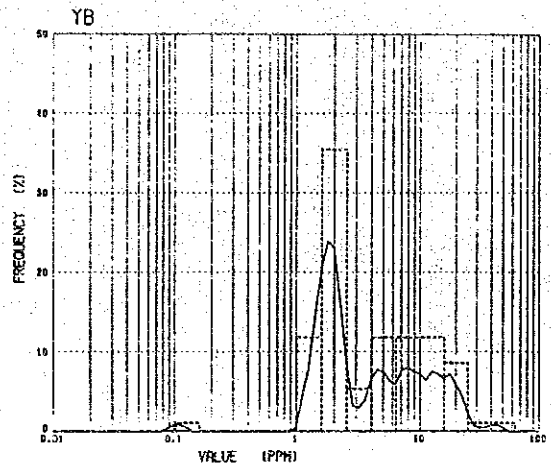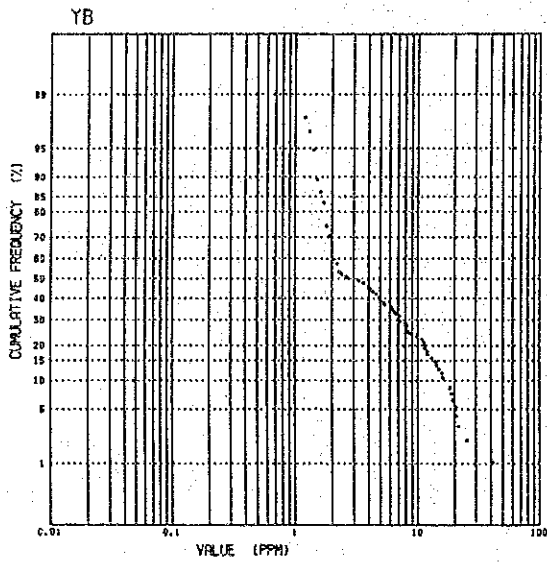

Apx. 37 Cumulative Frequency Distributions and Histograms of Elements – South Ruri Hill Sector –

SRH AREA

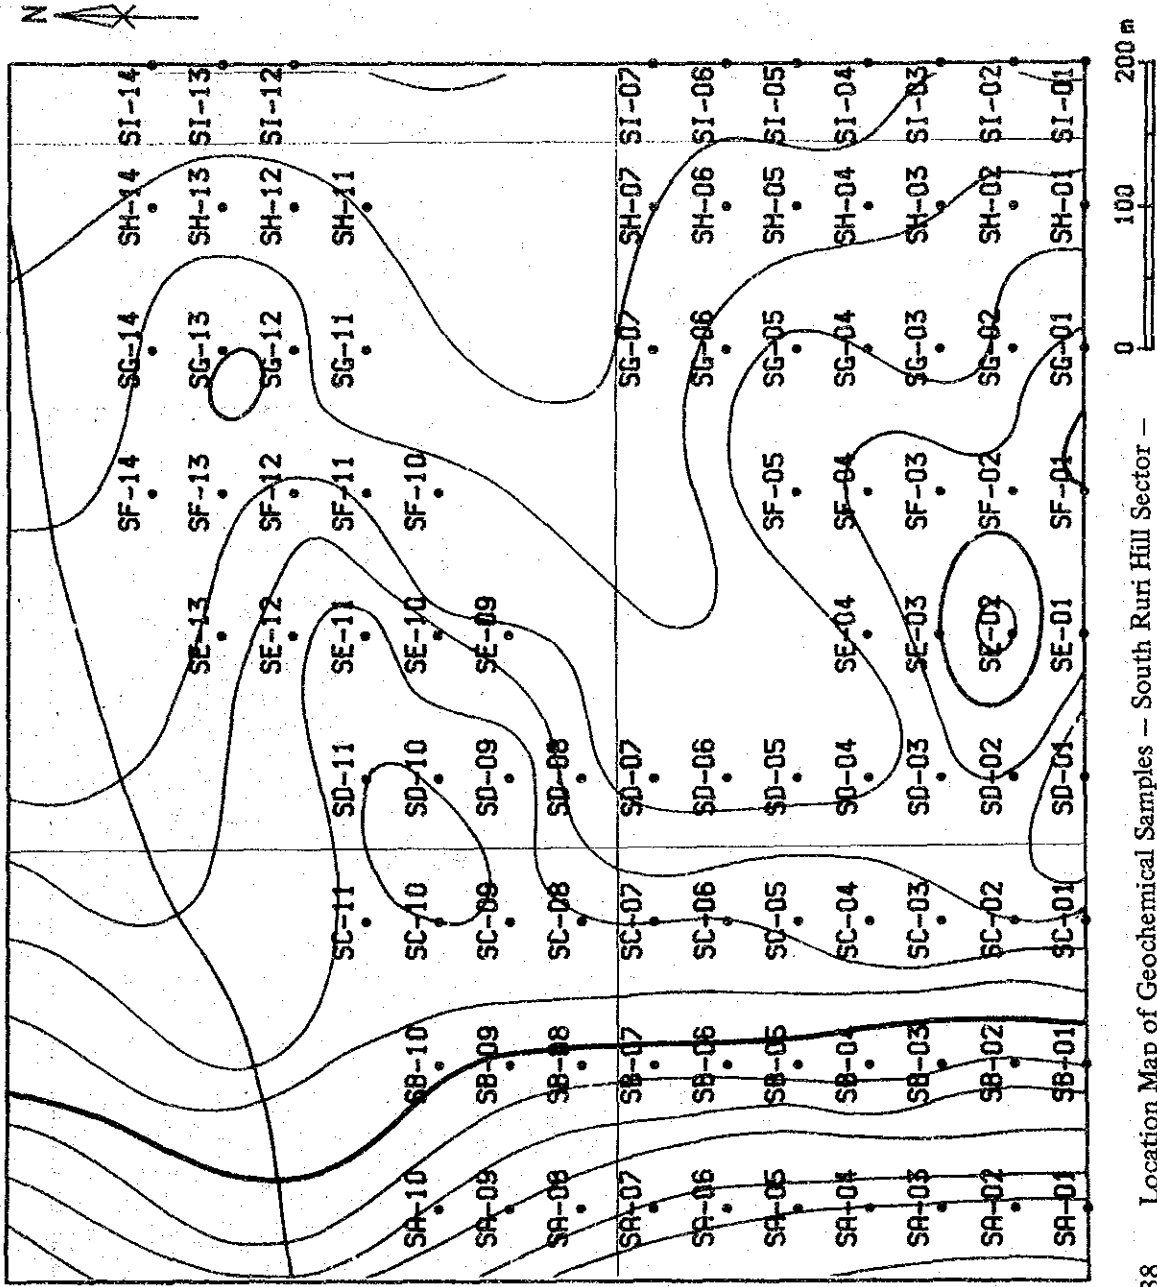

Apx. 38 Location Map of Geochemical Samples - South Ruri Hill Sector -

AREA NAME = SRH
 FILE NAME = P
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 1.4
 MINIMUM = .05
 THRESHOLD = .56
 MAP SCALE = 1:5000

LEGEND






ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND

CONTOUR VALUE (C)

SAMPLE POINT

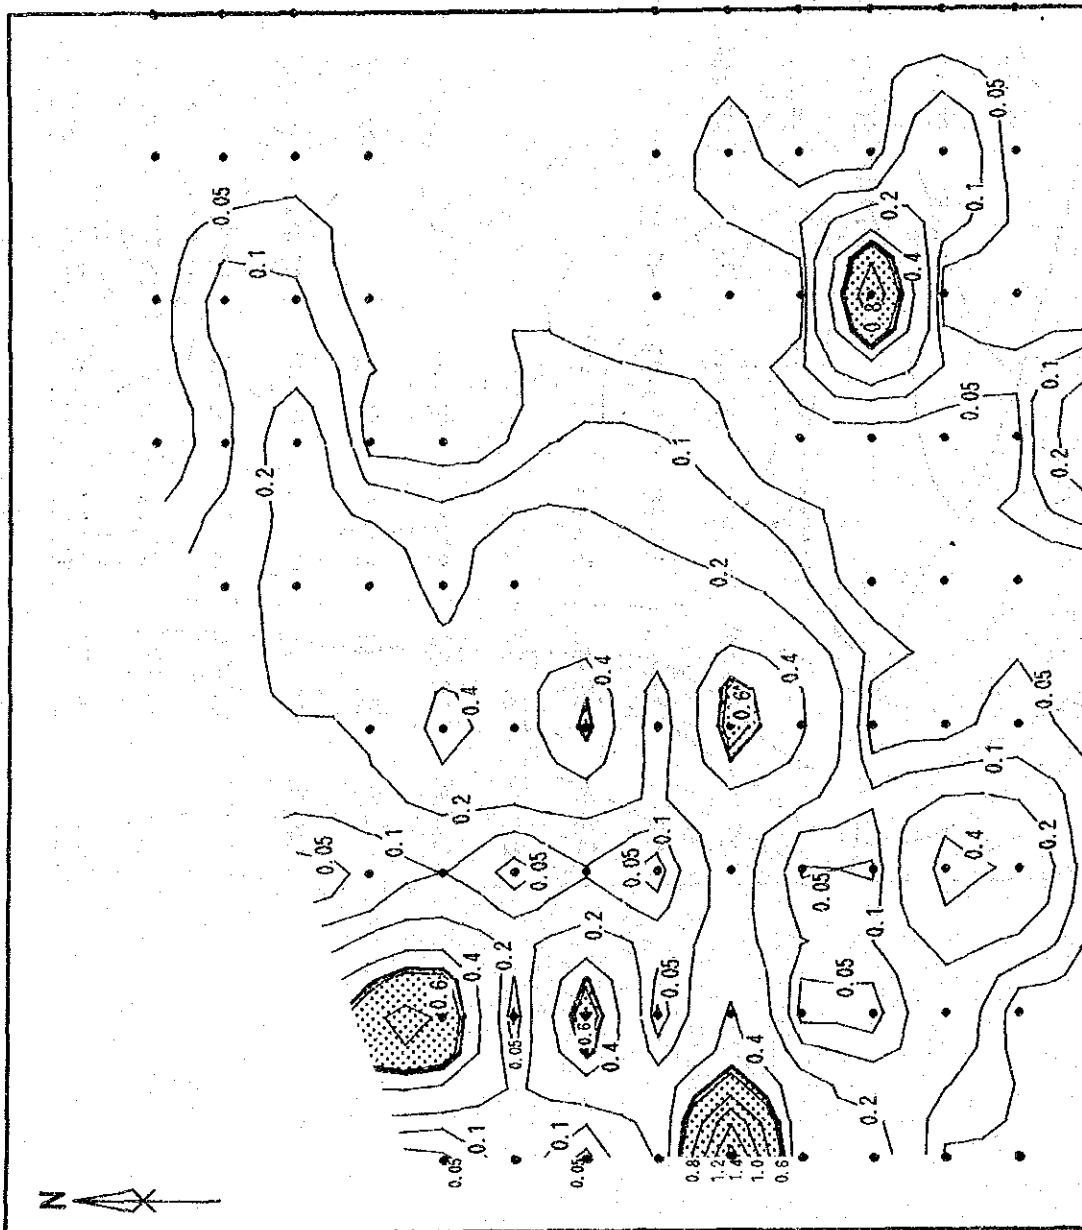

Apx. 39 Geochemical Density and Anomaly Map of P - South Ruri Hill Sector --

AREA NAME = SRH
 FILE NAME = NB
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 2000
 MINIMUM = 50
 THRESHOLD = 400
 MAP SCALE = 1:5000

LEGEND






ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND

CONTOUR VALUE (ppm)

SAMPLE POINT

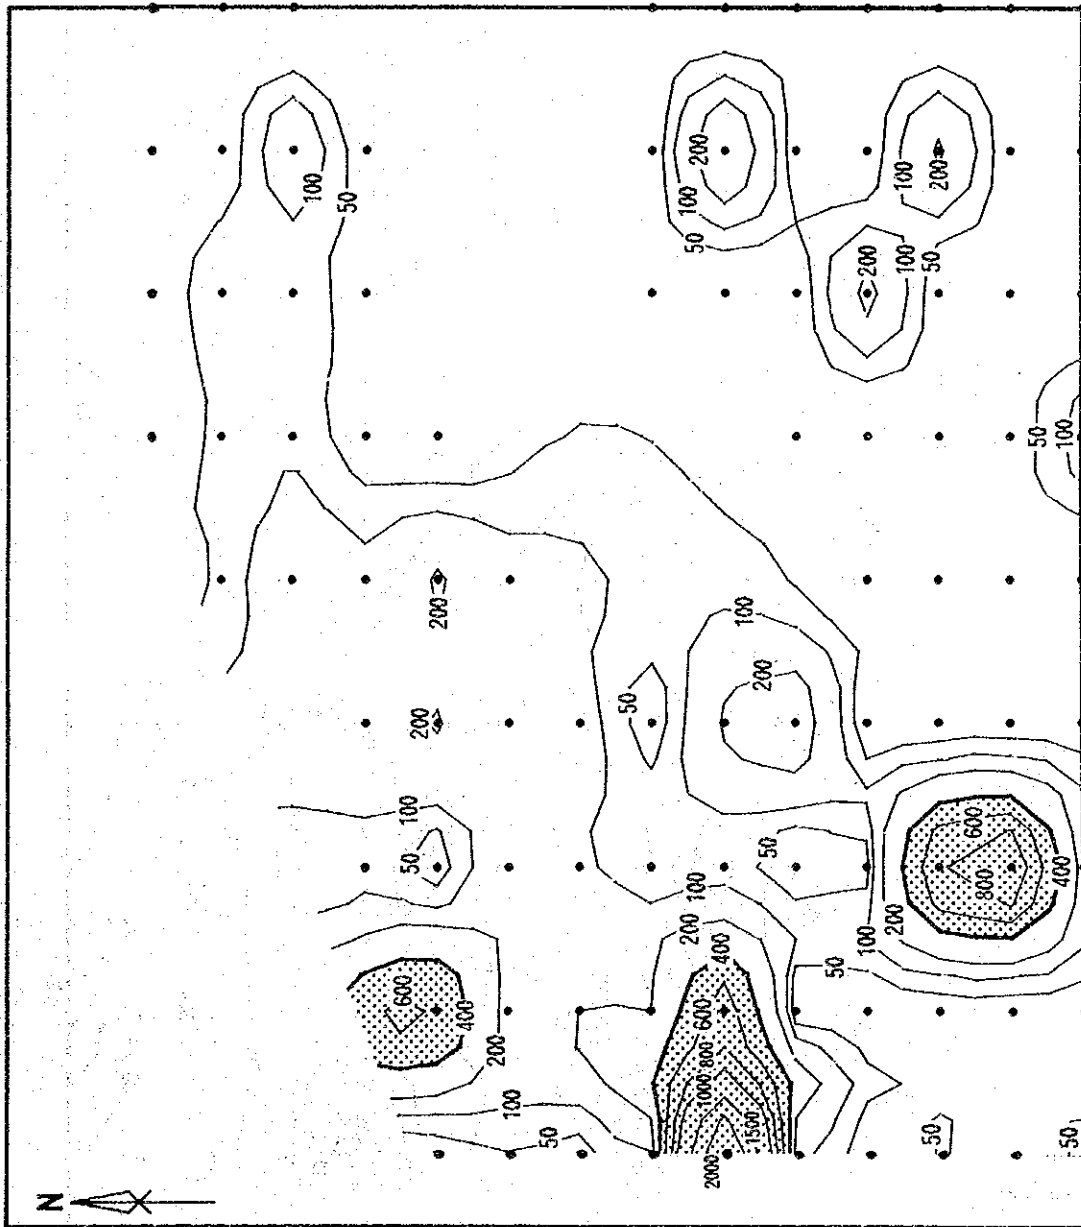

Apx. 40 Geochemical Density and Anomaly Map of Nb - South Ruri Hill Sector -

AREA NAME = SRH
 FILE NAME = Y
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 700
 MINIMUM = 100
 INTERVAL = 100
 THRESHOLD = 500
 MAP SCALE = 1:5000

LEGEND






ANOMALY ZONE

THRESHOLD CONTOUR LINE


CONTOUR LINE AND

CONTOUR VALUE (ppm)

SAMPLE POINT

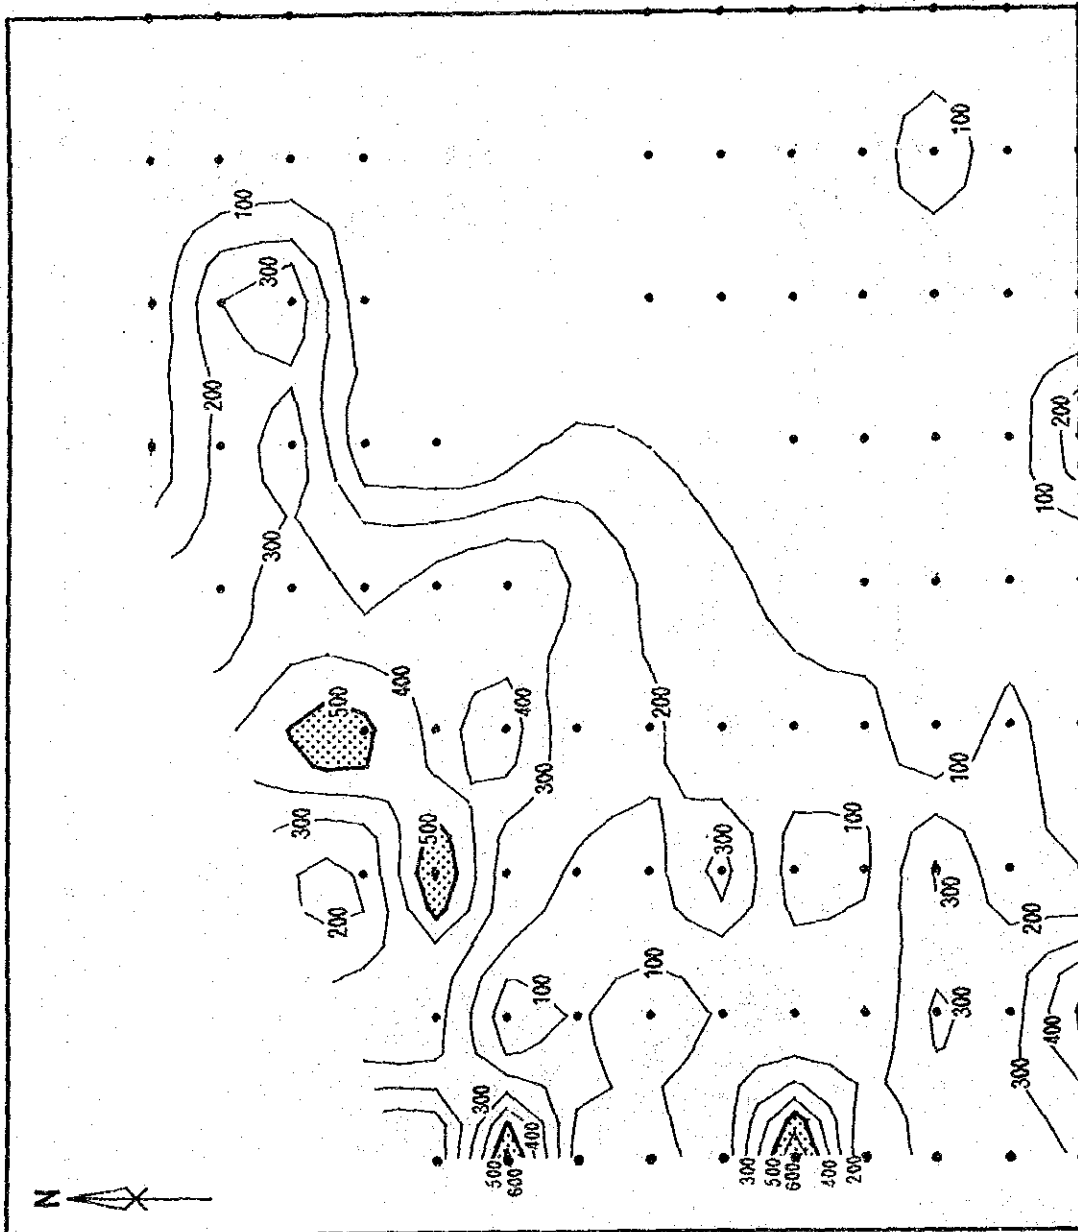

Apx. 41 Geochemical Density and Anomaly Map of Y - South Ruri Hill Sector -

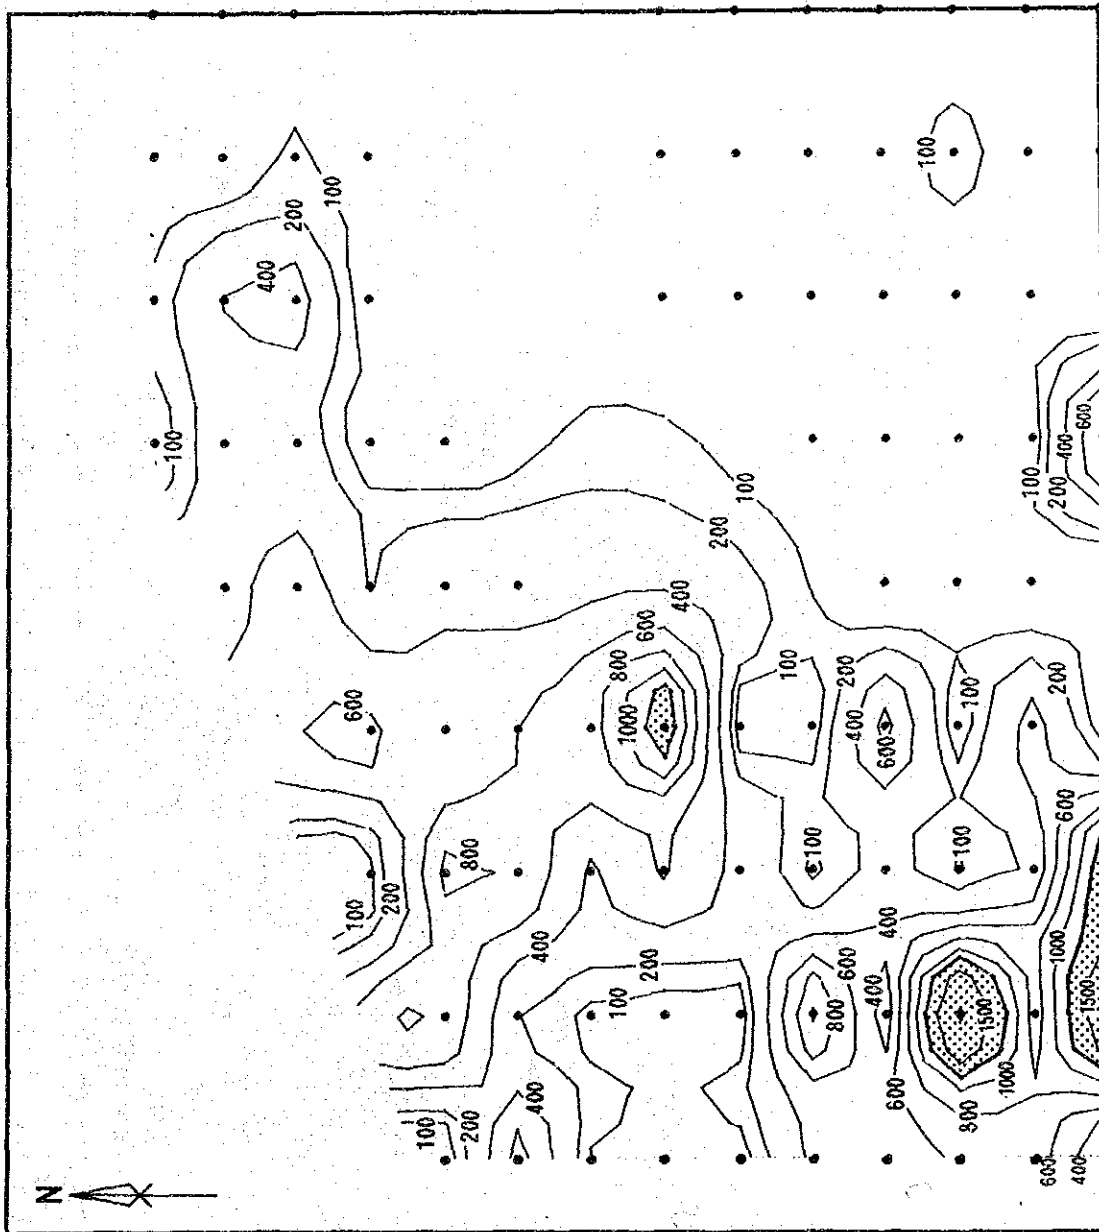

AREA NAME = SRH

FILE NAME = TH

NO. OF SAMPLE = 93

CONTOUR VALUE

MAXIMUM = 2000

MINIMUM = 100

THRESHOLD = 1200

MAP SCALE = 1:5000

LEGEND




ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND

CONTOUR VALUE (ppm)

SAMPLE POINT



Apx. 42 Geochemical Density and Anomaly Map of Th. -- South Ruri Hill Sector --

AREA NAME = SRH
 FILE NAME = LCN
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 20000
 MINIMUM = 1000
 THRESHOLD = 5400
 MAP SCALE = 1:5000

LEGEND





ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND
CONTOUR VALUE (ppm)



SAMPLE POINT

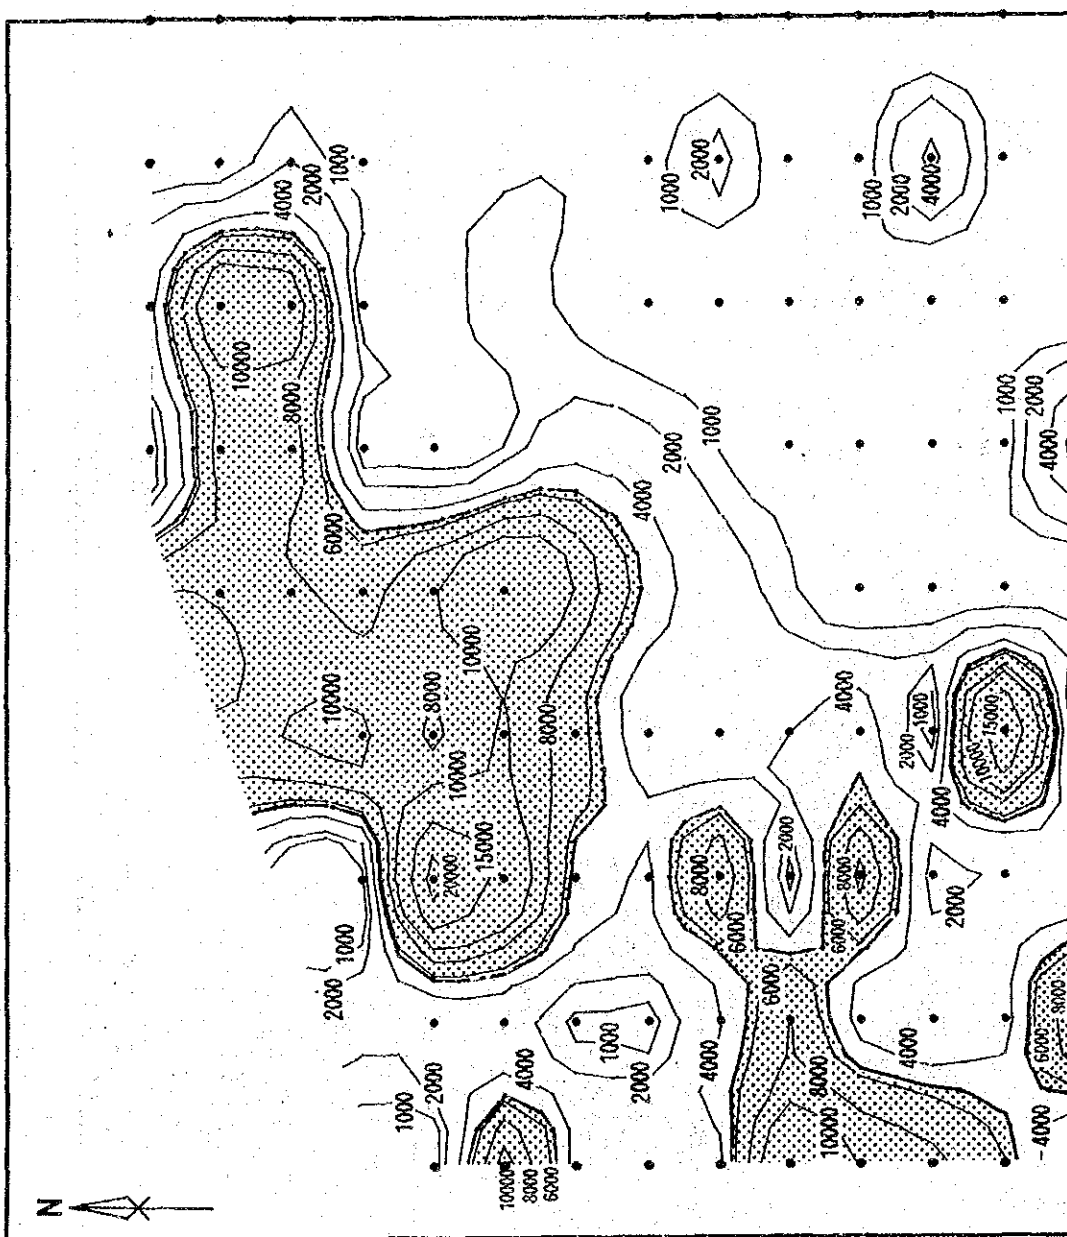

Apx. 43 Geochemical Density and Anomaly Map of La+Ce+Nd - South Ruri Hill Sector -

AREA NAME = SRH
 FILE NAME = EU
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 140
 MINIMUM = 10
 THRESHOLD = 85
 MAP SCALE = 1:5000

LEGEND





ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND

CONTOUR VALUE (ppm)


SAMPLE POINT

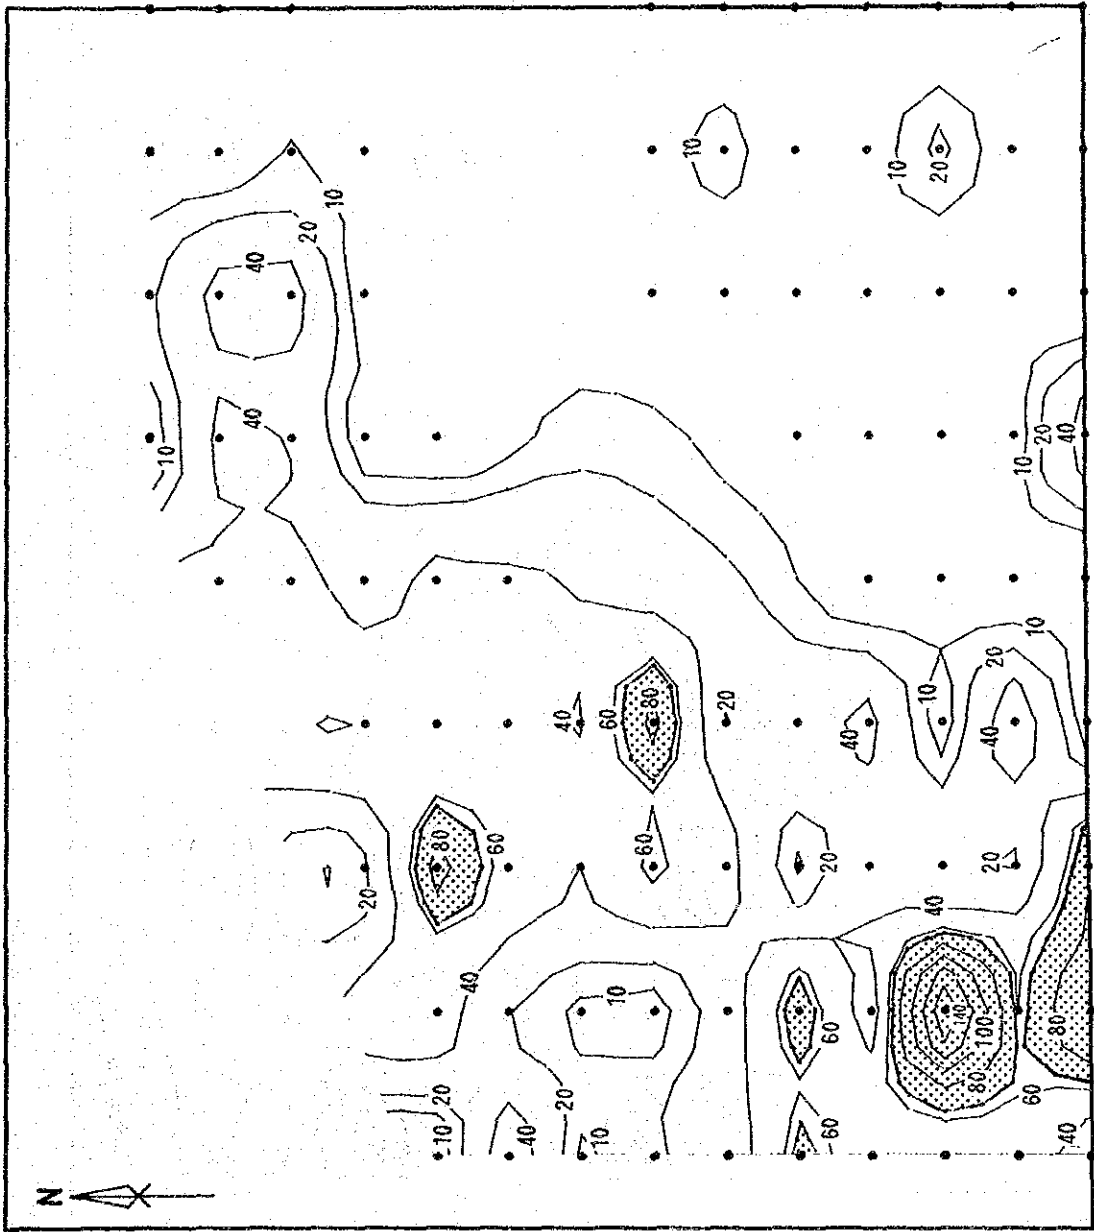

Apx. 44 Geochemical Density and Anomaly Map of Eu - South Ruri Hill Sector -

AREA NAME = SRH
 FILE NAME = YB
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 40
 MINIMUM = 4
 THRESHOLD = 15.5
 MAP SCALE = 1:5000

LEGEND






ANOMALY ZONE

THRESHOLD CONTOUR LINE

CONTOUR LINE AND

CONTOUR VALUE (ppm)

SAMPLE POINT

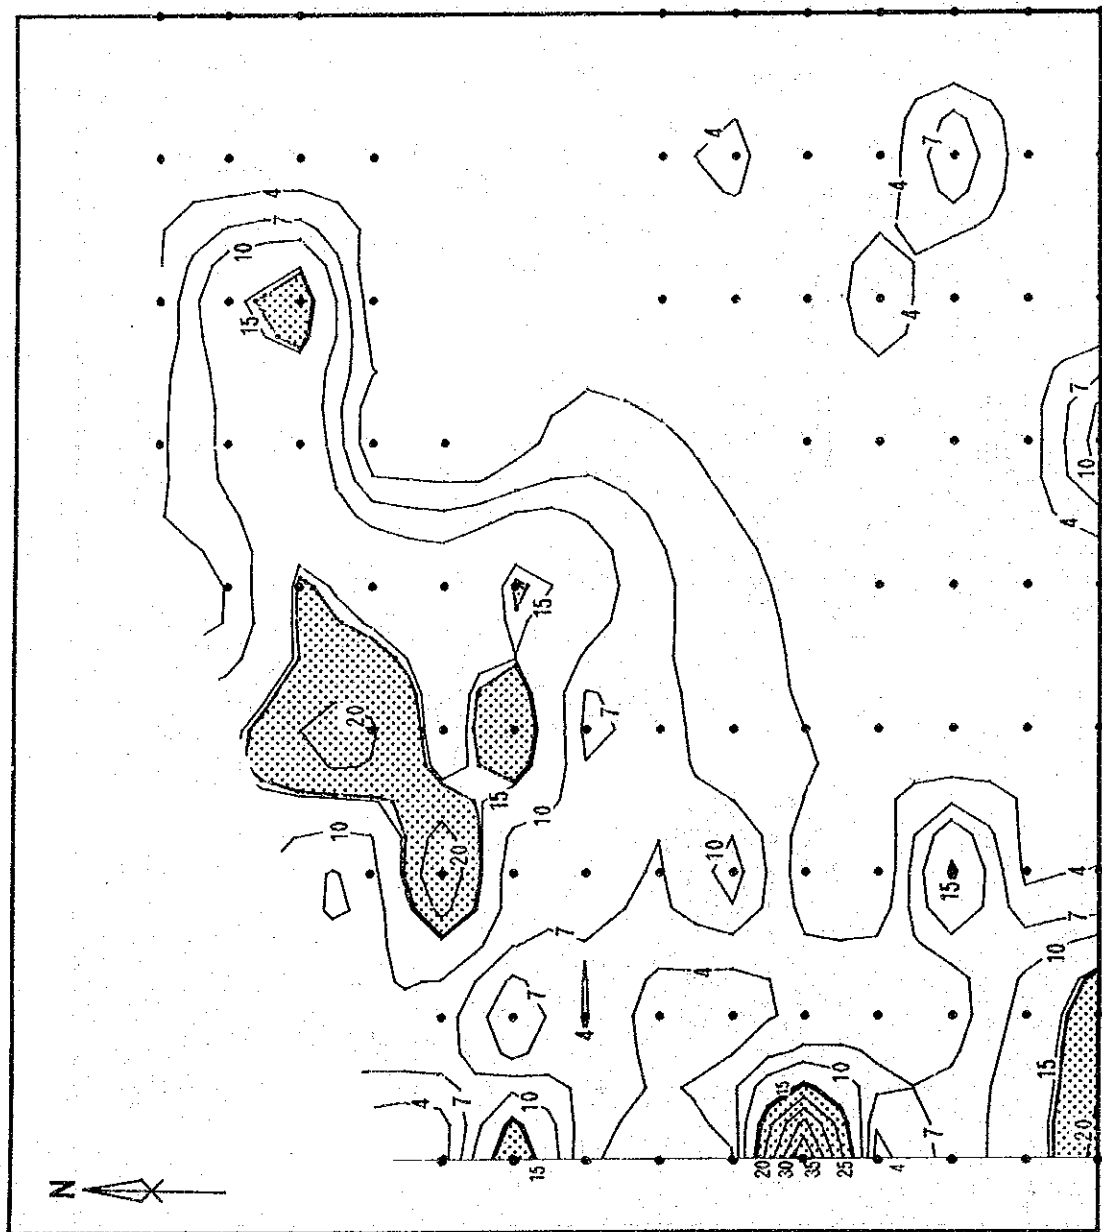

Apx. 45 Geochemical Density and Anomaly Map of Yb - South Ruri Hill Sector -

AREA NAME = SRH
 FILE NAME = GAMMA
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 5000
 MINIMUM = 600
 THRESHOLD = 2900
 MAP SCALE = 1:5000

LEGEND





ANOMALY ZONE

THRESHOLD CONTOUR LINE


CONTOUR LINE AND

CONTOUR VALUE (cps)

SAMPLE POINT

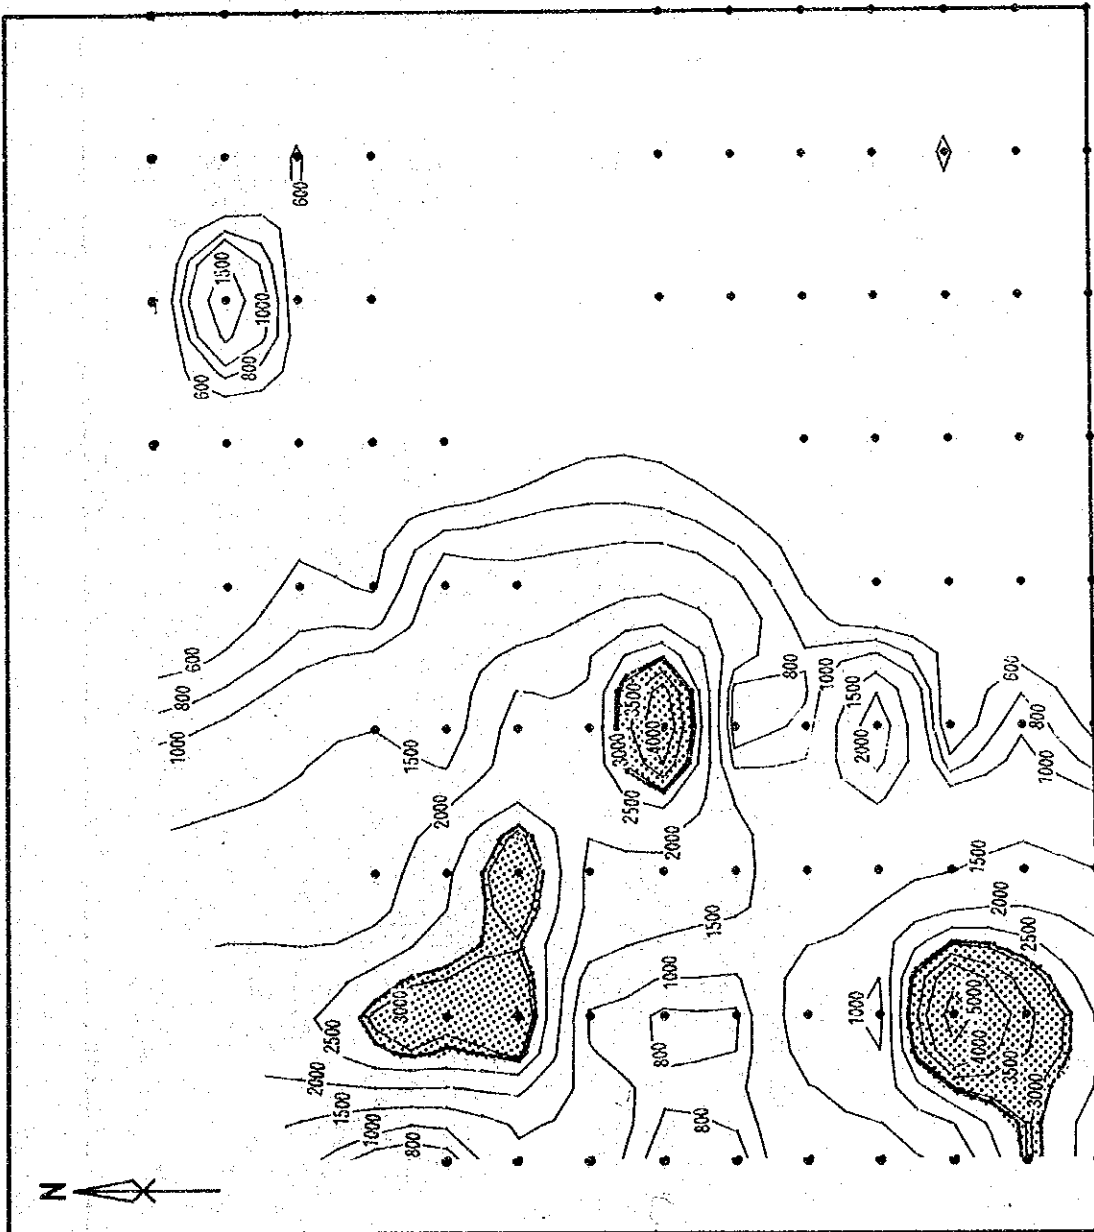

Apx. 46 Geochemical Density and Anomaly Map of γ -Ray - South Ruri Hill Sector -

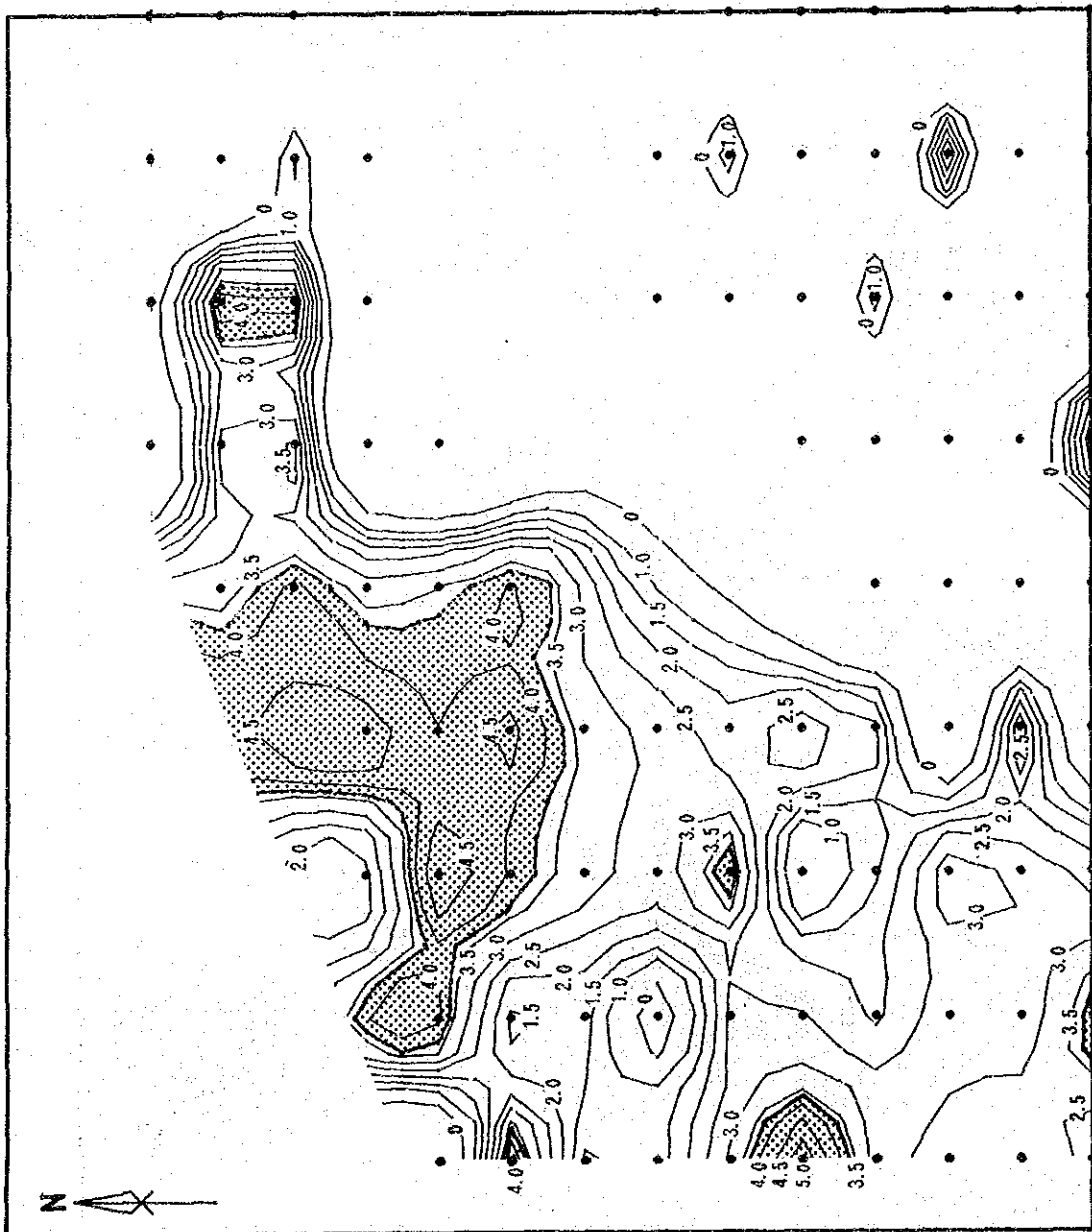

AREA NAME = SRH
 FILE NAME = SZ1
 NO. OF SAMPLE = 93
 CONTOUR VALUE
 MAXIMUM = 5
 MINIMUM = 0
 THRESHOLD = 3.7
 MAP SCALE = 1:5000

LEGEND



ANOMALY ZONE

THRESHOLD CONTOUR LINE







CONTOUR LINE AND

CONTOUR VALUE (SCORE)







SAMPLE POINT









Apx. 47 Geochemical Density and Anomaly Map of Z1 Component - South Ruri Hill Sector -

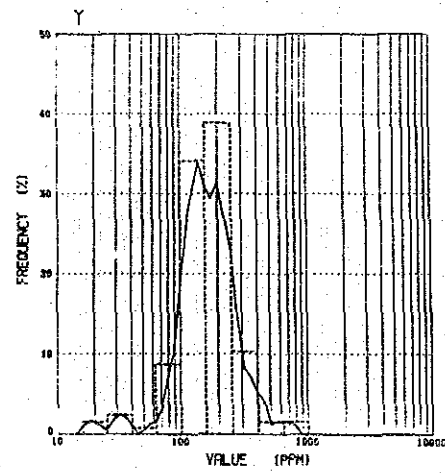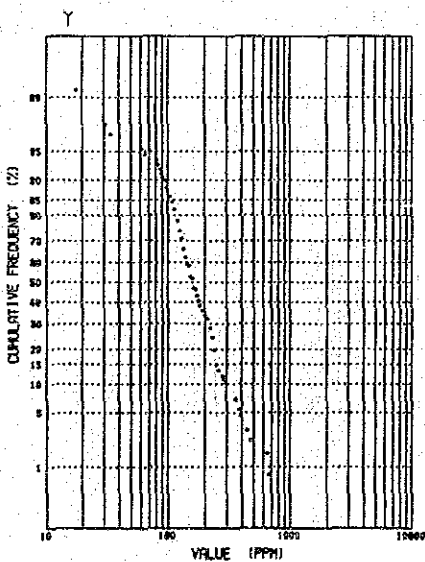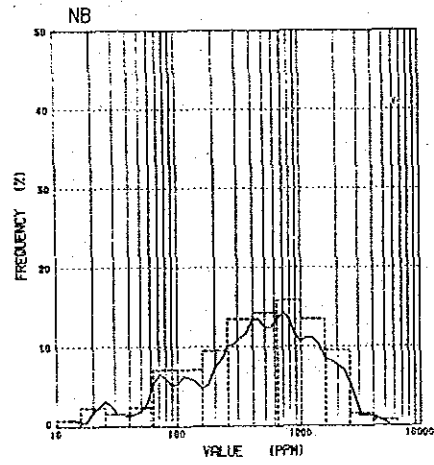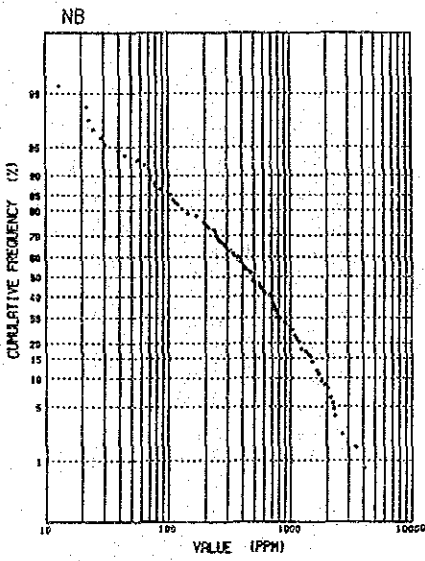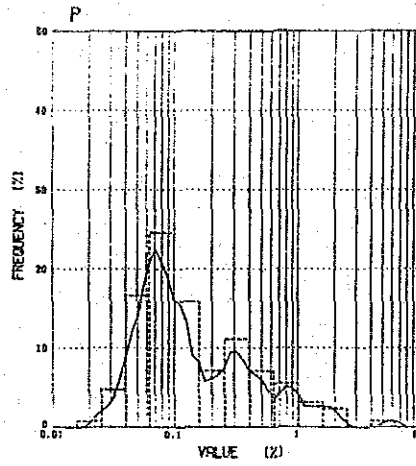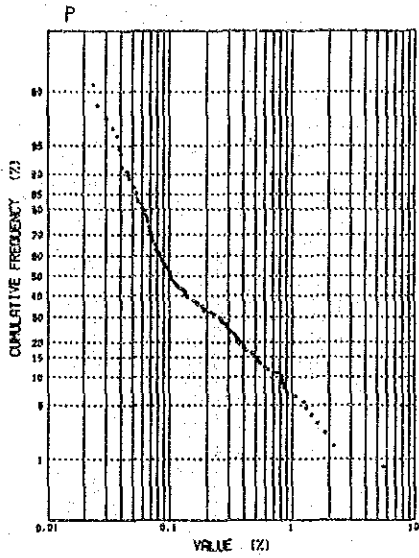

Apx. 48 Cumulative Frequency Distributions and Histograms of Elements -- Kuge Sector --

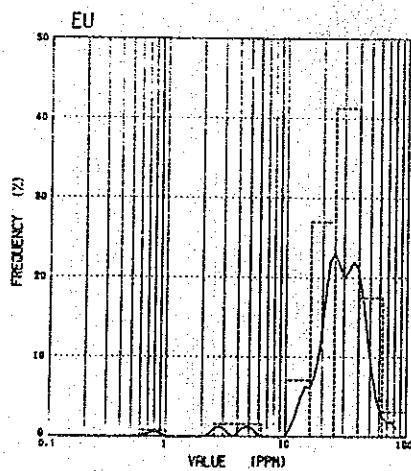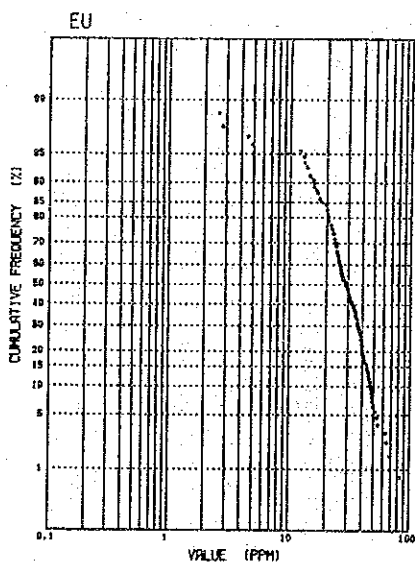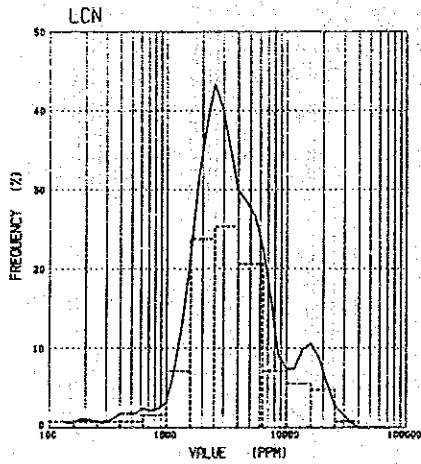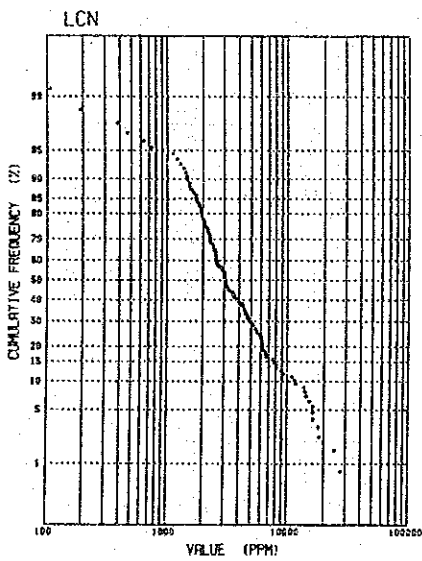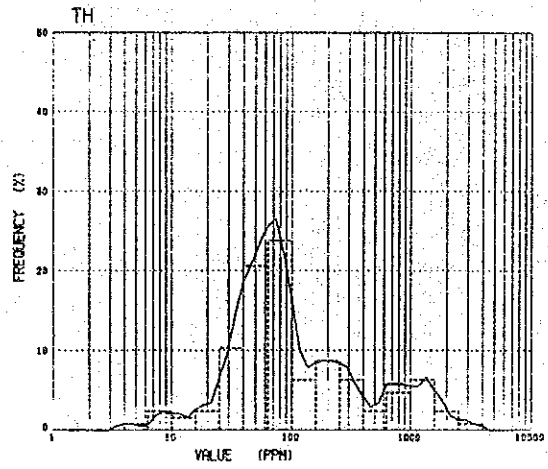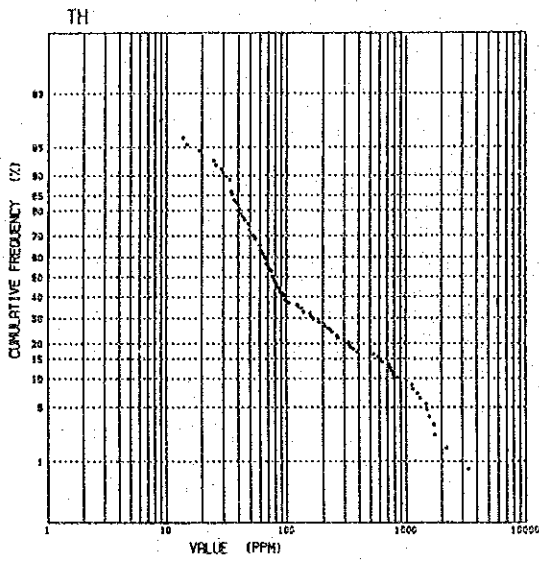


Apx. 48 Cumulative Frequency Distributions and Histograms of Elements -- Kuge Sector --

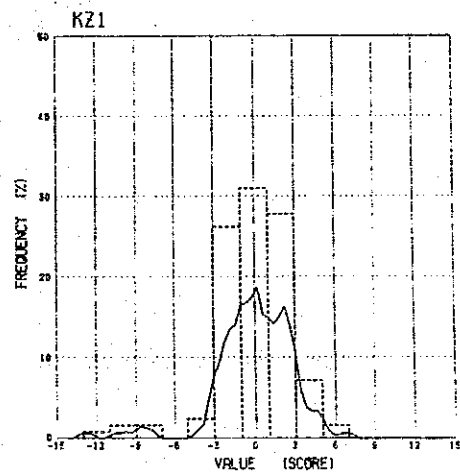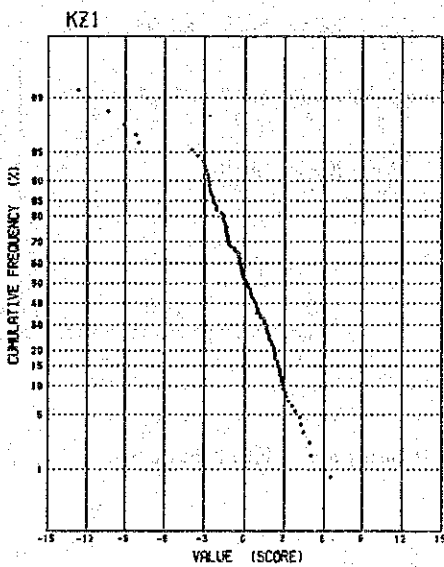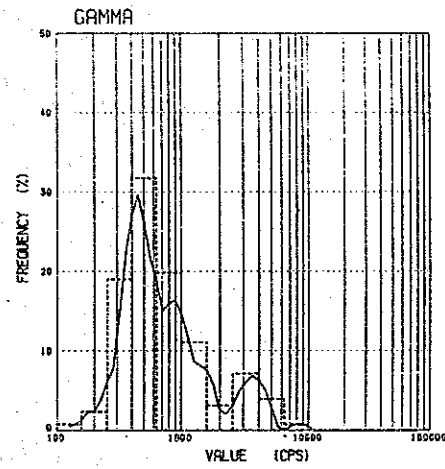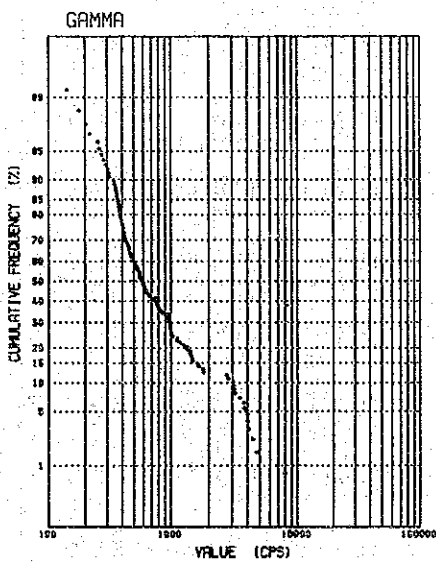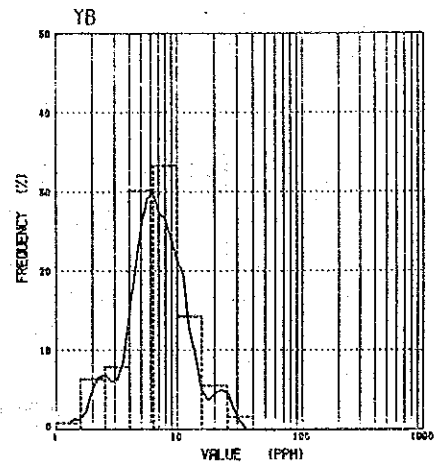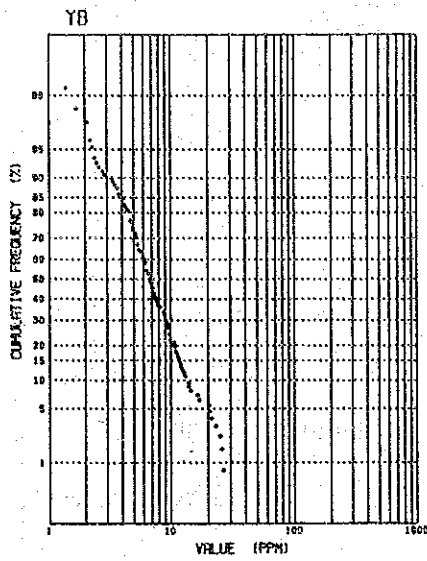

Apx. 48 Cumulative Frequency Distributions and Histograms of Elements — Kuge Sector —

KUGE AREA

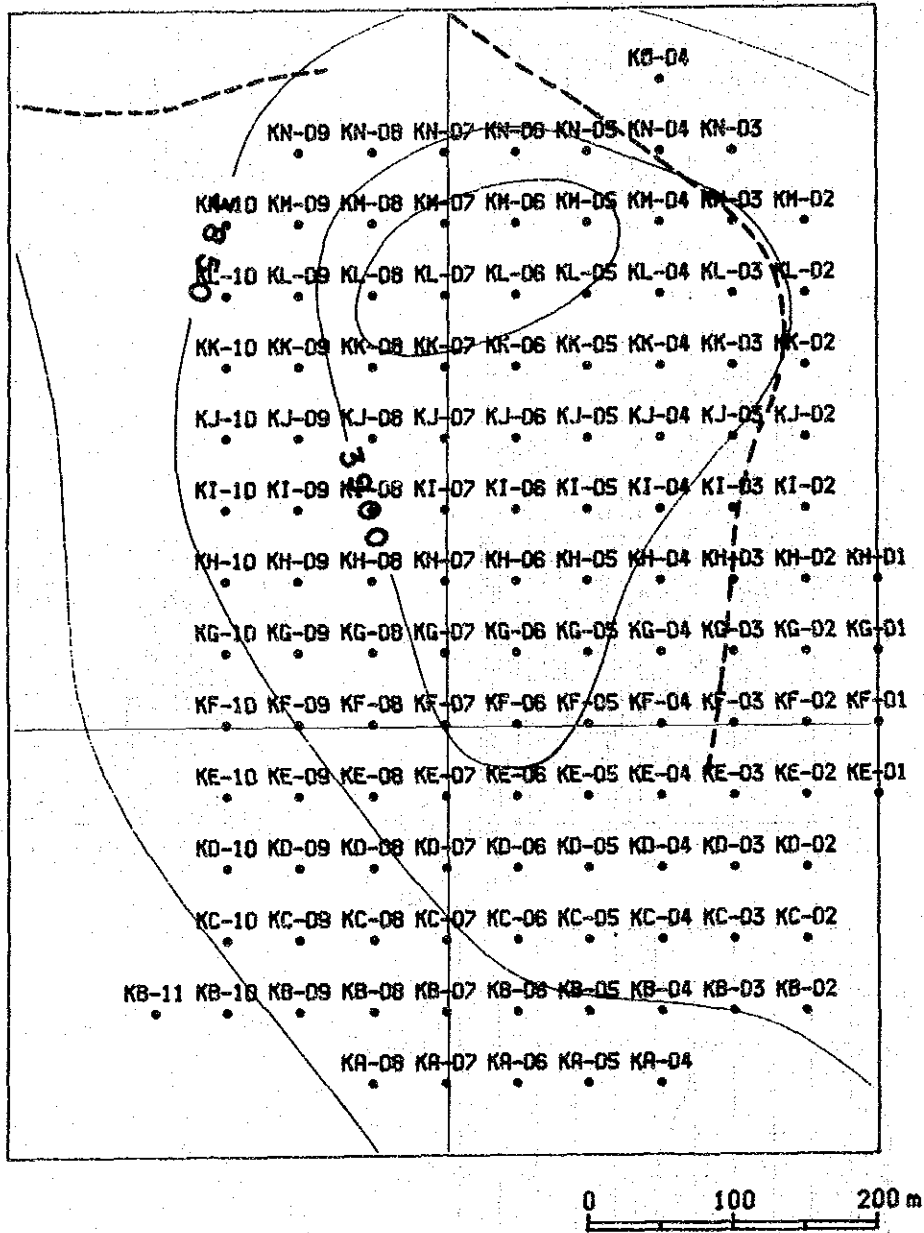

Apx. 49 Location Map of Geochemical Samples -- Kuge Sector --

AREA NAME = KUGE

FILE NAME = P

NO. OF SAMPLE = 126

CONTOUR VALUE


MAXIMUM = 5

MINIMUM = .1

THRESHOLD = .63


MAP SCALE = 1:5000

LEGEND



ANOMALY ZONE

THRESHOLD CONTOUR LINE




CONTOUR LINE AND

CONTOUR VALUE (%)






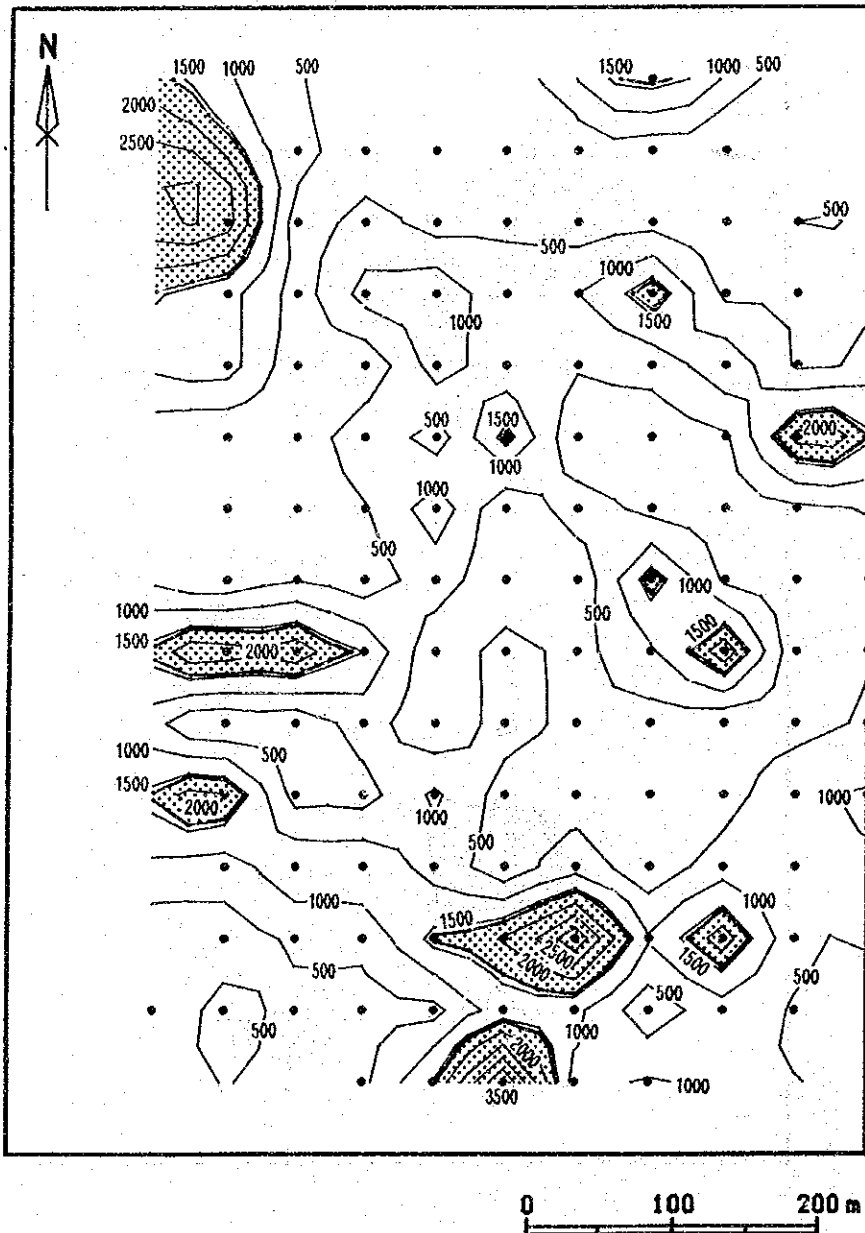
SAMPLE POINT

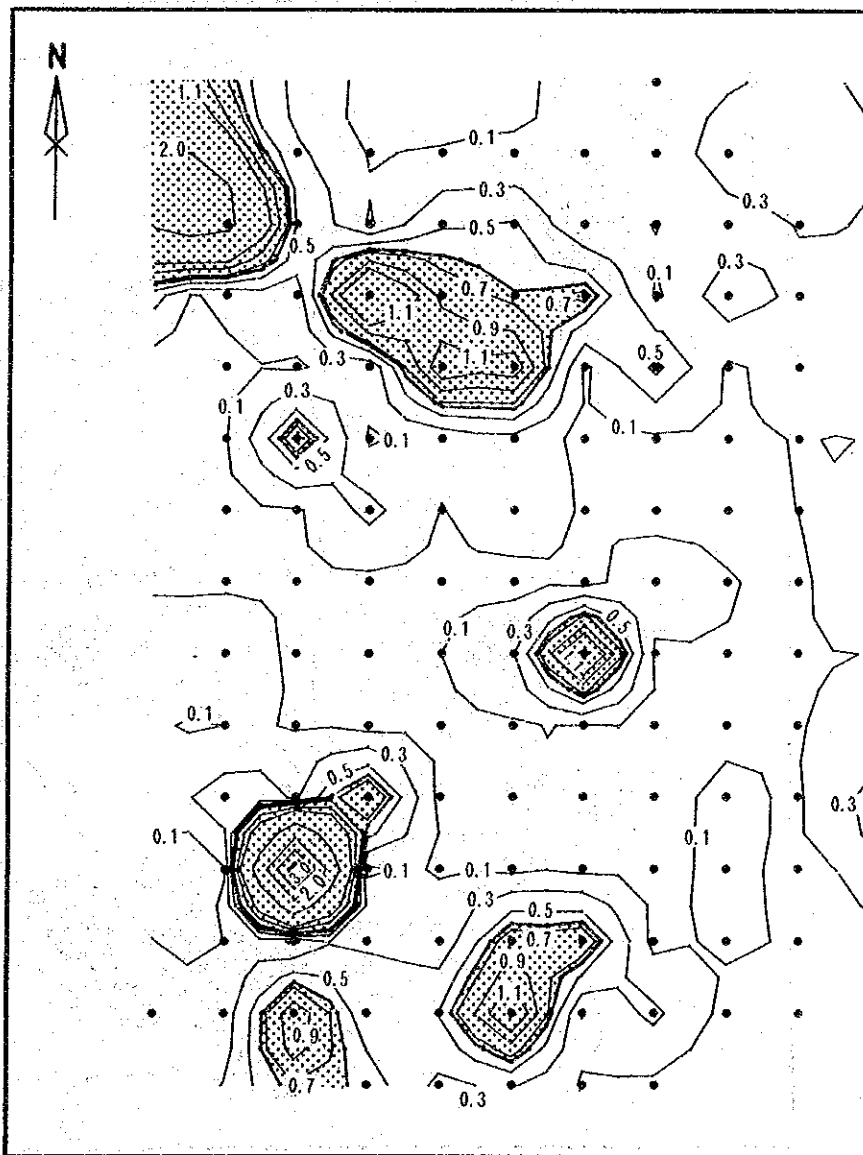

Apx. 50 Geochemical Density and Anomaly Map of P - Kuge Sector -

AREA NAME = KUGE
 FILE NAME = NB
 NO. OF SAMPLE = 126
 CONTOUR VALUE
 MAXIMUM = 4000
 MINIMUM = 500
 INTERVAL = 500
 THRESHOLD = 1600
 MAP SCALE = 1:5000

LEGEND
 ANOMALY ZONE
 THRESHOLD CONTOUR LINE
 CONTOUR LINE AND
 CONTOUR VALUE (ppm)
 SAMPLE POINT



Apx. 51 Geochemical Density and Anomaly Map of Nb — Kuge Sector —