

## APPENDIX



Appendix 1 Mineral assemblages of the rocks under thin section



Appendix 2 Mineral assemblages of the ores under polished section

Appendix 2 Mineral assemblages of the ores under polished section

Polished Section No.	Area	Occurrence	Chalcopyrite (Cp)	Bornite (Bn)	Chalcocite (Cc)	Covellite (Cv)	Cuprite (Cup)	Malachite (Mal)	Native Copper (Cu)	Molybdenite (Mo)	Tetrahedrite (Td)	Sphalerite (Sp)	Galena (Gn)	Pyrite (Py)	Magnetite (Mt)	Hematite (Hm)	Goethite (Goe)	Gangue minerals (G, Q, Quartz)	Remarks
1. MJJ-10 165.0m		(Cp)-(Py)dissemination	.											.	.			⊙	
2. MJJ-10 226.00m		(Mo)-(Bn)-(Cp)quartz veinlet and (Cp)-(Bn)dissemination	.	.	.					.				.	.			⊙	Thin plate of molybdenite (mo) in quartz veinlet.
3. MJJ-11 87.00m		py dissemination	.											●				⊙	
4. MJJ-12 100.00m		(Bn)-(Cc)quartz veinlet and Mt dissemination		.	.									.	●			⊙	
5. MJJ-12 191.00m		(Cp)-(Py)dissemination	.											.	.			⊙	
6. MJJ-13 57.80m		Cp dissemination	●															⊙	
7. MJJ-13 100.00m		(Mo)-(Bn)-(Cp)quartz veinlet and Mt dissemination	.	.						.				.	●			⊙	Thin plate of molybdenite (mo) in quartz veinlet.
8. MJC-1 58.60m		Cp veinlet and Cp dissemination	○	.	.									.				⊙	
9. MJC-1 137.90m		Cp dissemination	●	.	.									.	.			⊙	* Chalcocite and digenite occur as Cu-S series minerals
10. MJC-2 201.50m		(Cp)dissemination	.	.	*									.	.			⊙	
11. MJC-2 137.30m		Cp dissemination	●															⊙	
12. MJC-2 200.00m		Py-(Cp)quartz veinlet and Mt dissemination	.											●	●			⊙	

⊙ > > > > >

Appendix 3 Drilling logs of MJJ-10 to MJJ-13 and MJC-1 to MJC-2(1:200)

Depth	Strati-Column	Structure	Description	Alteration							Assay Results							
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm	
2.00			Non-core															
	+		Granodiorite silicified & fractured	1		1	2	1	1	2								
5.50			Dissemination of Py, Cp and Bo	3		1	2	1	2	2								
6.70				3		1	2	1	2	2								
8.20			Quartz Por	3		1	2	1	2	2								
10				3		1	2	1	2	2	10	100	<0.1	1.2	7170	22	28	<1
11.00			Granodiorite	1		1	2	2	2	2								
12.00				1		1	2	2	2	2								
			Quartz Por fractured intensely	1		1	2	2	2	2	14	100	<0.1	0.7	4195	15	26	4
			Abundant Qtz-veinlets	3		1	3	3	1	1								
			Dissemination of Py, Bo and Cp	3		1	3	3	1	1	18	100	-	-	3890	17	72	67
20				3		1	3	3	1	1								
			Quartz Por fractured intensely	4		1	3	3	1	1								
			Abundant Qtz-veinlets	4		1	3	3	1	1								
			Dissemination of Py, Cp and Bo	4		1	3	3	1	1	26	100	<0.1	1.0	4989	13	30	2
30				4		1	3	3	1	1	30	100	<0.1	1.9	8304	11	24	542
			Quartz Por	4		1	2	3	1	1								
33.00			Granodiorite Weakly fractured	4		1	2	3	1	1								
				4		1	2	3	1	1	34	100	-	-	540	14	129	9
			Dissemination of Py, Bo and Cp	1		1	1	1	2	2								
40				1		1	1	1	2	2	38	100	-	-	177	18	454	<1
40.50			Quartz Por	1		1	1	1	2	2								
41.00				1		1	1	1	2	2								
			Granodiorite fractured intensely	1		1	1	1	2	2	42	100	-	-	133	16	425	<1
				1		1	1	1	2	2								
46.80			Quartz Por fractured	3		1	1	1	2	2	46	100	-	-	421	12	138	<1
				3		1	1	1	2	2								
50				3		1	1	1	2	2	50	100	<0.1	0.9	4442	12	71	2



Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
											g/t	g/t	ppm	ppm	ppm	ppm		
60	L		Quartz Por fractured & argilized	3		1	1	1	1	1								
	L		Dissemination of Py, Cp and Bo	3		1	1	1	1	1	52	100	<0.1	1.7	5313	12	90	29
	L			3		1	1	1	1	1	54	100	—	—	2867	10	34	<1
	L			3		1	1	2	1	1	56	100	—	—	2382	14	55	2
	L			3		1	1	2	1	1	58	100	<0.1	4.6	22106	19	222	57
	L			3		1	1	2	1	1	60	100	<0.1	4.1	22113	14	186	42
66.20 69.10 70	L		Quartz Por fractured & argilized 60.0-67.0 shear-zone															
	L										62	100	—	—	2988	15	254	<1
	L									64	100	<0.1	1.6	5290	15	430	6	
	+		Granodiorite Weakly fractured	3		1	2	3	3	3	66	100	—	—	1635	13	99	1
	+			3		1	2	3	3	3	68	100	—	—	2326	15	115	2
L		Quartz Por	3		1	2	3	3	3	70	100	—	—	2017	10	45	7	
80	+		Granodiorite fractured	2		1	1	1	2	2								
	+			2		1	1	1	2	2	72	100	—	—	1985	15	562	11
	+		Dissemination Of Py and Cp	2		1	1	1	2	2	74	100	—	—	1841	11	303	8
	+			1		1	3	4	3	3	76	100	—	—	828	13	133	<1
	+			1		1	3	4	3	3	78	100	—	—	2116	9	138	5
	+			1		1	3	4	3	3	80	100	<0.1	4.0	4991	14	188	118
90	+		Granodiorite slicified & fractured	3		1	3	4	3	3								
	+			3		1	3	4	3	3	82	100	—	—	705	17	194	10
	+		Dissemination of Py, Cp and Bo	3		1	3	4	3	3	84	100	—	—	130	16	140	<1
	+			2		1	3	4	3	3	86	100	—	—	127	12	180	<1
	+			2		1	3	4	3	3	88	100	—	—	326	16	449	2
	+			2		1	3	4	3	3								
100	+		Granodiorite slicified, fractured & argilized	3		1	2	4	2	2								
	+			3		1	2	4	2	2								
	+		Stringer of molybdenite	3		1	2	4	2	2								
	+		Dissemination of Py, Cp and Bo	1		1	1	3	2	2								
	+			1		1	1	3	2	2								
	+			1		1	1	3	2	2								

Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm		
110	+		Granodiorite	1		1	1	3	2	2									
			Weakly fractured	1		1	1	3	2	2									
			109.0	1		1	1	3	2	2									
			Stringer of molybdenite	1		1	1	3	2	2									
				1		1	1	3	2	2									
				1		1	1	3	2	2									
120	+		Granodiorite	1		2	2	2	2	2									
			Weakly fractured	1		2	2	2	2	2									
			Epidote in fractures	1		2	2	2	2	2									
				1		1	1	3	2	2									
				1		1	1	3	2	2									
				1		1	1	3	2	2									
130	+		Granodiorite	1		1	1	2	2	2									
			Weakly fractured	1		1	1	2	2	2									
			128.0-129.0	1		1	1	2	2	2									
			Dissemination of Py & Cp	3		1	1	3	2	2									
				3		1	1	3	2	2									
				3		1	1	3	2	2									
140	+		Granodiorite	1		1	1	1	2	1									
			Weakly fractured	1		1	1	1	2	1									
			Dissemination v. Weakly	1		1	1	1	2	1									
				1		1	1	3	3	3									
				1		1	1	3	3	3									
				1		1	1	3	3	3									
150	+		Granodiorite	1		1	1	1	2	2									
			Weakly fractured	1		1	1	1	2	2									
			Veinlets of Qtz & Chl	1		1	1	1	2	2									
			Dissemination v. weakly	1		1	1	3	3	3									
				1		1	1	3	3	3	148	100	-	-	525	12	426	<1	
				1		1	1	3	3	3									

Depth	Stratigraphic Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm		
160	+	/	Granodiorite	1		1	1	1	1	2									
			Weakly fractured	1		1	1	1	1	2									
			158.5-162.0	1		1	1	1	1	2									
			Fault zone	1		1	1	1	1	2									
				1		1	2	3	3	3	158	100	<0.1	12.0	38285	19	221		5
				1		1	2	3	3	3									
166.40 167.90	+	/	Granodiorite	3		1	1	3	3	3									
			fractured weakly	3		1	1	3	3	3	162	100	--	--	454	15	349	<1	
			Dissemination	3		1	1	3	3	3									
			of Py & Cp	4		1	1	1	2	2	166	100	--	--	426	17	70	5	
				4		1	1	1	2	2									
170	+	/		4		1	1	1	2	2	170	100	--	--	721	16	160	<1	
			Granodiorite	1		1	1	1	1	2									
			fractured weakly	1		1	1	1	1	2									
			Dissemination	1		1	1	1	1	2									
180	+	/	of Py	1		1	1	1	1	2									
			Quartz veinlet	3		1	1	2	2	2									
			w:0.30	3		1	1	2	2	2									
			Ø179/00 m	3		1	1	2	2	2									
				3		1	1	2	2	2									
190	+	/	Granodiorite	2		1	1	2	2	2									
			v. weakly	2		1	1	2	2	2									
			Qtz-stringers	2		1	1	2	2	2									
			Ø182.5 m and	2		1	1	2	2	2									
			Ø185.5 m	2		1	1	3	3	1									
				2		1	1	3	3	1									
199.50 200	+	/	Granodiorite	1		1	1	2	3	3									
			fractured & argillized	1		1	1	2	3	3									
			Epidote and chlorite	1		1	1	2	3	3	194	100	--	--	662	12	123	6	
			abundant	1		1	1	1	3	3									
			Quartz Por	1		1	1	1	3	3									

Depth	Strati-column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
202.00	L L	X	Quartz Por fractured & argillized	1		1	1	1	3	3								
	+	X	Granodiorite argillized & fractured	1		1	1	1	3	3	202	100	-	-	214	15	81	<1
	+	X	Chlorite and epidote dominant	1		1	2	3	3	3	206	100	-	-	233	18	97	<1
210	L L	X	Granodiorite argillized & fractured	1		1	2	3	3	3	210	100	-	-	3227	15	60	14
	+	X	Chlorite and epidote abundant	2		1	3	4	3	3								
219.50	L L	X	Granodiorite argillized & fractured	2		1	3	4	3	3								
220	L L	X	Chlorite and epidote abundant	2		1	3	4	3	3	214	100	<0.1	2.6	20271	12	47	2
	+	X	Dissemination & stockwork of Py, Cp and Bo	2		1	3	4	3	3								
	+	X	Quartz Por fractured & argillized	2		1	3	4	3	3								
228.80	L L	X	Dissemination & stockwork of Py, Cp and Bo	4		1	1	1	2	2	222	100	-	-	195	11	84	2
230	L L	X	Dissemination & stockwork of Py, Cp and Bo	4		1	1	1	2	2	224	100	-	-	166	12	103	1
	+	X	Granodiorite fractured & argillized	4		1	3	3	3	3	226	100	-	-	258	15	59	6
231.50	L L	X	Granodiorite fractured & argillized	4		1	3	3	3	3								
232.60	L L	X	Quartz Por	4		1	3	3	3	3								
236.60	L L	X	Granodiorite fractured & strongly argillized	4		1	3	3	3	3	230	100	-	-	853	13	273	19
238.20	L L	X	Quartz Por	3		1	2	3	2	2								
240	L L	X	Granodiorite fractured & argillized	3		1	2	3	2	2	234	100	-	-	416	13	85	<1
	+	X	Granodiorite fractured & strongly argillized	3		1	3	4	3	3								
	+	X	Quartz Por	3		1	3	4	3	3	238	100	<0.1	10.8	35794	11	38	16
250	L L	X	Granodiorite fractured & argillized	3		1	3	4	3	3								
	+	X	Dissemination of Py & Cp	2		1	1	3	3	3								
	+	X	Epidote in fractures	2		1	1	3	3	3								
	+	X	Epidote in fractures	2		1	1	2	2	3								
	+	X	Epidote in fractures	2		1	1	2	2	3								
	+	X	Epidote in fractures	2		1	1	2	2	3								

Depth	Strat-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
260	+	/	Granodiorite fractured & argillized	1		1	1	2	2	3									
			Dissemination of Py & Cp	1		1	1	2	2	3									
			0257.00 Qtz-veinlet w.o. 40 m	3		1	1	2	2	3	256	100	--	--	112	13	81	<1	
				3		1	1	2	2	3									
				3		1	1	2	2	3	260	100	--	--	216	15	82	<1	
267.30 270	+	/	Granodiorite fractured & argillized	3		3	2	3	3	3									
			Dissemination of Py, Cp & Bo	3		3	2	3	3	3	264	100	--	--	622	15	230	<1	
			Quartz Por Strongly fractured	3		3	2	3	3	3	268	100	<0.1	1.9	4246	22	153	59	
			Shear zone	3		3	2	3	3	3									
271.50 279.30 280	+	/	Granodiorite fractured strongly	3		1	3	3	3	3	272	100	--	--	359	16	376	<1	
			Fault zone with sheared rocks	3		1	3	3	3	3									
				3		1	3	3	3	3	278	100	--	--	1168	15	177	6	
			Quartz Por	3		1	3	3	3	3									
282.50 283.60	+	/	Granodiorite fractured & argillized	1		1	1	4	3	3									
			Quartz Por	1		1	1	4	3	3	282	100	--	--	426	103	124	11	
			Granodiorite fractured & argillized	1		1	1	4	3	3									
290	+	/	Dissemination of Py & Cp	1		1	1	4	3	3									
				1		1	1	4	3	3									
291.20 292.90	+	/	Dissemination of Py & Cp	2		1	1	3	3	3									
			Quartz Por	2		1	1	3	3	3	292	100	<0.1	2.1	6480	14	106	469	
296.60 297.70	+	/	Granodiorite argillized	2		1	1	3	3	3									
			Quartz Por	2		1	1	3	3	3									
300	+	/	Granodiorite fractured	2		1	1	3	3	3	298	100	--	--	297	14	39	8	
				2		1	1	3	3	3									
301.3	+	/	Bottom	3		2	1	4	3	3									

Depth	Strati-Column	Structure	Description	Alteration					Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm	
14.00			Non-core															
	L	///	Quartz Por	1		2	2	1	1	1								
	L	///	Strongly fractured & weakly disseminated ore minerals	1		2	2	1	1	1								
	L	///		1		2	2	2	3	2								
10	L	///		1		2	2	2	3	2	10	100	-	-	251	10	28	242
25.70	L	///	Quartz Por fractured strongly	1		1	1	2	1	1								
	L	///		1		1	1	2	1	1								
	+	///	Granodiorite fractured strongly	1		3	1	2	3	4	14	100	<0.1	1.4	9722	11	20	131
	+	///		1		3	1	2	3	4								
20	+	///	Dissemination of Bo, Cp & Py	1		3	1	2	3	4	18	100	-	-	1898	14	52	23
	+	///		1		3	1	2	3	4								
	+	///	Granodiorite fractured	1		2	2	2	2	3								
	+	///		1		2	2	2	2	3	22	100	-	-	3685	13	27	131
	+	///	Dissemination & stockwork of Bo, Cp, Py	1		2	2	2	2	3								
	L	///		4		1	3	2	3	1	26	100	-	-	2272	10	25	235
	L	///	Quartz Por fractured	4		1	3	2	3	1								
30	L	///		4		1	3	2	3	1	30	100	-	-	2442	12	38	10
	L	///	Quartz Por fractured	4		1	3	2	3	1								
	L	///		4		1	3	2	3	1	34	100	-	-	834	10	33	87
	L	///	Dissemination of Cp, Py & Bo	4		1	3	2	3	1								
	L	///		4		1	3	3	2	1	38	100	-	-	943	14	25	25
	L	///		4		1	3	3	2	1								
40	L	///	Quartz Por fractured intensely	5		1	3	3	3	1								
	L	///		5		1	3	3	3	1	42	100	-	-	121	12	32	2
	L	///		2		2	1	2	2	2	46	100	-	-	3902	10	23	16
46.40	+	///	Granodiorite fractured	2		2	1	2	2	2								
50	+	///		2		2	1	2	2	2	50	100	-	-	1751	14	28	5

Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epitote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
				g/t	g/t	g/t	g/t	g/t	g/t	m	cm	g/t	g/t	ppm	ppm	ppm	ppm	
60	+		Granodiorite fractured weakly	3		2	1	1	2	2								
	+		Dissemination of Cp, Py & Bo	3		2	1	1	2	2	52	100	-	-	308	11	33	<1
	+			3		3	1	2	2	2	54	100	-	-	130	12	44	<1
	+			3		3	1	2	2	2	56	100	<0.1	2.2	8221	10	24	249
	+			3		3	1	2	2	2	58	100	-	-	737	12	39	<1
				3		3	1	2	2	60	100	-	-	866	14	57	8	
64.70 70	+		Granodiorite fractured moderately	3		3	1	3	2	2								
	+		Dissemination of Bo, Cp & Py	3		3	1	3	2	2	62	100	-	-	3799	12	37	9
	+			5		1	3	3	2	1	64	100	-	-	2196	12	41	96
	+			5		1	3	3	2	1	66	100	-	-	2153	13	30	18
	L		Quartz Por fractured strongly	5		1	3	3	2	1	68	100	-	-	1341	11	29	5
L			5		1	3	3	2	1	70	100	-	-	384	11	22	<1	
80	L		Quartz Por fractured strongly	5		1	3	3	2	1								
	L		Dissemination of Bo, Cp & Bo	5		1	3	3	2	1	72	100	-	-	2009	31	505	335
	L			5		1	3	3	2	1	74	100	-	-	1093	13	22	10
	L			4		1	5	4	2	1	76	100	-	-	350	10	28	25
	L		Mo-stringers occasionally	4		1	5	4	2	1	78	100	-	-	879	10	31	28
	L			4		1	5	4	2	1	80	100	<0.1	1.4	4284	12	22	24
88.50 90	L		Quartz Por Strongly fractured	4		1	5	4	2	1								
	L		Dissemination of Cp, Py & Bo	4		1	5	4	2	1	82	100	<0.1	3.3	9901	12	22	1089
	L			4		1	5	4	2	1	84	100	-	-	708	14	19	19
	L		Mo-stringers 80.0-85.0 sheared zone	1		2	1	3	3	2	86	100	-	-	2134	11	24	324
	L			1		2	1	3	3	2	88	100	-	-	3217	11	17	460
	+		Granodiorite fractured strongly	1		2	1	3	3	2	90	100	-	-	807	15	42	50
100	+		Granodiorite fractured strongly	3		3	1	2	2	2								
	+		Dissemination of Bo, Cp, Py and Mo	3		3	1	2	2	2	94	100	-	-	1014	15	34	20
	+			3		3	1	1	2	2								
	+		Mo-stringers occasionally	3		3	1	1	2	2	98	100	-	-	663	15	31	39

Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
110	+		Granodiorite fractured strongly	2		3	1	2	3	2								
	+		Dissemination of Cp, Py & Bo	2		3	1	2	3	2	102	100	-	-	448	12	36	<1
	+			3		2	1	2	3	3	106	100	-	-	629	15	47	<1
	+			3		2	1	2	3	3	110	100	-	-	179	11	41	5
120	+		Granodiorite fractured	3		3	1	2	3	3								
	+		Dissemination of Cp, Py, Bo								112	100	-	-	873	15	43	9
	+		Qtz stringers occasionally	3		2	2	1	2	2	114	100	-	-	238	12	39	21
	+			3		2	2	1	2	2	118	100	-	-	694	15	32	71
130	+		Granodiorite Strongly fractured	3		2	1	2	2	2								
	+		Dissemination of Cp, Py, Bo	3		2	1	2	2	2	122	100	-	-	3064	13	15	67
	+			3		2	1	1	2	1	126	100	-	-	639	13	37	9
	+			3		2	1	1	2	1	130	100	-	-	247	11	35	12
140	+		Granodiorite fractured strongly	3		1	1	1	2	1								
	+		Dissemination of Cp, Bo, Py	3		1	1	1	2	1	134	100	-	-	730	15	31	46
	+		Stockwork occasionally	3		1	1	1	2	2								
	+			3		1	1	1	2	2	138	100	<0.1	1.8	4509	17	36	4
150	+		Granodiorite fractured strongly	3		2	1	1	2	2								
	+		Dissemination of Cp, Py, Bo	3		2	1	1	2	2	142	100	-	-	2967	14	33	20
	+		Qtz stringers and veinlets abundantly	2		2	1	2	2	2	144	100	<0.1	0.7	6476	11	24	48
	+			2		2	1	2	2	2	146	100	<0.1	1.3	10482	14	18	448
150	+			2		2	1	2	2	2	148	100	-	-	1205	9	26	57
	+			2		2	1	2	2	2	150	100	-	-	457	15	24	4



Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Zeolite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
160	+		Granodiorite fractured moderately	2		2	1	2	2	2								
	+		Dissemination of Cp, Bo & Py	2		2	1	2	2	2	152	100	--	--	3582	15	22	56
	+			3		2	1	1	2	1	154	100	--	--	1134	18	24	113
	+			3		2	1	1	2	1	156	100	--	--	600	14	16	3
	+			3		2	1	1	2	1	158	100	--	--	1276	16	26	74
+		3		2	1	1	2	1	160	100	--	--	1751	16	28	8		
170	+		Granodiorite fractured moderately	3		2	1	2	2	2								
	+		Dissemination of Cp, Py & Bo	3		2	1	2	2	2	162	100	--	--	609	16	34	8
	+			3		2	2	1	2	2	164	100	--	--	2554	13	27	69
	+			3		2	2	1	2	2	166	100	--	--	1740	11	26	12
	+			3		2	2	1	2	2	168	100	--	--	1309	19	22	22
+		3		2	2	1	2	2	170	100	--	--	2892	13	21	101		
180	+		Granodiorite fractured moderately	3		2	2	2	2	2								
	+		Dissemination & stockwork of Cp, Bo & Py	3		2	2	2	2	2	172	100	--	--	1173	12	11	63
	+			3		2	2	2	2	2	174	100	--	--	1238	11	18	267
	+			3		1	1	2	1	1	176	100	<0.1	3.9	12304	12	11	387
	+			3		1	1	2	1	1	178	100	--	--	1244	14	20	20
+		3		1	1	2	1	1	180	100	--	--	3575	11	21	150		
190	+		Granodiorite fractured moderately	3		1	1	2	2	2								
	+		Dissemination of Bo, Cp & Py	3		1	1	2	2	2	184	100	--	--	2448	12	19	264
	+			3		1	1	2	2	2								
	+		3		1	1	2	2	2	188	100	--	--	838	11	21	53	
200	+		Granodiorite fractured moderately	3		1	1	2	2	2								
	+		Dissemination of Py, Cp, Bo	3		1	1	2	2	2	192	100	--	--	1732	13	20	171
	+			3		1	2	2	2	2	196	100	--	--	630	12	16	1
	+		Sericite and chlorite dominante	3		1	2	2	2	2	200	100	--	--	921	14	24	28

Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
210	+		Granodiorite fractured moderately	2		2	2	2	2	3								
	+		Dissemination of Bo, Cp & Py	3		2	2	2	2	3	202	100	-	-	896	21	35	5
	+			2		2	1	2	2	3	204	100	-	-	199	13	20	12
	+		Qtz-stringers abundant	2		2	1	2	2	3	206	100	-	-	2258	15	18	27
	+			2		2	1	2	2	3	208	100	-	-	1444	16	22	21
	+			2		2	1	2	2	3	210	100	-	-	1993	12	16	56
218.60 220	+		Granodiorite fractured strongly	2		2	2	2	2	3								
	+		Dissemination & stockwork of Bo, Cp & Py	2		2	2	2	2	3	212	100	-	-	3823	16	23	97
	+			2		3	1	3	2	3	214	100	-	-	1929	15	29	67
	+			2		3	1	3	2	3	216	100	-	-	1424	285	29	262
	+			2		3	1	3	2	3	218	100	-	-	624	11	19	1447
	L		Quartz Por fractured strongly	2		3	1	3	2	3	220	100	-	-	1693	11	10	145
222.50 230	L		Granodiorite fractured strongly	5		1	2	3	2	1								
	L			5		1	2	3	2	1	222	100	-	-	1255	13	16	58
	+		Granodiorite fractured strongly	5		1	2	3	2	1	224	100	-	-	767	13	17	44
	+			3		2	1	2	2	2	226	100	-	-	1440	19	28	259
	+			3		2	1	2	2	2	228	100	-	-	3073	13	25	124
	+			3		2	1	2	2	2	230	100	<0.1	4.0	12797	11	19	250
240	+		Granodiorite fractured strongly & argillized moderately	3		3	1	2	2	3								
	+			3		3	1	2	2	3	232	100	-	-	3662	15	21	93
	+		Dissemination & stockwork of Bo, Cp, Py and Mo	3		3	1	1	2	3	234	100	-	-	2802	14	17	720
	+			3		3	1	1	2	3	236	100	-	-	2460	21	49	253
	+			3		3	1	1	2	3	238	100	-	-	2403	15	26	156
	+			3		3	1	1	2	3	240	100	-	-	627	15	29	15
250	+		Granodiorite fractured moderately	2		3	1	2	2	3								
	+		Dissemination of Bo, Cp & Py	2		3	1	2	2	3	244	100	-	-	2718	15	89	201
	+			2		3	2	3	2	4								
	+		Mo-Stringers occasionally	2		3	2	3	2	4	248	100	-	-	1562	13	37	90

Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epigote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
											m	cm	g/t	g/t	ppm	ppm	ppm	ppm
260	+		Granodiorite fractured weakly	2		3	1	1	2	3								
	+			2		3	1	1	2	3	252	100	-	-	2124	15	35	252
	+			2		2	1	1	2	3	256	100	-	-	1420	13	73	60
	+			2		2	1	1	2	3	260	100	<0.1	0.6	4221	12	64	50
270	+		Granodiorite fractured strongly & argillized weakly	2		2	1	2	2	3								
	+			2		2	1	2	2	3	234	100	-	-	3236	11	19	109
	+		Dissemination of Bo, Cp & Py	3		2	1	2	2	3								
	+			3		2	1	2	2	3	268	100	-	-	1448	11	16	23
280	+		Granodiorite fractured weakly	3		5	1	1	2	2								
	+			3		5	1	1	2	2	272	100	-	-	407	11	47	<1
	+		Dissemination of Bo, Cp & Py	3		2	1	1	2	2	276	100	-	-	3221	11	6	419
	+			3		2	1	1	2	2	280	100	-	-	3361	12	43	176
290	+		Granodiorite fractured moderately	3		3	1	1	2	2								
	+		Dissemination of Bo, Cp & Py	3		3	1	1	2	2	284	100	-	-	1990	10	26	183
	+		Qtz-stringers occasionally	3		3	1	2	2	2								
	+			3		3	1	2	2	2	238	100	-	-	1358	12	22	70
300	+		Granodiorite fractured moderately	3		3	1	2	2	2								
	+		Dissemination of Bo, Cp, Py and Mo	3		3	1	2	2	2	292	100	-	-	1506	11	27	67
	+		Stockworks occasionally	1		2	1	1	2	1	296	100	-	-	1215	11	26	14
	+			1		2	1	1	2	1								
302.5	+		Bottom	2		2	1	2	2	4								

Depth	Strat-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
										m	cm	μ/t	g/t	ppm	ppm	ppm	ppm	
2.00			Non-core															
	L		Quartz Por fractured strongly	2		2	2	4	1	1								
	L		Dissemination of Cp & Py	2		2	2	4	1	1								
	L		Qtz-stringers occasionally	2		2	2	4	1	1								
10											10	100			2631	8	5	28
	L		Quartz Por Fractured strongly	4		1	3	4	1	1								
	L		Dissemination & stockwork of Cp, Bo, Py and Mo	5		1	2	2	1	1								
	L		Qtz-stringers occasionally	4		1	3	4	1	2								
20											18	100			3141	10	25	27
	L		Quartz Por fractured moderately	4		1	3	3	2	2								
	L		Dissemination of Bo, Cp, Mo and Py	4		1	3	3	2	2								
	L		Qtz-stringers occasionally	4		1	2	3	2	1	26	100			2807	7	16	668
30																		
	L		Quartz Por fractured moderately	4		1	3	3	2	2								
	L		Dissemination of Bo, Cp, Mo and Py	4		1	3	3	2	2	34	100			3827	11	20	87
36.40	L		Granodiorite fractured moderately	2		2	1	3	3	3								
38.80	L		Quartz Por	2		2	1	3	3	3								
40																		
	+		Granodiorite fractured weakly	1		2	1	2	3	2	42	100			1440	10	22	37
	+		Dissemination of Cp, Py, Bo	1		2	1	2	3	2								
	+		Qtz-stringers occasionally	1		2	1	2	3	1								
50											50	100			2853	8	9	92

Depth	Strati-Column	Structure	Description	Alteration							Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm		
60	+		Granodiorite fractured weakly	1		2	1	1	2	1									
	+		Films of Bo	1		2	1	1	2	1									
	+		Dissemination of Cp & Py	1		2	1	1	2	2									
	+			1		2	1	1	2	2	58	100	—	—	2475	11	15	35	
70	+		Granodiorite fractured moderately	1		2	1	1	2	3									
	+		Films of Bo	1		1	1	2	2	1									
	+		Qtz-stringers with Mo	1		1	2	2	3	2	66	100	—	—	2664	10	19	63	
	+			1		1	2	2	3	2									
80	+		Granodiorite fractured intensely	1		2	1	2	3	2									
	+		Dissemination of Bo, Cp & Py	1		2	1	2	3	2	74	100	—	—	413	11	24	17	
	+		Qtz-stringers with chl	1		2	1	2	2	2									
	+			1		2	1	2	2	2									
90	+		Granodiorite fractured strongly	1		2	1	2	3	2									
	+		Dissemination of Cp, Py & Bo	1		2	1	2	3	2	82	100	—	—	789	531	10	10	
	+		Qtz-stringers occasionally	1		2	1	2	3	2									
	+			1		2	1	2	3	2	90	100	—	—	1898	14	20	15	
100	+		Granodiorite fractured moderately	1		2	1	2	3	2									
	+		Dissemination of Bo, Cp & Py	1		2	1	2	3	2									
	+			1		3	1	2	3	2									
	+			1		3	1	2	3	2	98	100	—	—	712	11	13	13	

Depth	Strati-Column	Structure	Description	Alteration							Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo		
											m	cm	g/t	g/t	ppm	ppm	ppm	ppm		
105.00	+	/	Granodiorite fractured strongly	1		3	1	2	3	2										
			Dissemination of Bo, Cp, Py and Mo	1		3	1	2	3	2										
108.00	L	/	Quartz Por fractured strongly	4		2	3	2	3	1	106	100	--	--	1750	12	19	55		
109.20	+	/	Granodiorite	4		2	3	2	3	1										
110	L	/	Quartz Por																	
111.00	+	/	Granodiorite fractured strongly	1		2	2	2	3	3										
112.60	L	/	Quartz Por fractured strongly	1		2	2	2	3	3	114	100	--	--	1331	10	20	123		
120	L	/	Dissemination & stockwork of Bo, Cp, Mo and Py	4		1	3	2	2	2										
				4		1	3	2	2	2										
130	L	/	Quartz Por fractured strongly	4		1	3	2	2	2										
			Dissemination & stockwork of Bo, Cp, Mo and Py	4		1	3	2	2	2	122	100	<0.1	2.9	6252	10	12	252		
				4		1	3	3	2	1										
				4		1	3	3	2	1	130	100	--	--	588	10	13	8		
134.50	L	/	Quartz Por fractured moderately	4		2	3	2	2	1										
				1		2	2	3	3	2										
136.50	+	/	Granodiorite fractured	4		1	2	2	2	1										
140	L	/	Quartz Por fractured	4		1	2	2	2	1	138	100	--	--	202	10	24	12		
				4		1	2	2	2	1										
148.40	L	/	Quartz Por fractured moderately	4		1	3	3	2	1										
			Dissemination & stockwork of Cp, Py, Bo and Mo	4		1	3	3	2	1										
				1		2	2	3	3	2	146	100	--	--	1639	12	29	14		
150	+	/	Granodiorite fractured	1		2	2	3	3	2										

Depth	Strati-Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
160	+		Granodiorite fractured moderately	1		2	2	3	3	2								
	+		Dissemination & stockwork of Cp & Py	1		2	2	3	3	2	154	100	-	-	2456	12	11	57
	+		Sericite and chlorite dominate	1		2	2	3	3	2								
	+		Sericite and chlorite dominate	1		2	2	3	3	2								
161.30	+		Quartz Por fractured strongly	4		1	3	2	2	2	162	100	-	-	1379	10	23	17
170	L		Dissemination & stockwork of Cp, Bo & Py	4		1	2	2	2	2								
	L		Sericite and chlorite dominate	4		1	2	2	2	2	170	100	-	-	943	10	21	36
	L		Quartz Por fractured strongly	4		2	2	2	2	1								
	L		Dissemination & stockwork of Cp, Bo & Py	4		2	2	2	2	1								
180	L		Dissemination & stockwork of Cp, Bo & Py	4		2	3	2	2	1								
	L		Quartz Por fractured strongly	4		2	3	2	2	1	178	100	-	-	711	11	17	10
	L		Dissemination & stockwork of Cp, Bo & Py	4		2	2	2	2	1								
	L		Quartz Por fractured strongly	4		2	2	2	2	1								
184.50	+		Granodiorite fractured	4		2	2	2	2	1								
187.00	+		Quartz Por	2		2	1	2	2	1	186	100	-	-	1127	11	10	61
188.30	L		Granodiorite	2		2	1	2	2	1								
189.30	+		Films of Bo	2		2	1	2	2	1								
190	+		Films of Bo	2		2	1	2	2	1								
192.10	L		Quartz Por fractured	5		1	2	2	2	1								
	+		Granodiorite fractured moderately	5		1	2	2	2	1	194	100	-	-	2298	12	8	155
	+		Films of Bo & Cp	2		2	1	2	2	2								
200	+		Films of Bo & Cp	2		2	1	2	2	2								

Depth	Stratigraphic Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm	
210	+		Granodiorite fractured moderately	1		2	2	2	2	2								
	+		Dissemination of Bo, Cp & Py	1		2	2	2	2	2	202	100	-	-	903	14	11	59
	+		Films of Bo Cp	1		2	1	2	2	1								
	+		Films of Bo Cp	1		2	1	2	2	1	210	100	-	-	328	10	12	4
220	+		Granodiorite fractured strongly	1		2	1	2	2	1								
	+		Films of Bo & Cp	1		2	1	2	2	1								
	+		Qtz-stringers occasionally	1		2	1	2	3	2								
	+		Qtz-stringers occasionally	1		2	1	2	3	2	218	100	-	-	812	9	17	<1
230	+		Granodiorite fractured strongly	1		2	2	2	3	2								
	+		Films of Bo & Cp	1		2	2	2	3	2								
	+		Qtz-stringers with Cp & Py	1		2	1	2	2	1	226	100	-	-	410	14	24	3
	+		Qtz-stringers with Cp & Py	1		2	1	2	2	1								
240	+		Granodiorite fractured strongly	1		2	1	2	2	2								
	+		Films of Bo & Cp	1		2	1	2	2	2	234	100	-	-	1098	12	20	<1
	+		Films of Bo & Cp	1		2	2	3	3	2								
	+		Films of Bo & Cp	1		2	2	3	3	2								
248.50 250	+		Granodiorite fractured moderately	1		2	1	3	2	2								
	+		Dissemination & stockwork of Bo, Cp & Py	1		2	1	3	2	2	242	100	-	-	840	10	15	3
	+		Dissemination & stockwork of Bo, Cp & Py	1		2	1	3	2	2								
	L L		Quartz Por fractured strongly	1		2	1	3	2	2	250	100	-	-	1553	11	60	24



Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
254.30	L	/	Quartz Por fractured strongly	5		1	2	2	2										
			Dissemination & stockwork of Bo, Cp, Py	5		1	2	2	2	2									
260	+	/	Granodiorite fractured strongly	1		2	1	2	2										
			Dissemination & stockwork occasionally	1		2	1	2	2	2	258	100	-	-	574	14	12	5	
270	+	/	Granodiorite fractured moderately	1		3	1	2	2										
			Films of Bo & Cp	1		3	1	2	2	2									
			Qtz-veinlets with Cp & Py	1		2	1	3	3	2	266	100	-	-	566	10	13	17	
				1		2	1	3	3	2									
280	+	/	Granodiorite fractured weakly	1		2	1	2	2	1									
			Films of Bo & Cp	1		2	1	2	2	1	274	100	-	-	568	9	11	17	
			Qtz-stringers occasionally	1		3	1	2	2	1									
				1		3	1	2	2	1									
290	+	/	Granodiorite fractured moderately	1		2	1	3	3	2									
			Dissemination of Cp, Bo & Py	1		2	1	3	3	2	282	100	-	-	452	12	19	14	
				2		2	2	4	2	1									
				2		2	2	4	2	1	290	100	-	-	3115	8	14	32	
300	+	/	Granodiorite fractured moderately	1		2	1	3	2	2									
			Dissemination of Py & Cp	1		2	1	3	2	2									
				1		2	1	2	2	2									
				1		2	1	2	2	2	298	100	-	-	1380	11	15	18	
302	+	/	Bottom	1		2	1	2	2										

Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
											m	cm	g/t	g/t	DDE	DDE	DDE	DDE	
2.00			Non-core																
	+		Granodiorite fractured moderately	1			1	3	2	1									
	+		Cracks filled with limo. & clay	4			1	1	1	1									
	+		Qtz-stringers occasionally	2			2	3	2	2									
10											10	100	-	-	504	11	24	24	
	+		Granodiorite fractured moderately	1				2	3	2									
	+		Cracks filled with Bo, Cp, Cc, Py & Mo	1			1	4	2	2									
	+			1			1	4	4	3									
	+			1			1	4	3	2									
	+			2			2	3	3	2		18	100	-	-	1086	12	53	17
20				4			2	1	3	2									
	+		Granodiorite fractured moderately	3				2	2	2									
	+		Films of Bo, Cp & Py	2			1	2	3	2									
	+			2			2	2	4	3									
	+			2			1	2	3	2		26	100	-	-	167	13	45	1
	+			2			2	3	3	2									
30																			
	+		Granodiorite fractured strongly	2			3	4	3	2									
	+		Dissemination of Cp, Py, Bo, Mo and Cc	1			3	5	3	2		34	100	-	-	1023	10	39	66
	+			2			3	5	4	3									
40																			
	+		Granodiorite fractured strongly	1			2	5	3	2									
	+		Dissemination & stockwork of Cp, Py, Bo, Mo and Cc	1			2	5	3	2		42	100	-	-	1390	12	41	194
	+			2			2	3	4	3									
	+		Qtz-stringers occasionally	1			2	5	4	2									
50				2			2	4	3	2		50	100	-	-	2801	13	33	2

Depth	Stratigraphic Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
											g/t	g/t	ppm	ppm	ppm	ppm		
59.00 60	+		Granodiorite fractured moderately	1			2	3	3	2								
			Dissemination of Py, Cp, Bo, Mo and Cc	3			2	3	4	2								
				3			2	4	4	1								
				4			3	3	3	1								
4			Qtz-stringer occasionally	4			2	3	2	1	58	100	<0.1	3.5	17686	9	44	225
70	r		Diorite Por fractured strongly	4			2	3	2	1								
			Dissemination & stockwork of Py, Cp, Bo, Mo and Cc	4			3	3	2	2								
				4			3	4	1	1	66	100	<0.1	2.0	6275	9	14	78
				4			3	4	1	1								
			5			Films of minerals predominant	5			3	4	1	1					
76.00	r		Diorite Por fractured strongly	4			3	4	1	1								
			Dissemination & stockwork of Cp, Bo, Mo, Cc and Py	4			3	4	1	1								
				4			3	4	2	1	74	100	<0.1	4.4	12761	10	33	326
				4			3	4	2	1								
			3			Quartz Por fractured strongly	3			3	4	2	1					
80	L		Stockwork	3			3	4	2	1								
			3			3	4	2	1									
90	L		Quartz Por fractured moderately	3			2	4	2	1								
			Dissemination of Cp, Bo, Mo and Py	3			2	4	2	1	82	100	-	-	1910	7	15	559
				3			2	4	2	1								
				3			2	4	2	1								
			4			Qtz-stringers occasionally	4			2	4	1	1					
4			2	4	1	1	90	100	<0.1	1.3	6037	9	13	135				
100	L		Quartz Por fractured strongly	4			2	4	1	1								
			Dissemination & stockwork of Cp, Bo, Cc Mo and Py	4			2	4	1	1								
				4			2	4	1	1								
				4			2	4	1	1								
			4			2	4	1	1	98	100	-	-	3338	9	16	142	

Depth	Strati-Column	Structure	Description	Alteration							Assay Results							
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
110	L		Quartz Por fractured intensely	4			2	4	1	1								
	L		Dissemination & stockwork of Cp, Bo, Mo and Py	1			3	3	1	1								
	L			3			3	5	2	1	106	100	<0.1	0.7	4468	10	16	12
	L			3			3	5	2	1								
119.00 120	L		Quartz Por fractured Strongly	3			2	5	1	1								
	L		Dissemination & stockwork Of Cp, Bo, Mo and Py	5			3	3	1	1								
	L			5			2	3	1	1	114	100	-	-	665	3	2	231
	L			5			3	3	1	1								
	L			5			2	3	1	1								
	+		Granodiorite	5			3	3	1	1								
126.40 128.20	L		Quartz Por fractured intensely	3			3	4	2	1								
	L		Dissemination & stockwork	3			3	3	3	1	122	100	-	-	1696	8	13	194
	L		Granodiorite stockwork	3			3	4	2	1								
	L			3			2	3	2	1								
130	L	Quartz Por fractured strongly	3			2	3	2	1	130	100	<0.1	1.5	6937	9	13	12	
140	L		Dissemination & stockwork of Cp, Bo, Mo and Py	4			1	2	3	1								
	L		Qtz-stringers abundant	4			2	2	3	2								
	L			4			2	4	1	1								
	L			3			2	5	1	1	138	100	<0.1	1.1	4751	9	8	44
	L			3			2	4	1	1								
144.00	L	Quartz Por fractured strongly	3			2	4	1	1									
147.00	L		Dissemination & stockwork	3			2	5	1	1								
	L		Granodiorite fractured strongly	4			3	4	1	1								
149.00	+		Diorite Por fractured strongly	4			3	4	1	1	146	100	<0.1	2.9	7825	10	15	32
150	+		Granodiorite	3			4	5	1	1								
	+		Granodiorite	4			2	4	2	1								

Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
160	+	X	Dark gray Granodiorite (dioritic)	4			2	4	2	1									
	+		Dissemination & stockwork of Cp, Bo, Mo, Cc and Py	4			2	4	2	1									
	+			4			2	4	2	1	154	100	-	-	716	11	13	1417	
	+			4			2	3	2	1									
	+		Qtzstringers abundant	4			2	3	2	1									
170	+	X	Dark gray Granodiorite (dioritic)	4			2	3	2	1									
	+		Dissemination & stockwork of Cp, Bo, Mo, Cc and Py	4			2	3	2	1	162	100	<0.1	1.0	4116	13	17	66	
	+			3			2	4	1	1									
	+			5			3	1	1	1									
	+		Qtz-stringers abundant	5			3	1	1	1									
				4			2	4	1	1	170	100	<0.1	1.4	7839	9	9	384	
175.20	+	X	Granodiorite (dioritic)	4			2	4	1	1									
	+		Dissemination & stockwork	4			2	4	1	1									
				5			3	2	2	1									
180	L	X	Quartz Por fractured strongly	5			3	2	2	1									
	L		Dissemination & stockwork	3			4	5	1	1	178	100	<0.1	1.8	5214	7	8	414	
	L			5			3	2	1	1									
180.60	+	X	Granodiorite fractured weakly	5			3	2	1	1									
	+		Films of Bo, Cp and Py	5			2	3	2	1									
	+			5			2	3	2	1	186	100	<0.1	2.1	6304	8	33	138	
	+			3			2	3	2	1									
	+			3			2	3	2	1									
190	+	X	Granodiorite fractured weakly	2			2	3	2	1									
	+		Cracks with Bo, Cp and Py	2			2	3	2	1									
	+			2			2	3	2	1	194	100	<0.1	1.9	6087	12	15	316	
	+			2			2	3	2	1									
	+		Qtz-stringers common	2			2	3	2	1									
				2			2	3	2	1									
200				2			2	3	2	1									

Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
210	+		Granodiorite fractured weakly	3			2	3	3	1									
			Cracks with Bo, Cp and Py	3			2	3	3	1	202	100	-	-	3078	10	12	159	
			Qtz-stringers occasionally	3			2	3	3	1									
				3		2	3	3	1										
				3		2	3	2	1	210	100	<0.1	2.4	6809	8	15	556		
220	+		Granodiorite fractured weakly	3			2	4	2	1									
			Films of Bo, Cp & Py	3			2	4	2	1									
			Qtz-stringers occasionally	3			3	5	1	1									
				5		3	3	1	1	218	100	<0.1	3.5	11098	5	21	620		
				5		3	3	1	1										
230	+		Granodiorite fractured strongly	3			3	5	1	1									
			Dissemination & stockwork of Bo, Cp, Cc, Mo and Py	3			3	5	1	1									
				3		3	5	1	1										
				3		3	5	1	1	226	100	<0.1	4.3	13683	8	11	189		
				3		3	5	1	1										
240	+		Granodiorite fractured strongly	3			2	4	1	1									
			Dissemination & stockwork of Bo, Cp, Cc, Mo and Py	3			2	4	1	1									
				3		2	4	1	1	234	100	<0.1	1.5	4115	11	10	61		
				3		2	4	1	1										
				3		2	4	1	1										
250	+		Granodiorite fractured strongly	3			3	5	1	1									
			Dissemination & stockwork of Bo, Cp, Cc, Mo and Py	3			3	5	1	1	242	100	<0.1	1.7	4132	9	6	151	
				3		3	5	1	1										
				3		3	5	1	1										
				3		3	5	1	1	250	100	<0.1	1.8	5835	8	49	357		

Depth	Strati-Column	Structure	Description	Alteration						Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
260	+		Granodiorite silicified strongly & fractured	3			3	5	1	1									
			Dissemination & stockwork of Cp, Bc, Mo, Cc and Py	3			3	5	1	1									
				3			3	5	1	1									
				4			3	5	1	1	258	100	-	-	3185	7	45	307	
				4			3	5	1	1									
270	+		Granodiorite silicified & fractured strongly	4			3	4	1	1									
			Qtz stringers abundant	4			3	4	1	1									
			Dissemination & stockwork of bo, Cp, Mo, Cc and Py	4			4	5	1	1	266	100	<0.1	2.5	5385	9	18	74	
				4			4	5	1	1									
			Bottom	4			4	5	1	1									
280																			
290																			
300																			

Depth	Stratigraphic Column	Structure	Description	Alteration							Assay Results							
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
10	+		Non-Core															
	+		Granodiorite															
	+		Strongly altered and weathered															
	+	X																
20	+		Granodiorite (dioritic)	1		2	4	4	2	2								
	+		Dissemination of Py & Cp	1		2	4	4	2	2								
	+			1		2	4	4	2	2								
	+			2		1	3	5	1	3	15	100	—	—	3586	14	11	78
	+			2		1	3	5	1	3	18	100	<0.1	1.5	5286	19	40	169
	+			2		1	3	5	1	3								
30	+		Granodiorite (dioritic)	1		1	3	5	1	3								
	+		Strongly fractured & argilized	1		1	3	5	1	3	22	100	<0.1	4.9	11415	18	69	48
	+			1		1	3	5	1	3								
	+		Dissemination of Py, Cp, Bo and Mo	1		1	3	5	1	3	26	100	—	—	3886	16	84	45
	+			1		1	3	5	1	3	28	100	—	—	1665	14	24	22
	+			2		1	2	5	1	2	30	100	<0.1	2.0	8273	12	37	1036
40	+		Granodiorite (dioritic)	2		1	3	5	2	1								
	+		Strongly fractured & altered	2		1	3	5	2	1	32	100	<0.1	2.1	6235	13	33	27
	+			2		1	3	5	2	1	34	100	<0.1	1.3	4303	18	36	29
	+		Dissemination of Py, Cp, Bo and Mo	2		1	3	5	2	1	36	100	<0.1	1.6	5778	13	30	37
	+			2		1	3	5	2	1	38	100	<0.1	5.3	10145	9	30	307
	+			2		1	3	5	2	1	40	100	<0.1	5.9	10341	15	32	1239
50	+		Granodiorite (dioritic)	2		2	3	4	3	3								
	+		Strongly fractured & altered	2		2	3	4	3	3	42	100	<0.1	2.3	4838	15	18	434
	+			2		2	3	4	3	3	44	100	—	—	3627	11	25	206
	+		Dissemination of Bo, Cp, Py and Mo	3		2	3	2	3	1	46	100	—	—	1620	10	28	223
	+			3		2	3	2	3	1	48	100	<0.1	7.5	14580	9	18	150
	+			3		2	3	2	3	1	50	100	—	—	3788	14	15	212



Depth	Strat. Column	Structure	Description	Alteration						Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
												g/t	g/t	ppm	ppm	ppm	ppm	
60	+	/ / / / /	Granodiorite Strongly fractured & argilized	1		2	3	4	5	3								
				1		2	3	4	5	3	52	100	-	-	3067	11	22	14
			Dissemination of Bo, Cp, Py and Mo	1		2	3	4	5	3	54	100	-	-	3856	12	22	82
				3		1	2	5	4	2	56	100	<0.1	1.7	9626	14	31	137
				3		1	2	5	4	2	58	100	-	-	2638	13	10	471
				3		1	2	5	4	2								
66.35	+	/ / / / /	Granodiorite Strongly fractured & argilized	3		1	2	4	4	2	61	100	-	-	1912	12	15	42
				3		1	2	4	4	2	62	100	-	-	1458	9	20	9
				3		1	2	4	4	2								
			Diorite Por. Strongly silicified & fractured	3		1	2	3	2	3	66	100	-	-	626	12	21	46
				3		1	2	3	2	3	68	100	-	-	1027	14	30	388
				3		1	2	3	2	3	70	100	-	-	895	16	37	15
74.39	+	/ / / / /	Dissemination of Cp, Py, Bo and Mo	3		2	2	4	3	3								
				3		2	2	4	3	3	72	100	-	-	1733	20	43	210
			Granodiorite Strongly argilized & fractured	3		2	2	4	3	3	74	100	-	-	358	15	13	16
				3		2	2	3	3	2	76	100	-	-	1141	15	24	10
				3		2	2	3	3	2	78	100	-	-	697	14	14	74
				3		2	2	3	3	2	80	100	-	-	1532	16	15	60
80	+	/ / / / /	Granodiorite fractured & argilized	3		1	1	4	3	3								
				3		1	1	4	3	3	83	100	<0.1	6.5	4593	19	19	68
			Dissemination of Py, Mo, Cp and Bo	3		1	1	4	3	3	86	100	-	-	821	15	17	111
				3		1	2	4	3	3								
				3		1	2	4	3	3	90	100	-	-	434	15	17	25
				3		1	2	4	3	3								
90	+	/ / / / /	Granodiorite fractured, argilized & silicified	3		1	2	2	2	3								
				3		1	2	2	2	3								
			Dissemination of Py, Cp, Mo and Bo	3		1	2	2	2	3	94	100	-	-	562	14	15	77
				3		1	2	4	2	3								
				3		1	2	4	2	3	98	100	-	-	775	18	24	58
				3		1	2	4	2	3								
100	+	/ / / / /	Granodiorite fractured, argilized & silicified	3		1	2	2	2	3								
				3		1	2	2	2	3								

Depth	Strati-Column	Structure	Description	Alteration							Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
110	+		Granodiorite	3		1	2	4	2	3									
			Weakly fractured & argilized	3		1	2	4	2	3	102	100	--	--	804	11	16	259	
			Dissemination of Cp, Bo, Py	3		1	2	4	2	3									
				3		1	2	4	3	2	106	100	--	--	1480	13	16	259	
				3		1	2	4	3	2									
				3		1	2	4	3	2	110	100	--	--	1059	17	37	169	
120	+		Granodiorite	3		1	3	5	3	1									
			Strongly fractured & argilized	3		1	3	5	3	1									
			Dissemination of Cp, Py, Bo	3		1	3	5	3	1	114	100	--	--	1241	16	32	16	
				3		1	2	4	2	1									
				3		1	2	4	2	1	118	100	--	--	1895	14	26	23	
				3		1	2	4	2	1									
130	+		Granodiorite	2		1	3	5	2	1									
			fractured & argilized	2		1	3	5	2	1	122	100	--	--	862	11	13	6	
			Dissemination of Py, Cp and Kolydenite	2		1	3	5	2	1									
				2		1	3	5	2	1	126	100	--	--	1518	17	25	50	
				2		1	3	5	2	1									
				2		1	3	5	2	1	130	100	--	--	846	13	12	33	
140	+		Granodiorite	2		1	3	5	3	1									
			fractured & argilized	2		1	3	5	3	1									
			Dissemination of Py, Mo and a few Cp, Bo	2		1	3	5	3	1	134	100	--	--	1781	11	14	63	
				2		1	3	5	3	1									
				2		1	3	5	3	1	138	100	--	--	664	12	14	5	
				2		1	3	5	3	1									
150	+		Granodiorite	3		1	2	3	2	1									
			Strongly silicified & fractured	3		1	2	3	2	1	142	100	--	--	1027	11	9	56	
			Dissemination of Py, Mo and a few Cp, Bo	3		1	2	3	2	1									
				3		1	3	5	3	1	146	100	--	--	485	26	21	950	
				3		1	3	5	3	1									
				3		1	3	5	3	1	150	100	--	--	286	16	15	16	

Depth	Strati-Column	Structure	Description	Alteration							Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
150.40	r	X	Diorite Por Strongly silicified Mo-veinlets	2	1	4	5	3	1										
2				1	4	5	3	1											
2			1	4	5	3	1	154	100	-	-	406	17	24	31				
2			1	4	5	2	1												
2			1	4	5	2	1	158	100	-	-	515	25	23	134				
160	r			2	1	4	5	2	1										
170	r	/	Diorite Por silicified	3	1	4	5	1	1										
				3	1	4	5	1	1	162	100	-	-	355	25	19	1187		
			3	1	4	5	1	1											
			3	1	3	4	1	1	166	100	-	-	222	28	23	119			
			3	1	3	4	1	1											
3	1	3	4	1	1	170	100	-	-	394	21	19	334						
180	r	/	Diorite Por silicified	2	1	4	5	2	1										
				2	1	4	5	2	1										
			2	1	4	5	2	1	174	100	-	-	333	18	20	42			
			2	1	4	3	2	1											
			2	1	4	3	2	1	178	100	-	-	659	24	21	30			
2	1	4	3	2	1														
182.67	+	/	Granodiorite silicified	3	1	3	4	3	1										
				3	1	3	4	3	1	182	100	-	-	445	7	9	877		
			3	1	3	4	3	1											
			3	3	2	3	2	1	186	100	-	-	1084	15	9	47			
			3	3	2	3	2	1											
3	3	2	3	2	1	190	100	-	-	1126	15	9	206						
190	+	/	Granodiorite silicified	2	2	4	5	2	1										
				2	2	4	5	2	1										
			2	2	4	5	2	1	194	100	-	-	626	15	10	26			
			2	2	4	5	2	1											
			2	2	4	5	2	1											
200	+	/		3	2	3	4	2	1	200	100	-	-	313	11	9	8		
202	+	/	Bottom																

Depth	Strati-Column	Structure	Description	Alteration							Assay Results							
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo
				m	cm	g/t	g/t	ppm	ppm	ppm	ppm							
2.00	+		Non-Core															
			Granodiorite Strongly altered & weathered	1		1	1	1	1	1								
			Quartz veinlet and stringers	3		1	4	5	4	4								
				3		1	4	5	4	4								
10				3		1	4	5	4	4	10	100	-	-	1666	28	38	1430
20	+		Granodiorite Strongly fractured & altered	3		1	4	5	4	4								
				3		1	4	5	4	4								
			Quartz veinlet and stringers with Py & Cp	3		1	4	5	4	4								
				3		1	4	5	4	4								
				3		1	4	5	4	4	18	100	-	-	534	15	22	10
				3		1	4	5	4	4								
30	+		Granodiorite silicified Strongly fractured & altered	3		1	4	5	4	4								
				3		1	4	5	4	4								
				3		1	4	5	4	4								
			Dissemination of Py, Cp & molybdenite	1		1	4	4	2	3	26	100	-	-	628	11	28	3
				1		1	4	4	2	3								
				1		1	4	4	2	3								
40	+		Granodiorite silicified Weakly fractured & altered	1		1	3	4	3	3								
				1		1	3	4	3	3								
				1		1	3	4	3	3	34	100	-	-	1121	10	31	64
				1		1	3	2	1	2								
				1		1	3	2	1	2								
				1		1	3	2	1	2								
50	+		Granodiorite Strongly fractured	3		1	3	4	4	2								
				3		1	3	4	4	2	42	100	-	-	1653	19	375	21
			Dissemination weakly of Py and Cp	3		1	3	4	4	2								
				3		1	3	4	4	2								
				3		1	3	4	4	2								
				3		1	3	4	4	2	50	100	-	-	1479	10	28	<1

Depth	Stratigraphic Column	Structure	Description	Alteration							Assay Results								
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo	
												g/t	g/t	ppm	ppm	ppm	ppm		
60	+	/	Granodiorite	2		1	3	3	3	2									
			Weakly fractured & altered	2		1	3	3	3	2									
			Dissemination of Py and Cp	2		1	3	3	3	2									
			Abundant kaolinite	2		1	4	4	3	2	58	100	-	-	1333	12	24	9	
				2		1	4	4	3	2									
				2		1	4	4	3	2									
70	+	/	Granodiorite	1		1	4	4	3	2									
			Weakly fractured & altered	1		1	4	4	3	2									
			Dissemination of Py & Cp	1		1	4	4	3	2									
				1		1	5	4	3	2	66	100	-	-	2983	11	33	55	
				1		1	5	4	3	2									
				1		1	5	4	3	2									
80	+	/	Granodiorite	1		1	5	4	3	2									
			fractured & altered	1		1	5	4	3	2									
			Dissemination of Py & Cp	1		1	5	4	3	2	74	100	-	-	2588	9	24	41	
			Quartz veinlet with Py & Cp	1		1	4	4	3	2									
				1		1	4	4	3	2									
				1		1	4	4	3	2									
90	+	/	Granodiorite	1		1	4	4	3	3									
			fractured & altered	1		1	4	4	3	3	82	100	<0.1	1.5	5374	11	28	1	
			Dissemination of Py & Cp	1		1	4	4	3	3									
				1		1	3	5	4	4									
				1		1	3	5	4	4									
				1		1	3	5	4	4	90	100	-	-	1456	10	23	<1	
100	+	/	Granodiorite	2		1	5	5	4	4									
			fractured & altered	2		1	5	5	4	4									
			Dissemination of Py & Cp	2		1	5	5	4	4									
			Quartz veinlet with Py & Cp	2		1	3	5	4	4									
				2		1	3	5	4	4	98	100	-	-	2188	16	35	4	
				2		1	3	5	4	4									

Depth	Strati-Column	Structure	Description	Alteration							Assay Results									
				Quartz	Biotite	K-feldspar	Sericite	Kaoline	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo		
												g/t	g/t	ppm	ppm	ppm	ppm			
110	+	/	Granodiorite fractured & altered	3		1	3	3	4	2										
			Dissemination of Py, Cp, Bo and Mo	3		1	3	3	4	2										
				3		1	3	4	4	3	106	100	-	-	2039	11	28	4		
				3		1	3	4	4	3										
				3		1	3	4	4	3										
120	+	/	Granodiorite fractured & altered	2		1	3	4	3	2										
			Quartz veinlet with Py & Cp	2		1	3	4	3	2										
			Dissemination of Py and Cp	2		1	3	4	3	2	114	100	-	-	1017	13	28	7		
				3		1	3	5	4	2										
				3		1	3	5	4	2										
130	+	/	Granodiorite fractured & altered	1		1	1	3	2	2										
			Quartz veinlet with Py & Cp	1		1	1	3	2	2	122	100	-	-	393	12	26	4		
				1		1	1	3	2	2										
				1		1	3	3	2	2										
				1		1	3	3	2	2										
140	+	/	Granodiorite fractured and altered	1		1	2	3	3	3										
			Quartz veinlet with Py and Cp	1		1	2	3	3	3										
				1		1	2	3	3	3										
				1		1	4	4	3	3										
				1		1	4	4	3	3	138	100	-	-	1209	14	26	29		
150	+	/	Granodiorite fractured and weakly altered	3		1	2	2	2	2										
			Quartz veinlet with Py & Cp	3		1	2	2	2	2										
				3		1	2	2	2	2										
				3		1	3	5	3	3	146	100	-	-	966	13	26	<1		
				3		1	3	5	3	3										

Depth	Stratigraphic Column	Structure	Description	Alteration						Assay Results										
				Quartz	Biotite	K-feldspar	Sericite	Kaolinite	Chlorite	Epidote	Depth	Core	Au	Ag	Cu	Pb	Zn	Mo		
										m	cm	g/t	g/t	ppm	ppm	ppm	ppm			
160	+	/	Granodiorite weakly fractured and altered	2		1	2	2	1	1										
				2		1	2	2	1	1										
			Mineralization in fractures (Cp, Py)	2		1	2	2	1	1	154	100	-	-	292	12	31	<1		
				1		1	4	4	3	3										
				1		1	4	4	3	3										
170	+	/	Granodiorite weakly fractured and altered	1		1	2	2	4	2										
				1		1	2	2	4	2	162	100	-	-	1657	14	22	61		
			Dissemination of Py and Cp	1		1	2	2	4	2										
				1		1	2	2	4	2										
				1		1	2	2	4	2										
180	+	/	Granodiorite fractured and altered	1		1	1	1	2	1										
				1		1	1	1	2	1										
			Carbonate minerals in fractures	1		1	1	1	2	1										
				1		1	4	5	4	3										
				1		1	4	5	4	3	178	100	-	-	1215	11	38	11		
190	+	/	Granodiorite fractured and altered	1		1	3	4	4	3										
				1		1	3	4	4	3										
			Dissemination of Py and Cp	1		1	3	4	4	3										
			Chlorite in fracture with carbonate minerals	1		1	3	4	4	3	186	100	-	-	409	21	62	13		
				1		1	3	4	4	3										
200	+	/	Granodiorite strongly fractured and altered	1		1	4	4	4	3										
				1		1	4	4	4	3										
			Kaolinite and carbonate minerals in fractured	1		1	4	4	4	3	194	100	<0.1	1.2	4971	16	31	9		
				1		1	4	4	4	3										
				1		1	4	4	4	3										
201.5	+	/	Bottom																	

Appendix 4 Assay data of Drill core samples



Assay Results  
分析成績報告書

平成6年2月23日

1994-02-23

大手開発株式会社  
地質・環境部 御中

Drilling Cores of Junin Project

大手開発株式会社  
地科学試験所



下記の通りご報告申し上げます。

エクアドル ボーリングコア

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo
1	MJJ-10	10.00	<0.1	1.2	7170	22	28	<1
2		14.00	<0.1	0.7	4195	15	26	4
3		18.00	-	-	3890	17	72	67
4		22.00	<0.1	5.0	73871	14	85	37
5		26.00	<0.1	1.0	4989	13	30	2
6		30.00	<0.1	1.9	8304	11	24	542
7		34.00	-	-	540	14	129	9
8		38.00	-	-	177	18	454	<1
9		42.00	-	-	133	16	425	<1
10		46.00	-	-	421	12	138	<1
11		50.00	<0.1	0.9	4442	12	71	2
12		52.00	<0.1	1.7	5313	12	90	29
13		54.00	-	-	2867	10	34	<1
14		56.00	-	-	2382	14	55	2
15		58.00	<0.1	4.6	22106	19	222	57
16		60.00	<0.1	4.1	22113	14	186	42
17		62.00	-	-	2988	15	254	<1
18		64.00	<0.1	1.6	5290	15	430	6
19		66.00	-	-	1635	13	99	1
20		68.00	-	-	2326	15	115	2
21		70.00	-	-	2017	10	45	7
22		72.00	-	-	1985	15	562	11
23		74.00	-	-	1841	11	303	8
24		76.00	-	-	828	13	133	<1
25		78.00	-	-	2116	9	138	5

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm			
	供	試	Au	Ag	Cu	Pb	Zn	Mo			
26	MJJ-10	80.00	<0.1	4.0	4991	14	188	118			
27		82.00	-	-	705	17	194	10			
28		84.00	-	-	130	16	140	<1			
29		86.00	-	-	127	12	180	<1			
30		88.00	-	-	326	16	449	2			
31		148.00	-	-	525	12	426	<1			
32		158.00	<0.1	12.0	38285	19	221	5			
33		162.00	-	-	454	15	349	<1			
34		166.00	-	-	426	17	70	5			
35		170.00	-	-	721	16	160	<1			
36		190.00	-	-	1130	12	127	<1			
37		194.00	-	-	662	12	123	6			
38		202.00	-	-	214	15	81	<1			
39		206.00	-	-	233	18	97	<1			
40		210.00	-	-	3227	15	60	14			
41		214.00	<0.1	2.6	20271	12	47	2			
42		222.00	-	-	195	11	84	2			
43		224.00	-	-	166	12	103	1			
44		226.00	-	-	258	15	59	6			
45		230.00	-	-	853	13	273	19			
46		234.00	-	-	416	13	85	<1			
47		238.00	<0.1	10.8	35794	11	38	16			
48		256.00	-	-	112	13	81	<1			
49		260.00	-	-	216	15	82	<1			
50		264.00	-	-	622	15	230	<1			
51		268.00	<0.1	1.9	4246	22	153	59			
52		272.00	-	-	359	16	376	<1			
53		278.00	-	-	1168	15	177	6			
54		282.00	-	-	426	103	124	11			
55		292.00	<0.1	2.1	6480	14	106	469			
56		298.00	-	-	297	14	69	8			
57	MJJ-11	10.00	-	-	251	10	28	242			
58		14.00	<0.1	1.4	9722	11	20	131			
59		18.00	-	-	1898	14	52	23			
60		22.00	-	-	3685	13	27	131			

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm		
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo		
61	MJJ-11	26.00	-	-	2272	10	25	235		
62		30.00	-	-	2442	12	38	10		
63		34.00	-	-	834	10	33	87		
64		38.00	-	-	943	14	25	25		
65		42.00	-	-	121	12	32	2		
66		46.00	-	-	3902	10	23	16		
67		50.00	-	-	1751	14	28	5		
68		52.00	-	-	308	11	33	<1		
69		54.00	-	-	130	12	44	<1		
70		56.00	<0.1	2.2	8221	10	24	249		
71		58.00	-	-	737	12	39	<1		
72		60.00	-	-	866	14	57	8		
73		62.00	-	-	3799	12	37	9		
74		64.00	-	-	2196	12	41	96		
75		66.00	-	-	2153	13	30	18		
76		68.00	-	-	1341	11	29	5		
77		70.00	-	-	384	11	22	<1		
78		72.00	-	-	2009	31	505	335		
79		74.00	-	-	1093	13	22	10		
80		76.00	-	-	350	10	28	25		
81		78.00	-	-	879	10	31	28		
82		80.00	<0.1	1.4	4284	12	22	24		
83		82.00	<0.1	3.3	9901	12	22	1089		
84		84.00	-	-	708	14	19	19		
85		86.00	-	-	2134	11	24	324		
86		88.00	-	-	3217	11	17	460		
87		90.00	-	-	807	15	42	50		
88		94.00	-	-	1014	15	34	20		
89		98.00	-	-	663	15	31	39		
90		102.00	-	-	448	12	36	<1		
91		106.00	-	-	629	15	47	<1		
92		110.00	-	-	179	11	41	5		
93		112.00	-	-	873	15	43	9		
94		114.00	-	-	238	12	39	21		
95		118.00	-	-	694	15	32	71		

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm			
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo			
96	MJJ-11	122.00	-	-	3064	13	15	67			
97		126.00	-	-	639	13	37	9			
98		130.00	-	-	247	11	35	12			
99		134.00	-	-	730	15	31	46			
100		138.00	<0.1	1.8	4509	17	36	4			
101		140.00	-	-	2513	14	24	20			
102		142.00	-	-	2967	14	33	20			
103		144.00	<0.1	0.7	6476	11	24	48			
104		146.00	<0.1	1.3	10482	14	18	448			
105		148.00	-	-	1205	9	26	57			
106		150.00	-	-	457	15	24	4			
107		152.00	-	-	3582	15	22	56			
108		154.00	-	-	1134	18	24	113			
109		156.00	-	-	600	14	16	3			
110		158.00	-	-	1276	16	26	74			
111		160.00	-	-	1751	16	28	8			
112		162.00	-	-	609	16	34	8			
113		164.00	-	-	2554	13	27	69			
114		166.00	-	-	1740	11	26	12			
115		168.00	-	-	1309	19	22	22			
116		170.00	-	-	2892	13	21	101			
117		172.00	-	-	1173	12	11	63			
118		174.00	-	-	1238	11	18	267			
119		176.00	<0.1	3.9	12304	12	11	387			
120		178.00	-	-	1244	14	20	20			
121		180.00	-	-	3575	11	21	150			
122		184.00	-	-	2448	12	19	264			
123		188.00	-	-	838	11	21	53			
124		192.00	-	-	1732	13	20	171			
125		196.00	-	-	630	12	16	1			
126		200.00	-	-	921	14	24	28			
127		202.00	-	-	896	21	35	5			
128		204.00	-	-	199	13	20	12			
129		206.00	-	-	2258	15	18	27			
130		208.00	-	-	1444	16	22	21			

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo
131	MJJ-11	210.00	-	-	1993	12	16	56
132		212.00	-	-	3823	16	23	97
133		214.00	-	-	1929	15	29	67
134		216.00	-	-	1424	285	29	262
135		218.00	-	-	624	11	19	1447
136		220.00	-	-	1693	11	10	145
137		222.00	-	-	1255	13	16	58
138		224.00	-	-	767	13	17	44
139		226.00	-	-	1440	19	28	259
140		228.00	-	-	3073	13	25	124
141		230.00	<0.1	4.0	12797	11	19	250
142		232.00	-	-	3662	15	21	93
143		234.00	-	-	2802	14	17	720
144		236.00	-	-	2460	21	49	253
145		238.00	-	-	2403	15	26	156
146		240.00	-	-	627	15	29	15
147		244.00	-	-	2718	15	89	201
148		248.00	-	-	1562	13	37	90
149		252.00	-	-	2124	15	35	252
150		256.00	-	-	1420	13	73	60
151		260.00	<0.1	0.6	4221	12	64	50
152		264.00	-	-	3326	11	19	109
153		268.00	-	-	1448	11	16	23
154		272.00	-	-	407	11	47	<1
155		276.00	-	-	3221	11	6	419
156		280.00	-	-	3361	12	43	176
157		284.00	-	-	1990	10	26	183
158		288.00	-	-	1858	12	22	70
159		292.00	-	-	1606	11	27	67
160		296.00	-	-	1215	11	26	14
161	MJJ-12	10.00	-	-	2631	8	5	28
162		18.00	-	-	3141	10	25	27
163		26.00	-	-	2807	7	16	668
164		34.00	-	-	3827	11	20	87
165		42.00	-	-	1440	10	22	37

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm			
	供	試	Au	Ag	Cu	Pb	Zn	Mo			
166	MJJ-12	50.00	-	-	2853	8	9	92			
167		58.00	-	-	2475	11	15	35			
168		66.00	-	-	2664	10	19	63			
169		74.00	-	-	413	11	24	17			
170		82.00	-	-	789	531	10	10			
171		90.00	-	-	1898	14	20	15			
172		98.00	-	-	712	11	13	13			
173		106.00	-	-	1750	12	19	55			
174		114.00	-	-	1331	10	20	123			
175		122.00	<0.1	2.9	6252	10	12	252			
176		130.00	-	-	588	10	13	8			
177		138.00	-	-	202	10	24	12			
178		146.00	-	-	1639	12	29	14			
179		154.00	-	-	2456	12	11	57			
180		162.00	-	-	1379	10	23	17			
181		170.00	-	-	943	10	21	36			
182		178.00	-	-	711	11	17	10			
183		186.00	-	-	1127	11	10	61			
184		194.00	-	-	2298	12	8	155			
185		202.00	-	-	903	14	11	59			
186		210.00	-	-	328	10	12	4			
187		218.00	-	-	812	9	17	<1			
188		226.00	-	-	410	14	24	3			
189		234.00	-	-	1098	12	20	<1			
190		242.00	-	-	840	10	15	3			
191		250.00	-	-	1553	11	60	24			
192		258.00	-	-	574	14	12	5			
193		266.00	-	-	566	10	13	17			
194		274.00	-	-	568	9	11	17			
195		282.00	-	-	452	12	19	14			
196		290.00	-	-	3115	8	14	32			
197		298.00	-	-	1380	11	15	18			
198	MJJ-13	10.00	-	-	504	11	24	24			
199		18.00	-	-	1086	12	53	17			
200		26.00	-	-	167	13	45	1			

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm			
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo			
201	MJJ-13	34.00	-	-	1023	10	39	66			
202		42.00	-	-	1390	12	41	194			
203		50.00	-	-	2801	13	33	2			
204		58.00	<0.1	3.5	17686	9	44	225			
205		66.00	<0.1	2.0	6275	9	14	78			
206		74.00	<0.1	4.4	12761	10	33	326			
207		82.00	-	-	1910	7	15	559			
208		90.00	<0.1	1.3	6037	9	13	135			
209		98.00	-	-	3338	9	16	142			
210		106.00	<0.1	0.7	4468	10	16	12			
211		114.00	-	-	665	3	2	231			
212		122.00	-	-	1696	8	13	194			
213		130.00	<0.1	1.5	6937	9	13	12			
214		138.00	<0.1	1.1	4751	9	8	44			
215		146.00	<0.1	2.9	7825	10	15	32			
216		154.00	-	-	716	11	13	1417			
217		162.00	<0.1	1.0	4116	13	17	66			
218		170.00	<0.1	1.4	7839	9	9	384			
219		178.00	<0.1	1.8	5214	7	8	414			
220		186.00	<0.1	2.1	6304	8	33	138			
221		194.00	<0.1	1.9	6087	12	15	316			
222		202.00	-	-	3078	10	12	159			
223		210.00	<0.1	2.4	6809	8	15	556			
224		218.00	<0.1	3.5	11098	5	21	620			
225		226.00	<0.1	4.3	13683	8	11	189			
226		234.00	<0.1	1.5	4115	11	10	61			
227		242.00	<0.1	1.7	4132	9	6	151			
228		250.00	<0.1	1.8	5835	8	49	357			
229		258.00	-	-	3185	7	45	307			
230		266.00	<0.1	2.5	5385	9	18	74			
231	MJC-1	10.00	<0.1	1.7	10458	12	10	8			
232		15.00	-	-	3586	14	11	78			
233		18.00	<0.1	1.5	5286	19	40	169			
234		22.00	<0.1	4.9	11415	18	69	48			
235		26.00	-	-	3886	16	84	45			

No	Sample		ppm	ppm	ppm	ppm	ppm	ppm		
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo		
236	MJC- 1	28.00	-	-	1665	14	24	22		
237		30.00	<0.1	2.0	8273	12	37	1036		
238		32.00	<0.1	2.1	6235	13	33	27		
239		34.00	<0.1	1.3	4303	18	36	29		
240		36.00	<0.1	1.6	5778	13	30	37		
241		38.00	<0.1	5.3	10145	9	30	307		
242		40.00	<0.1	5.9	10341	15	32	1239		
243		42.00	<0.1	2.3	4838	15	18	434		
244		44.00	-	-	3627	11	25	206		
245		46.00	-	-	1620	10	28	223		
246		48.00	<0.1	7.5	14580	9	18	150		
247		50.00	-	-	3788	14	15	212		
248		52.00	-	-	3067	11	22	14		
249		54.00	-	-	3856	12	22	82		
250		56.00	<0.1	1.7	9626	14	31	137		
251		58.00	-	-	2638	13	10	471		
252		61.00	-	-	1912	12	15	42		
253		62.00	-	-	1458	9	20	9		
254		66.00	-	-	626	12	21	46		
255		68.00	-	-	1027	14	30	388		
256		70.00	-	-	895	16	37	15		
257		72.00	-	-	1733	20	43	210		
258		74.00	-	-	358	15	13	16		
259		76.00	-	-	1141	15	24	10		
260		78.00	-	-	697	14	14	74		
261		80.00	-	-	1532	16	15	60		
262		83.00	<0.1	6.5	4593	19	19	68		
263		86.00	-	-	821	15	17	111		
264		90.00	-	-	434	15	17	25		
265		94.00	-	-	562	14	15	77		
266		98.00	-	-	775	18	24	58		
267		102.00	-	-	804	11	16	259		
268		106.00	-	-	1480	13	16	259		
269		110.00	-	-	1059	17	37	169		
270		114.00	-	-	1241	16	32	16		



No	Sample		ppm		ppm		ppm		ppm		ppm	
	供	試 品	Au	Ag	Cu	Pb	Zn	Mo				
271	MJC- 1	118.00	-	-	1895	14	26	23				
272		122.00	-	-	862	11	13	6				
273		126.00	-	-	1518	17	25	50				
274		130.00	-	-	846	13	12	33				
275		134.00	-	-	1781	11	14	66				
276		138.00	-	-	664	12	14	5				
277		142.00	-	-	1027	11	9	56				
278		146.00	-	-	485	26	21	950				
279		150.00	-	-	286	16	15	16				
280		154.00	-	-	406	17	24	31				
281		158.00	-	-	515	25	23	134				
282		162.00	-	-	355	25	19	1187				
283		166.00	-	-	222	28	23	119				
284		170.00	-	-	394	21	19	334				
285		174.00	-	-	333	18	20	42				
286		178.00	-	-	659	24	21	30				
287		182.00	-	-	445	7	9	877				
288		186.00	-	-	1084	15	9	47				
289		190.00	-	-	1126	15	9	206				
290		194.00	-	-	626	15	10	26				
291		200.00	-	-	313	11	9	8				
292	MJC- 2	10.00	-	-	1666	28	38	1430				
293		18.00	-	-	534	15	22	10				
294		26.00	-	-	628	11	28	3				
295		34.00	-	-	1121	10	31	64				
296		42.00	-	-	1653	19	375	21				
297		50.00	-	-	1479	10	28	<1				
298		58.00	-	-	1333	12	24	9				
299		66.00	-	-	2983	11	33	55				
300		74.00	-	-	2588	9	24	41				
301		82.00	<0.1	1.5	5374	11	28	1				
302		90.00	-	-	1456	10	23	<1				
303		98.00	-	-	2188	16	35	4				
304		106.00	-	-	2039	11	28	4				
305		114.00	-	-	1017	13	28	7				



Appendix 5 Generalized drilling results

Appendix 5 Generalized drilling results


Drill Hole No.	Machine Type	Drilling Period	Drilling Depth	core		Drilling Shift			Drilling Speed	
				Length (m)	Recovery (%)	Drilling	Preparation & Removing	Total	m per Total shift	m per met shift
MJJ-10	L-38	1993-10-31	301.30	299.30	99.34	28	98	126	2.39	10.76
		1993-11-26								
MJJ-11	L-38	1993-10-31	302.50	300.50	99.34	31	30	61	4.96	9.76
		1993-12-10								
MJJ-12	L-38	1993-10-3	302.00	300.00	99.34	31	12	43	7.02	9.74
		1993-10-24								
MJJ-13	L-38	1993-8-9	270.00	262.13	97.09	39	19	58	4.66	6.92
		1993-9-22								
MJC-1	L-38	1993-10-31	202.00	182.05	90.12	51	32	83	2.43	3.96
		1993-12-12								
MJC-2	L-38	1993-12-30	201.50	199.50	99.00	16	25	41	4.91	12.59
		1994-1-20								

Appendix 6 Progress record of holes  
(MJJ-10 to MJJ-13 and MJC-1 to MJC-2)

Appendix 6 Summary record of drilling activities

	Area	J U N I N Area				Cuellaje Area		
	D/D No.	MJJ-10	MJJ-11	MJJ-12	MJJ-13	MJC- 1	MJC- 2	
Drilling period	Preparation(A) Day. (Men)	7/25 ~10/30 98. (516)	10/24 ~10/30 7. (84)	9/28~10/2 7. (84)	7/25~8/8 15. (264)	10/17~10/30 14. (168)	12/19~12/29 11. (156)	
	Drilling(B) Days. (Men)	10/31 ~11/28 27. (226)	10/31 ~12/10 41. (356)	10/3 ~10/24 22. (240)	8/9 ~9/22 45. (504)	10/31~12/12 43. (422)	12/30~1/20 22. (204)	
	Removing(C) Days. (Men)	11/27 1. (12)	12/11 ~12/25 15. (124)	10/25~10/27 3. (36)	9/23~9/25 3. (36)	12/13~12/25 13. (168)	1/21~1/22 2. (24)	
	Total(D)	126. (744)	63. (564)	32. (360)	63. (804)	70. (758)	35. (384)	
Depth	Depth planned(E)	300.00	300.00	300.00	300.00	200.00	200.00	
	Depth drilled(F)	301.00	302.50	302.00	270.00	202.00	201.50	
Core Recovery	Overburden(G)	2.00	2.00	2.00	4.00	2.00	2.00	
	Core length(H)	299.00	300.50	300.00	262.13	182.05	199.50	
	Recovery(H/F)	99.33	99.34	99.34	97.09	90.12	99.01	
	Unit Recovery	0 ~ 50	96.00	96.00	96.00	92.00	81.00	96.00
		50 ~ 100	100.00	100.00	100.00	100.00	82.10	100.00
		100 ~ 150	100.00	100.00	100.00	100.00	100.00	100.00
150 ~ 200		100.00	100.00	100.00	100.00	97.00	100.00	
200 ~ 250		100.00	100.00	100.00	100.00			
250 ~ 300	100.00	100.00	100.00	80.65				
Casing	H W Casing	60.00	123.00	40.00	9.00	-	15.00	
	N W Casing	116.00	186.00	112.00	85.00	9.14	51.00	
	B W Casing	256.00	256.00	258.00	185.00	-	-	
Drilling Efficiency	F/B m/Day	11.15	7.38	13.73	6.00	4.70	9.16	
	F/D m/Day	2.39	4.80	9.44	4.29	2.89	5.16	
	(B)/F Men/m	0.72	1.18	0.79	1.87	2.09	1.01	
	(D)/F Men/m	2.47	1.87	1.19	2.98	3.75	1.91	


Appendix 7 Summary record of drilling activities  
(MJJ-10 to MJJ-13 and MJC-1 to MJC-2)

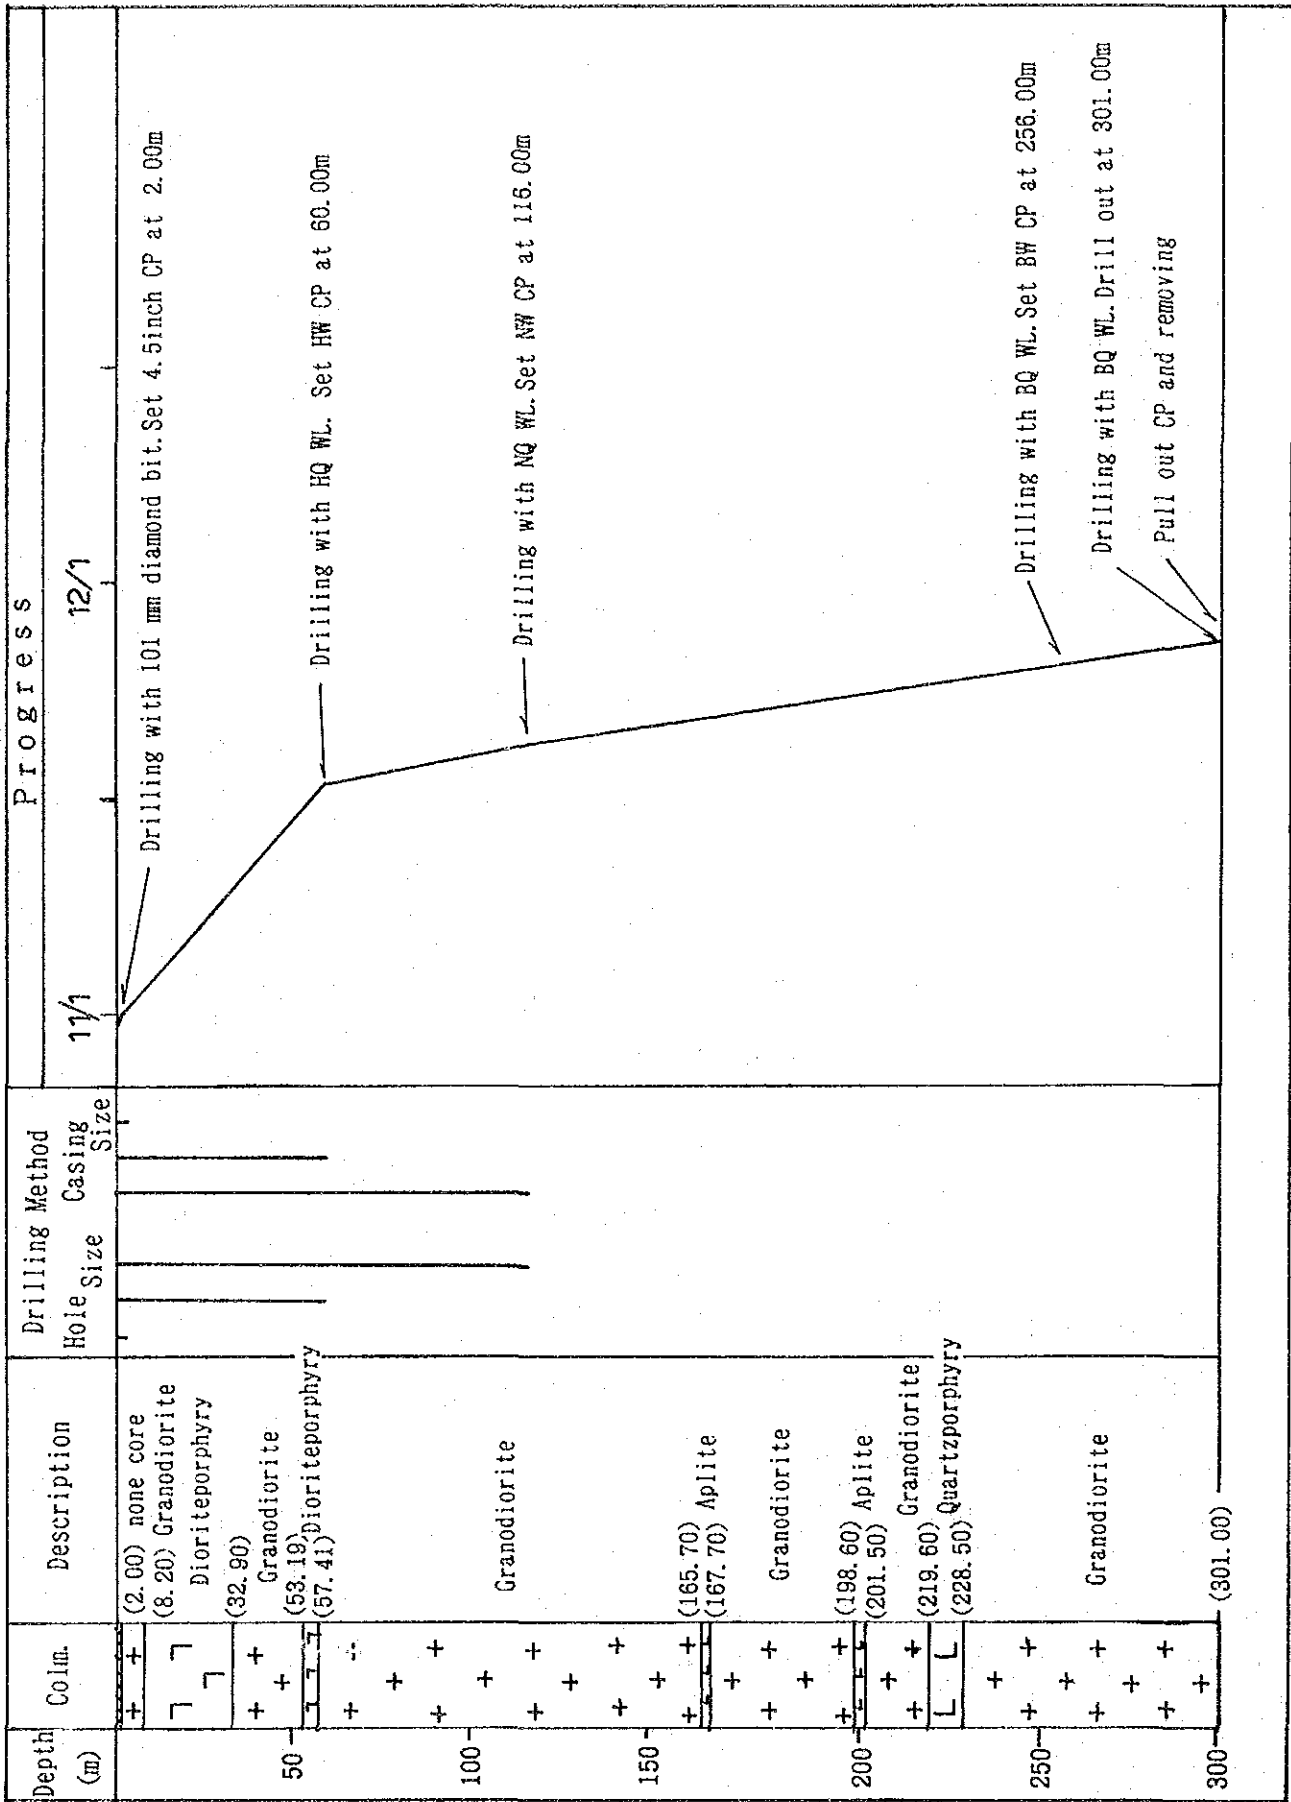


Appendix 7(1) Progress record of hole MJJ-10






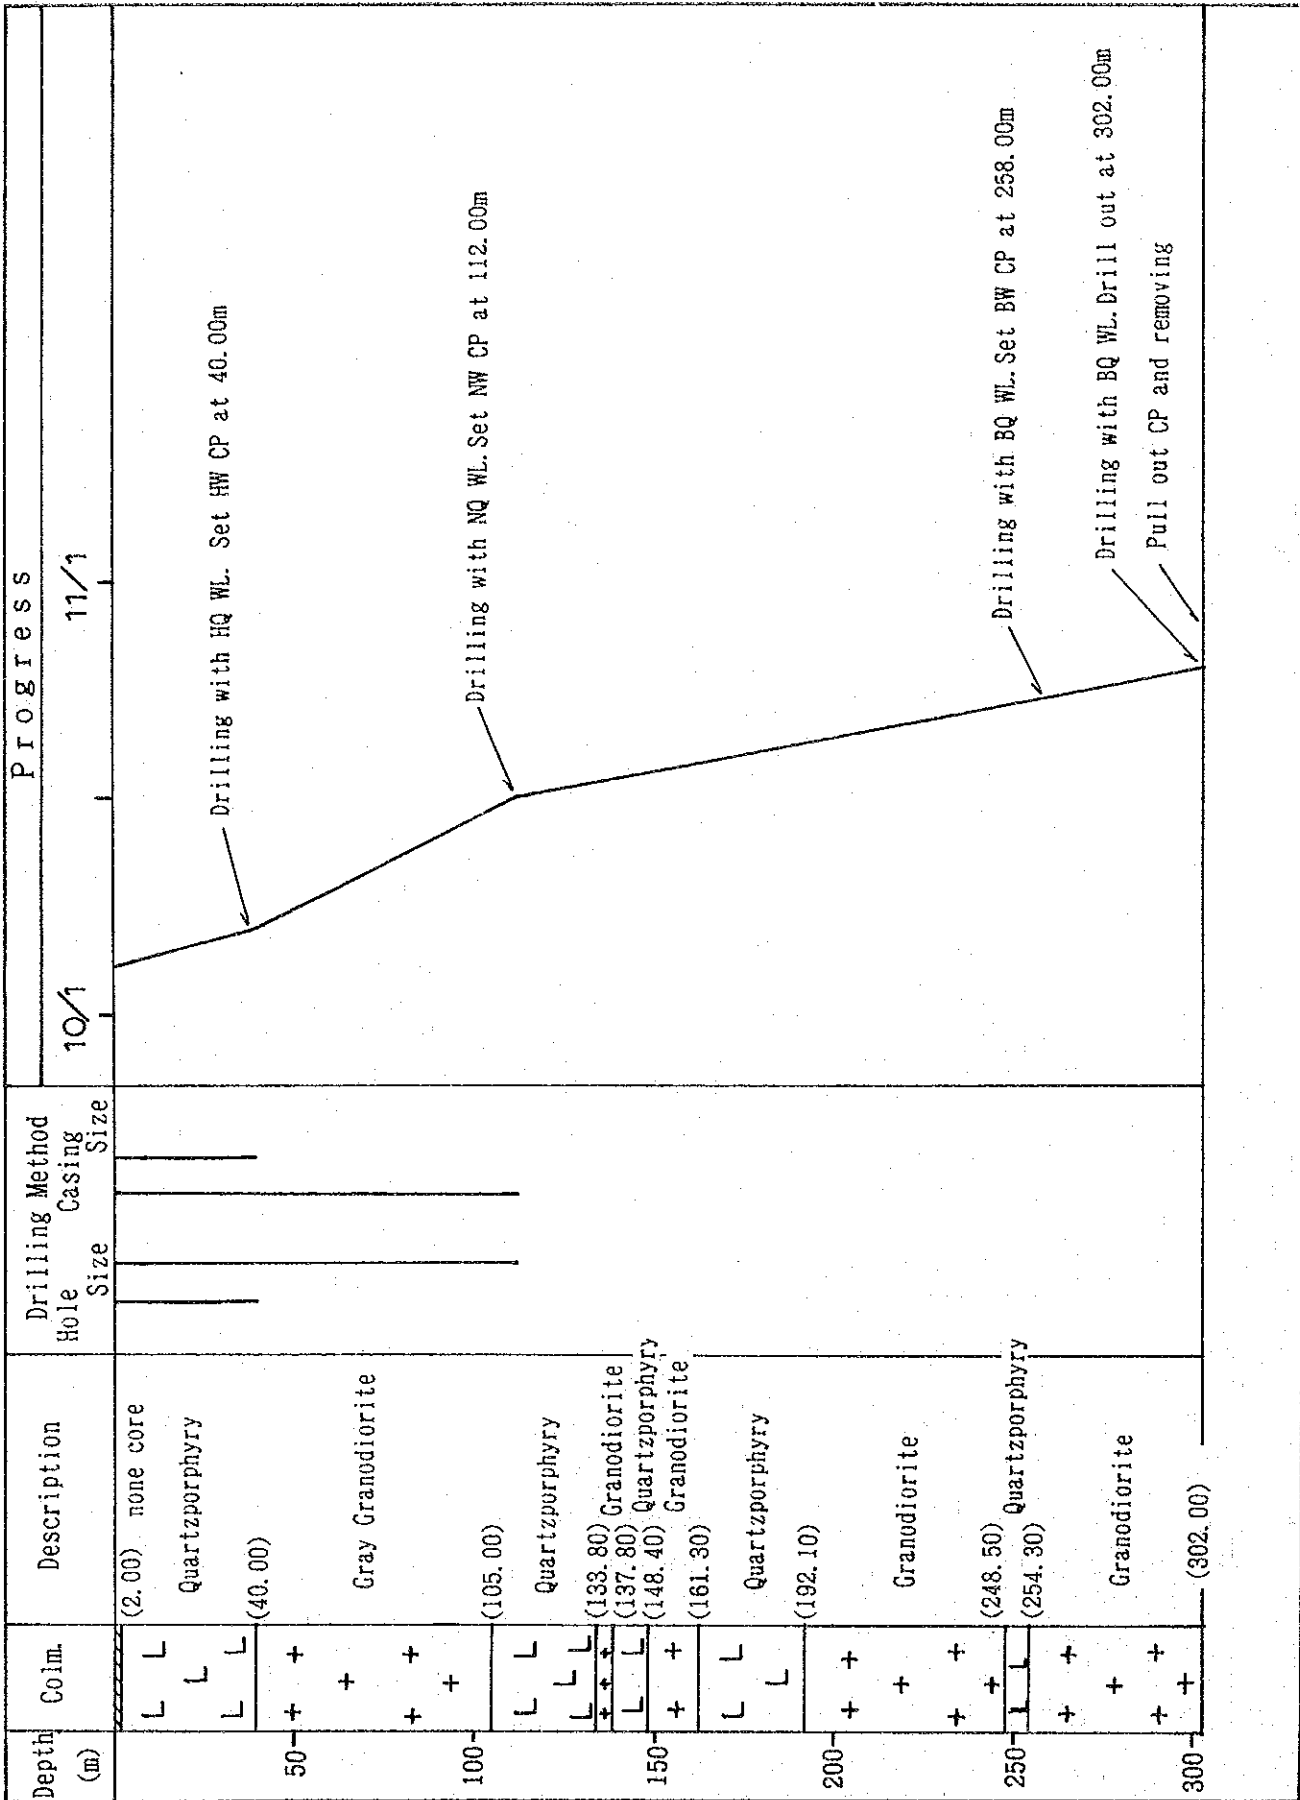


Appendix 7(3) Progress record of hole MJJ-12

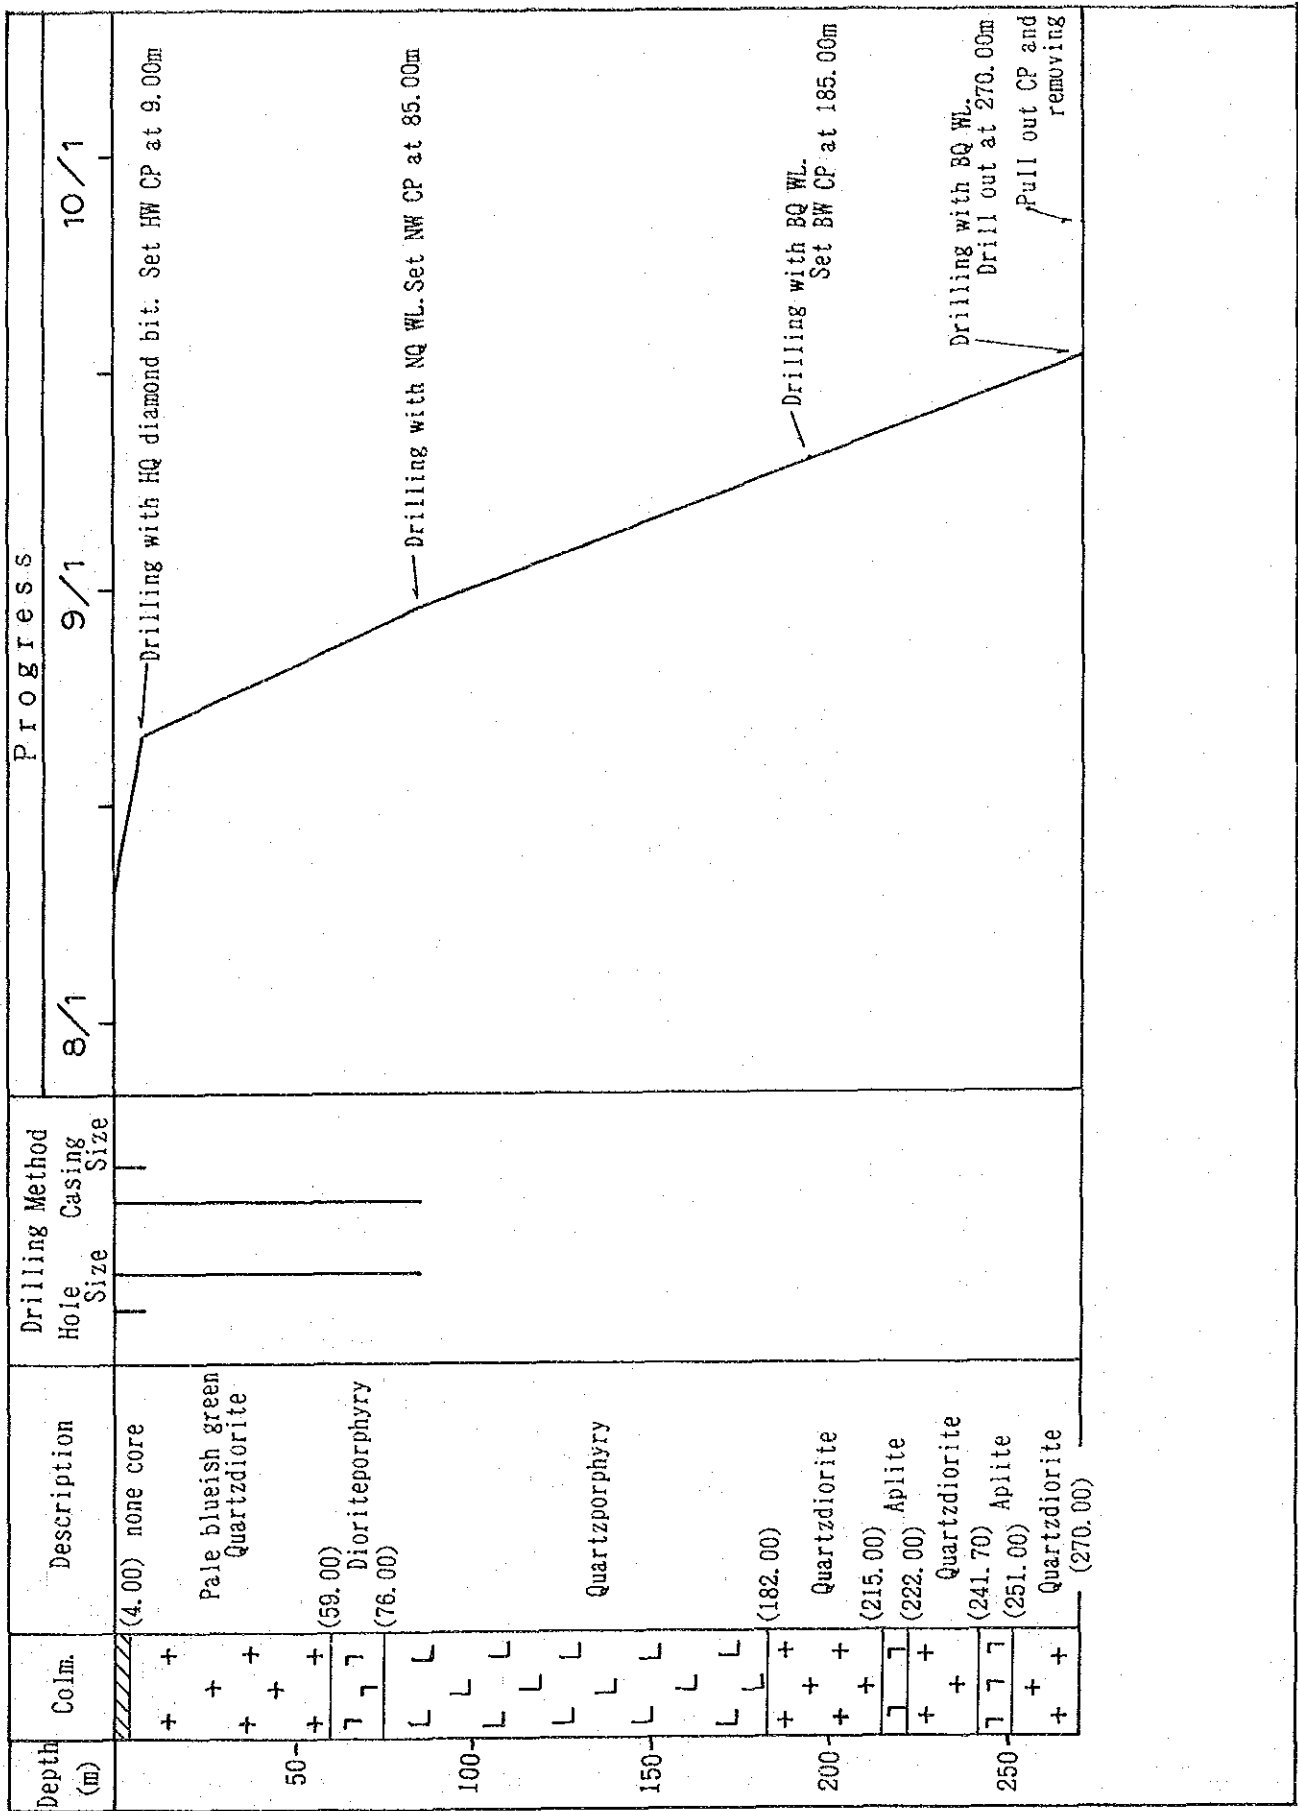

Appendix 7(4) Progress record of hole MJJ-13

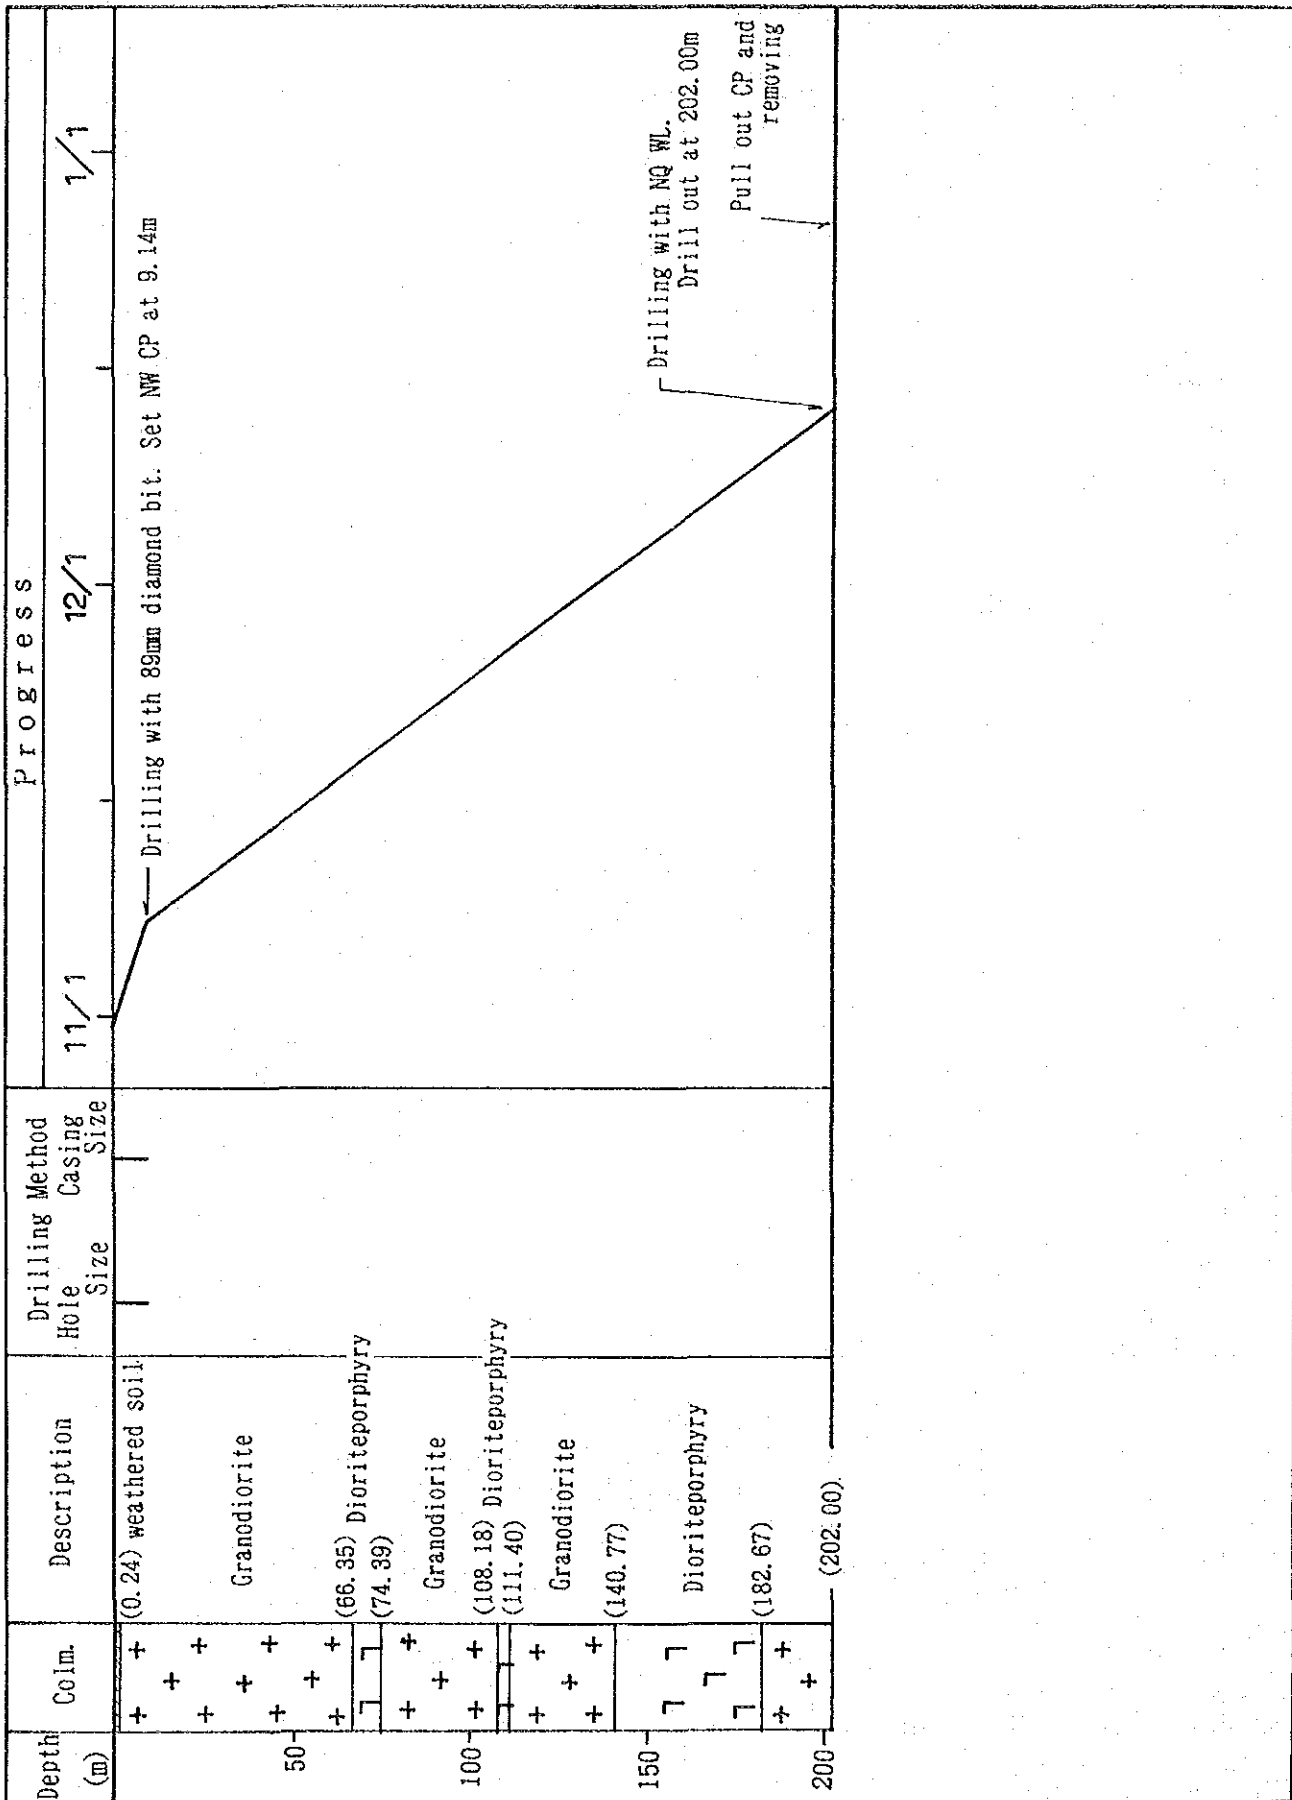

Appendix 7(5) Progress record of hole MJC-1

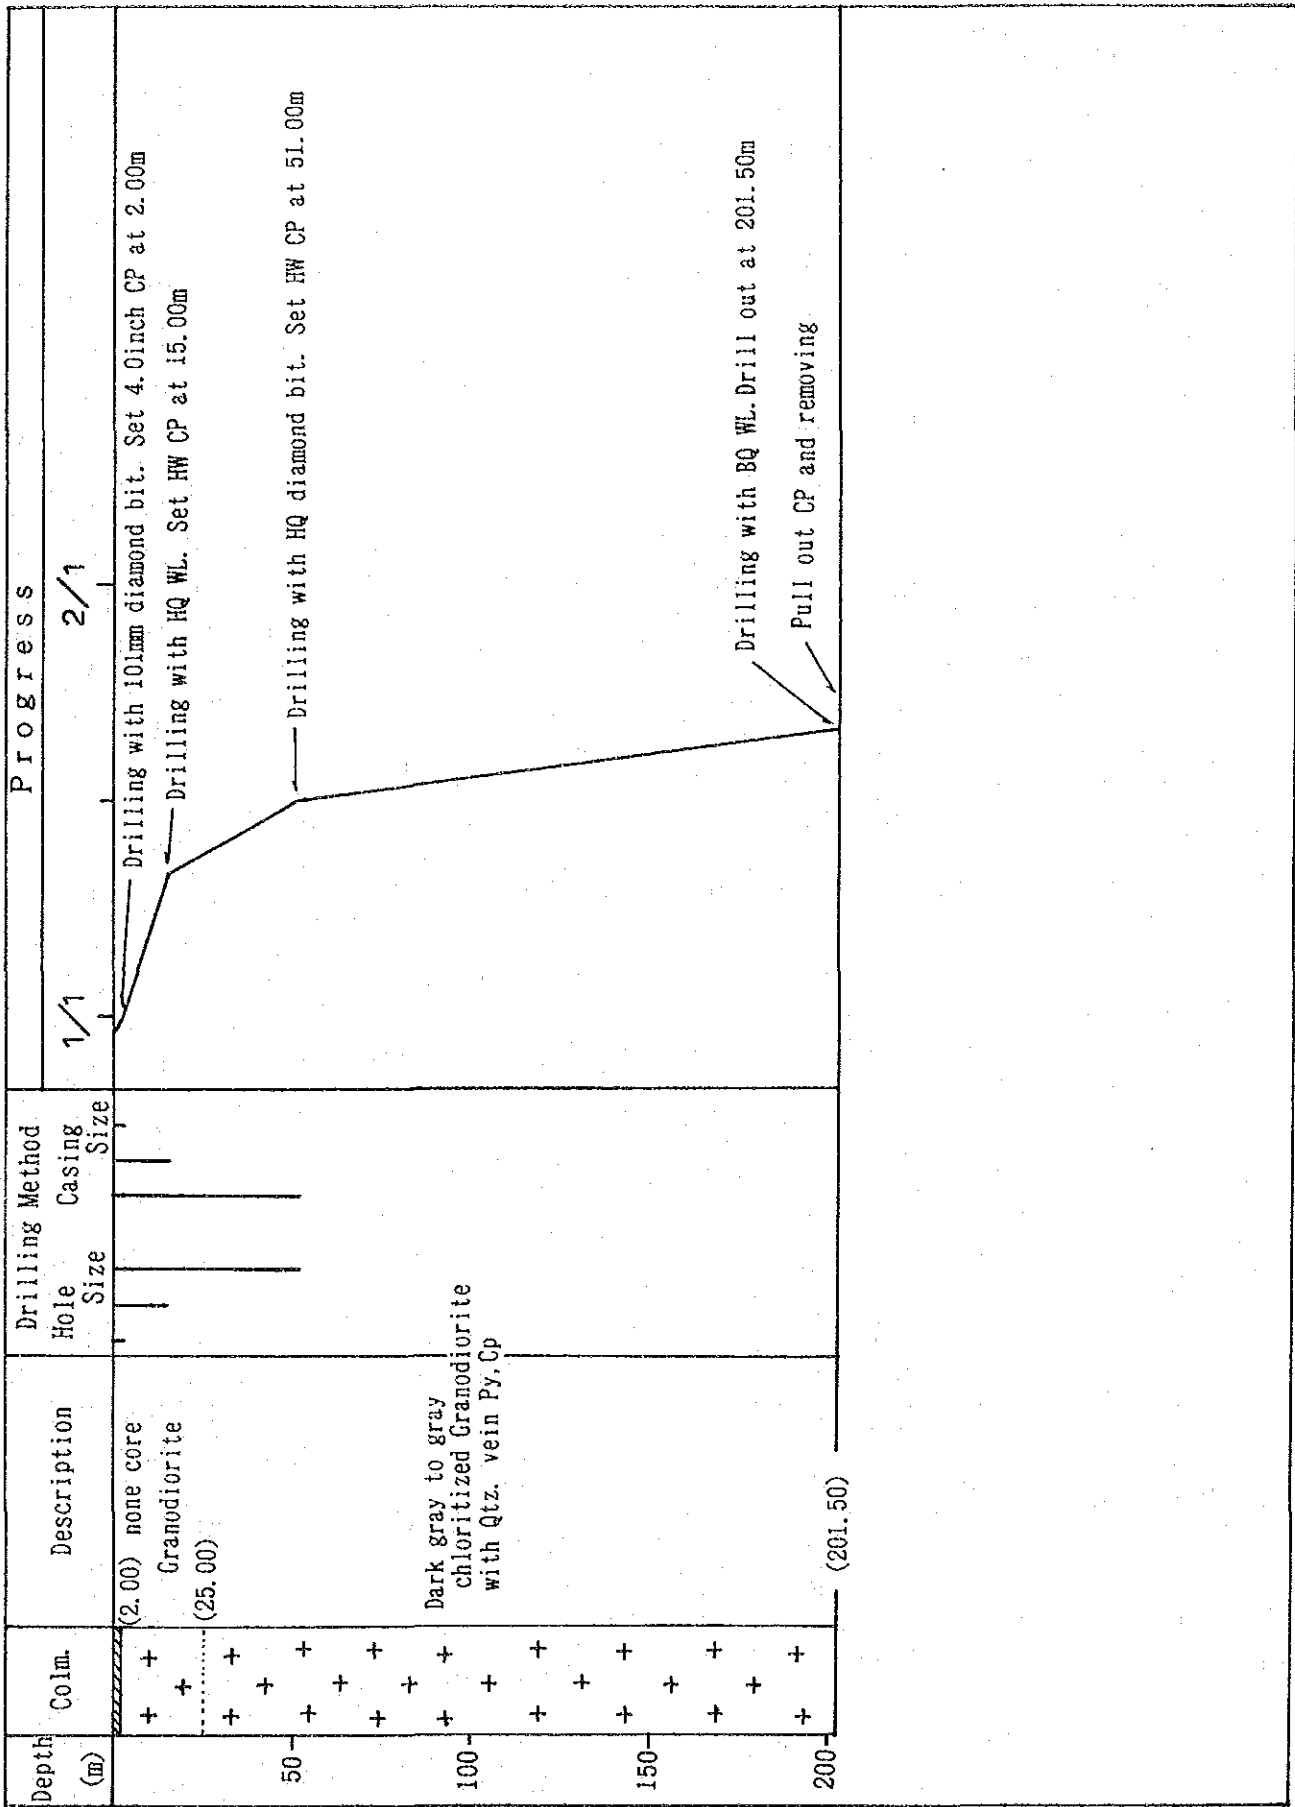

Appendix 7(6) Progress record of hole MJC-2

**Appendix 8 Drilling equipments and consumed materials**

## Appendix 8 Drilling equipments and consumed material

### A. Drilling equipment

Article	Model	Specification	Quantity
Drilling Machine	L-38	Maker: Longyear Capacity: BQ WL 725m Dimensions: Height 1450mm Length 2150mm Width 1170mm Weight (without Power Unit): 1150Kg	1 set
Diesel Engine	F-3L	Maker: 三井ドイツ Horse Power: 48HP/2200rpm	1 set
Drilling Pump	535RQ	Maker: Longyear Piston Diameter 70mm Stroke 70mm MAX Capacity 140ℓ/min MAX Pressure 56Kg/cm <sup>2</sup> Weight (Without Power Unit): 450Kg	1 set
Diesel Engine	F-2L	Maker: YANMAR Horse Power: 18HP/1800rpm	1 set
Wireline Hoist	WLH-S	Maker: Longyear Hoisting Capacity 250m	1 set
Diesel Engine	NS-40C	Maker: YANMAR Horse Power: 5HP/2400rpm	1 set
Mixer	Jet Type	Run by Drilling Pump	1 set
Drill Rod		NQWL (3.00m/joint)	89 joint
		BQWL (3.00m/joint)	150 joint
		HW (3.00m/joint)	25 joint
		NW (3.00m/joint)	35 joint
		BW (2.80m/joint)	98 joint

B. Materials consumed

AREA	Article	Light Oil	Cement	Bentonite	Remarks
	Hole No.	Engine(l)	50Kg/Sx(Sx)	50Kg/Sx(Sx)	
JUNIN	MJJ-10	3,176	30	125	
	MJJ-11	4,022	50	120	
	MJJ-12	2,419	30	110	
	MJJ-13	4,536	100	140	
CUELLO	MJC- 1	3,846	55	105	
	MJC- 2	2,302	45	55	

C. Bit consumed

AREA	Bit Type Hole No.	P Q (10m)			H Q			N Q			B Q		
		Drill Length	Bit	Reamer	Drill Length	Bit	Reamer	Drill Length	Bit	Reamer	Drill Length	Bit	Reamer
JUNIN	MJJ-10	2.00	1	0	116.00	7	1	140.00	6	2	45.30	2	1
	MJJ-11	2.00	1	0	123.00	10	6	133.00	9	5	46.50	3	1
	MJJ-12	-	0	0	112.50	6	3	154.00	7	3	34.30	3	2
	MJJ-13	-	0	0	70.00	4	2	111.60	6	4	88.40	9	4
CUELLO	MJC-1	-	0	0	9.14	1	1	202.00	11	3	0.00	0	0
	MJC-2	2.00	1	0	54.00	3	2	137.00	5	3	13.50	2	1





