

Appendix 4

Assay results of drilling core



MJOB-G1

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G1- 1	23.80	24.70	0.9	N.D	N.D	0.42	N.D	0.02	16.86
G1- 2	26.70	27.40	0.7	N.D	N.D	0.27	N.D	0.02	16.83
G1- 3	27.80	28.80	1	N.D	N.D	0.43	N.D	0.02	16.12
G1- 4	28.80	29.80	1	N.D	N.D	0.34	N.D	0.02	16.44
G1- 5	29.80	31.05	1.25	N.D	N.D	0.21	N.D	0.02	15.49
G1- 6	31.05	32.05	1	N.D	N.D	0.06	N.D	<0.01	12.68
G1- 7	32.05	33.05	1	N.D	N.D	0.19	N.D	<0.01	10.10
G1- 8	33.05	34.05	1	N.D	N.D	0.04	N.D	<0.01	7.99
G1- 9	34.05	35.55	1.5	N.D	N.D	0.25	N.D	0.02	15.69
G1- 10	42.20	42.60	0.4	N.D	N.D	0.33	N.D	<0.01	9.39
G1- 11	85.25	86.40	1.15	N.D	N.D	0.04	N.D	<0.01	14.51
G1- 12	98.30	99.45	1.15	N.D	N.D	0.23	N.D	0.01	12.42
G1- 13	105.00	106.20	1.2	N.D	N.D	0.05	N.D	0.01	12.39
G1- 14	106.20	107.20	1	N.D	N.D	0.16	N.D	0.01	12.99
G1- 15	107.20	108.20	1	N.D	N.D	0.17	N.D	0.01	13.76
G1- 16	108.20	109.20	1	N.D	N.D	0.08	N.D	0.02	14.84
G1- 17	109.20	109.70	0.5	N.D	N.D	0.09	N.D	0.02	14.22

MJOB-G2

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G2- 1	206.45	207.45	1	N.D	N.D	<0.01	N.D	0.02	13.19
G2- 2	207.45	208.45	1	N.D	N.D	<0.01	19.0	0.02	10.86
G2- 3	208.45	209.85	1.4	N.D	N.D	<0.01	26.0	0.08	11.95
G2- 4	211.65	212.65	1	N.D	N.D	0.02	32.0	0.21	11.50
G2- 5	212.65	213.65	1	N.D	N.D	0.09	N.D	0.27	16.23
G2- 6	213.65	214.65	1	N.D	N.D	0.15	N.D	0.35	18.30
G2- 7	214.65	215.65	1	N.D	N.D	0.02	N.D	0.22	15.11
G2- 8	215.65	216.65	1	N.D	N.D	0.30	19.0	0.10	19.65
G2- 9	216.65	217.65	1	N.D	N.D	0.13	N.D	0.05	15.03
G2- 10	217.65	219.35	1.7	N.D	N.D	0.08	N.D	0.19	13.64
G2- 11	222.40	223.40	1	N.D	N.D	0.06	N.D	0.47	18.76
G2- 12	223.40	224.40	1	N.D	N.D	0.04	13.0	0.09	22.47
G2- 13	224.40	225.40	1	N.D	N.D	0.17	N.D	0.22	21.12
G2- 14	225.40	226.05	0.65	N.D	N.D	0.11	N.D	0.21	18.69

MJOB-G3

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G3- 1	115.15	115.85	0.7	N.D	N.D	0.62	N.D	0.02	13.93
G3- 2	115.85	117.00	1.15	N.D	N.D	0.27	N.D	0.02	15.59
G3- 3	117.00	118.00	1	N.D	N.D	0.22	N.D	0.01	12.18
G3- 4	118.00	119.10	1.1	N.D	N.D	0.61	N.D	0.01	15.50
G3- 5	119.10	120.10	1	N.D	N.D	0.79	N.D	0.01	9.18
G3- 6	120.10	121.30	1.2	N.D	N.D	0.50	N.D	0.01	9.98
G3- 7	128.90	130.00	1.1	N.D	0.5	0.18	N.D	<0.01	7.70
G3- 8	130.00	131.00	1	N.D	N.D	0.20	N.D	<0.01	9.22
G3- 9	131.00	131.65	0.65	N.D	N.D	0.65	N.D	0.01	10.38
G3- 10	131.65	133.00	1.35	N.D	0.5	<0.01	N.D	<0.01	3.85
G3- 11	133.45	134.45	1	N.D	3.5	4.33	N.D	0.04	58.68
G3- 12	134.45	135.45	1	N.D	3.9	7.92	N.D	0.04	55.12
G3- 13	135.45	136.45	1	N.D	5.3	5.89	N.D	0.04	56.40
G3- 14	136.45	137.45	1	N.D	3.2	3.39	N.D	0.04	60.89
G3- 15	137.45	138.60	1.15	N.D	2.6	3.00	N.D	0.04	61.80
G3- 16	140.00	141.00	1	N.D	3.6	3.72	N.D	0.07	62.98
G3- 17	141.00	142.15	1.15	N.D	4.4	7.21	N.D	0.06	58.12
G3- 18	142.15	142.80	0.65	N.D	1.5	0.11	N.D	<0.01	25.90
G3- 19	142.80	143.80	1	N.D	1.2	0.02	N.D	<0.01	9.95
G3- 20	143.80	144.80	1	N.D	2.0	<0.01	N.D	0.07	17.10
G3- 21	144.80	145.80	1	N.D	2.0	0.02	N.D	0.46	11.79
G3- 22	145.80	147.20	1.4	N.D	2.9	0.02	N.D	0.55	16.70
G3- 23	147.20	148.20	1	N.D	5.9	0.51	N.D	0.27	14.88
G3- 24	148.20	149.20	1	N.D	2.0	0.29	N.D	0.38	19.96
G3- 25	149.20	150.20	1	N.D	2.3	0.50	N.D	0.25	13.47
G3- 26	150.20	151.20	1	N.D	1.4	0.28	N.D	0.04	15.79
G3- 27	151.20	152.20	1	N.D	1.4	0.07	N.D	0.21	22.65
G3- 28	152.20	153.20	1	N.D	1.4	0.20	N.D	0.02	23.70
G3- 29	153.20	154.20	1	N.D	1.0	0.03	N.D	<0.01	24.59
G3- 30	154.20	155.20	1	N.D	1.1	0.13	N.D	0.01	19.29
G3- 31	155.20	156.20	1	N.D	1.3	0.38	N.D	0.01	23.41
G3- 32	156.20	157.20	1	N.D	1.6	0.41	N.D	<0.01	33.60
G3- 33	157.20	158.20	1	N.D	2.0	1.31	N.D	0.02	32.82
G3- 34	158.20	159.20	1	N.D	1.5	0.90	N.D	<0.01	22.72
G3- 35	159.20	160.20	1	N.D	1.0	0.12	N.D	<0.01	13.90
G3- 36	160.20	161.20	1	N.D	1.0	0.10	N.D	<0.01	15.99
G3- 37	161.20	162.20	1	N.D	2.0	0.57	N.D	0.03	15.99
G3- 38	162.20	163.20	1	N.D	N.D	0.15	N.D	0.01	12.76
G3- 39	163.20	164.20	1	N.D	N.D	0.54	N.D	0.01	18.35
G3- 40	164.20	165.20	1	N.D	2.0	2.82	N.D	0.02	26.52
G3- 41	165.20	166.65	1.45	N.D	N.D	0.17	N.D	<0.01	16.47
G3- 42	167.15	168.15	1	N.D	2.0	0.14	N.D	0.03	14.15
G3- 43	168.15	169.15	1	N.D	2.0	0.41	N.D	0.03	17.76
G3- 44	169.15	170.15	1	N.D	N.D	0.16	N.D	0.03	15.15
G3- 45	170.15	171.15	1	N.D	N.D	0.39	N.D	0.03	13.85
G3- 46	171.15	172.15	1	N.D	N.D	0.44	N.D	0.03	16.63
G3- 47	172.15	173.20	1.05	N.D	N.D	0.40	N.D	0.03	17.71
G3- 48	173.20	174.80	1.6	N.D	N.D	1.41	N.D	0.02	18.90
G3- 49	174.80	175.80	1	N.D	N.D	0.30	N.D	0.02	13.07
G3- 50	175.80	176.80	1	N.D	N.D	0.43	N.D	0.02	12.75

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G3- 51	176.80	177.80	1	N.D	2.0	1.24	N.D	0.02	14.11
G3- 52	177.80	178.70	0.9	N.D	1.5	1.42	N.D	0.02	14.83
G3- 53	178.70	179.90	1.2	N.D	N.D	0.01	N.D	0.03	13.85
G3- 54	185.35	186.35	1	N.D	N.D	0.08	N.D	0.01	17.42
G3- 55	186.35	187.35	1	N.D	N.D	0.28	N.D	0.01	21.82
G3- 56	187.35	188.35	1	N.D	N.D	0.08	N.D	0.01	19.42
G3- 57	188.35	189.90	1.55	N.D	N.D	0.05	N.D	0.01	21.98
G3- 58	189.90	190.90	1	N.D	N.D	0.10	N.D	<0.01	28.49
G3- 59	190.90	191.90	1	N.D	N.D	0.10	N.D	0.02	32.48
G3- 60	191.90	192.90	1	N.D	N.D	0.32	N.D	<0.01	21.12
G3- 61	192.90	193.90	1	N.D	N.D	0.29	N.D	<0.01	22.10
G3- 62	193.90	194.90	1	N.D	N.D	0.05	N.D	<0.01	19.13
G3- 63	194.90	195.90	1	N.D	N.D	0.14	N.D	<0.01	18.66
G3- 64	195.90	196.90	1	N.D	2.5	0.57	N.D	0.03	27.02
G3- 65	196.90	197.90	1	N.D	1.0	0.27	N.D	0.01	15.16
G3- 66	197.90	198.90	1	N.D	N.D	0.10	N.D	<0.01	15.65
G3- 67	198.90	199.90	1	N.D	N.D	0.09	N.D	0.01	17.60
G3- 68	199.90	200.90	1	N.D	1.5	0.48	N.D	0.02	24.46
G3- 69	200.90	202.45	1.55	N.D	1.0	0.30	N.D	0.01	19.09
G3- 70	202.45	203.45	1	N.D	2.0	0.78	N.D	0.03	19.70
G3- 71	203.45	204.45	1	N.D	2.0	0.21	N.D	0.01	17.22
G3- 72	204.45	205.45	1	N.D	2.5	0.28	N.D	0.01	18.57
G3- 73	205.45	206.20	0.75	N.D	2.0	0.28	N.D	0.01	18.02
G3- 74	206.20	207.20	1	N.D	N.D	0.38	N.D	0.01	26.03
G3- 75	207.20	208.20	1	N.D	1.5	0.16	N.D	<0.01	17.84
G3- 76	208.20	209.20	1	N.D	1.0	0.16	N.D	<0.01	15.06
G3- 77	209.20	210.20	1	N.D	1.5	0.22	N.D	<0.01	25.51
G3- 78	210.20	211.20	1	N.D	1.5	0.30	N.D	<0.01	19.19
G3- 79	211.20	212.20	1	N.D	1.5	0.31	N.D	<0.01	18.01
G3- 80	212.20	213.20	1	N.D	1.0	0.40	N.D	0.01	21.24
G3- 81	213.20	214.00	0.8	N.D	N.D	0.31	N.D	<0.01	18.98
G3- 82	214.00	215.00	1	N.D	1.0	0.14	N.D	<0.01	19.23
G3- 83	215.00	216.00	1	N.D	N.D	0.08	N.D	<0.01	24.33
G3- 84	216.00	217.00	1	N.D	1.0	0.30	N.D	0.01	24.46
G3- 85	217.00	218.00	1	N.D	1.0	0.32	N.D	<0.01	17.73
G3- 86	218.00	219.00	1	N.D	N.D	0.15	N.D	<0.01	14.56
G3- 87	219.00	220.00	1	N.D	1.5	0.43	N.D	0.13	15.58
G3- 88	220.00	221.00	1	N.D	N.D	0.33	N.D	0.03	16.94
G3- 89	221.00	222.00	1	N.D	N.D	0.38	N.D	<0.01	21.02
G3- 90	222.00	223.00	1	N.D	N.D	0.36	N.D	<0.01	18.92
G3- 91	223.00	224.00	1	N.D	N.D	0.37	N.D	0.01	22.38
G3- 92	224.00	225.00	1	N.D	N.D	0.22	N.D	0.01	19.95
G3- 93	225.00	226.00	1	N.D	N.D	0.17	N.D	0.01	18.51
G3- 94	226.00	227.00	1	N.D	1.0	0.14	N.D	0.01	18.63
G3- 95	227.00	228.00	1	N.D	1.5	0.26	N.D	0.05	18.86
G3- 96	228.00	229.00	1	N.D	1.0	0.26	N.D	0.01	25.58
G3- 97	229.00	230.00	1	N.D	1.0	0.36	N.D	0.01	20.34
G3- 98	230.00	231.00	1	N.D	1.5	0.37	N.D	0.04	19.14
G3- 99	231.00	232.00	1	N.D	2.0	0.64	N.D	0.03	21.09
G3- 100	232.00	233.50	1.5	N.D	N.D	0.41	N.D	0.09	19.36

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G3- 101	246.10	247.25	1.15	N.D	N.D	0.30	N.D	0.17	16.01
G3- 102	279.50	281.50	2	N.D	2.2	0.17	39	3.47	14.54
G3- 103	281.50	283.50	2	N.D	1.7	0.18	39	3.76	13.24
G3- 104	283.50	285.50	2	N.D	1.0	0.06	39	1.78	11.46
G3- 105	285.50	288.20	2.7	<0.1	1.5	0.17	19	1.91	11.59
G3- 106	121.30	123.30	2	<0.1	<0.5	0.01	N.D	0.01	7.66
G3- 107	123.30	125.30	2	<0.1	<0.5	0.01	N.D	0.01	5.39
G3- 108	125.30	127.30	2	N.D	<0.5	0.01	N.D	0.01	7.14
G3- 109	127.30	128.90	1.6	N.D	<0.5	0.03	N.D	0.01	8.95

AVERAGE

stockwork	115.15-133.00	17.85	0.22	0.01
massive sulphide	133.45-138.60	5.15	4.85	0.04
massive sulphide	140.00-142.80	2.80	4.32	0.06
massive sulphide only		7.95	4.66	0.04
stockwork	142.80-166.65	23.85	0.40	0.11
stockwork	167.15-179.90	12.75	0.59	0.03
stockwork	185.35-233.50	48.15	0.27	0.02
stockwork	246.10-247.25	1.15	0.30	0.17
stockwork	279.50-288.20	8.70	0.15	2.66

MJOB-G4

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G4- 1	82.90	83.90	1.00	<0.1	2.3	0.72	N.D	1.54	12.28
G4- 2	83.90	84.70	0.80	<0.1	1.5	0.03	N.D	0.65	10.98

MJOB-G5

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G5- 1	134.00	135.50	1.5	<0.1	<0.5	0.26	N.D	0.01	14.21
G5- 2	135.50	136.90	1.4	<0.1	<0.5	0.40	N.D	0.01	11.53
G5- 3	136.90	138.00	1.1	0.1	1.7	1.12	N.D	0.05	56.42
G5- 4	138.00	139.00	1	0.3	2.4	0.94	79	0.07	58.51
G5- 5	139.00	140.00	1	0.1	1.5	0.92	44	0.05	57.97
G5- 6	140.00	141.00	1	0.2	1.5	0.85	49	0.05	58.17
G5- 7	141.00	142.00	1	0.1	1.5	1.02	44	0.04	58.29
G5- 8	142.00	143.00	1	0.2	1.8	0.45	44	0.04	58.33
G5- 9	143.00	144.00	1	0.2	2.0	0.49	79	0.04	60.64
G5- 10	144.00	145.00	1	0.1	1.6	0.61	54	0.04	59.25
G5- 11	145.00	146.00	1	0.1	1.2	1.61	39	0.04	57.21
G5- 12	146.00	147.00	1	<0.1	1.0	2.37	19	0.04	57.69
G5- 13	147.00	148.00	1	0.1	1.5	3.70	N.D	0.03	55.08
G5- 14	148.00	149.00	1	0.4	2.9	3.69	39	0.03	53.85
G5- 15	149.00	150.00	1	0.1	1.5	1.05	N.D	0.04	59.22
G5- 16	150.00	151.00	1	<0.1	1.2	1.74	N.D	0.04	57.27
G5- 17	151.00	152.00	1	<0.1	1.3	2.18	N.D	0.04	56.20
G5- 18	152.00	153.00	1	<0.1	1.2	1.97	N.D	0.04	57.46
G5- 19	153.00	154.00	1	0.1	1.6	2.31	N.D	0.04	58.20
G5- 20	154.00	155.00	1	0.1	1.3	2.23	N.D	0.04	56.56
G5- 21	155.00	156.00	1	0.1	1.0	2.00	N.D	0.05	56.61
G5- 22	156.00	157.00	1	0.1	1.0	1.74	29	0.05	55.95
G5- 23	157.00	158.00	1	0.1	1.0	1.33	N.D	0.05	54.28
G5- 24	158.00	159.00	1	0.2	1.2	1.21	N.D	0.06	58.30
G5- 25	159.00	160.00	1	<0.1	1.0	1.04	N.D	0.06	55.71
G5- 26	160.00	161.00	1	<0.1	0.9	1.31	N.D	0.05	57.01
G5- 27	161.00	162.00	1	<0.1	1.3	1.50	N.D	0.05	54.10
G5- 28	162.00	163.00	1	<0.1	1.2	1.82	N.D	0.04	55.98
G5- 29	163.00	164.00	1	0.1	1.6	1.75	N.D	0.03	54.54
G5- 30	164.00	165.00	1	<0.1	2.3	1.37	29	0.03	52.43
G5- 31	165.00	166.00	1	0.4	2.0	1.24	29	0.03	54.44
G5- 32	166.00	167.00	1	0.1	2.0	1.04	N.D	0.03	57.13
G5- 33	167.00	168.00	1	<0.1	2.1	1.25	N.D	0.03	54.89
G5- 34	168.00	169.00	1	<0.1	1.7	0.84	N.D	0.03	43.26
G5- 35	169.00	170.60	1.6	<0.1	1.8	0.55	N.D	0.03	40.47
G5- 36	170.60	173.00	2.4	<0.1	<0.5	0.03	N.D	0.06	8.12
G5- 37	173.00	175.00	2	<0.1	<0.5	0.02	N.D	0.10	6.22
G5- 38	175.00	177.00	2	<0.1	<0.5	0.02	N.D	0.09	6.86
G5- 39	177.00	179.00	2	<0.1	<0.5	0.04	N.D	0.45	7.42
G5- 40	179.00	181.00	2	<0.1	<0.5	0.08	N.D	0.92	8.24

AVERAGE

stockwork	134.00-136.90	2.9	0.33	0.01
massive sulphide	136.90-170.60	33.7	1.47	0.04
stockwork	170.60-181.00	10.4	0.04	0.31

MJOB-G11

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G11- 1	161.00	162.85	1.85	N.D	N.D	<0.01	N.D	0.01	32.88
G11- 2	162.85	163.80	0.95	N.D	N.D	0.01	N.D	0.04	36.28
G11- 3	163.80	164.45	0.65	N.D	<0.5	0.28	N.D	0.02	17.58
G11- 4	164.45	165.25	0.80	N.D	N.D	0.02	N.D	0.01	14.84
G11- 5	187.80	187.95	0.15	<0.1	7.3	3.84	N.D	0.08	30.60

AVERAGE

stockwork	161.70-162.85	1.85		<0.01	0.01
massive sulphide	162.85-165.25	2.40		0.09	0.02
stockwork	187.80-187.95	0.15		3.84	0.08

MJOB-13

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G13- 1	152.80	154.40	1.60	0.1	2.0	0.17	60.0	0.04	55.30

MJOB-14

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G14- 1	119.80	120.45	0.65	<0.1	2.5	1.38	41	0.02	55.61
G14- 2	120.45	123.20	2.75	<0.1	0.2	0.14	<10	0.01	21.44
G14- 3	123.20	124.20	1	<0.1	1.5	0.62	77	0.03	54.61
G14- 4	124.20	125.20	1	<0.1	1.2	1.06	52	0.06	56.00
G14- 5	125.20	126.20	1	<0.1	1.0	1.04	44	0.07	59.91
G14- 6	126.20	127.20	1	<0.1	0.8	1.38	40	0.05	59.97
G14- 7	127.20	128.85	1.65	<0.1	1.0	1.38	45	0.04	57.37
G14- 8	128.85	130.40	1.55	<0.1	N.D	0.13	<10	0.01	15.66
G14- 9	130.40	131.40	1	<0.1	3.7	2.80	48	0.02	52.49
G14- 10	131.40	132.40	1	<0.1	2.4	1.70	45	0.02	48.03
G14- 11	132.40	133.85	1.45	<0.1	2.1	2.02	45	0.02	48.08
G14- 12	133.85	134.65	0.8	<0.1	1.3	0.56	27	0.01	20.87
G14- 13	134.65	135.65	1	<0.1	3.4	2.01	54	0.02	53.17
G14- 14	135.65	136.70	1.05	<0.1	4.2	3.24	45	0.02	53.20
G14- 15	136.70	138.20	1.5	<0.1	0.3	0.61	17	0.02	20.73
G14- 16	138.20	139.65	1.45	<0.1	1.7	0.51	30	0.03	32.38
G14- 17	139.65	140.60	0.95	<0.1	0.2	0.71	28	0.01	15.36
G14- 18	140.60	141.60	1	<0.1	1.6	1.21	28	0.02	30.93
G14- 19	141.60	143.15	1.55	<0.1	1.3	0.51	28	0.02	29.80
G14- 20	143.15	144.05	0.9	<0.1	2.0	0.80	54	0.03	56.19
G14- 21	144.05	144.60	0.55	<0.1	1.2	0.51	40	0.02	39.52
G14- 22	144.60	145.60	1	<0.1	1.9	1.40	48	0.02	54.94
G14- 23	145.60	146.60	1	N.D	1.6	1.53	38	0.02	53.17
G14- 24	146.60	147.60	1	N.D	2.0	1.80	42	0.03	54.47
G14- 25	147.60	148.60	1	N.D	1.5	1.28	40	0.05	54.10
G14- 26	148.60	149.60	1	N.D	1.6	1.37	42	0.06	55.65
G14- 27	149.60	150.60	1	<0.1	1.7	1.20	48	0.05	56.32
G14- 28	150.60	151.60	1	<0.1	2.1	1.27	46	0.05	55.01
G14- 29	151.60	152.60	1	<0.1	1.8	1.05	44	0.05	56.18
G14- 30	152.60	153.60	1	<0.1	1.9	1.12	84	0.05	55.19
G14- 31	153.60	154.70	1.1	N.D	2.5	1.20	24	0.05	55.76
G14- 32	154.70	155.70	1	N.D	2.5	1.06	34	0.05	60.44
G14- 33	155.70	156.70	1	N.D	3.0	1.08	38	0.05	62.13
G14- 34	156.70	158.05	1.35	<0.1	2.5	1.02	36	0.05	60.24
G14- 35	158.05	159.15	1.1	<0.1	<0.5	0.13	N.D	0.01	21.67
G14- 36	159.15	160.15	1	0.1	2.5	2.83	32	0.05	59.16
G14- 37	160.15	161.30	1.15	0.1	2.5	2.83	23	0.04	59.80
G14- 38	161.30	162.30	1	0.3	4.0	3.52	26	0.04	53.46
G14- 39	162.30	163.30	1	0.3	2.0	9.17	13	0.04	56.87
G14- 40	163.30	164.75	1.45	0.3	4.0	6.81	38	0.05	56.89
G14- 41	164.75	167.35	2.6	0.2	<0.5	0.38	N.D	0.08	25.42
G14- 42	167.35	168.35	1	0.1	16.0	10.75	N.D	1.24	35.83
G14- 43	168.35	169.50	1.15	<0.1	7.0	4.02	N.D	0.53	28.55
G14- 44	169.50	171.50	2	<0.1	3.5	1.06	N.D	0.44	25.42
G14- 45	171.50	173.50	2	<0.1	2.5	0.64	11	1.06	20.87
G14- 46	173.50	175.50	2	<0.1	1.0	0.44	N.D	0.41	19.74
G14- 47	175.50	177.50	2	<0.1	1.0	0.25	N.D	0.15	17.09
G14- 48	177.50	179.50	2	<0.1	1.0	0.55	N.D	0.10	20.81
G14- 49	179.50	181.50	2	N.D	<0.5	0.36	N.D	0.41	14.38
G14- 50	181.50	183.50	2	N.D	<0.5	0.36	N.D	0.23	14.93

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G14- 51	183.50	185.50	2	N.D	<0.5	0.32	N.D	0.10	14.76
G14- 52	185.50	187.50	2	N.D	0.5	0.47	N.D	0.10	16.38
G14- 53	187.50	189.50	2	N.D	1.0	0.58	N.D	0.20	17.12
G14- 54	189.50	191.50	2	N.D	1.0	0.62	N.D	0.21	16.38
G14- 55	191.50	193.50	2	N.D	1.5	0.64	N.D	0.05	18.50
G14- 56	193.50	195.50	2	N.D	1.0	0.52	N.D	0.11	17.05
G14- 57	195.50	197.50	2	N.D	1.0	0.53	N.D	0.12	18.69
G14- 58	197.50	199.50	2	N.D	0.5	0.30	N.D	0.10	16.12
G14- 59	199.50	201.50	2	<0.1	1.0	0.15	N.D	0.20	21.27
G14- 60	201.50	203.50	2	<0.1	0.5	0.14	N.D	0.33	15.32
G14- 61	203.50	205.50	2	<0.1	1.0	0.27	N.D	0.45	16.27
G14- 62	205.50	207.50	2	0.20	0.5	0.11	N.D	0.42	17.04
G14- 63	207.50	209.50	2	N.D	1.0	0.14	N.D	0.27	15.94
G14- 64	209.50	211.50	2	<0.1	1.0	0.24	N.D	0.16	16.54
G14- 65	211.50	213.50	2	<0.1	3.3	0.39	N.D	0.29	17.94
G14- 66	213.50	215.50	2	<0.1	2.5	0.27	N.D	0.33	16.34
G14- 67	215.50	217.50	2	<0.1	2.3	0.27	N.D	0.30	19.49
G14- 68	217.50	219.50	2	N.D	2.5	0.30	N.D	0.29	18.73
G14- 69	219.50	221.50	2	<0.1	3.3	0.37	N.D	0.35	16.15
G14- 70	221.50	223.50	2	<0.1	2.4	0.22	N.D	0.41	15.28
G14- 71	223.50	225.50	2	<0.1	8.0	0.98	N.D	0.24	20.44
G14- 72	225.50	227.50	2	N.D	0.5	0.06	N.D	0.82	10.16
G14- 73	227.50	230.50	3	<0.1	2.0	0.37	N.D	0.88	14.15

AVERAGE	(m)	Cu(%)	Zn(%)
massive sulphide only	37.1	1.88	0.04
massive sulphide 119.80-164.75	44.95	1.60	0.03
stockwork 164.75-171.50	6.75	2.74	0.44
stockwork 171.50-230.50	59.00	0.37	0.32

MJOB-G15

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G15- 1	179.20	180.35	1.15	0.2	3.7	1.70	32	0.06	56.00
G15- 2	180.35	180.75	0.4	N.D	<0.5	0.07	<10	0.02	27.18
G15- 3	180.75	181.60	0.85	0.2	4.2	2.16	33	0.05	59.73
G15- 4	181.60	182.20	0.6	N.D	<0.5	0.06	N.D	0.01	21.07
G15- 5	182.20	183.20	1	0.2	4.2	1.84	34	0.06	57.08
G15- 6	183.20	184.65	1.45	0.2	4.6	2.47	18	0.04	52.49
G15- 7	184.65	185.65	1	<0.1	<0.5	0.27	<10	0.01	27.89
G15- 8	185.65	186.65	1	0.2	3.2	1.63	34	0.06	56.25
G15- 9	186.65	187.65	1	0.2	3.4	1.72	38	0.06	57.60
G15- 10	187.65	188.65	1	0.3	3.3	1.66	35	0.06	56.25
G15- 11	188.65	189.65	1	0.2	5.4	3.44	39	0.06	55.93
G15- 12	189.65	190.65	1	0.2	4.0	2.16	43	0.07	57.90
G15- 13	190.65	191.65	1	0.2	2.8	1.47	37	0.08	56.83
G15- 14	191.65	192.95	1.3	0.2	2.8	0.92	53	0.08	56.51
G15- 15	192.95	193.10	0.15	<0.1	<0.5	0.17	<10	0.02	29.75
G15- 16	193.10	194.10	1	0.2	2.1	0.90	34	0.05	57.00
G15- 17	194.10	195.10	1	0.1	2.8	0.69	27	0.04	55.61
G15- 18	195.10	196.10	1	0.1	2.8	0.92	32	0.04	55.84
G15- 19	196.10	197.10	1	N.D	3.0	0.63	36	0.04	56.74
G15- 20	197.10	198.10	1	<0.1	2.3	0.58	35	0.04	55.16
G15- 21	198.10	199.10	1	<0.1	2.9	1.37	39	0.05	56.40
G15- 22	199.10	200.10	1	<0.1	3.1	2.01	32	0.03	55.52
G15- 23	200.10	201.10	1	<0.1	2.6	1.48	29	0.03	56.34
G15- 24	201.10	202.10	1	<0.1	2.0	2.18	25	0.03	55.57
G15- 25	202.10	203.10	1	<0.1	2.0	1.32	22	0.05	55.08
G15- 26	203.10	204.10	1	<0.1	2.0	1.20	28	0.06	55.86
G15- 27	204.10	205.10	1	<0.1	2.5	1.52	18	0.03	60.06
G15- 28	205.10	206.10	1	<0.1	2.9	1.84	25	0.03	56.59
G15- 29	206.10	207.10	1	<0.1	2.2	1.28	24	0.05	56.87
G15- 30	207.10	208.10	1	<0.1	2.4	1.08	22	0.05	57.41
G15- 31	208.10	209.10	1	<0.1	2.4	1.47	21	0.05	58.24
G15- 32	209.10	210.60	1.5	<0.1	3.4	1.35	60	0.04	56.91
G15- 33	210.60	211.65	1.05	N.D	<0.5	0.09	N.D	0.02	16.52
G15- 34	211.65	212.30	0.65	<0.1	3.8	1.99	30	0.04	53.79
G15- 35	178.85	179.20	0.35	<0.1	1.0	2.10	<10	0.01	53.73

AVERAGE	(m)	Cu(%)	
massive Sulphide	29.9	1.55	0.05
178.85-179.20	0.35	2.10	0.01
179.20-212.30	33.10	1.41	0.05

MJOB-G16

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G16- 1	186.30	186.90	0.60	N.D	<0.5	0.14	N.D	0.04	24.97
G16- 2	186.90	187.90	1.00	0.1	5.0	1.69	38	0.06	54.24
G16- 3	187.90	188.90	1.00	0.1	4.6	1.68	42	0.05	55.51
G16- 4	188.90	189.40	0.50	0.1	3.4	1.42	27	0.03	56.92

AVERAGE

massive sulphide 186.30-186.90 0.60 0.14 0.04
 stockwork 164.75-171.50 2.50 1.63 0.05

MJOB-17

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
G17- 1	215.90	216.90	1.00	0.2	3.5	0.80	64	0.10	50.77
G17- 2	216.90	217.90	1.00	N.D	2.5	0.82	53	0.06	58.18
G17- 3	217.90	218.90	1.00	<0.1	3.3	1.71	32	0.04	59.24
G17- 4	218.90	219.90	1.00	<0.1	3.5	0.87	48	0.05	57.79
G17- 5	219.90	220.90	1.00	<0.1	3.8	1.30	48	0.04	55.20
G17- 6	220.90	221.90	1.00	<0.1	3.9	1.28	39	0.05	57.40
G17- 7	221.90	222.80	0.90	<0.1	3.4	1.43	22	0.03	59.19

AVERAGE

massive sulphide 215.90-222.80 6.90 1.17 0.05

MJOB-D4


Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
D4- 1	17.10	19.60	2.50	<0.1	N.D	0.39	N.D	0.05	15.16
D4- 2	19.60	21.00	1.40	N.D	N.D	0.22	N.D	0.07	17.66
D4- 3	21.00	22.80	1.80	<0.1	N.D	0.19	N.D	0.08	19.82
D4- 4	22.80	24.00	1.20	<0.1	N.D	0.21	N.D	0.16	33.69
D4- 5	24.00	25.00	1.00	<0.1	N.D	0.20	N.D	0.28	39.13
D4- 6	25.00	26.70	1.70	<0.1	N.D	0.23	N.D	0.10	24.06
D4- 7	26.70	27.70	1.00	<0.1	N.D	0.51	N.D	0.10	23.46
D4- 8	27.70	28.10	0.40	N.D	12.7	5.85	N.D	0.14	19.06
D4- 9	29.95	31.90	1.95	N.D	<0.5	0.32	N.D	0.19	23.22
D4- 10	31.90	33.45	1.55	N.D	N.D	0.22	N.D	0.15	31.49
D4- 11	33.45	36.35	2.90	N.D	<0.5	0.31	N.D	0.30	25.41

MJOB-A2

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
A2- 1	100.25	102.00	1.75	N.D	<0.5	<0.01	N.D	0.01	7.49
A2- 2	102.00	103.50	1.50	N.D	N.D	<0.01	N.D	0.01	7.05
A2- 3	184.80	185.40	0.60	N.D	N.D	<0.01	N.D	0.01	9.74

MJOB-F2

Sample No.	Depth(m)		Length (m)	Au(g/t)	Ag(g/t)	Cu(%)	Pb(ppm)	Zn(%)	Fe2O3 (%)
	From	To							
F2- 1	45.20	47.20	2.00	N.D	N.D	0.01	N.D	<0.01	25.39
F2- 2	47.20	49.20	2.00	N.D	N.D	<0.01	N.D	<0.01	20.43
F2- 3	49.20	51.20	2.00	N.D	N.D	<0.01	N.D	0.01	18.39
F2- 4	51.20	53.20	2.00	N.D	N.D	0.01	N.D	<0.01	17.16

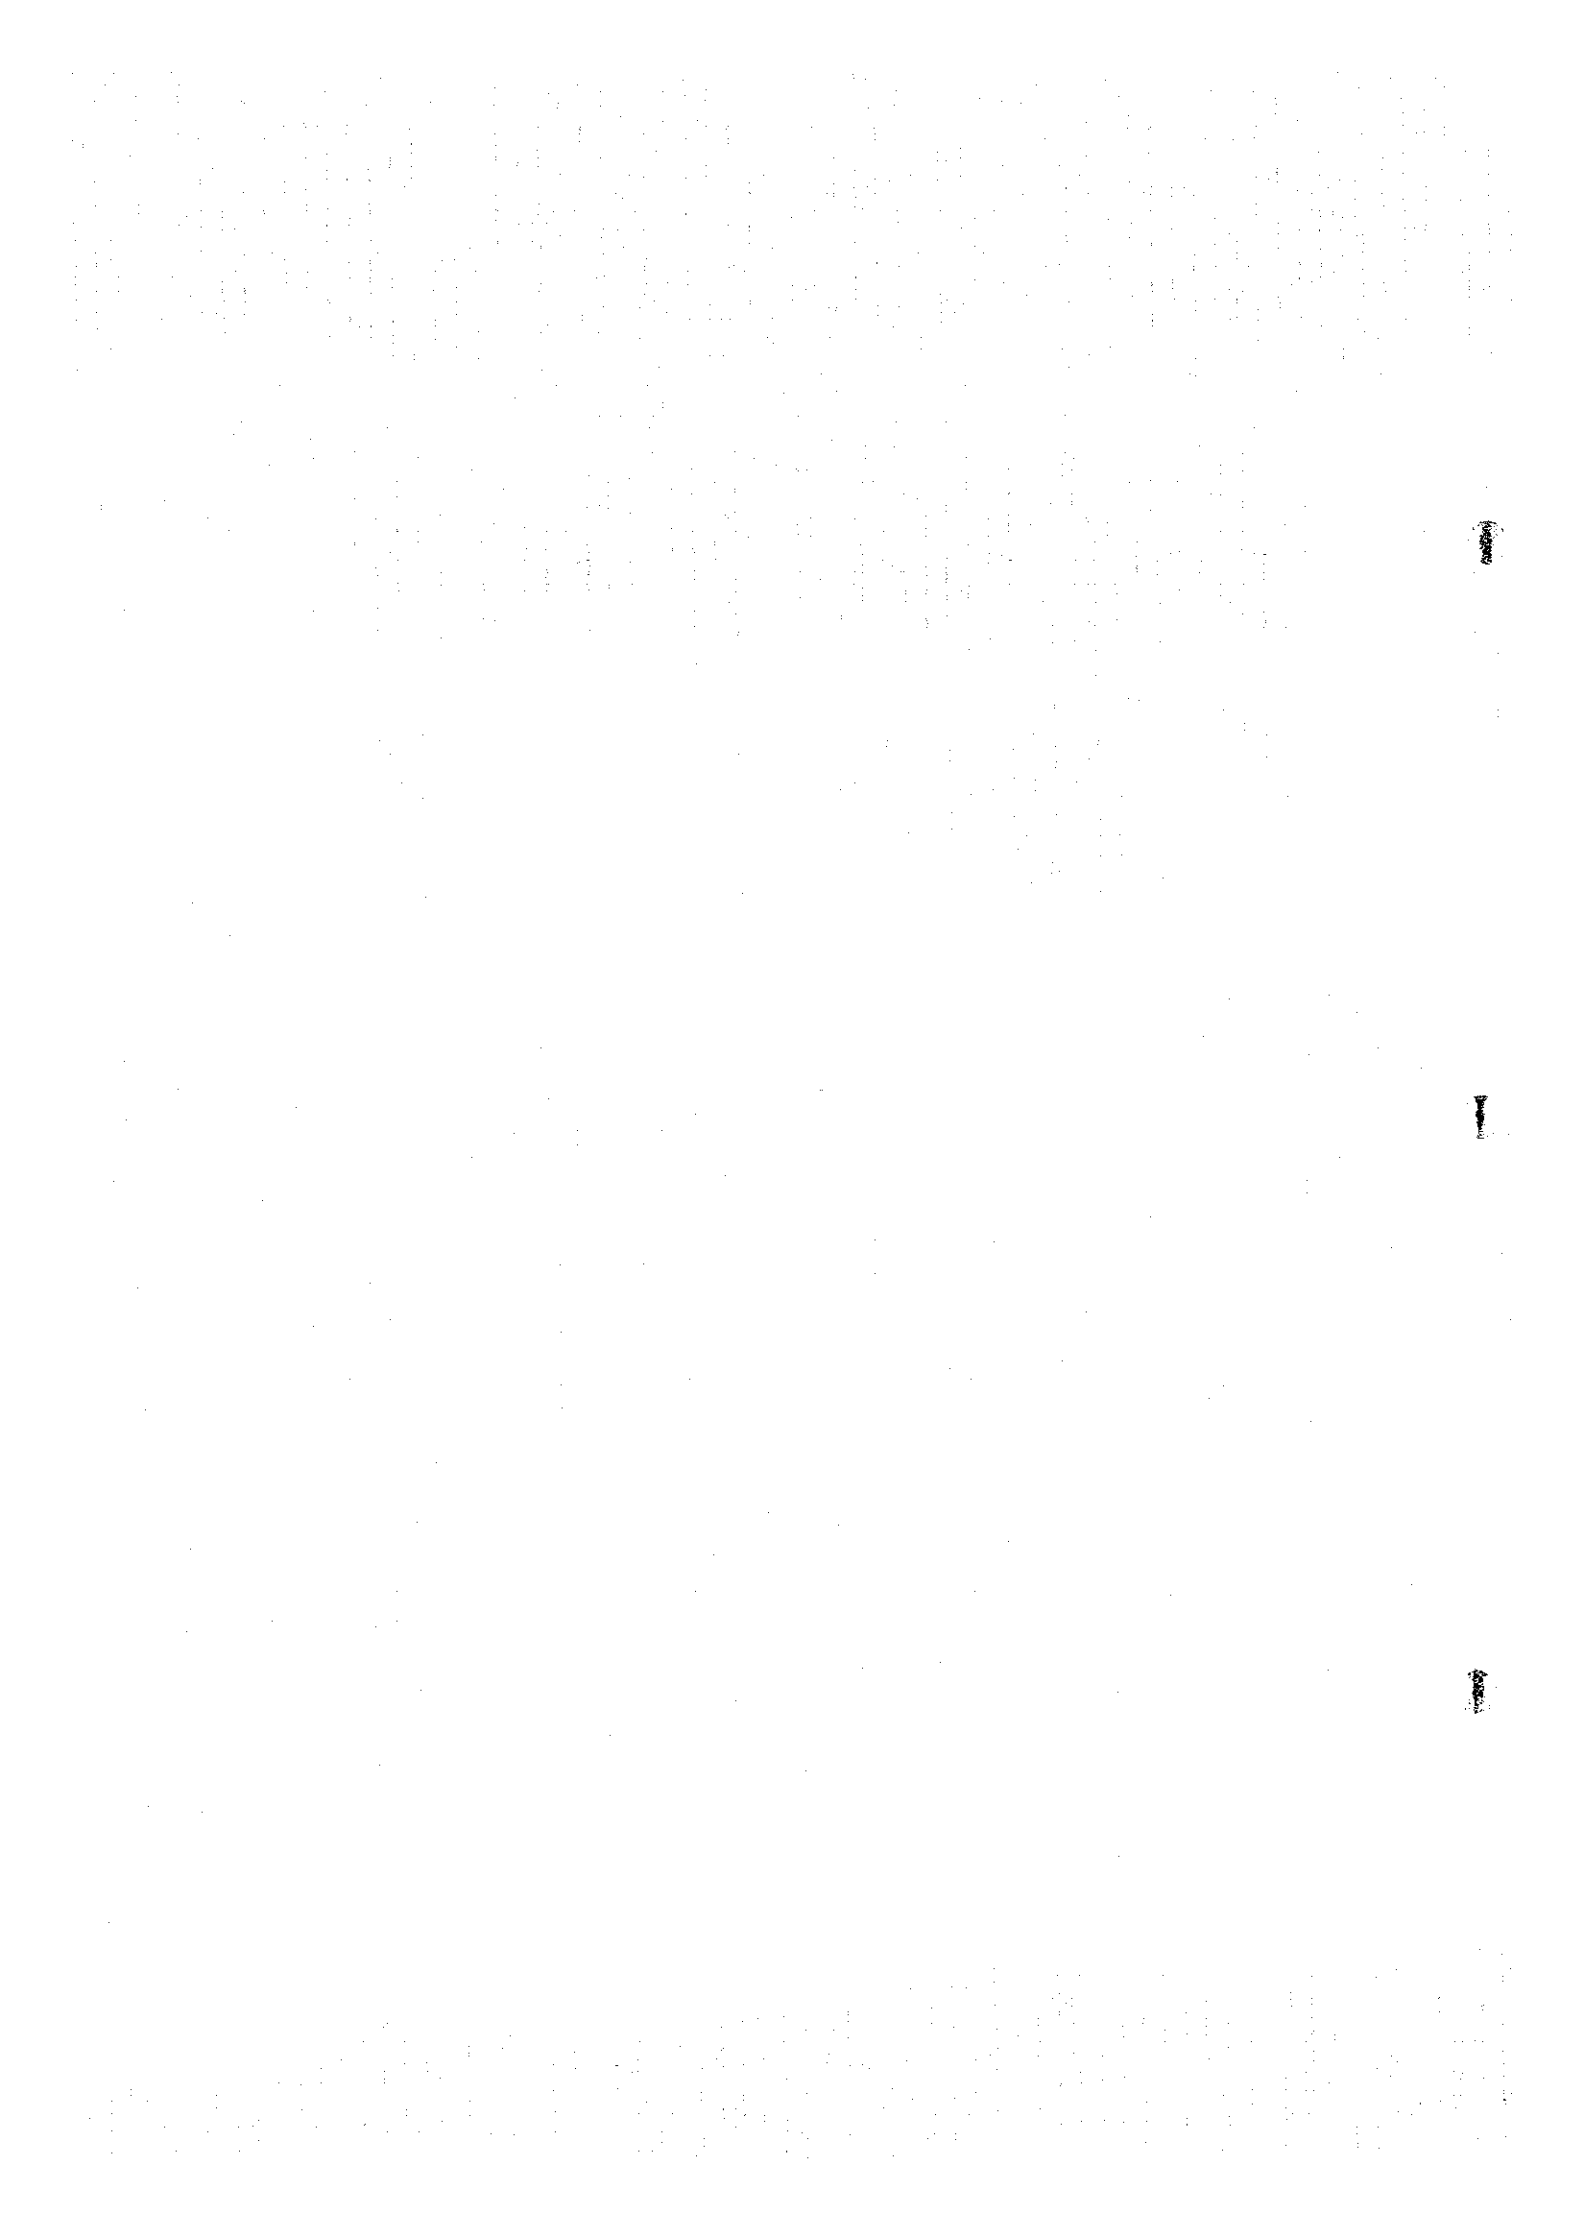

Appendix 5

Photographs of ore polished section



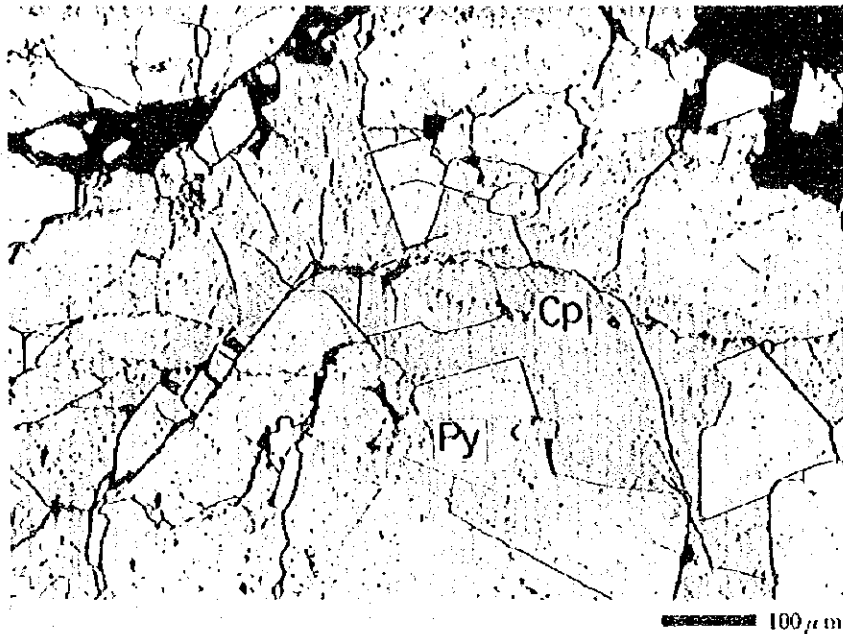


Photo. 1
Bore hole no.: G5
Depth: 147.80m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

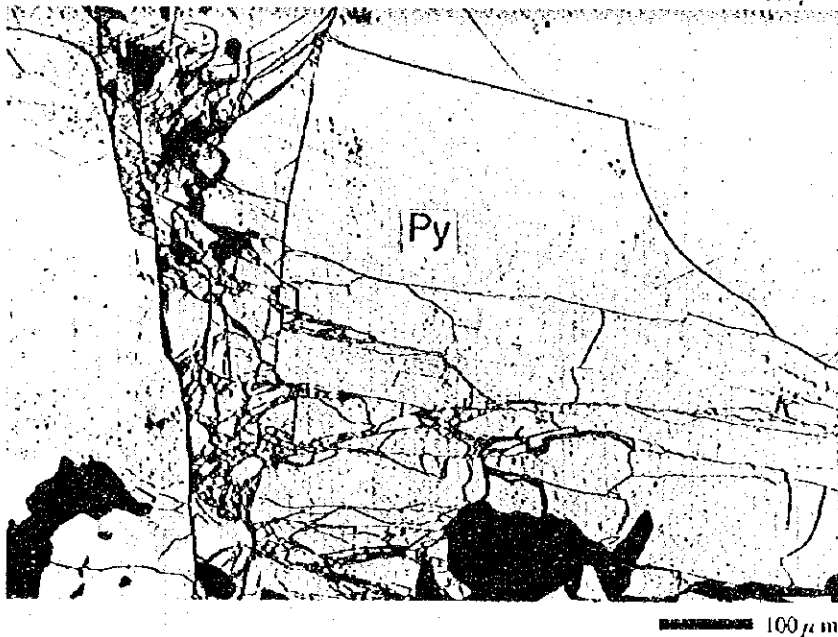


Photo. 2
Bore hole no.: G11
Depth: 163.00m
Hematite dominant siliceous ore

Py: Pyrite

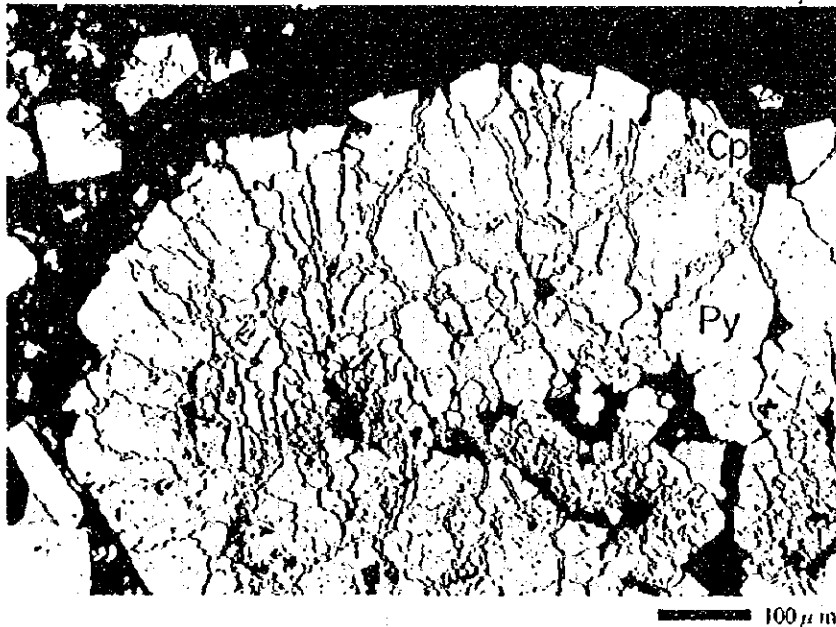


Photo. 3
Bore hole no.: G14
Depth: 132.20m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

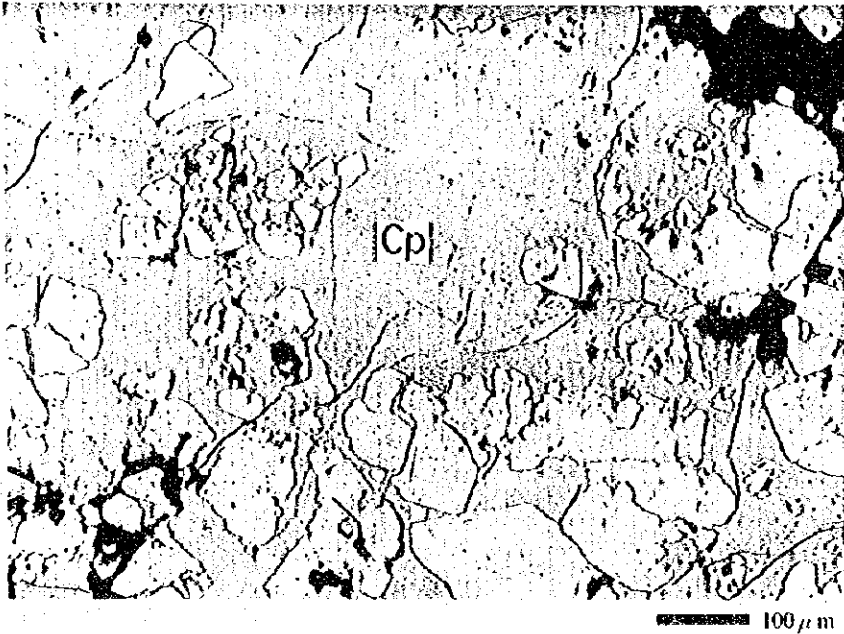


Photo. 4
Bore hole no.: G15
Depth: 189.00m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

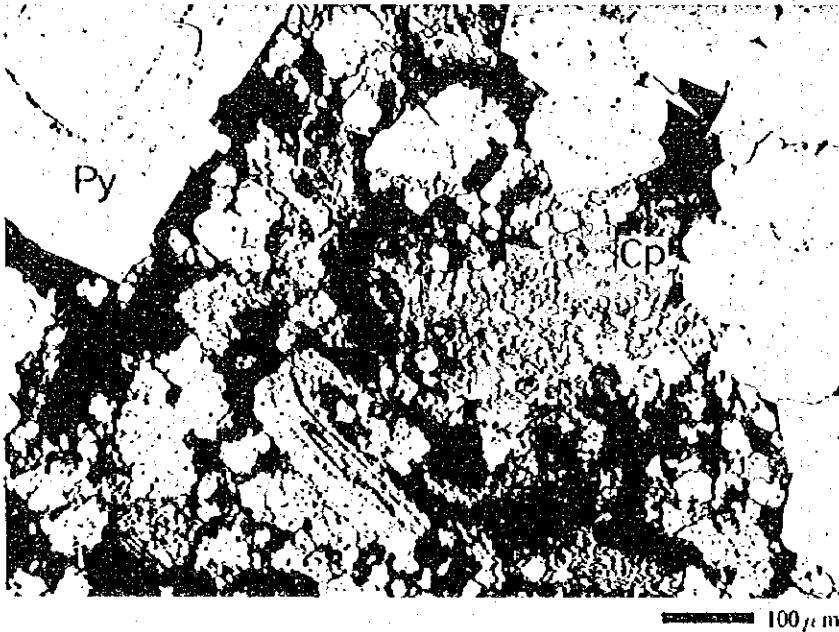


Photo. 5
Bore hole no.: G14
Depth: 150.00m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

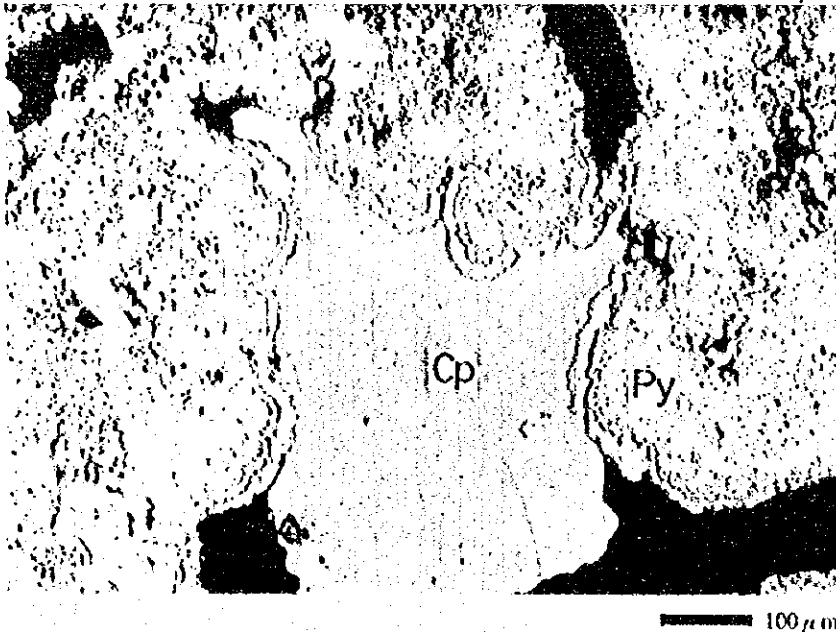


Photo. 6
Bore hole no.: G3
Depth: 136.90m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

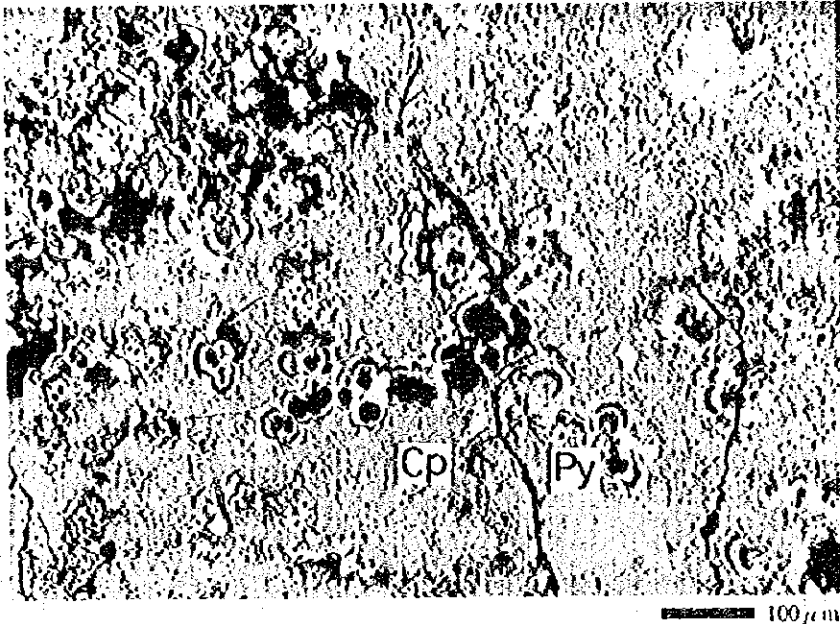


Photo. 7
Bore hole no.: G3
Depth: 134.50m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

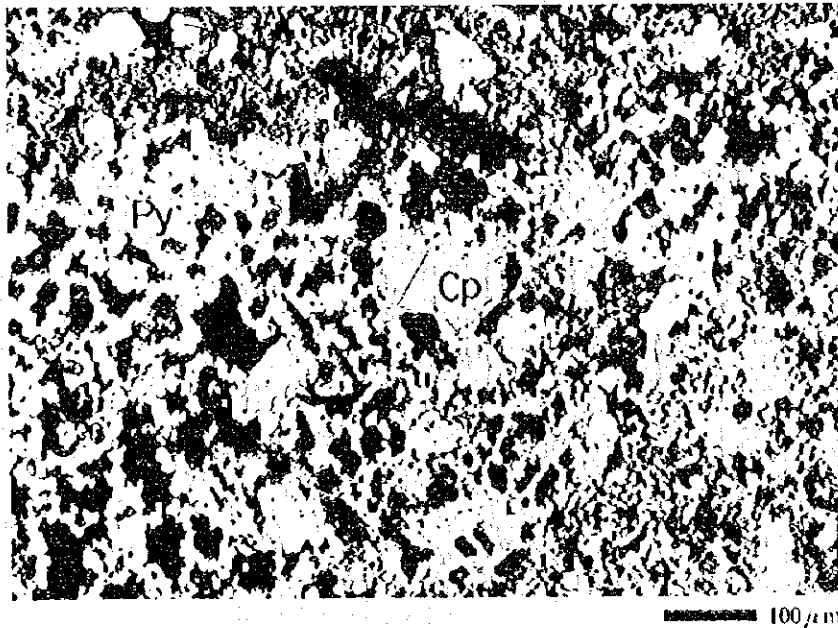


Photo. 8
Bore hole no.: G5
Depth: 147.80m
Massive sulphide ore

Py: Pyrite
Cp: Chalcopyrite

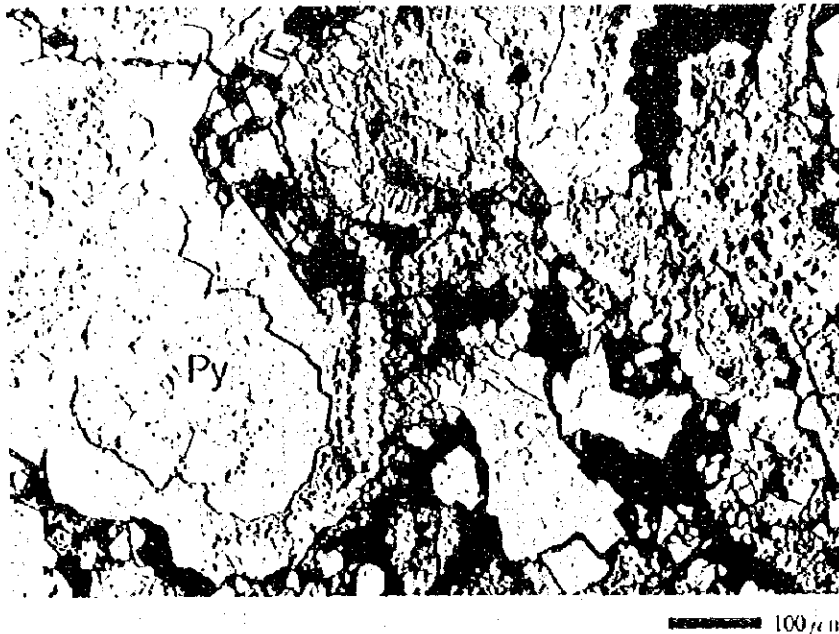


Photo. 9
Bore hole no.: G5
Depth: 147.80m
Massive sulphide ore

Py: Pyrite

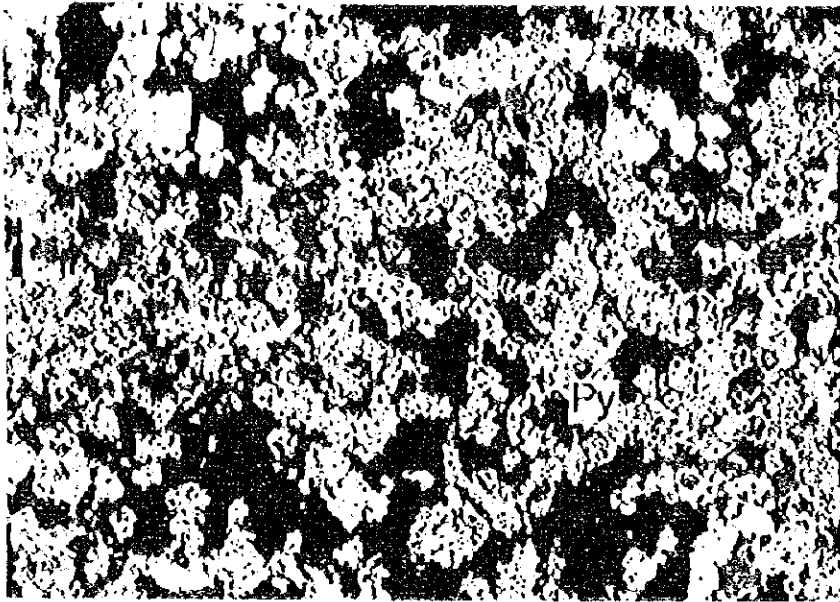


Photo. 10
Bore hole no.: G3
Depth: 134.50m
Massive sulphide ore

Py: Pyrite

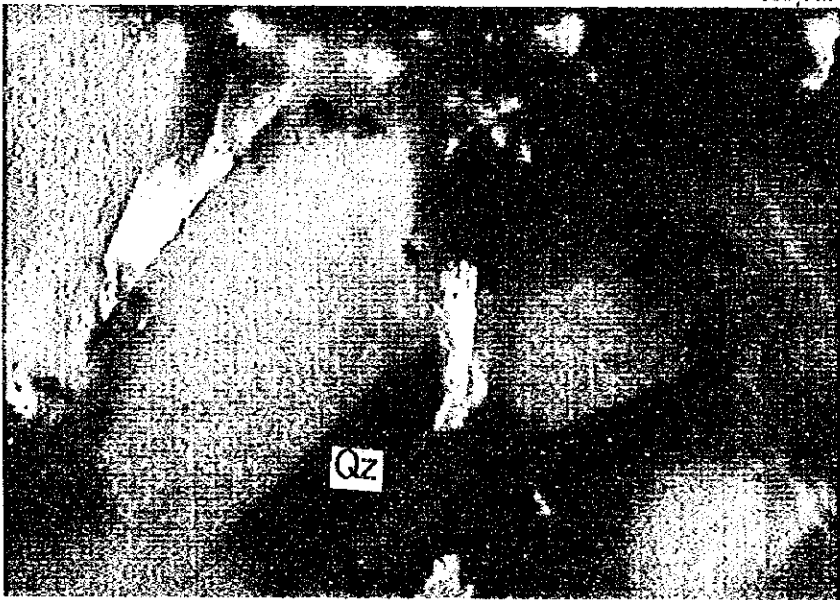


Photo. 11
Bore hole no.: G11
Depth: 163.00m
Hematite dominant siliceous ore

Qz: Quartz



Photo. 12
Bore hole no.: G11
Depth: 163.00m
Hematite dominant siliceous ore

Ht: Hematite
Mt: Magnetite
Qz: Quartz

JICA