

## 5. テクニカル・ノート

### オキナワ道路整備計画準備調査

#### テクニカル・ノート

JICA 調査団は、サンタクルス県公共事業・土地整備局(SOPOT)と技術的な協議を実施し、添付の事項について確認した。なお、各事項については、日本での解析、外務省及び JICA との協議を経て最終的に決定される。

サンタクルス 2016 年 5 月 18 日

---

カルロス ソーサ  
局長  
サンタクルス県公共事業・土地整備局

---

中村友彦  
業務主任  
JICA 準備調査団

## 添 付

### 1. 本テクニカル・ノートでの合意事項

本テクニカル・ノートでの合意事項は、道路舗装構造の検討方針及びポリビア側負担事項の内、現状の EIA ライセンスの取得手続き状況を反映した EIA ライセンス及び樹木の伐採・抜根許可の取得手続きのスケジュールについてである。

2014 年 8 月 29 日に署名、合意したテクニカル・ノートの内容の内、本テクニカル・ノートで更新した内容以外は有効である。

### 2. 道路舗装構造の検討方針

道路構造は設計交通荷重に耐えうるコンクリート層、下層路盤、構築路床から構成されるが、これらの厚さの複数の代替案を検討し、経済的な案を提案する。また、アスファルト舗装についても検討し、コンクリート舗装と比較して経済的な案を提案する。

### 3. ポリビア側負担事項

- ・ EIA ライセンス及び伐採・抜根許可書の取得

ポリビア側は、Okinawa1~Okinawa3 間道路の EIA カテゴリーが「2」と決定された事を受け、抜根・伐採計画及び EIA レポートを作成し、EIA ライセンスを 2017 年 5 月 31 日までに取得する。

付属文書：2014 年 8 月 29 日に署名したテクニカル・ノート

**Estudio Preparatorio para el Proyecto de Pavimentación de  
la Carretera Okinawa I,II,III**

**Memorando Técnico**

La Misión de JICA mantuvo conversaciones técnicas con distintas autoridades de Bolivia tales como la Secretaría de Obras Públicas y Ordenamiento Territorial del Gobierno Autónomo Departamental de Santa Cruz (SOPOT), Servicio De Caminos (SEDCAM), Administradora Boliviana de Caminos (ABC), la Alcaldía de Santa Cruz de la Sierra y la Alcaldía de Okinawa, y confirmó los ítems descritos en el Documento Adjunto. Con respecto a cada uno de dichos ítems, se definirá después de hacer análisis de los resultados del Estudio Preparatorio y mantener conversaciones con la Cancillería del Japón y JICA.

Santa Cruz, 29 de agosto de 2014



Ing. Carlos Hugo SOSA ARREAZA  
Secretario de Obras Públicas y  
Ordenamiento Territorial del  
Gobierno Autónomo Departamental  
de Santa Cruz



Ing. Tomohiko NAKAMURA  
Jefe de los consultores  
Misión del Estudio Preparatorio de  
JICA

**Documento Adjunto**

**1. Contenido del Proyecto**

- Pavimentación de la Carretera Okinawa (Tramo de unos 35 km de distancia desde la Intersección de Okinawa 1 hasta la de Okinawa 3) .
- Mejoramiento de Cunetas, Alcantarillas transversales y alcantarillas a las cuales fluye finalmente el agua de dichas cunetas de la mencionada Carretera
- Mejoramiento de las aceras de las comunidades habitadas, ubicadas sobre dicha Carretera (Okinawa2, San Miguel, alrededores de la Intersección de Okinawa 3)
- Señalizaciones horizontales y verticales de todo el trayecto de dicha Carretera (línea eje, etc.)
- Mejoramiento de 5 intersecciones sobre dicha Carretera (Okinawa1, Okinawa2, San Miguel, Zona Franca~Okinawa2,3, Okinawa3)
- Mejoramiento de otras intersecciones y de rampa de acceso desde la entrada de construcciones hasta dicha Carretera
- Reconstrucción del Puente

**2. Normativa de estructura geométrica de camino**

- Normativa de AASHTO
- Velocidad de diseño : 80km/hora
- Pendiente(bombeo) transversal vial estándar : 2 %

**3. Normativa de diseño estructural para pavimentación de camino**

- tipo de pavimentación : pavimentación de concreto asfáltico o de hormigón
- vida útil diseñada : 10 años en caso de la pavimentación de concreto asfáltico, 20 años en caso de la pavimentación de hormigón
- método de diseño (Normativa aplicable) : AASHTO GUIDE FOR Design of Pavement Structures (AASHTO 1993)、"Análisis de teoría elástica de multi-estrato" (Japan Road Association)

4. Perfil normal vial

- En la mayor parte del trayecto de la Carretera

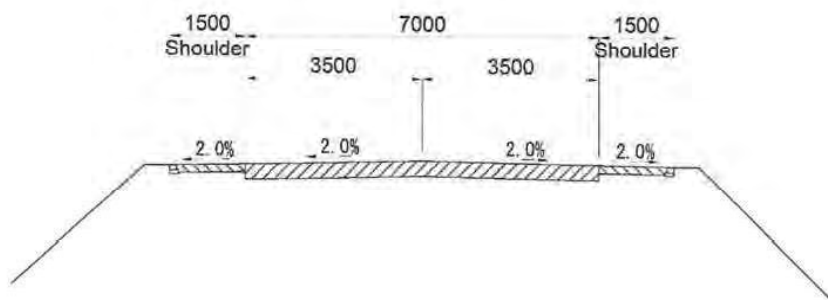


Figura 4-1 Perfil transversal normal vial en la mayor parte del trayecto de la Carretera

- Áreas habitadas

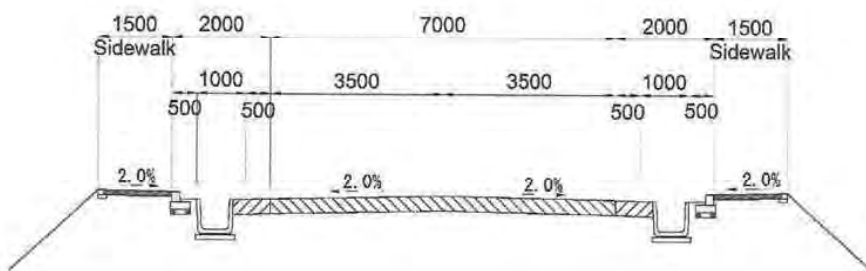


Figura 4-2 Perfil transversal normal vial en las áreas habitadas

5. Mejoramiento de canal de drenaje

Como se menciona en la Figura 5-1, las instalaciones de drenaje existentes ubicadas desde Okinawa 1 hasta el Puente, en un tramo de unos 9.7 km de distancia, están conectadas con la hidrovía existente, pasando por las alcantarillas ubicadas a lo largo de la Ruta 10.

Las instalaciones de drenaje desde dicho puente hasta Okinawa 3, en un tramo de unos 25.4 km de distancia, están conectadas con el río Pailón sobre el cual está construido dicho puente.

Para mantener la estructura vial en buen estado, se necesitará elevar la cota de la rasante del camino en tramos donde se inunda la carretera. Por lo tanto, se

Handwritten signature or initials.

instalarán alcantarillas transversales para no cambiar el drenaje de agua en momento de inundaciones.

El plan definitivo se definirá en consideración al resultado del estudio de campo que se llevará a cabo en el próximo mes de diciembre, en la época de lluvias.



Figura 5-1 Ríos · hidroviás en los alrededores de la carretera Okinawa y tramos inundados de dicha carretera

6. Mejoramiento de intersecciones y caminos de acceso

Abajo se mencionan propuestas para mejorar cada intersección.

· Intersección de Okinawa 1


La Misión mantuvo conversaciones con ABC sobre el alcance de obras ( Ver el Anexo-1)



Figura 6-1 Propuesta para el mejoramiento de la Intersección de Okinawa 1

YTT

• Intersección de Okinawa 2

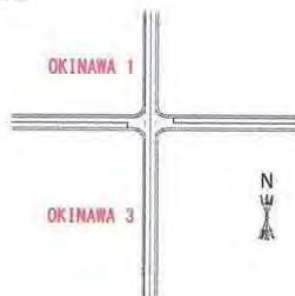

Figur6-2 Propuesta para el mejoramiento de la Intersección Okinawa2

• Intersección de Okinawa2 y 3~Zona Franca

Con respecto al alcance de obras, la Misión mantuvo conversaciones con ingenieros encargados de diseño de SEDCAM. (Ver el Anexo-2)

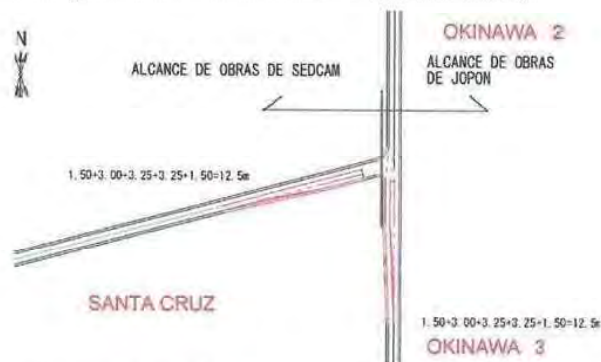


Figura 6-3 Propuesta para el mejoramiento de la Intersección de Okinawa2,3~ Zona Franca

1778

• Intersección de San Miguel

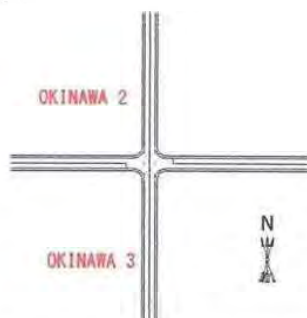


Figura 6-4 Propuesta para el mejoramiento de la Intersección de San Miguel

• Intersección de Okinawa 3

Con respecto al alcance de obras, la Misión mantuvo conversaciones con ingenieros encargados de diseño de SEDCAM. (Ver el Anexo-3)



Figura 6-5 Propuesta para el mejoramiento de la Intersección de Okinawa 3

1773



7. Reconstrucción del puente

7-1 Plano de ubicación del puente a ser reconstruido

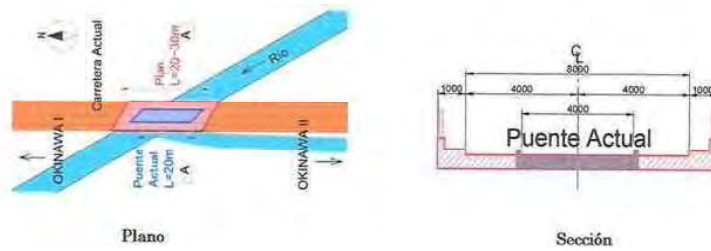


Figura 7-1 Plano de ubicación del puente a ser reconstruido

7-2 Tipo de puente y longitud de luz

Tabla 7-1 Examen comparativo de tipo de puente

Número de luces	2 luces		1 luz	
Tipo de puente	Puente de viga I Hormigón Armado	Puente de viga I Pretensado	Puente mixto	
Sección				
Longitud de puente 30m	2@15=30 m	1@30=30 m	1@30=30 m	
Facilidad de ejecución	Las obras serán complicadas debido a que se necesitará estancar el río para la construcción de pilas.	Será facil hacer obras por no tener necesidad de estancar el río.	Será facil hacer obras por no tener necesidad de estancar el río.	
Mantenimiento	Se necesitará poco mantenimiento por ser de hormigón.	Se necesitará poco mantenimiento por ser pretensado.	Se requiere con frecuencia el mantenimiento por ser de acero.	
Plazo de obras	Se necesitará bastante tiempo para construir pilas.	No se necesitan pilas. Es posible ejecutar obras en corto tiempo .	No se necesitan pilas. Es posible ejecutar obras en corto tiempo .Sin embargo, se necesita tiempo de transporte debido a ser fabricadas en algún tercer país.	
Proporción de costo de construcción	1.0	1.0	1.4	
prioridad	2	1(recomendable)	3	

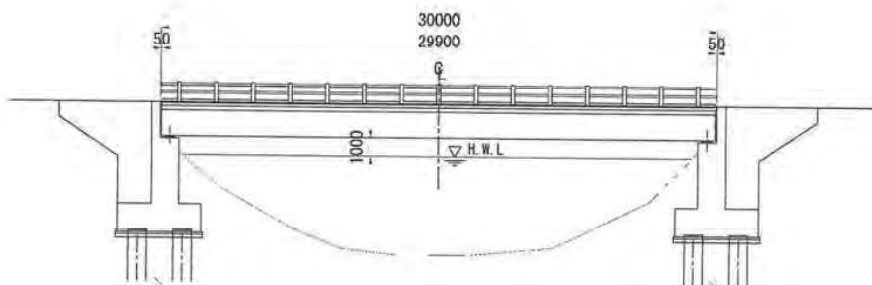


Figura 7-2 Elevación lateral y transversal del puente

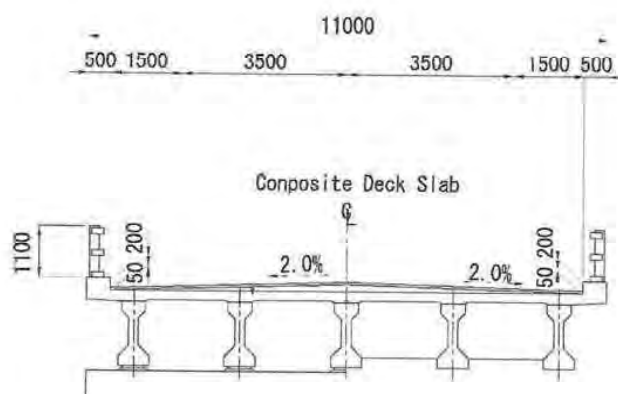


Figura 7-3 Sección transversal del puente

### 7-3 Normativa de diseño de puente

Método de diseño(base aplicable): Se aplicará la normativa del Japón.

Carga viva: carga viva B (equivalente a 125% de HS20-44)

Carga en momento de sismo:

Carga viva en momento de sismo : Se utilizará el coeficiente sísmico diseñada  $K_h=0.1$ .

### 8. Medidas de seguridad

Se asegurará la seguridad de peatones en las áreas habitadas debido a que se mejore la carretera y eleve la velocidad de vehículos. Como se menciona en la Figura. 4-2, se asegurará la seguridad de peatones a través de elevarse el nivel de superficie de



carretera e instalarse cunetas a ambos lados de la carretera. Además, en las intersecciones se examinará a instalar pasos peatonales e instalarán marcas viales como “paso peatonal”, “máxima velocidad 20km/h” y “sonorizadores”.


9. Responsabilidades a ser asumidas por la parte boliviana

9-1 Consideraciones socio-ambientales

- Obtención de licencia ambiental de EIA

La parte boliviana quedó acordado con el siguiente cronograma de obtención de licencia ambiental de EIA para la Carretera Okinawa I~III.

Tabla 9-1 Cronograma de obtención de la licencia ambiental de EIA

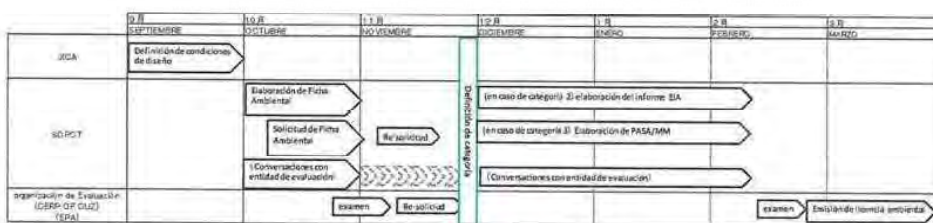

※1 : Exami previuso presentar la ficha ambiental entre finales de octubre y principios de noviembre  
 ※2 : En caso de no haber re-solicitud, se adelantará la fecha de elaboración del informe EIA.  
 ※3 : PAEA= plan de seguimiento ambiental  
 MNM (PAM)= Plan de mitigación ambiental

- Plan de monitoreo ambiental

La parte boliviana quedó acordado con el siguiente plan de monitoreo ambiental.

Tabla 9-2 Propuesta del plan de monitoreo ambiental

Items ambientales	Items	Lugar	Frecuencia arriba : antes de obras medio : durante obras abajo : después de obras	Entidad responsable
			[antes] [durante] [después]	
aire	PM <sub>10</sub> , PM <sub>2.5</sub> , CO, O <sub>3</sub> , NOx, SOx, polvo, olor, Dirección de viento, velocidad de viento	Punto inicial (zona urbana) ; punto intermedio (entre Okinawa1 y 2) ; punto intermedio (okinawa2) ; punto intermedio (okinawa2~3) ; punto final (zona urbana)	1 vez/antes de EIA) 1 vez/cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOC
ruidos + vibraciones	Nivel de ruidos + vibraciones	Zona habitada (okinawa1,2,3, san miguel) ; área escolar(okinawa1) ; área agrícola (entre Okinawa1 y2, entre 2 y 3)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOC
Calidad de agua	pH, SS, COD, DO, oxígeno, conductividad, turbiedad, olor, color	pozo(uzn o abn) cerca de la carretera)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOC
biosfera	Flora y fauna	Okinawa1-3 (dentro del Desecho de vía)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOC

Handwritten signature or initials.

• Con respecto al monitoreo ambiental previo

La parte boliviana, de acuerdo con el plan de monitoreo ambiental previo arriba descrito, acordó con la ejecución de monitoreo ambiental previo como parte de responsabilidades a ser asumidas por el país receptor del Proyecto. La parte boliviana informará a la parte japonesa el resultado de dicho monitoreo.

• Obtención de permiso de desmonte y poda de árboles

La parte boliviana acordó con la obtención de permiso de desmonte y corte de árboles que hay entre Okinawa 1 ~ Okinawa 3, de acuerdo con el cronograma de desmonte y corte de árboles.

Tabla 9-3 Cronograma de obtención de permiso de desmonte y corte de árboles.



(B) PASA=plan de seguimiento ambiental  
MMI(PMM)=plan de mitigación ambiental

9-2 Traslado de instalaciones (tuberías de agua, postes de energía eléctrica, etc.) y de casetas de vigilancia

La parte boliviana, con base al plano esquemático de mejoramiento de dicha Carretera y plano de ubicación de instalaciones como tuberías de agua, postes de energía eléctrica y casetas de vigilancia que se adjuntarán al Borrador del Informe Final, que se presentará en marzo de 2015, terminará de desplazar las instalaciones necesarias antes de la convocatoria de precalificación de constructoras (posiblemente en octubre de 2015).

9-3 Disposición del campamento provisional para obras y de botadero de residuos

La parte boliviana, consultando con los consultores y constructoras a la hora del inicio de obras, dispondrá de un patio o área provisional para colocar materiales y equipos, construir plantas y campamento. La extensión de dicho patio será de varias hectáreas a definirse. Además, asegurará un botadero de residuos sólidos cerca del sitio de obras. La Alcaldía de Okinawa asegurará un

177


patio provisional (1 hectárea) para obras cerca de Okinawa 2. Y, está de acuerdo con el uso de botadero ubicado a unos 14 km al norte de Okinawa 1.

**9-4 Impulso de mejoramiento de los caminos en sus contornos**


La parte boliviana, con el fin de lograr más eficacia del mejoramiento de la Carretera Okinawa, impulsará a distintas ejecutoras, del Proyecto de pavimentación de la carretera entre Santa Cruz y Okinawa3 (Proyecto de la Gobernación de Santa Cruz y de la Alcaldía de Santa Cruz de la Sierra), Mejoramiento de la Ruta 10 entre Okinawa1~Los Troncos (Proyecto de ABC), y Construcción del Puente Banegas (Proyecto de ABC), para que terminen dichos Proyectos antes de finales del año 2017.




Anexo-1 Conversaciones sobre la interseccion Okinawa1

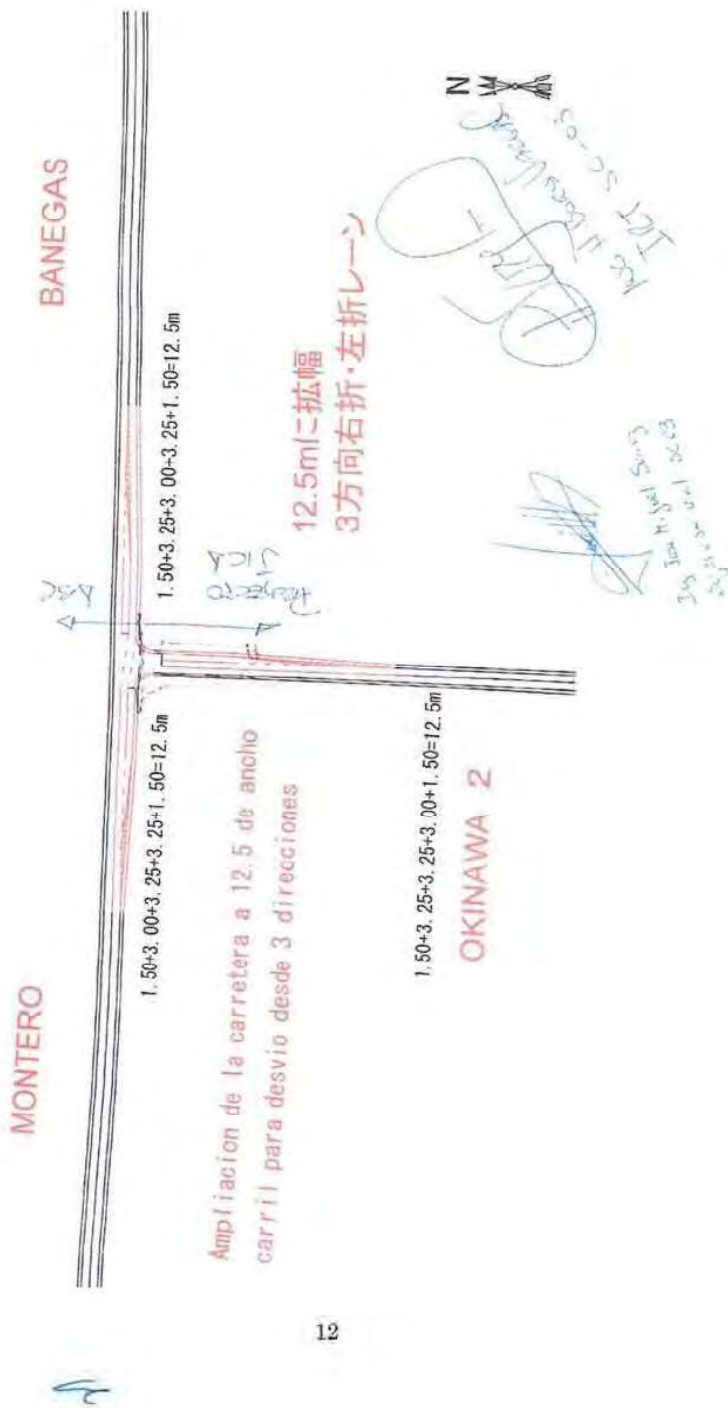

Anexo-2 Conversacion sobre la interseccion Zona Franca~Okinawa2,3

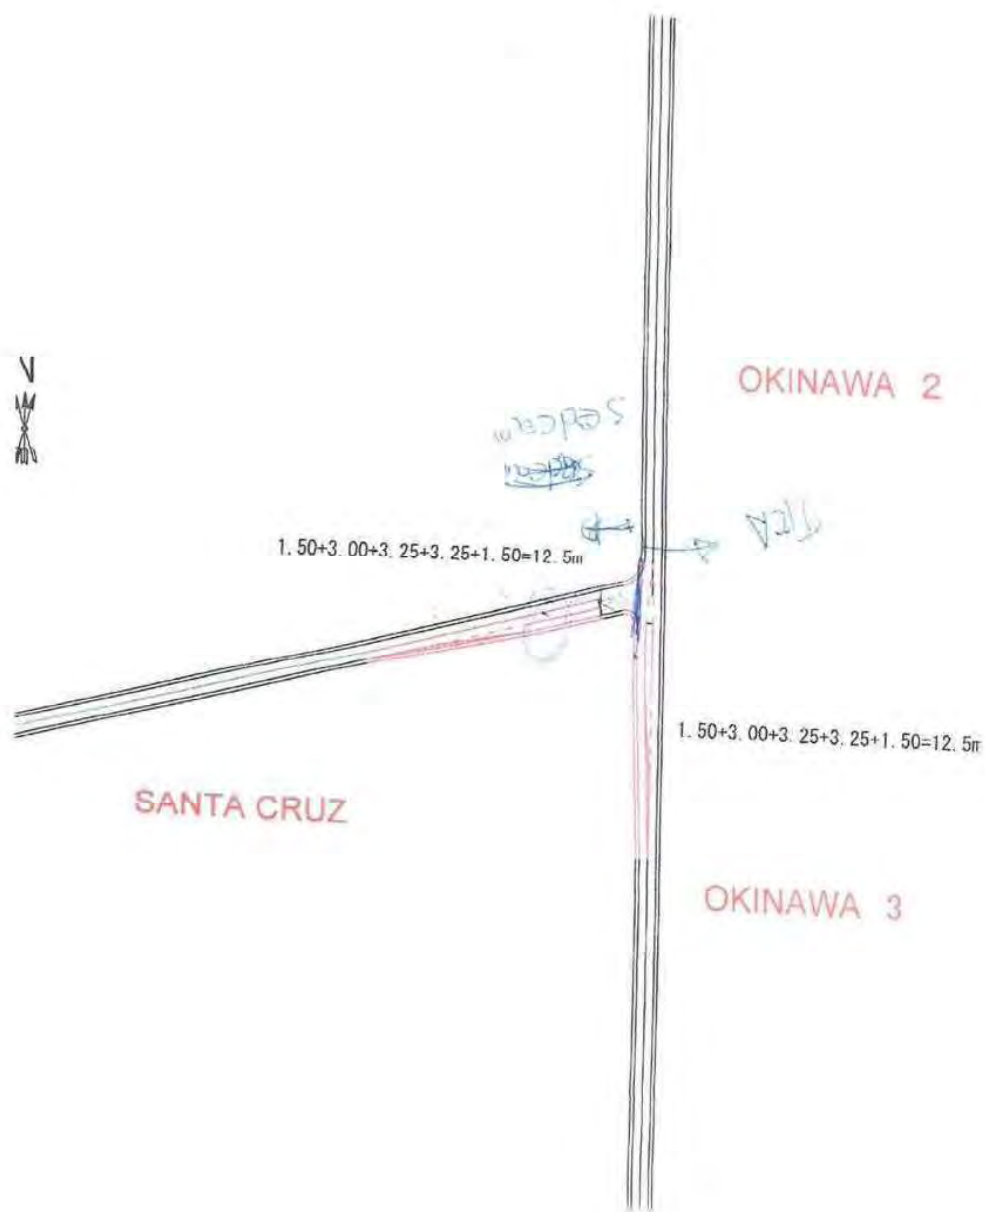

Anexo-3 Conversacion sobre la interseccion de Okinawa3






**Estudio Preparatorio para el Proyecto de Pavimentación de  
la Carretera Okinawa I,II,III**

**Memorando Técnico**


La Misión de JICA mantuvo conversaciones técnicas con la Secretaría de Obras Públicas y Ordenamiento Territorial del Gobierno Autónomo Departamental de Santa Cruz (SOPOT) y confirmó los ítems descritos en el Documento Adjunto. Con respecto a cada uno de dichos ítems, se definirá después de hacer análisis y mantener conversaciones con la Cancillería del Japón y JICA.

Santa Cruz, 18 de mayo de 2016



---

Ing. Carlos Hugo SOSA A.  
Secretario de Obras Públicas y  
Ordenamiento Territorial del  
Gobierno Autónomo Departamental  
de Santa Cruz



---

Ing. Tomohiko NAKAMURA  
Jefe de los consultores  
Misión del Estudio Preparatorio de  
JICA

## Documento Adjunto

### 1. Ítems acordados en el presente Memorando Técnico

Los ítems acordados en el presente Memorando Técnico, dentro de los lineamientos del análisis de la estructura de pavimentación de las carreteras y las responsabilidades a asumirse por la parte boliviana: los trámites para conseguir Licencia Ambiental y el permiso de ABT para corte y desmonte de árboles.

Dentro del contenido del Memorando Técnico, firmado el día 29 de agosto de 2014, los ítems son vigentes salvo el contenido renovado en el presente Memorando Técnico.

### 2. Líneamientos para el análisis de la estructura de pavimentación de carretera

La estructura de carretera se compondrá de capa de hormigón que pueda resistir a la carga de tráfico diseñada, subbase y plataforma (o subrasante) a construirse. Sin embargo, se analizarán distintas opciones del espesor y se propondrá una opción económica. También, se analizará la pavimentación asfáltica y se propondrá una opción económica en comparación con la pavimentación de hormigón.

### 3. Responsabilidades a asumirse por la parte boliviana

- Obtención de la Licencia Ambiental y el permiso de tala y desmonte

Debido a que se ha definido la categoría "2" para la Carretera Okinawa1~Okinawa3, la parte boliviana elaborará un informe del EEIA y plan de tala y desmonte de árboles, y obtendrá la Licencia Ambiental antes del día 31 de mayo de 2017.

Documento Anexo : Memorando Técnico firmado el día 29 de agosto de 2014

**Estudio Preparatorio para el Proyecto de Pavimentación de  
la Carretera Okinawa I,II,III**

**Memorando Técnico**

La Misión de JICA mantuvo conversaciones técnicas con distintas autoridades de Bolivia tales como la Secretaría de Obras Públicas y Ordenamiento Territorial del Gobierno Autónomo Departamental de Santa Cruz (SOPOT), Servicio De Caminos (SEDCAM), Administradora Boliviana de Caminos (ABC), la Alcaldía de Santa Cruz de la Sierra y la Alcaldía de Okinawa, y confirmó los ítems descritos en el Documento Adjunto. Con respecto a cada uno de dichos ítems, se definirá después de hacer análisis de los resultados del Estudio Preparatorio y mantener conversaciones con la Cancillería del Japón y JICA.

Santa Cruz, 29 de agosto de 2014



Ing. Carlos Hugo SOSA ARREAZA  
Secretario de Obras Públicas y  
Ordenamiento Territorial del  
Gobierno Autónomo Departamental  
de Santa Cruz



Ing. Tomohiko NAKAMURA  
Jefe de los consultores  
Misión del Estudio Preparatorio de  
JICA

**Documento Adjunto**

**1. Contenido del Proyecto**

- Pavimentación de la Carretera Okinawa (Tramo de unos 35 km de distancia desde la Intersección de Okinawa 1 hasta la de Okinawa 3) .
- Mejoramiento de Cunetas, Alcantarillas transversales y alcantarillas a las cuales fluye finalmente el agua de dichas cunetas de la mencionada Carretera
- Mejoramiento de las aceras de las comunidades habitadas, ubicadas sobre dicha Carretera (Okinawa2, San Miguel, alrededores de la Intersección de Okinawa 3)
- Señalizaciones horizontales y verticales de todo el trayecto de dicha Carretera (línea eje, etc.)
- Mejoramiento de 5 intersecciones sobre dicha Carretera (Okinawa1, Okinawa2, San Miguel, Zona Franca~Okinawa2,3, Okinawa3)
- Mejoramiento de otras intersecciones y de rampa de acceso desde la entrada de construcciones hasta dicha Carretera
- Reconstrucción del Puente

**2. Normativa de estructura geométrica de camino**

- Normativa de AASHTO
- Velocidad de diseño : 80km/hora
- Pendiente(bombeo) transversal vial estándar : 2 %

**3. Normativa de diseño estructural para pavimentación de camino**

- tipo de pavimentación : pavimentación de concreto asfáltico o de hormigón
- vida útil diseñada : 10 años en caso de la pavimentación de concreto asfáltico, 20 años en caso de la pavimentación de hormigón
- método de diseño (Normativa aplicable) : AASHTO GUIDE FOR Design of Pavement Structures (AASHTO 1993) , "Análisis de teoría elástica de multi-estrato" (Japan Road Association)

1773

4. Perfil normal vial

- En la mayor parte del trayecto de la Carretera

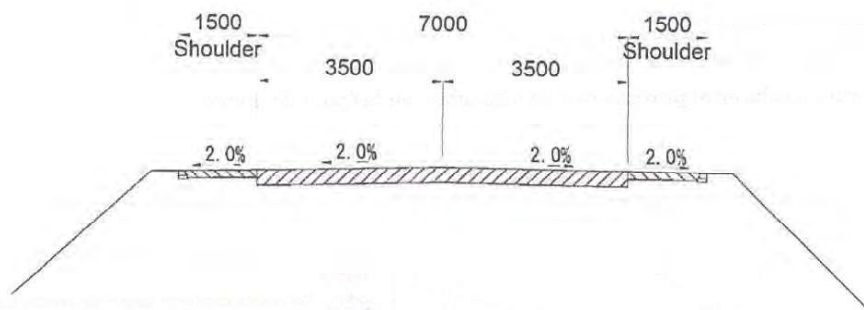


Figura 4-1 Perfil transversal normal vial en la mayor parte del trayecto de la Carretera

- Áreas habitadas

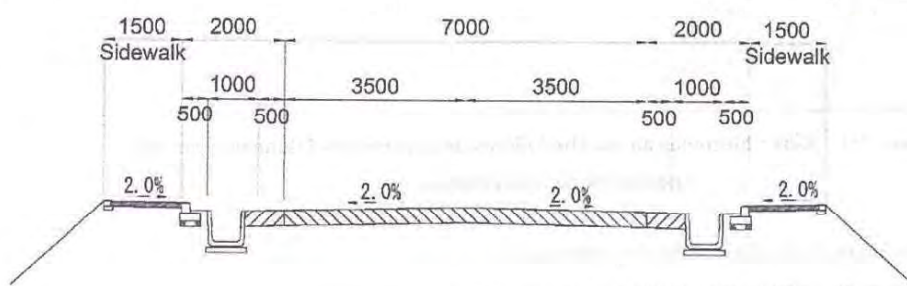


Figura 4-2 Perfil transversal normal vial en las áreas habitadas

5. Mejoramiento de canal de drenaje

Como se menciona en la Figura 5-1, las instalaciones de drenaje existentes ubicadas desde Okinawa 1 hasta el Puente, en un tramo de unos 9.7 km de distancia, están conectadas con la hidrovía existente, pasando por las alcantarillas ubicadas a lo largo de la Ruta 10.

Las instalaciones de drenaje desde dicho puente hasta Okinawa 3, en un tramo de unos 25.4 km de distancia, están conectadas con el río Pailón sobre el cual está construido dicho puente.

Para mantener la estructura vial en buen estado, se necesitará elevar la cota de la rasante del camino en tramos donde se inunda la carretera. Por lo tanto, se

VHJ

instalarán alcantarillas transversales para no cambiar el drenaje de agua en momento de inundaciones.

El plan definitivo se definirá en consideración al resultado del estudio de campo que se llevará a cabo en el próximo mes de diciembre, en la época de lluvias.



Figura 5-1 Ríos • hidrovoías en los alrededores de la carretera Okinawa y tramos inundados de dicha carretera

6. Mejoramiento de intersecciones y caminos de acceso

Abajo se mencionan propuestas para mejorar cada intersección.

- Intersección de Okinawa 1

La Misión mantuvo conversaciones con ABC sobre el alcance de obras ( Ver el Anexo-1)



Figura 6-1 Propuesta para el mejoramiento de la Intersección de Okinawa 1

- Intersección de Okinawa 2



Figur6-2 Propuesta para el mejoramiento de la Intersección Okinawa2

- Intersección de Okinawa2 y 3~Zona Franca

Con respecto al alcance de obras, la Misión mantuvo conversaciones con ingenieros encargados de diseño de SEDCAM. (Ver el Anexo-2)

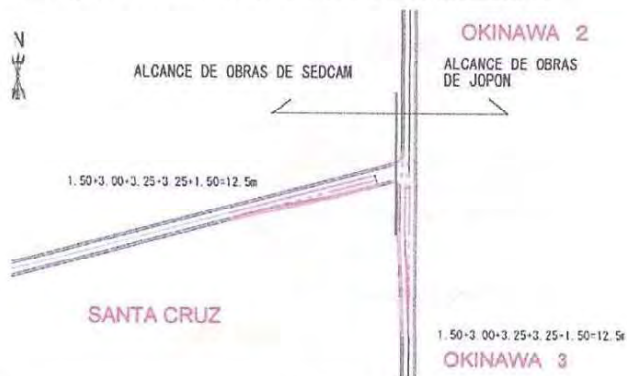


Figura 6-3 Propuesta para el mejoramiento de la Intersección de Okinawa2,3~ Zona Franca

1771

• Intersección de San Miguel

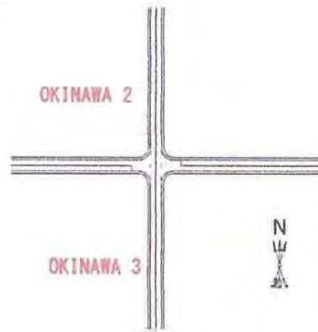


Figura 6-4 Propuesta para el mejoramiento de la Intersección de San Miguel

• Intersección de Okinawa 3

Con respecto al alcance de obras, la Misión mantuvo conversaciones con ingenieros encargados de diseño de SEDCAM. (Ver el Anexo-3)



Figura 6-5 Propuesta para el mejoramiento de la Intersección de Okinawa 3

4

1773



7. Reconstrucción del puente

7-1 Plano de ubicación del puente a ser reconstruido

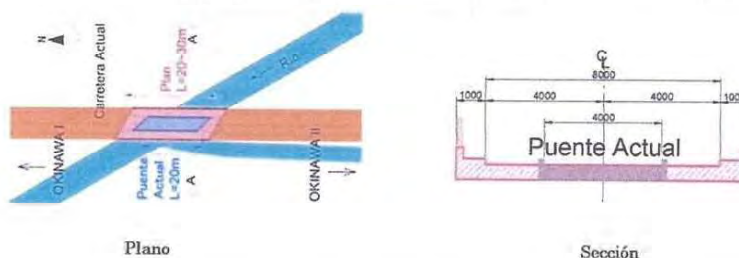


Figura 7-1 Plano de ubicación del puente a ser reconstruido

7-2 Tipo de puente y longitud de luz

Tabla 7-1 Examen comparativo de tipo de puente

Número de luces	2 luces	1 luz	
Tipo de puente	Puente de viga I Hormigón Armado	Puente de viga I Pretensado	Puente mixto
Sección			
Longitud de puente 30m	2@15=30 m	1@30=30 m	1@30=30 m
Facilidad de ejecución	Las obras serán complicadas debido a que se necesitará estancar el río para la construcción de pilas.	Será facil hacer obras por no tener necesidad de estancar el río.	Será facil hacer obras por no tener necesidad de estancar el río.
Mantenimiento	Se necesitará poco mantenimiento por ser de hormigón.	Se necesitará poco mantenimiento por ser pretensado.	Se requiere con frecuencia el mantenimiento por ser de acero.
Plazo de obras	Se necesitará bastante tiempo para construir pilas.	No se necesitan pilas. Es posible ejecutar obras en corto tiempo .	No se necesitan pilas. Es posible ejecutar obras en corto tiempo .Sin embargo, se necesita tiempo de transporte debido a ser fabricadas en algún tercer país.
Proporción de costo de construcción	1.0	1.0	1.4
prioridad	2	1(recomendable)	3

Handwritten mark resembling a stylized 'A' or 'B'.

Handwritten signature or initials.

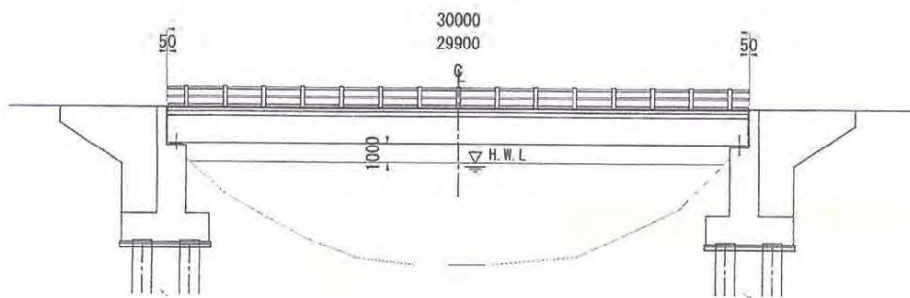


Figura 7-2 Elevación lateral y transversal del puente

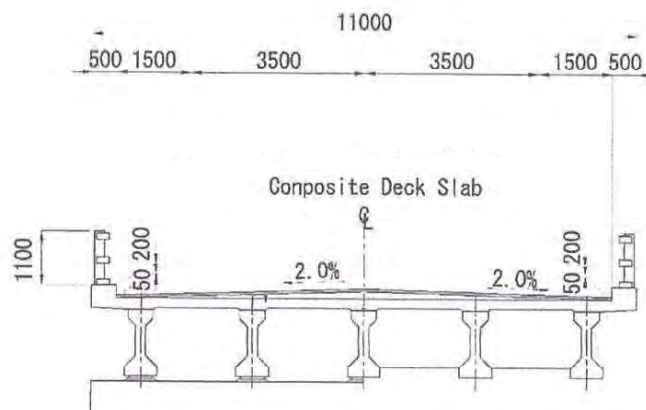


Figura 7-3 Sección transversal del puente

**7-3 Normativa de diseño de puente**

Método de diseño(base aplicable): Se aplicará la normativa del Japón.

Carga viva: carga viva B (equivalente a 125% de HS20-44)

Carga en momento de sismo:

Carga viva en momento de sismo : Se utilizará el coeficiente sísmico diseñada  $K_h=0.1$ .

**8. Medidas de seguridad**

Se asegurará la seguridad de peatones en las áreas habitadas debido a que se mejore la carretera y eleve la velocidad de vehículos. Como se menciona en la Figura. 4-2, se asegurará la seguridad de peatones a través de elevarse el nivel de superficie de



Handwritten signature or initials.

carretera e instalarse cunetas a ambos lados de la carretera. Además, en las intersecciones se examinará a instalar pasos peatonales e instalarán marcas viales como "paso peatonal", "máxima velocidad 20km/h" y "sonorizadores".


9. Responsabilidades a ser asumidas por la parte boliviana

9-1 Consideraciones socio-ambientales

- Obtención de licencia ambiental de EIA

La parte boliviana quedó acordado con el siguiente cronograma de obtención de licencia ambiental de EIA para la Carretera Okinawa I~III.

Tabla 9-1 Cronograma de obtención de la licencia ambiental de EIA

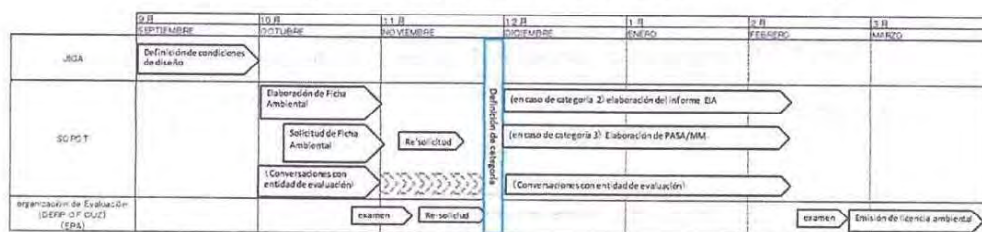

■ 1 : Está previsto presentar la ficha ambiental antes finales de octubre y primeros de noviembre  
 ■ 2 : En caso de no haber re-solicitud se adelanta la fecha de elaboración del informe EA  
 ■ 3 : PASA = plan de seguimiento ambiental  
 ■ MM(PMA) = Plan de mitigación ambiental

- Plan de monitoreo ambiental

La parte boliviana quedó acordado con el siguiente plan de monitoreo ambiental.

Tabla 9-2 Propuesta del plan de monitoreo ambiental

Items ambientales	Items	Lugar	Frecuencia arriba : antes de obras ; durante obras ; abajo : después de obras	Entidad responsable
			[antes] [durante] [después]	
aire	PM <sub>10</sub> , PM <sub>2.5</sub> , CO <sub>2</sub> , NOx, SOx, polvo, olor Dirección de viento, velocidad de viento	Punto inicial (área urbana) , punto intermedio (entre Okinawa1 y 2) , punto intermedio (okinawa2) - punto intermedio (okinawa2~3 M) - punto final (área urbana)	1 vez(antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOT
ruidos + vibraciones	Nivel de ruidos + vibraciones	Zona habitada (okinawa1,2,3 km miguel) , área escolar(okinawa2), área agrícola (entre Okinawa 1y2, entre 2 y 3)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOT
Calidad de agua	pH, SS, COD, DO, acetim, conductividad, turbiedad, olor, color	pozo(uno o dos + cerca de la carretera)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOT
biosfera	Fauna y flora	Okinawa1-3 (dentro del Derecho de vía)	1 vez antes de EIA) 1 vez /cada 3 meses 1 vez/cada 6 meses	Constructora o SOPOT


• Con respecto al monitoreo ambiental previo

La parte boliviana, de acuerdo con el plan de monitoreo ambiental previo arriba descrito, acordó con la ejecución de monitoreo ambiental previo como parte de responsabilidades a ser asumidas por el país receptor del Proyecto. La parte boliviana informará a la parte japonesa el resultado de dicho monitoreo.

• Obtención de permiso de desmonte y poda de árboles

La parte boliviana acordó con la obtención de permiso de desmonte y corte de árboles que hay entre Okinawa 1 ~ Okinawa 3, de acuerdo con el cronograma de desmonte y corte de árboles.

**Tabla 9-3 Cronograma de obtención de permiso de desmonte y corte de árboles.**

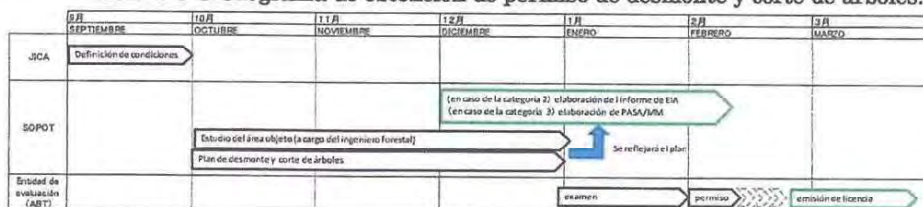

※1 PASA=plan de seguimiento ambiental  
MM (PMM) =plan de mitigación ambiental

**9-2 Traslado de instalaciones (tuberías de agua, postes de energía eléctrica, etc.) y de casetas de vigilancia**

La parte boliviana, con base al plano esquemático de mejoramiento de dicha Carretera y plano de ubicación de instalaciones como tuberías de agua, postes de energía eléctrica y casetas de vigilancia que se adjuntarán al Borrador del Informe Final, que se presentará en marzo de 2015, terminará de desplazar las instalaciones necesarias antes de la convocatoria de precalificación de constructoras (posiblemente en octubre de 2015).

**9-3 Disposición del campamento provisional para obras y de botadero de residuos**

La parte boliviana, consultando con los consultores y constructoras a la hora del inicio de obras, dispondrá de un patio o área provisional para colocar materiales y equipos, construir plantas y campamento. La extensión de dicho patio será de varias hectáreas a definirse. Además, asegurará un botadero de residuos sólidos cerca del sitio de obras. La Alcaldía de Okinawa asegurará un

patio provisional (1 hectárea) para obras cerca de Okinawa 2. Y, está de acuerdo con el uso de botadero ubicado a unos 14 km al norte de Okinawa 1.

**9-4 Impulso de mejoramiento de los caminos en sus contornos**


La parte boliviana, con el fin de lograr más eficacia del mejoramiento de la Carretera Okinawa, impulsará a distintas ejecutoras, del Proyecto de pavimentación de la carretera entre Santa Cruz y Okinawa3 (Proyecto de la Gobernación de Santa Cruz y de la Alcaldía de Santa Cruz de la Sierra), Mejoramiento de la Ruta 10 entre Okinawa1~Los Troncos (Proyecto de ABC), y Construcción del Puente Banegas (Proyecto de ABC), para que terminen dichos Proyectos antes de finales del año 2017.

→


111



Anexo-2 Conversacion sobre la interseccion Zona Franca~Okinawa2,3

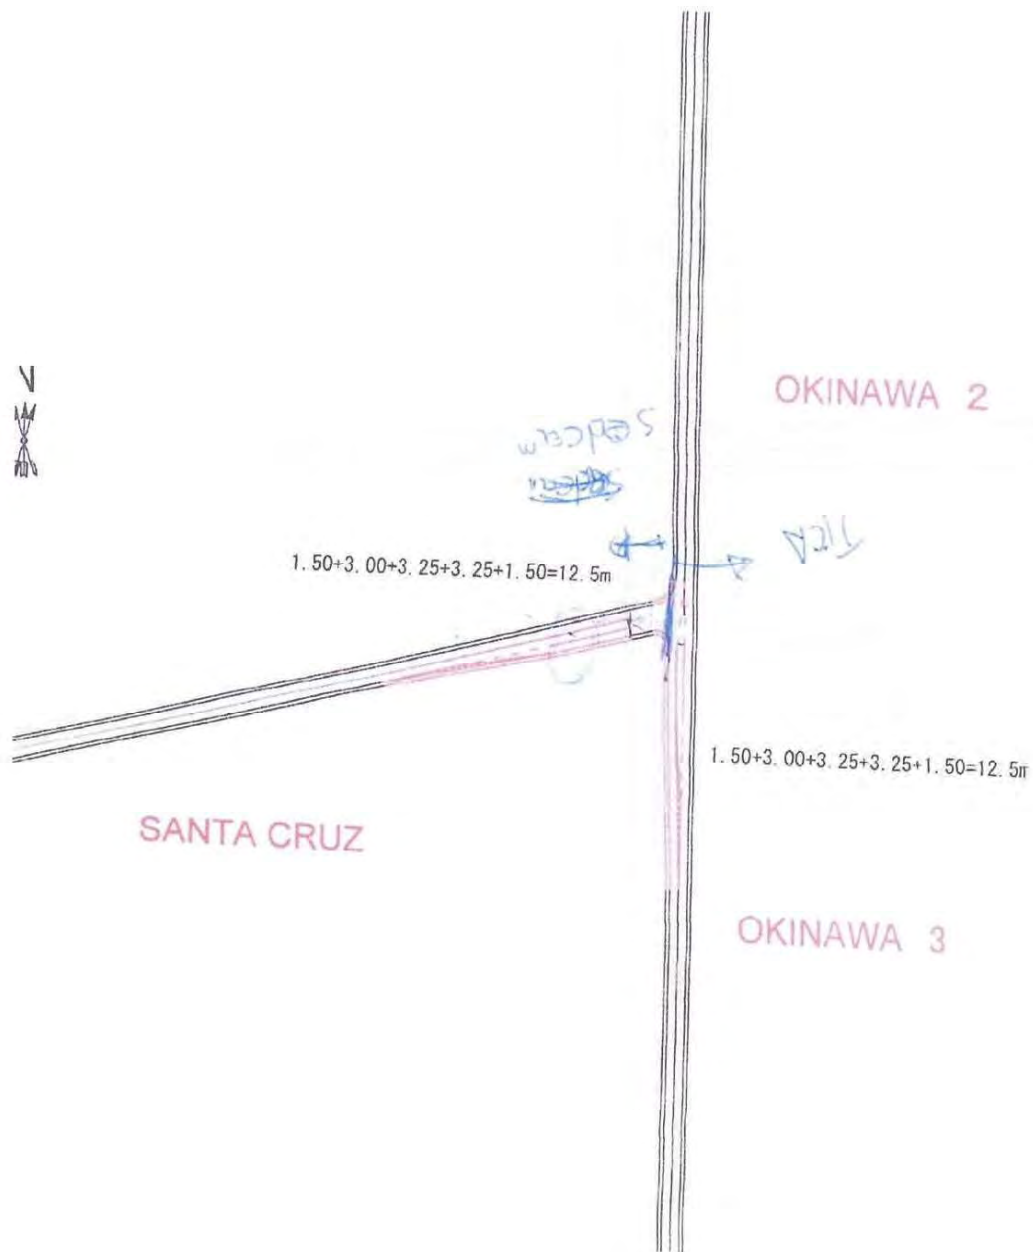

Anexo-3 Conversacion sobre la interseccion de Okinawa3

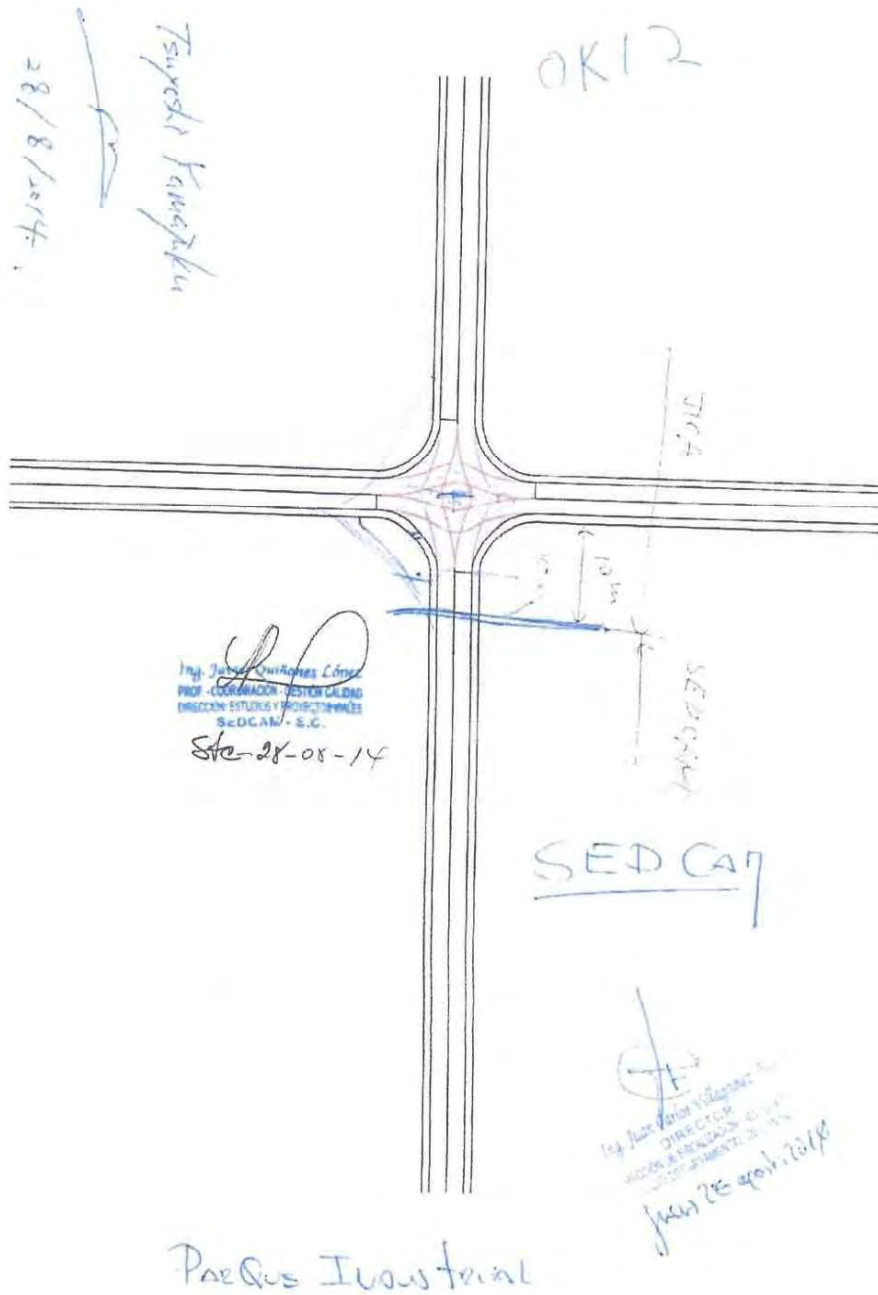



## 6. 環境社会配慮【EI (EIA) 裁定書】

EI 裁定書 (DIA) (仮訳)

070202/06/DIA/No7059/18.

国家環境管轄機関は証明する：

環境法 1333 号を遵守し、且つ、環境・生物の多様性、環境予防・管理規定 (RPCA) の評価手続きに基づき、カルロス・ウーゴ・ソサ・アレアサが代理人となるサンタクルス県自治政府は、環境申請書 7059/15 及び「オキナワ I-II-III 道路建設」の EIA-解析調査を提出した。同プロジェクトはサンタクルス県ワルネス郡オキナワ市をサイトとしている。環境の視点から判断して最低限の必要条件を満たしており、よって同プロジェクトの実施を許可する。

EI 裁定書 (DIA) は、環境予防・管理規定に定めている点検・監視・管理手続きを実施するために、承認済み EIA 調査、特に、防止・緩和プログラム (PPM) 及び適用・環境フォローアップ計画 (PASA) と共に構成されている。

上記の計画及び EIA 調査に記載されていることを確実に遂行しない場合には、上記法律 1333 号及びその規定 (大統領令 24176) 及び関連法規に基づいて制裁が適用される。

しかるべき目的のために認証する。

環境・気候変動局長

環境・生物の多様性・気候変動・森林管理

及び開発次官室

マリア・クリスチーナ・アレジャーノ・デ・フランク


環境・水資源省次官

環境・生物の多様性・気候変動・森林管理

環境・水資源省

シンサ・ビビアナ・シルバ・マツラナ

ラパス、2018年1月29日

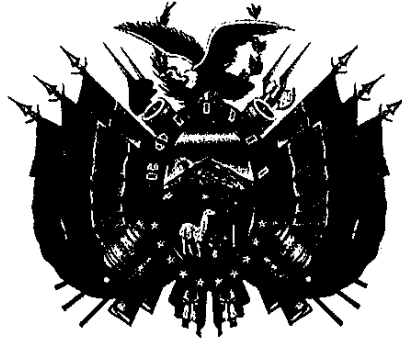

**DECLARATORIA DE IMPACTO AMBIENTAL (DIA)**  
**070202/06/DIA/N° 7059/18.**

**LA AUTORIDAD AMBIENTAL COMPETENTE NACIONAL**

**CERTIFICA:**

Que, dando cumplimiento al artículo 25° de la Ley N° 1333 del Medio Ambiente, y con ajustes al Procedimiento de Evaluación de Impacto Ambiental del Reglamento de Prevención y Control Ambiental (RPCA), el **Gobierno Autónomo Departamental de Santa Cruz**, legalmente representado por el **Ing. Carlos Hugo Sosa Arreaza**, ha presentado la Ficha Ambiental N° 7059/15 y el correspondiente Estudio de Evaluación de Impacto Ambiental – Analítico Específico del proyecto **“CONSTRUCCIÓN CARRETERA OKINAWA I - II - III”**, el mismo se encuentra ubicado en el municipio de Okinawa I, provincia Warnes del departamento de Santa Cruz, habiéndose cumplido con los requisitos mínimos desde el punto de vista ambiental, por lo cual queda autorizada la implementación del proyecto.

La presente Declaratoria de Impacto Ambiental (DIA) se constituye conjuntamente el Estudio de Evaluación de Impacto Ambiental aprobado, en particular con el Programa de Prevención y Mitigación (PPM) y el Plan de Aplicación y Seguimiento Ambiental (PASA), en referencia para la realización de los Procedimientos de inspección, vigilancia y control, establecidos en el Reglamento de Prevención y Control Ambiental.

En caso de no darse estricto cumplimiento a lo previsto en los planes anteriormente mencionados y el Estudio de Evaluación de Impacto Ambiental, se aplicarán las sanciones previstas en la Ley N° 1333 sus Reglamentos (Decreto Supremo 24176) y demás disposiciones conexas.

Es cuanto certifico para los fines consiguientes.

**Lic. María Cristina Arellano de Frank**  
DIRECTORA GENERAL DE MEDIO  
AMBIENTE Y CAMBIOS CLIMATICOS  
VMABCCGDF - MMAY A

**Cynthia Viviana Silva Maturana**  
VICEMINISTRA DE MEDIO AMBIENTE,  
BIODIVERSIDAD, CAMBIOS CLIMATICOS Y  
DE GESTIÓN Y DESARROLLO FORESTAL  
MMAY A

La Paz, 29 de enero de 2018.

## 7. 収集資料リスト


### 収集資料リスト

調査名:ボリビア国\_オキナワ道路整備計画準備調査

番号	資料の名称	形態 図書・ビデオ 地図・写真等	オリジナル/ コピー	発行機関	発行年
1	気象観測データ(2007年～2014年)	EXCEL	コピー	ボリビア農業技術センター (Centro Tecnológico Agropecuario en Bolivia (CETABOL))	-
2	PACAY 及び PAILAS における河川観測データ (水位・気温) (2010年～2014年)	EXCEL	コピー	SEARPI (Servicio de Encauzamiento de Aguas y Regularización del Río Pirai)	2014年
3	オキナワ移住地 I における降雨データ (1977年～2013年)	EXCEL	コピー	SENAMHI (Servicio Nacional de Meteorología e Hidrología)	2014年
4	BALANCE HIDRICO SUPERFICIAL DE BOLIVIA	PDF	コピー	環境・水資源省	1992年
5	INSTITUTO NACIONAL DE ESTADÍSTICA 2011	図書	コピー	国立統計研究所 (INSTITUTO NACIONAL DE ESTADÍSTICA)	2012年
6	環境法 1333 号	PDF	コピー	ボリビア国	1992年
7	LIBRO ROJO FLORA AMENAZADA	PDF	コピー	環境・水資源省	2012年
8	LIBROJO COMPLETO	PDF	コピー	環境・水資源省	2009年
9	森林法	PDF	コピー	ボリビア国	2001年
10	サンタクルス県道路地図	PDF	コピー	サンタクルス県	2017年 他
11	NUEVOS MANUALES ABC	PDF	コピー	ABC	2008年

## 8. 技術資料

### 8-1 SPT 試験実施位置図

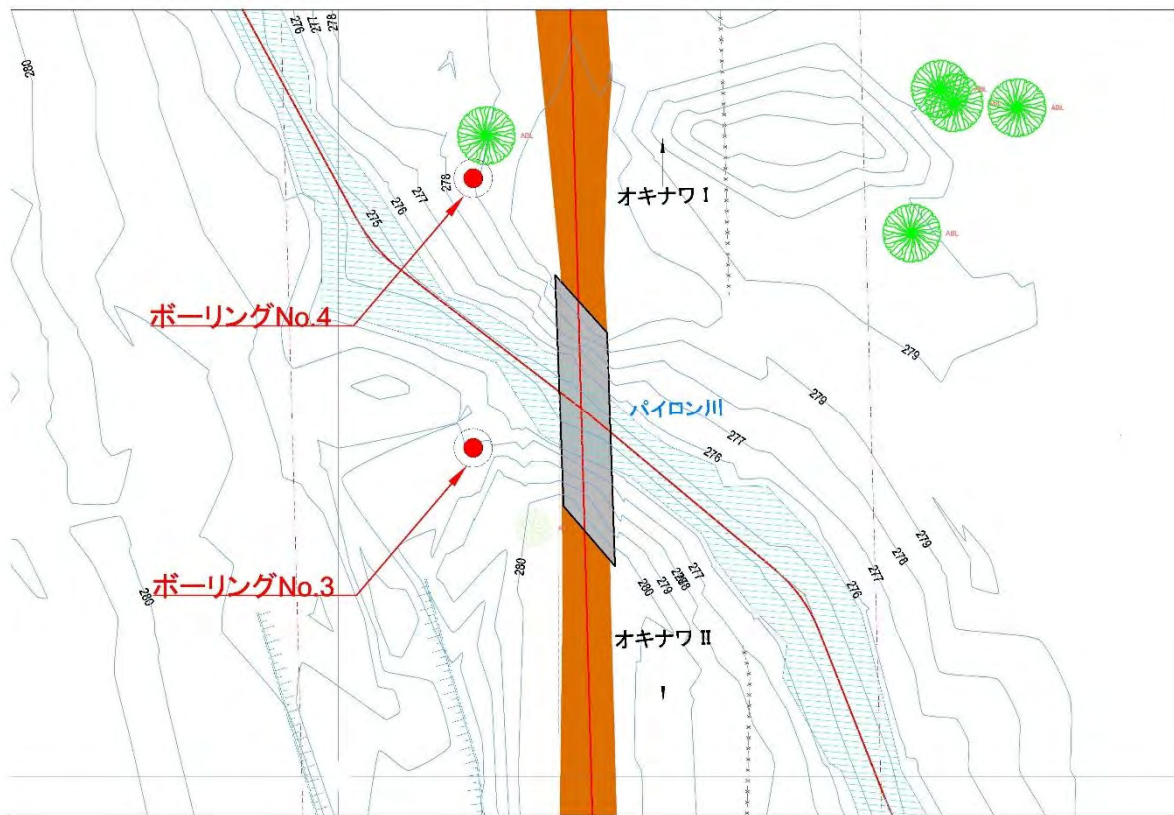

技術資料 SPT 試験結果 (P3)

FIELD REGISTER										OFF-SITE REGISTER									
Scale	Depth (m)	Geotechnical Profile	Visual Description of the Material	Soil Classif. USCS & AASHTO	Strength of Soils Parameters			Effective Pressure (kg/cm <sup>2</sup> )	Correction Factor CF	Number of Blows					Depth (m)	Penetration Resistance Chart Number of Blows Vs Depth	Allowable Stress (Kg/cm <sup>2</sup> )		
					Friction Angle (°)	Cohesion (kg/cm <sup>2</sup> )	Soil Density γ <sub>d</sub> (t/m <sup>3</sup> )			15 cm Initiates	30 cm Finales	Ng 60- depth	Ng corr- pressure	Ng corr- blows				Ng scale	
	0.00																		
	1.30		Clay with medium to high plasticity, in weak in-situ condition, with soft consistency, in saturated state and of dark brown coloration with reddish patinas. Alluvial Fan Geological Interpretation	CL A-7-6 (14)	1	0.370	1.680	0.185	1.000	2	5	5	5.00	5	5	1.10		0.65	
	2.60		Clay with low plasticity, in weak in-situ condition, with soft consistency, in saturated state and of dark brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CL A-6 (8)	2	0.340	1.700	0.354	1.349	2	5	5	6.74	7	6	2.10		0.69	
	3.10		Silt with very fine sand mixtures, in weak in-situ condition, with soft consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	ML A-4 (7)	10	0.130	1.800	0.529	1.214	2	6	6	7.29	7	7	3.10		0.99	
	N.F.																		
	4.90		Silty sand with no plasticity, in firm in-situ condition, with medium compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	28	0.000	1.900	0.619	1.162	6	13	13	15.11	15	14	4.10		1.85	
	6.50		Clay with low plasticity, in weak to firm in-situ condition, with soft to medium consistency, in saturated state and of brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CL A-4 (8)	2	0.360	1.780	0.707	1.118	6	12	12	13.41	13	12	5.10		1.20	
	8.30		Silt with very fine sand mixtures, in weak to partially firm in-situ condition, with soft to medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	ML A-4 (4)	13	0.150	1.840	0.867	1.050	2	4	4	4.20	4	4	7.10		1.05	
	9.40		Silty sand with no plasticity, in firm in-situ condition, with medium compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	29	0.000	1.940	1.043	0.988	12	16	16	15.81	15	14	9.10		1.52	
	10.50		Silt with very fine sand mixtures, in partially firm in-situ condition, with soft to medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	ML A-4 (8)	14	0.170	1.860	1.122	0.963	4	9	9	8.67	9	8	10.00		1.38	
	12.10		Clay with medium plasticity, in firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CL A-6 (13)	2	0.390	1.880	1.218	0.936	6	13	13	12.17	12	11	11.10		1.48	
	13.50		Silty sand with no plasticity, in firm in-situ condition, with medium to dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-4 (1)	30	0.000	1.960	1.306	0.912	5	17	17	15.51	15	14	12.10		1.51	
	15.20		Clay with high plasticity, in firm in-situ condition, with medium consistency, in saturated state and of reddish brown coloration with light brown patinas. Alluvial Fan Geological Interpretation	CH A-7-6 (20)	3	0.460	1.880	1.485	0.870	8	18	18	15.65	15	14	14.00		1.89	
	16.60		Clay with low plasticity, firm in-situ condition, with medium consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (7)	4	0.420	1.880	1.573	0.850	5	19	19	16.16	16	14	15.00		1.93	
	18.50		Clay with low plasticity, firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (10)	4	0.420	1.880	1.661	0.832	6	20	20	16.64	16	14	16.00		2.00	
	19.80		Clay with medium to high plasticity, firm in-situ condition, with medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CL A-7-6 (16)	4	0.420	1.880	1.766	0.812	3	11	11	8.93	9	8	17.20		1.50	
	20.60		Clay with medium to high plasticity, firm in-situ condition, with medium consistency, in saturated state and of light gray coloration with dark brown patinas. Alluvial Fan Geological Interpretation	CL A-7-6 (17)	4	0.490	1.900	1.837	0.799	4	15	15	11.98	12	11	18.00		1.53	
	22.20		Clay with low plasticity, firm in-situ condition, with medium consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	CL A-4 (8)	4	0.490	1.900	1.925	0.783	5	20	20	15.66	15	14	19.00		1.56	
	23.40		Clay with medium to high plasticity, firm in-situ condition, with very compacted to heavy consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CL A-7-6 (18)	4	0.490	1.900	2.022	0.766	6	18	17	13.03	13	12	20.10		1.73	
	25.60		Silt with very fine sand mixtures, in firm to consolidated in-situ condition, with very compacted to heavy consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	ML A-4 (8)	20	0.230	1.940	2.103	0.753	5	17	16	12.05	12	11	21.00		1.76	
	26.80		Silt with very fine sand mixtures, in consolidated in-situ condition, with heavy consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	ML A-4 (7)	20	0.230	1.940	2.193	0.739	6	21	20	14.79	15	13	22.00		1.80	
	28.20		Silty sand with no plasticity, in consolidated to firm in-situ condition, with medium to dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-4 (1)	31	0.000	2.030	2.283	0.726	9	41	40	29.04	22	20	23.00		2.50	
	30.10		Clay with medium plasticity, firm in-situ condition, with medium consistency, in saturated state and of brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (12)	6	0.490	1.900	2.375	0.712	Penetro 30 cm con 38					24.00		R		
								2.469	0.699	20	56	55	38.48	27	24	25.00		3.94	
								2.563	0.687	Penetro 15 cm con 25					26.00		R		
								2.659	0.675	Penetro 15 cm con 20					27.00		R		
								2.762	0.662	21	21	20	13.26	13	12	28.00		1.11	
								2.855	0.651	6	13	12	7.83	8	7	29.00		2.33	
								2.954	0.640	7	16	15	9.61	10	9	30.10		2.38	

END OF BOREHOLE

技術資料 SPT 試驗結果 (P4)

FIELD REGISTER				OFF-SITE REGISTER														
Scale	Depth (m)	Geotechnical Profile	Visual Description of the Material	Soil Classif. System USCS & AASHTO	Strength of Soils Parameters			Effective Pressure (kg/cm <sup>2</sup> )	Correction Factor CF	Number of Blows			Penetration Resistance Index			Depth (m)	Penetration Resistance Chart Number of Blows Vs Depth	Allowable Stress (Kg/cm <sup>2</sup> )
					Friction Angle (°)	Cohesion (kg/cm <sup>2</sup> )	Soil Density γ <sub>d</sub> (t/m <sup>3</sup> )			15 cm Initiates	30 cm	60 cm	Ng corr.- pressure	Ng corr.- blows	Ng <sub>scale</sub>			
0.00																		
1.00	1.50		Clay with medium to high plasticity, in weak in-situ condition, with soft consistency, in saturated state and of reddish coloration. Alluvial Fan Geological Interpretation	CL A-7-6 (17)	1	0.370	1.680	0.185	1.000	2	6	6	6.00	6	6	1.10		0.65
2.00	2.80		Clay with medium plasticity, in partially firm in-situ condition, with soft to medium consistency, in saturated state and of brown coloration with light gray patinas. Alluvial Fan Geological Interpretation	CL A-6 (10)	2	0.340	1.700	0.354	1.349	2	9	9	12.14	12	12	2.10		1.00
3.00	3.40		Clay with low plasticity, in weak in-situ condition, with soft consistency, in saturated state and of reddish brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (9)	2	0.340	1.700	0.524	1.218	2	5	5	6.09	6	6	3.10		0.75
4.00	N.F.																	
5.00	5.00		Silty sand with no plasticity, in firm in-situ condition, with medium compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	28	0.000	1.900	0.638	1.152	10	27	27	31.11	23	21	4.10		2.88
6.00	7.00		Poorly graded sand with little fine-grained soils, in firm in-situ condition, with medium compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SP-SM A-2-4 (0)	28	0.000	1.890	0.817	1.069	10	36	36	38.50	27	24	6.10		2.94
7.00	8.90		Silt with no to low plasticity, in weak to firm in-situ condition, with soft to medium consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	ML A-4 (5)	13	0.150	1.840	0.981	1.008	3	4	4	4.03	4	4	8.00		1.14
8.00	10.30		Silty sand with no plasticity, in loose in-situ condition, with low compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	29	0.000	1.940	1.075	0.977	3	7	7	6.84	7	6	9.10		0.67
9.00	11.40		Clay with medium plasticity, firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (11)	2	0.390	1.880	1.160	0.925	4	8	8	7.62	8	7	10.00		0.76
10.00	12.10		Clay with low plasticity, firm in-situ condition, with medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CL A-6 (11)	2	0.390	1.880	1.259	0.902	4	11	11	10.17	10	9	11.10		1.11
11.00	14.20		Silty sand with no plasticity, in firm to consolidated in-situ condition, with medium to dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	30	0.000	1.960	1.347	0.902	4	16	16	14.44	14	13	12.10		1.53
12.00	15.40		Silty sand with no plasticity, in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	30	0.000	1.960	1.433	0.881	15	45	45	39.67	27	25	13.00		2.59
13.00	16.50		Clay with high plasticity, firm in-situ condition, with medium consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	CH A-7-5 (19)	3	0.460	1.880	1.529	0.860	Penetro 30 cm con 53					14.00		R	
14.00	18.20		Clay with high plasticity, with the presence of isolated clasts in small percentage, in firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CH A-7-6 (20)	4	0.490	1.900	1.625	0.839	Penetro 15 cm con 24					15.00		R	
15.00	20.10		Clay with high plasticity, with the presence of isolated clasts in small percentage, in firm in-situ condition, with medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	CH A-7-6 (20)	4	0.490	1.900	1.716	0.821	7	21	21	17.24	16	15	16.00		1.99
16.00	21.50		Clay with medium to high plasticity, firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CL A-7-6 (17)	4	0.420	1.880	1.822	0.801	7	22	22	17.63	16	15	17.20		2.08
17.00	23.60		Clay with low plasticity, with the presence of isolated clasts in small percentage, in firm in-situ condition, with medium consistency, in saturated state and of brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (11)	4	0.490	1.900	1.892	0.789	6	21	21	16.56	16	14	18.00		1.55
18.00	25.50		Silty sand with no plasticity, in firm to consolidated in-situ condition, with medium to dense compactness, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	30	0.000	2.000	1.982	0.773	8	22	22	17.01	16	14	19.00		1.71
19.00	26.60		Silty sand with no plasticity, in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	31	0.000	2.030	2.081	0.757	9	28	27	20.43	18	16	20.10		1.75
20.00	27.20		Clay with medium to high plasticity, firm in-situ condition, with medium consistency, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	CL A-7-6 (16)	4	0.490	1.900	2.162	0.744	11	20	19	14.14	14	13	21.00		1.79
21.00	28.70		Clay with low plasticity, with the presence of isolated clasts in small percentage, in firm in-situ condition, with medium consistency, in saturated state and of brown coloration. Alluvial Fan Geological Interpretation	CL A-6 (11)	4	0.490	1.900	2.252	0.730	7	17	16	11.69	12	11	22.00		1.83
22.00	30.10		Silty sand with no plasticity, in firm to consolidated in-situ condition, with medium to dense compactness, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	30	0.000	2.000	2.342	0.717	8	21	20	14.35	14	13	23.00		1.87
23.00	25.50		Silty sand with no plasticity, in firm to consolidated in-situ condition, with medium to dense compactness, in saturated state and of dark brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	30	0.000	2.000	2.436	0.704	12	40	39	27.47	21	19	24.00		1.80
24.00	26.60		Silty sand with no plasticity, in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	31	0.000	2.030	2.536	0.691	20	55	54	37.30	26	24	25.00		2.27
25.00	27.20		Silty sand with no plasticity, in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	31	0.000	2.030	2.637	0.678	Penetro 30 cm con 55					26.00		R	
26.00	28.70		Very poorly graded sand with little fine-grained soils in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SP-SM A-2-4 (0)	31	0.000	2.020	2.740	0.665	Penetro 15 cm con 25					27.00		R	
27.00	28.70		Very poorly graded sand with little fine-grained soils in consolidated in-situ condition, with dense compactness, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	SM A-2-4 (0)	31	0.000	2.030	2.839	0.653	20	16	15	9.81	10	9	28.00		4.42
28.00	28.70		Silt with no to low plasticity, in firm in-situ condition, with medium consistency, in saturated state and of light brown coloration with brown patinas. Alluvial Fan Geological Interpretation	ML A-4 (6)	20	0.230	1.940	2.933	0.642	6	13	12	7.72	8	7	29.00		4.54
29.00	30.10		Silt with no to low plasticity, in firm in-situ condition, with medium consistency, in saturated state and of light brown coloration. Alluvial Fan Geological Interpretation	ML A-4 (7)	20	0.230	1.940	3.037	0.630	7	17	16	10.10	10	9	30.10		4.67

END OF BOREHOLE

## 8-2 排水計算

### (1) 降雨量データ

出典: 国立気象水文局 (Servicio Nacional de Meteorología e Hidrología (SENAMHI))

期間: 1987~2013

1987年													合計
日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	
1	50.8	0.0	0.0	0.0	68.2	0.0	41.5	0.0	0.0	0.0	86.7	21.0	268.2
2	0.0	0.0	38.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	38.1
3	10.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.2
4	10.3	0.0	70.5	0.0	8.5	27.3	0.0	0.0	0.0	0.0	0.0	0.0	116.6
5	0.0	5.1	0.0	0.0	0.0	80.3	0.0	95.5	0.0	0.0	0.0	0.0	180.9
6	0.0	4.4	10.5	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	19.4
7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	30.5	0.0	80.0	0.0	110.5
8	0.0	4.0	0.0	0.0	12.1	0.0	0.0	0.0	0.0	16.0	0.0	15.8	47.9
9	0.0	0.0	31.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	31.5
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
12	0.0	0.0	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.0
13	21.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	24.5	0.0	46.4
14	60.0	0.0	0.0	0.0	7.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	67.2
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.1	53.0	0.0	57.1
16	4.5	5.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.5
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	80.0	80.0
18	23.3	15.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	58.3
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
20	0.0	0.0	0.0	0.0	13.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.6
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.1	0.0	0.0	17.1
22	10.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
24	100.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	31.0	0.0	131.9
25	39.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	53.1	92.1
26	4.1	0.0	20.0	0.0	0.0	0.0	0.0	0.0	0.0	13.0	0.0	0.0	37.1
27	10.2	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	0.0	0.0	72.3	102.5
28	0.0	0.0	0.0	0.0	0.0	0.0	50.5	0.0	0.0	0.0	0.0	0.0	50.5
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
30	0.0	****	18.0	0.0	0.0	0.0	0.0	0.0	49.0	0.0	0.0	0.0	67.0
31	35.1	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	10.0	45.1
合計	380.3	33.5	188.6	4.0	114.1	107.6	112.0	95.5	79.5	70.2	275.2	252.2	1712.7
平均	29.2	6.7	31.4	4.0	19.0	53.8	37.3	95.5	39.8	14.0	55.0	42.0	35.6
最大	100.9	15.0	70.5	4.0	68.2	80.3	50.5	95.5	49.0	20.0	86.7	80.0	100.9
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	13.0	5.0	6.0	1.0	6.0	2.0	3.0	1.0	2.0	5.0	5.0	6.0	55.0

## 1988年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	43.8	0.0	0.0	43.8
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	52.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	52.2
6	53.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	53.3
7	0.0	0.0	2.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.2	7.2
8	0.0	0.0	0.0	15.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.3	27.6
9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.9	2.3	0.0	0.0	18.2
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
12	0.0	0.0	30.5	10.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	41.3
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
14	0.0	0.0	0.0	6.9	0.0	0.0	0.0	0.0	20.1	0.0	0.0	0.0	27.0
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	16.6	0.0	0.0	16.6
16	0.0	38.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	38.1
17	0.0	20.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.2
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	41.1	0.0	41.1
19	0.0	0.0	0.0	11.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.8
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.9	0.0	0.0	1.9
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
22	0.0	0.0	0.0	11.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.0
23	47.5	0.0	10.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	57.6
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
25	0.0	0.0	0.0	29.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	29.5
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	25.5	44.5	0.0	70.0
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
28	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
29	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	27.0	0.0	27.0
30	0.0	****	10.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0
31	5.0	****	0.0	****	0.0	****	0.0	10.0	****	8.5	****	0.0	23.5
合計	158.0	58.3	52.6	85.3	0.0	0.0	0.0	10.0	36.0	98.6	112.6	17.5	628.9
平均	39.5	29.2	13.2	14.2	0.0	0.0	0.0	10.0	18.0	16.4	37.5	8.8	20.8
最大	53.3	38.1	30.5	29.5	0.0	0.0	0.0	10.0	20.1	43.8	44.5	12.3	53.3
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	4.0	2.0	4.0	6.0	0.0	0.0	0.0	1.0	2.0	6.0	3.0	2.0	30.0

## 1989年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
2	23.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.0
3	0.0	0.0	19.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	19.1
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	0.0	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.0
6	51.6	60.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	111.6
7	0.0	19.0	23.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	42.5
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	46.4	0.0	46.4
9	0.0	0.0	13.5	15.1	0.0	0.0	22.5	0.0	0.0	0.0	0.0	0.0	51.1
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	33.5	0.0	10.2	43.7
12	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.1	20.1
13	0.0	42.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.2	62.4
14	10.3	0.0	9.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.3	30.1
15	50.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	50.2
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	62.5	62.5
18	0.0	0.0	0.0	11.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.6
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	88.6	0.0	0.0	0.0	0.0	88.6
21	51.2	0.0	0.0	0.0	0.0	0.0	0.0	39.3	0.0	6.5	4.5	0.0	101.5
22	0.0	21.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	21.9
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	63.9	0.0	0.0	0.0	0.0	63.9
24	10.0	0.0	0.0	0.0	0.0	27.3	0.0	13.5	0.0	0.0	0.0	99.5	150.3
25	0.0	0.0	13.8	44.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	58.3
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.2	0.0	15.2
27	0.0	0.0	0.0	0.0	0.0	0.0	9.5	25.5	0.0	0.0	0.0	0.0	35.0
28	0.0	0.0	0.0	3.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	24.5	28.3
29	0.0	****	0.0	11.5	0.0	13.0	0.0	0.0	0.0	0.0	0.0	0.0	24.5
30	0.0	****	3.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.0
31	14.5	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	0.0	14.5
合計	210.8	143.1	86.4	86.5	0.0	40.3	32.0	230.8	0.0	40.0	66.1	247.3	1183.3
平均	30.1	35.8	12.3	17.3	0.0	20.2	16.0	46.2	0.0	20.0	22.0	35.3	25.5
最大	51.6	60.0	23.5	44.5	0.0	27.3	22.5	88.6	0.0	33.5	46.4	99.5	99.5
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	7.0	4.0	7.0	5.0	0.0	2.0	2.0	5.0	0.0	2.0	3.0	7.0	44.0



## 1990年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	20.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.2
2	0.0	10.0	6.5	0.0	0.0	53.1	0.0	0.0	0.0	0.0	0.0	0.0	69.6
3	88.5	0.0	4.5	0.0	20.3	0.0	0.0	0.0	0.0	6.0	0.0	0.0	119.3
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	41.2	7.2	48.4
5	0.0	0.0	0.0	0.0	0.0	30.8	0.0	0.0	0.0	0.0	0.0	0.0	30.8
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.8	0.0	0.0	0.0	23.8
7	27.4	43.0	0.0	0.0	40.3	0.0	0.0	0.0	0.0	0.0	0.0	12.1	122.8
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	100.3	0.0	0.0	0.0	0.0	0.0	8.4	0.0	0.0	0.0	0.0	0.0	108.7
10	10.1	23.3	0.0	14.5	20.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	67.9
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
12	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.1	0.0	0.0	6.1
14	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
15	31.5	7.5	0.0	0.0	17.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	56.2
16	0.0	0.0	0.0	71.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	71.5
17	90.9	0.0	46.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	137.7
18	0.0	6.1	0.0	0.0	0.0	0.0	0.0	23.0	0.0	83.5	0.0	0.0	112.6
19	7.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.1	27.3
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
21	0.0	14.5	0.0	0.0	0.0	0.0	8.3	0.0	0.0	0.0	62.5	0.0	85.3
22	0.0	0.0	12.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.9	0.0	18.9
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
24	0.0	0.0	0.0	4.9	0.0	17.3	0.0	0.0	0.0	0.0	0.0	0.0	22.2
25	0.0	10.0	82.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	92.4
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
27	0.0	0.0	0.0	0.0	7.0	0.0	0.0	8.0	13.2	0.0	0.0	30.5	58.7
28	0.0	0.0	0.0	8.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.5
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
30	0.0	****	0.0	0.0	20.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0
31	7.8	****	9.8	****	50.0	****	0.0	0.0	****	12.7	****	0.0	80.3
合計	363.7	114.4	162.0	99.4	195.0	101.2	16.7	31.0	37.0	108.3	110.6	69.9	1409.2
平均	45.5	16.3	27.0	24.8	24.4	33.7	8.3	15.5	18.5	27.1	36.9	17.5	24.6
最大	100.3	43.0	82.4	71.5	50.0	53.1	8.4	23.0	23.8	83.5	62.5	30.5	100.3
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	8.0	7.0	6.0	4.0	8.0	3.0	2.0	2.0	2.0	4.0	3.0	4.0	53.0

## 1991年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.2	1.0	****	5.2
2	25.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.4	0.0	****	30.7
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.4	****	3.4
5	0.0	0.0	0.0	60.0	0.0	0.0	0.0	0.0	11.5	0.0	0.0	****	71.5
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.0	****	13.0
7	18.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	18.5
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
9	0.0	0.0	0.0	0.0	0.0	8.4	0.0	0.0	6.4	0.0	0.0	****	14.8
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.9	****	11.9
11	0.0	50.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	50.3
12	100.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	100.2
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
14	92.3	68.6	23.5	17.5	33.8	0.0	0.0	0.0	0.0	0.0	0.0	****	235.7
15	0.0	3.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.0	****	12.5
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
18	0.0	3.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	26.5	****	29.5
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
21	0.0	0.0	0.0	0.0	0.0	8.4	3.2	0.0	0.0	0.0	0.0	****	11.6
22	0.0	0.0	28.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	28.5
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	39.2	0.0	****	39.2
24	0.0	7.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	7.8
25	29.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	29.5
26	0.0	0.0	0.0	2.5	0.0	0.0	0.0	0.0	0.0	0.0	56.5	****	59.0
27	68.3	11.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.5	0.0	****	94.8
28	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.5	0.0	0.0	****	3.5
29	6.3	****	0.0	0.0	4.2	0.0	0.0	0.0	5.0	0.0	0.0	****	15.5
30	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	19.5	0.0	****	19.5
31	0.0	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	****	0.0
合計	340.4	144.2	52.0	80.0	38.0	16.8	3.2	0.0	26.4	83.8	121.3	****	906.1
平均	48.6	24.0	26.0	26.7	19.0	8.4	3.2	0.0	6.6	16.8	17.3	****	19.7
最大	100.2	68.6	28.5	60.0	33.8	8.4	3.2	0.0	11.5	39.2	56.5	****	100.2
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	****	0.0
個数	7.0	6.0	2.0	3.0	2.0	2.0	1.0	0.0	4.0	5.0	7.0	****	39.0

## 1992年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	4.4	0.0	0.0	0.0	122.5	0.0	6.0	0.0	17.8	10.1	0.0	0.0	160.8
2	0.0	49.7	0.0	0.0	3.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	53.1
3	0.0	0.0	0.0	1.1	0.5	0.0	0.0	0.0	0.0	0.0	24.5	0.0	26.1
4	0.0	17.9	3.2	0.0	0.0	0.0	0.0	0.0	0.0	10.4	0.0	0.0	31.5
5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	28.6	28.6
6	0.0	0.0	0.0	0.0	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5
7	0.0	0.0	0.0	43.1	15.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	58.1
8	12.3	0.0	1.5	10.5	11.0	0.5	0.0	0.0	0.0	0.0	0.0	0.0	35.8
9	7.0	0.0	0.0	0.0	0.0	0.8	0.0	0.0	0.0	0.0	0.0	120.0	127.8
10	55.0	0.0	0.0	0.0	3.9	0.0	0.0	0.0	29.5	0.0	0.0	8.5	96.9
11	0.0	21.7	0.0	38.5	0.0	0.0	0.0	0.0	49.5	0.0	0.0	0.0	109.7
12	0.0	10.7	0.0	17.5	0.0	0.0	0.0	0.0	21.5	0.0	0.0	0.0	49.7
13	55.5	10.0	5.1	0.0	6.8	0.0	0.0	0.0	9.5	0.0	0.0	0.0	86.9
14	203.5	0.0	0.0	0.0	0.0	0.5	6.5	0.0	0.0	0.0	0.0	0.0	210.5
15	23.9	53.1	4.2	0.0	0.0	0.0	1.0	0.0	0.0	0.0	30.6	0.0	112.8
16	0.0	45.1	0.0	0.0	0.0	0.0	0.0	1.5	0.0	9.5	0.0	0.0	56.1
17	0.0	15.0	0.0	0.0	8.9	0.0	0.0	43.0	0.0	0.0	0.0	3.6	70.5
18	0.0	55.0	0.0	0.0	0.6	0.0	0.0	21.5	3.1	0.0	0.0	0.0	80.2
19	0.0	53.0	0.0	9.1	0.0	0.0	0.0	10.3	0.0	0.0	0.0	0.0	72.4
20	15.5	0.0	0.0	70.1	0.0	0.0	0.0	10.0	0.0	0.0	0.0	0.0	95.6
21	0.0	0.0	70.8	4.5	0.0	4.0	0.0	0.9	0.0	0.0	0.0	0.0	80.2
22	0.0	0.0	5.0	24.5	0.0	0.0	0.0	0.0	0.0	0.0	18.0	0.0	47.5
23	0.0	0.0	0.0	10.5	0.0	0.0	0.0	0.0	0.0	0.0	2.2	0.0	12.7
24	0.0	0.0	0.0	10.5	3.0	0.0	0.0	0.0	66.6	0.0	0.0	0.0	80.1
25	3.0	0.0	0.0	8.0	0.0	0.0	0.0	0.0	9.5	0.0	0.0	0.0	20.5
26	0.0	10.5	2.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.0
27	0.0	0.0	75.0	0.0	0.0	0.4	0.0	0.0	0.0	0.0	0.0	0.0	75.4
28	0.0	0.0	16.0	1.0	16.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	33.6
29	0.0	0.0	0.0	0.0	4.0	0.0	0.0	0.0	0.0	19.8	16.7	0.0	40.5
30	0.0	****	0.0	0.0	0.0	10.3	0.0	0.0	77.5	0.0	0.0	0.0	87.8
31	0.0	****	0.0	****	11.9	****	0.0	0.2	****	0.0	****	0.0	80.3
合計	380.1	341.7	183.3	248.9	209.6	16.5	13.5	87.4	284.5	49.8	92.0	241.0	2148.3
平均	42.2	31.1	20.4	19.2	15.0	2.8	4.5	12.5	31.6	12.4	18.4	48.2	21.5
最大	203.5	55.0	75.0	70.1	122.5	10.3	6.5	43.0	77.5	19.8	30.6	120.0	203.5
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	9.0	11.0	9.0	13.0	14.0	6.0	3.0	7.0	9.0	4.0	5.0	5.0	95.0

## 1993年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.5	3.2	20.7
2	0.0	15.5	16.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	32.0
3	0.0	0.0	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.0
4	24.6	0.0	4.8	6.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	36.1
5	0.0	10.0	0.0	6.6	0.0	0.0	14.4	0.0	0.0	0.0	20.0	0.0	51.0
6	15.2	120.0	0.0	0.0	0.0	0.0	4.5	0.0	0.0	0.0	6.2	0.0	145.9
7	32.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	0.0	0.0	0.0	32.5
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.3	0.0	0.0	0.0	0.3
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.2	0.0	0.0	0.0	0.0	5.2
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.2	0.0	7.2
12	0.0	0.0	0.0	0.0	0.0	0.0	24.5	0.0	0.0	0.0	0.0	0.0	24.5
13	0.0	10.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.5
14	0.0	0.0	0.0	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5
15	12.0	0.0	0.0	0.0	3.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.9
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.0	7.0	13.0
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.0	0.0	18.0
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	20.0	0.0	28.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	48.7
20	0.0	0.0	0.0	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	5.2	9.7
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	16.5	0.0	26.5	0.0	0.0	43.0
22	0.0	0.0	4.0	0.0	0.0	0.0	0.0	2.2	0.0	4.5	0.0	15.5	26.2
23	0.0	0.0	0.0	0.0	5.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.5
24	7.1	0.0	8.8	0.0	7.5	0.0	0.0	0.0	13.5	0.0	34.0	0.0	70.9
25	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
26	0.0	0.0	0.0	0.0	3.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.0
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.0	8.0	22.0
28	0.0	0.0	0.0	0.0	0.0	0.0	6.5	0.0	0.0	0.0	0.0	0.0	6.5
29	0.0	****	0.0	0.0	0.0	0.0	10.5	0.0	5.1	0.0	0.0	0.0	15.6
30	0.0	****	0.0	0.0	0.0	0.0	0.0	13.6	0.0	0.0	0.0	0.0	13.6
31	0.0	****	6.8	****	0.0	****	0.0	0.0	****	0.0	****	0.0	6.8
合計	110.9	156.0	69.6	13.3	29.9	0.0	60.4	37.5	19.4	31.0	122.9	38.9	689.8
平均	18.5	39.0	11.6	6.6	4.3	0.0	12.1	9.4	4.8	15.5	15.4	7.8	13.2
最大	32.0	120.0	28.7	6.7	7.5	0.0	24.5	16.5	13.5	26.5	34.0	15.5	120.0
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	6.0	4.0	6.0	2.0	7.0	0.0	5.0	4.0	4.0	2.0	8.0	5.0	53.0

## 1994年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
2	20.0	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	49.0	0.0	0.0	73.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	32.2	32.2
5	0.0	41.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	41.5
6	0.0	0.0	0.0	11.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.0	17.8
7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	26.5	0.0	0.0	2.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	29.3
10	0.0	30.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	30.2
11	0.0	30.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	30.3
12	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5	0.0	7.5	13.5
13	0.0	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5
14	4.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.0	0.0	0.0	0.0	19.3
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
16	0.0	12.9	7.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	28.3	10.1	59.1
17	0.0	3.9	0.0	0.5	0.0	0.0	0.0	0.0	0.0	0.0	12.0	0.0	16.4
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	14.4	0.0	0.0	0.0	0.0	100.2	0.0	0.0	0.0	0.0	0.0	0.0	114.6
20	12.0	0.0	12.9	0.0	0.0	100.1	0.0	0.0	0.0	0.0	0.0	0.0	125.0
21	19.5	0.0	0.0	0.0	6.1	0.0	0.0	0.0	0.0	0.0	0.0	40.0	65.6
22	0.0	32.5	0.0	0.0	0.0	0.0	42.0	0.0	0.0	2.5	0.0	0.0	77.0
23	0.0	0.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.2
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.1	0.0	0.0	10.1
25	12.4	0.0	0.1	0.0	0.0	2.1	0.0	0.0	0.0	0.0	0.0	0.0	14.6
26	3.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.6
27	0.0	0.0	0.0	0.0	131.0	0.0	0.0	0.0	0.0	0.0	0.2	27.1	158.3
28	0.0	23.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.3	0.0	18.9	55.1
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
30	0.0	****	26.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	26.0
31	4.9	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0	0.0	4.9
合計	117.6	180.9	50.8	15.1	137.1	202.4	42.0	0.0	15.0	75.4	40.5	142.3	1019.1
平均	13.1	18.1	10.2	5.0	68.5	67.5	42.0	0.0	15.0	15.1	13.5	17.8	26.0
最大	26.5	41.0	26.0	11.8	131.0	100.2	42.0	0.0	15.0	49.0	28.3	40.0	131.0
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	9.0	10.0	5.0	3.0	2.0	3.0	1.0	0.0	1.0	5.0	3.0	8.0	50.0

## 1995年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	25.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	25.0
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	5.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.4
5	2.9	0.0	0.0	0.0	9.5	0.0	1.0	0.0	0.0	0.0	10.5	0.0	23.9
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
7	0.0	0.0	0.0	0.0	0.0	1.5	0.0	0.0	0.0	0.0	0.0	23.0	24.5
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.1	3.1
9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
10	0.0	25.6	0.0	0.0	0.0	0.0	0.0	0.0	13.0	0.0	0.0	0.0	38.6
11	0.0	55.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	22.5	0.0	77.8
12	0.0	15.0	22.9	0.0	0.0	0.0	1.0	0.0	0.0	10.3	0.0	0.0	49.2
13	0.0	3.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.3
14	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
15	10.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.5	0.0	20.5
17	0.0	10.1	7.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.6
18	0.0	0.0	0.0	0.0	0.0	0.0	5.0	0.0	0.0	0.0	0.0	0.0	5.0
19	0.0	0.0	5.5	0.0	0.0	0.0	0.0	0.0	5.7	0.0	0.0	0.0	11.2
20	0.0	0.0	0.0	35.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	35.5
21	0.0	0.0	2.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5	0.0	7.0
22	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	0.0	0.0	15.5	16.0
23	24.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	24.1
24	0.0	0.0	7.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.1
25	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
27	0.0	13.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.2
28	0.0	0.0	14.5	0.0	0.0	0.0	0.0	0.0	41.1	0.0	0.0	2.5	58.1
29	64.1	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	64.1
30	0.0	****	0.0	0.0	0.0	0.0	3.8	0.0	0.0	0.0	0.0	0.0	3.8
31	0.0	****	9.5	****	0.0	****	0.0	0.0	****	0.0	****	0.0	9.5
合計	101.1	147.5	69.5	35.5	14.9	1.5	10.8	0.0	59.8	10.8	58.0	44.1	553.5
平均	25.3	21.1	9.9	35.5	7.4	1.5	2.7	0.0	19.9	5.4	14.5	11.0	14.0
最大	64.1	55.3	22.9	35.5	9.5	1.5	5.0	0.0	41.1	10.3	22.5	23.0	64.1
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	4.0	7.0	7.0	1.0	2.0	1.0	4.0	0.0	3.0	2.0	4.0	4.0	39.0

## 1996年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	13.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.0
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.0	0.0	18.0
3	0.0	29.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	29.5
4	72.5	7.0	0.0	0.0	0.0	0.0	0.0	0.0	104.1	0.0	0.0	0.0	183.6
5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.9	0.0	0.0	7.9
6	0.0	11.0	0.0	0.0	0.0	0.0	0.0	7.5	0.0	0.0	0.0	0.0	18.5
7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.6	0.0	0.0	54.2	57.8
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.2	9.2
10	0.0	0.0	0.0	6.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.1
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
12	14.2	8.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	36.0	0.0	0.0	58.2
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
14	0.0	0.0	0.0	0.0	11.9	0.0	0.0	78.5	0.0	0.0	0.0	0.0	90.4
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
16	0.0	0.0	0.0	17.3	30.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	47.6
17	0.0	0.0	29.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.9	0.0	39.8
18	2.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.0
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	35.9	0.0	0.0	35.9
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
22	10.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.8	0.0	0.0	0.0	26.3
23	0.0	0.0	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	9.9	10.9
24	0.0	18.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.1
25	0.0	0.0	7.5	14.5	0.0	0.0	0.0	0.0	0.0	61.0	0.0	0.0	83.0
26	0.0	18.2	0.0	0.0	0.0	0.0	0.0	20.0	0.0	12.0	0.0	8.5	58.7
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
28	10.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.9
29	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	72.0	0.0	72.0
30	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	20.0
31	0.0	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	0.0	0.0
合計	110.1	91.8	37.4	37.9	56.2	0.0	0.0	106.0	123.5	152.8	99.9	101.8	917.4
平均	22.0	15.3	18.7	12.6	14.0	0.0	0.0	35.3	41.2	30.6	33.3	20.4	24.3
最大	72.5	29.5	29.9	17.3	30.3	0.0	0.0	78.5	104.1	61.0	72.0	54.2	104.1
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	5.0	6.0	2.0	3.0	4.0	0.0	0.0	3.0	3.0	5.0	3.0	5.0	39.0

## 1997年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	30.0	0.0	0.0	0.0	0.0	4.5	****	0.0	0.0	0.0	0.0	12.9	47.4
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.5	0.0	0.0	0.0	0.0	7.5
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	0.0	21.8	0.0	0.0	0.0	21.3	0.0	0.0	0.0	0.0	0.0	0.0	43.1
6	0.0	0.0	0.0	0.0	0.0	42.3	0.0	0.0	0.0	67.5	2.4	0.0	112.2
7	0.0	0.0	1.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.0	8.4	13.7
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	8.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.9
10	0.0	0.0	5.3	49.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	55.2
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
12	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.0	0.0	0.0	14.0
13	0.0	0.0	20.0	0.0	0.0	10.1	0.0	0.0	0.0	0.0	0.0	83.5	113.6
14	0.0	0.0	0.0	0.0	0.0	7.1	0.0	0.0	27.5	17.0	57.5	0.0	109.1
15	30.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	30.2
16	0.0	3.6	0.0	0.0	0.0	7.2	0.0	0.0	0.0	0.0	0.0	0.0	10.8
17	1.2	0.0	0.0	0.0	0.0	10.3	0.0	0.0	0.0	0.0	0.0	0.0	11.5
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	42.0	3.3	0.0	106.1	0.0	0.0	0.0	60.0	0.0	0.0	0.0	0.0	211.4
20	0.0	0.0	0.0	2.5	0.0	0.0	0.0	12.0	14.0	0.0	0.0	0.0	28.5
21	0.0	0.0	0.0	0.0	20.3	0.0	0.0	0.0	1.0	0.0	0.0	0.0	21.3
22	0.0	0.0	0.0	0.0	16.4	0.0	5.3	0.0	0.0	0.0	0.0	0.0	21.7
23	0.0	0.0	20.4	0.0	9.5	0.0	7.2	0.0	0.0	24.0	0.0	7.8	68.9
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0	0.0	10.0
25	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
26	0.0	20.0	0.0	8.9	0.0	7.0	0.0	0.0	0.0	0.0	0.0	0.0	35.9
27	0.0	0.0	18.5	0.0	0.0	9.4	0.0	0.0	0.0	0.0	6.1	0.0	34.0
28	0.0	0.0	0.0	0.0	0.0	12.5	0.0	0.0	0.0	0.0	7.8	0.0	20.3
29	0.0	****	0.0	0.0	0.0	1.0	0.0	0.0	4.6	0.0	0.0	0.0	5.6
30	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	52.0	0.0	52.0
31	42.0	****	0.0	****	0.0	****	7.1	0.0	****	0.0	****	0.0	49.1
合計	154.3	48.7	65.5	167.4	46.2	132.7	19.6	79.5	47.1	122.5	139.8	112.6	1135.9
平均	25.7	12.2	13.1	41.8	15.4	12.1	6.5	26.5	11.8	30.6	20.0	28.2	20.3
最大	42.0	21.8	20.4	106.1	20.3	42.3	7.2	60.0	27.5	67.5	57.5	83.5	106.1
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	6.0	4.0	5.0	4.0	3.0	11.0	3.0	3.0	4.0	4.0	7.0	4.0	58.0

## 1998年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	3.3	0.0	0.0	0.1	0.0	0.0	0.0	0.0	3.4
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.1	20.1
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.8	0.0	0.0	0.0	0.0	10.8
5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.7	0.0	0.0	2.7
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.6	0.5	25.5	32.6
7	3.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	0.0	23.3
8	0.0	0.0	0.0	11.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.2
9	0.0	35.4	0.0	0.0	0.0	0.0	0.0	2.0	4.9	0.0	0.0	0.0	42.3
10	0.0	6.1	21.1	0.0	0.0	7.5	0.0	0.0	0.0	0.0	29.0	0.0	63.7
11	0.0	0.0	22.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	22.2
12	8.3	0.0	0.0	0.0	5.4	0.0	0.0	0.0	3.2	0.0	0.0	0.0	16.9
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	27.7	0.0	0.0	27.7
14	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.2	0.0	0.0	11.2
15	0.0	0.0	2.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.3
16	0.0	0.0	0.0	54.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	16.1	70.6
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
18	0.0	0.0	0.0	0.0	0.0	5.5	0.0	0.0	5.9	0.0	0.0	0.0	11.4
19	0.0	0.0	6.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.5
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
21	0.0	36.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	36.0
22	38.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	38.8
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.1	0.0	0.0	0.0	0.0	14.1
24	0.0	0.0	0.0	2.5	0.0	0.0	0.0	0.0	0.0	0.0	63.1	0.0	65.6
25	0.0	0.0	30.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	30.1
26	0.0	36.5	0.0	0.0	7.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	44.4
27	0.0	0.0	0.0	10.5	0.0	0.0	0.0	0.0	20.0	0.0	0.0	12.0	42.5
28	0.0	0.0	0.0	0.0	6.9	0.0	0.0	0.0	62.0	0.0	0.0	0.0	68.9
29	7.7	****	0.0	0.0	3.3	0.0	0.0	0.0	6.1	0.0	29.5	0.0	46.6
30	10.2	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.2
31	4.8	****	24.3	****	0.0	****	0.0	****	0.0	****	0.0	****	29.1
合計	73.1	114.0	106.5	78.7	26.8	13.0	0.0	27.0	122.1	48.2	122.1	73.7	805.2
平均	12.2	28.5	17.8	19.7	5.4	6.5	0.0	6.8	17.4	12.0	30.5	18.4	15.9
最大	38.8	36.5	30.1	54.5	7.9	7.5	0.0	14.1	62.0	27.7	63.1	25.5	63.1
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	6.0	4.0	6.0	4.0	5.0	2.0	0.0	4.0	7.0	4.0	4.0	4.0	50.0

## 1999年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	4.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	24.6
2	0.0	0.0	5.1	0.0	0.0	0.0	13.0	0.0	0.0	0.0	0.0	0.0	18.1
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	46.1	0.0	0.0	0.0	8.2	0.0	0.0	0.0	0.0	0.0	0.0	41.1	95.4
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
7	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	77.0	0.0	75.2	0.0	152.2
9	9.1	0.0	40.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	49.1
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
11	1.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	77.9	79.1
12	20.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.3
13	20.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.2
14	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	14.5	34.5
15	0.0	0.0	12.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.5
16	0.0	0.0	0.0	29.0	0.0	0.0	0.0	0.0	0.0	11.5	0.0	0.0	40.5
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
18	0.0	0.0	0.0	0.0	0.0	66.0	0.0	0.0	0.0	0.0	0.0	0.0	66.0
19	29.8	36.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	59.5	35.0	160.5
20	0.0	3.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.6
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
22	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
23	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
25	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	56.1	0.0	56.1
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
27	0.0	2.6	0.0	0.0	0.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.7
28	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.5
29	0.0	****	23.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.8
30	36.9	****	0.0	0.0	0.0	0.0	0.0	0.0	10.1	0.0	0.0	0.0	47.0
31	0.0	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	0.0	0.0
合計	175.1	51.5	81.4	29.0	8.3	66.0	13.0	0.0	107.1	11.5	190.8	188.5	922.2
平均	21.9	10.3	20.4	29.0	4.2	66.0	13.0	0.0	35.7	11.5	63.6	37.7	28.5
最大	46.1	36.2	40.0	29.0	8.2	66.0	13.0	0.0	77.0	11.5	75.2	77.9	77.9
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	8.0	5.0	4.0	1.0	2.0	1.0	1.0	0.0	3.0	1.0	3.0	5.0	34.0

## 2000年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	17.5	0.0	0.0	3.6	0.0	0.0	0.0	0.0	21.1
2	0.0	0.0	7.7	0.0	0.0	0.0	3.0	0.0	14.0	0.0	0.0	0.0	24.7
3	0.0	30.2	0.0	0.0	7.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	38.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	46.8	46.8
5	0.0	0.0	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5
6	0.0	72.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	72.5
7	0.0	0.0	0.0	0.0	0.0	2.0	0.0	0.0	0.0	0.0	0.0	0.0	2.0
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.2	12.2
9	0.0	0.0	24.2	0.0	0.0	0.0	103.6	0.0	0.0	0.0	0.0	0.0	127.8
10	0.0	0.0	24.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	24.3
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	40.0	0.0	0.0	40.0
12	0.0	0.0	53.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	53.2
13	0.0	12.2	0.0	17.9	0.0	0.0	0.0	5.1	0.0	0.0	119.0	0.0	154.2
14	0.0	0.0	63.2	0.0	0.0	0.0	0.0	0.0	9.0	0.0	0.0	19.8	92.0
15	0.0	0.0	0.0	0.0	6.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.3
16	0.0	0.0	0.0	0.0	0.0	12.2	0.0	0.0	0.0	0.0	0.0	0.0	12.2
17	0.0	0.0	0.0	26.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	26.7
18	0.0	0.0	2.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.1
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.8	0.0	3.8
21	0.0	110.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	110.2
22	0.0	0.0	10.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0
23	40.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.6	0.0	44.6
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	20.0
25	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
26	20.0	0.0	0.0	7.3	0.0	5.5	0.0	0.0	0.0	0.0	0.0	0.0	32.8
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.3	0.0	0.0	0.0	0.0	23.3
28	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.3	0.0	0.0	0.0	0.0	1.3
29	0.0	15.5	0.0	0.0	0.0	0.0	19.1	0.0	0.0	0.0	99.1	0.0	133.7
30	8.5	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.5
31	0.0	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0	0.0	0.0
合計	68.5	240.6	184.7	56.4	31.6	19.7	125.7	33.3	23.0	60.0	226.5	78.8	1148.8
平均	22.8	48.1	26.4	14.1	10.5	6.6	41.9	8.3	11.5	30.0	56.6	26.3	25.3
最大	40.0	110.2	63.2	26.7	17.5	12.2	103.6	23.3	14.0	40.0	119.0	46.8	119.0
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	3.0	5.0	7.0	4.0	3.0	3.0	3.0	4.0	2.0	2.0	4.0	3.0	43.0

## 2001年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.9	0.0	0.0	11.9
2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.5	7.5
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	0.0	10.9	0.0	0.0	0.0	0.0	7.5	0.0	0.0	6.7	0.0	0.0	25.1
6	0.0	0.0	0.0	45.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	45.3
7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
8	20.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.0
9	24.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	24.2
10	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
11	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.9	17.9
12	33.9	0.0	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	57.0
13	0.0	0.0	22.0	0.0	0.0	0.0	0.0	0.0	0.0	7.3	0.0	0.0	29.3
14	0.0	0.0	6.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	60.1	40.1	106.2
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	21.0	0.0	21.0
16	16.0	0.0	0.0	0.0	0.0	13.3	0.0	0.0	0.0	0.0	8.2	0.0	37.5
17	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.5	0.0	0.0	0.0	0.0	8.5
19	0.0	0.0	42.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	42.3
20	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.9	0.0	0.0	2.9
21	0.0	72.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.5	76.4
22	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
23	0.0	0.0	0.0	0.0	10.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.5
24	0.0	0.0	0.0	75.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	75.0
25	0.0	0.0	0.0	0.0	58.4	0.0	0.0	0.0	76.9	0.0	0.0	0.0	135.3
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.0	0.0	13.0
27	0.0	12.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.1
28	0.0	20.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.5	0.0	22.7
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	28.5	0.0	28.5
30	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	28.9	28.9
31	4.8	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0	3.5	8.3
合計	98.9	116.1	93.4	120.3	68.9	13.3	7.5	8.5	76.9	28.8	133.3	101.4	867.3
平均	19.8	29.0	23.4	60.2	34.4	13.3	7.5	8.5	76.9	7.2	22.2	16.9	26.6
最大	33.9	72.9	42.3	75.0	58.4	13.3	7.5	8.5	76.9	11.9	60.1	40.1	76.9
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	5.0	4.0	4.0	2.0	2.0	1.0	1.0	1.0	1.0	4.0	6.0	6.0	37.0

## 2002年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	16.8	0.0	25.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	76.6	119.1
2	0.0	0.0	0.0	0.0	0.0	0.0	3.5	0.0	0.0	0.0	0.0	29.9	33.4
3	0.0	29.7	0.0	0.0	0.0	0.0	10.5	0.0	0.0	0.0	15.8	5.5	61.5
4	0.0	4.9	0.0	0.0	0.0	0.0	0.2	0.0	0.0	0.0	0.0	1.5	6.6
5	16.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	16.9
6	0.0	0.0	0.0	0.0	0.0	17.1	0.0	0.0	0.0	0.0	0.0	0.0	17.1
7	0.0	0.0	0.0	0.0	0.0	5.9	0.0	0.0	0.0	0.0	0.0	71.1	77.0
8	0.0	0.0	3.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.3	8.8
9	0.0	0.0	7.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	38.0	45.7
10	0.0	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.7	9.2
11	0.0	0.0	0.0	2.0	0.0	1.1	0.0	0.0	0.0	0.0	0.0	0.0	3.1
12	0.0	0.2	30.3	13.9	0.0	0.0	0.0	0.0	3.0	0.0	0.0	17.5	64.9
13	0.0	0.0	0.0	22.5	0.0	0.0	0.0	0.0	0.2	0.0	0.0	0.4	23.1
14	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.5	10.0
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.8	0.0	0.0	7.2	8.0
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.0	0.0	4.7	9.7
17	0.0	0.5	0.0	3.5	0.0	0.0	0.0	0.0	0.0	0.8	0.0	0.0	4.8
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	0.0	49.1	9.5	0.0	9.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	68.1
20	0.0	0.0	0.0	0.0	6.5	0.0	0.0	10.3	0.0	0.0	0.0	70.6	87.4
21	0.0	49.9	1.0	0.0	0.0	0.0	0.0	3.3	0.0	0.4	2.2	0.0	56.8
22	0.0	0.0	0.0	0.0	0.0	0.0	9.5	0.1	0.0	0.0	0.0	0.0	9.6
23	0.0	4.9	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	9.0	15.9
24	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5	1.5
25	0.0	0.0	0.0	16.9	0.0	0.0	0.5	0.0	0.0	0.0	0.0	0.0	17.4
26	0.0	2.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.5
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.7	0.0	0.0	0.0	0.0	0.7
28	0.0	2.5	0.0	0.0	0.0	0.0	0.0	23.1	0.0	0.0	7.6	0.0	33.2
29	0.0	****	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	5.8	5.0	12.0
30	0.0	****	0.0	1.2	20.1	0.0	0.0	0.0	0.0	2.8	5.0	0.0	29.1
31	27.7	****	0.0	****	0.0	****	0.0	0.0	****	0.0	****	1.5	29.2
合計	65.9	144.2	83.7	61.2	36.1	24.1	24.2	37.5	4.0	9.0	36.9	355.5	882.3
平均	16.5	16.0	10.5	8.7	12.0	8.0	4.8	7.5	1.3	2.2	6.2	19.8	9.5
最大	27.7	49.9	30.3	22.5	20.1	17.1	10.5	23.1	3.0	5.0	15.8	76.6	76.6
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	4.0	9.0	8.0	7.0	3.0	3.0	5.0	5.0	3.0	4.0	6.0	18.0	75.0

## 2003年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	5.0	0.0	0.1	0.0	0.0	0.0	0.0	0.0	0.0	5.7	5.4	16.2
2	5.7	11.0	0.0	6.9	0.0	0.0	0.0	0.0	0.0	3.4	0.0	2.1	29.1
3	5.3	0.0	108.7	16.0	0.0	5.5	0.0	0.0	0.0	3.8	0.0	6.2	145.5
4	0.0	0.0	0.0	8.9	0.0	0.8	0.0	0.0	0.0	0.0	0.0	21.6	31.3
5	0.6	1.7	0.0	2.1	0.0	0.0	0.0	0.0	0.0	108.8	0.0	9.5	122.7
6	0.4	3.9	4.4	0.0	0.0	0.0	0.0	14.6	0.0	0.0	0.0	3.7	27.0
7	0.0	0.0	0.0	0.0	0.0	0.0	2.4	0.0	0.0	0.0	0.0	0.0	2.4
8	0.0	0.2	7.5	0.0	0.0	0.0	5.1	0.0	34.6	0.0	0.0	0.0	47.4
9	0.0	0.3	8.5	42.5	0.0	0.0	0.0	0.0	0.9	8.3	0.0	1.7	62.2
10	0.0	0.0	0.2	0.0	0.0	0.0	0.0	0.0	0.0	2.7	45.2	0.1	48.2
11	97.5	1.6	0.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.9	107.5
12	28.1	4.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.2	0.0	50.7
13	13.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.5
14	2.5	0.0	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.8	6.8
15	0.0	0.0	0.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.1
16	0.0	12.6	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0	27.1
17	0.0	7.0	0.2	0.5	0.0	0.0	0.0	0.0	0.0	0.0	0.3	0.0	8.0
18	56.2	0.1	0.0	34.9	0.0	0.0	0.0	0.0	0.0	0.0	28.3	0.0	119.5
19	8.7	0.0	0.2	2.5	0.0	0.0	0.0	0.0	0.0	33.7	0.0	0.0	45.1
20	0.0	15.5	18.0	0.0	0.0	0.0	0.0	0.0	8.5	5.0	0.0	0.0	47.0
21	0.0	0.0	0.2	0.0	0.0	0.0	0.0	0.0	0.3	0.0	0.0	0.0	0.5
22	0.0	0.0	0.0	0.0	2.9	0.0	0.0	0.0	0.0	0.6	0.0	30.0	33.5
23	29.0	0.0	0.0	0.0	0.5	0.0	0.0	13.6	0.0	0.0	0.0	0.0	43.1
24	0.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.4	0.0	0.0	0.0	0.6
25	0.0	0.2	18.7	0.0	0.0	0.0	0.0	12.3	0.0	0.0	7.8	1.0	40.0
26	0.0	0.2	0.0	0.0	2.7	0.0	0.0	0.0	0.0	4.0	0.0	0.0	6.9
27	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.4	1.9
28	1.1	0.0	0.0	0.0	0.0	1.8	0.0	0.0	0.6	0.0	12.8	3.5	19.8
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.3	0.0	4.3
30	0.0	****	1.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	68.4	0.0	70.1
31	0.0	****	3.4	****	0.0	****	0.0	0.0	****	5.3	****	0.0	8.7
合計	250.3	63.7	178.3	114.4	6.1	8.1	7.5	40.5	45.3	175.6	191.0	105.9	1186.7
平均	17.9	4.5	11.1	12.7	2.0	2.7	3.8	13.5	7.6	17.6	21.2	7.1	10.1
最大	97.5	15.5	108.7	42.5	2.9	5.5	5.1	14.6	34.6	108.8	68.4	30.0	108.8
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	14.0	14.0	16.0	9.0	3.0	3.0	2.0	3.0	6.0	10.0	9.0	15.0	104.0

## 2004年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.2	0.0	0.0	8.2
2	0.0	0.0	0.0	3.1	0.0	0.0	0.0	0.0	0.0	1.1	0.0	0.0	4.2
3	0.0	0.0	60.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.9	63.2
4	0.0	1.1	0.0	0.0	14.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.6
5	3.0	37.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.3	0.0	44.6
6	0.0	0.4	0.0	0.4	4.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.2
7	0.0	0.0	0.0	0.0	0.0	0.0	52.9	0.0	0.0	0.0	0.0	0.0	52.9
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.0	15.0
9	0.0	0.0	2.4	0.0	0.0	0.0	6.2	0.0	0.0	7.7	0.0	31.9	48.2
10	0.0	0.0	0.0	0.0	0.0	44.9	0.0	0.0	0.0	0.0	29.1	0.3	74.3
11	11.3	0.0	6.2	0.0	0.0	0.5	0.0	0.0	0.0	0.0	0.0	1.0	19.0
12	0.0	2.2	0.0	8.6	17.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	28.3
13	1.9	3.4	0.4	0.0	0.0	0.0	0.0	0.0	0.0	39.5	0.0	11.9	57.1
14	4.0	0.0	16.6	2.1	0.0	0.0	0.0	0.0	0.0	1.3	0.0	1.1	25.1
15	0.0	0.4	6.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.7	14.0	27.5
16	0.0	0.0	0.0	1.1	0.0	0.0	0.0	0.0	0.0	0.0	17.9	2.4	21.4
17	0.0	0.0	8.3	3.6	0.0	0.0	0.0	0.0	0.0	69.8	13.8	0.0	95.5
18	0.0	144.2	0.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	144.6
19	37.4	0.1	0.0	2.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	39.8
20	1.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.9	2.8
21	9.9	0.0	0.0	0.0	0.0	2.2	0.0	0.0	0.0	0.0	0.0	0.0	12.1
22	0.2	0.0	0.0	0.0	0.0	1.6	0.0	0.0	0.0	0.0	0.0	0.0	1.8
23	0.0	0.0	0.0	4.9	0.0	4.7	0.0	0.0	0.0	44.5	0.0	0.0	54.1
24	0.0	0.0	0.0	0.0	1.7	1.0	0.0	0.0	0.0	45.2	0.0	0.0	47.9
25	0.0	0.0	0.0	0.0	22.1	6.6	0.0	0.0	0.0	1.3	2.0	0.0	32.0
26	0.0	0.0	0.0	0.0	4.8	26.5	0.0	0.0	0.0	5.6	0.0	0.0	36.9
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.3	10.2	0.0	12.5
28	2.2	0.0	0.0	0.0	0.0	0.0	53.5	0.0	64.1	0.0	0.0	0.0	119.8
29	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	3.7	0.0	5.1	12.7	22.5
30	0.0	****	2.0	0.0	0.0	0.0	0.0	0.0	****	0.0	0.0	25.8	27.8
31	0.0	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0	0.0	0.0
合計	71.8	189.1	104.0	26.1	64.5	88.0	112.6	0.0	67.8	226.5	89.1	120.4	1159.9
平均	8.0	23.6	10.4	3.3	10.8	11.0	37.5	0.0	33.9	20.6	11.1	9.3	16.3
最大	37.4	144.2	60.3	8.6	22.1	44.9	53.5	0.0	64.1	69.8	29.1	31.9	144.2
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	9.0	8.0	10.0	8.0	6.0	8.0	3.0	0.0	2.0	11.0	8.0	13.0	86.0

## 2005年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	44.7	44.7
2	4.3	0.0	0.0	4.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.0
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.2	0.0	0.0	3.2
5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	42.6	0.0	42.6
6	0.0	0.7	0.0	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	57.1	59.0
7	0.0	0.0	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.0
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.5	0.0	0.0	3.5
9	0.0	52.0	0.0	0.0	0.0	2.7	0.0	0.0	0.0	0.0	0.0	0.0	54.7
10	24.8	6.7	0.0	0.0	0.0	0.0	0.0	0.0	7.5	0.0	82.2	2.6	123.8
11	1.2	0.8	0.0	0.0	0.0	0.0	0.0	0.0	0.5	0.0	10.5	0.0	13.0
12	0.0	0.0	0.0	23.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.5
13	5.8	0.0	44.3	0.0	0.0	44.5	0.0	0.0	0.0	0.0	0.1	1.0	95.7
14	0.6	0.0	0.0	0.0	0.5	0.0	0.0	0.0	0.0	18.2	0.0	0.0	19.3
15	7.6	0.0	0.0	0.0	23.1	0.0	0.0	0.0	0.0	2.0	0.0	0.0	32.7
16	0.0	0.0	0.0	0.0	9.4	0.0	12.2	0.0	0.0	8.2	3.2	0.0	33.0
17	0.0	0.0	0.0	0.0	1.8	0.0	0.0	0.0	0.0	24.6	0.0	2.5	28.9
18	0.0	0.0	0.0	0.0	0.5	0.0	5.5	0.0	0.0	0.0	0.2	0.0	6.2
19	0.0	0.0	3.0	0.0	0.0	0.7	0.0	0.0	0.0	0.0	15.7	1.0	20.4
20	0.0	0.0	0.0	0.0	30.9	1.3	0.0	0.0	0.0	0.0	0.0	0.3	32.5
21	0.0	0.0	1.4	0.0	0.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.0
22	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
23	0.0	0.0	0.0	6.1	0.3	0.0	0.0	2.0	0.0	0.0	0.0	0.0	8.4
24	0.0	0.0	0.0	4.4	0.0	0.0	0.0	0.0	58.0	0.0	17.0	38.0	117.4
25	20.0	0.0	0.0	4.3	0.0	0.0	0.0	0.0	0.1	27.5	0.0	0.7	52.6
26	0.0	3.2	0.0	0.0	0.0	6.9	0.0	0.0	0.0	0.0	0.0	0.2	10.3
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
28	0.0	4.5	0.0	0.3	0.0	0.0	0.0	0.0	0.0	4.0	0.0	4.7	13.5
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.9	0.0	2.6	14.5
30	0.0	****	5.0	0.0	0.0	0.0	0.0	31.5	9.8	0.0	0.0	0.0	46.3
31	8.9	****	0.0	****	0.0	****	0.0	36.2	****	0.0	****	40.1	85.2
合計	73.2	67.9	53.7	43.3	69.3	56.1	17.7	69.7	75.9	103.1	171.5	195.5	996.9
平均	9.2	11.3	13.4	7.2	6.9	11.2	8.8	23.2	15.2	11.5	21.4	15.0	12.9
最大	24.8	52.0	44.3	23.5	30.9	44.5	12.2	36.2	58.0	27.5	82.2	57.1	82.2
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	8.0	6.0	4.0	6.0	10.0	5.0	2.0	3.0	5.0	9.0	8.0	13.0	79.0



## 2006年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	5.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.5	0.0	0.0	0.0	15.4
2	1.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.2
3	15.0	0.0	0.0	0.2	0.0	30.7	0.0	0.0	0.0	0.0	4.0	37.0	86.9
4	0.0	0.0	13.9	43.3	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	58.2
5	0.0	0.0	0.0	1.9	0.0	0.3	0.0	0.0	0.0	10.1	19.0	0.0	31.3
6	0.0	0.0	0.0	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	1.0
7	0.0	0.0	0.0	0.0	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	1.2
8	0.0	10.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.0	13.9
9	6.7	34.2	0.0	0.0	0.0	74.0	0.0	1.1	4.5	0.0	0.0	44.5	165.0
10	7.2	0.0	6.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.9
11	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.0	0.0	0.0	8.0
12	40.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	40.1
13	2.5	68.7	3.7	0.0	0.0	0.0	11.5	0.0	0.0	0.3	0.0	0.0	86.7
14	0.0	0.0	2.4	1.5	0.0	0.0	3.1	0.0	0.0	32.5	0.0	0.0	39.5
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.0	22.1	0.0	0.0	24.1
16	0.0	0.0	0.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.6
17	0.0	28.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	28.3
18	0.0	0.0	2.5	0.0	8.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.7
19	20.5	0.0	0.0	0.0	10.5	0.0	0.0	0.0	26.8	4.7	0.0	1.0	63.5
20	2.3	0.0	88.5	0.0	1.4	4.1	0.0	0.0	3.5	0.0	0.0	47.5	147.3
21	3.5	0.0	0.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.7	7.4
22	12.1	0.0	0.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.2
23	0.0	24.8	0.0	0.0	0.0	0.0	10.2	0.0	13.0	14.6	0.0	0.0	62.6
24	1.0	10.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	11.8
25	0.0	0.0	4.1	0.0	0.0	11.7	0.0	0.0	0.0	0.0	0.0	12.5	28.3
26	0.0	0.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.9
27	0.0	19.7	0.0	0.0	0.0	0.0	0.0	0.1	27.3	0.0	0.0	0.0	47.1
28	0.0	3.4	8.0	0.0	0.0	0.0	0.0	0.0	4.3	0.0	1.1	0.0	16.8
29	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.5	7.5
30	0.0	****	1.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.8
31	0.0	****	1.5	****	0.0	****	0.0	****	20.2	****	0.0	0.0	21.7
合計	122.0	201.2	134.0	46.9	20.1	124.0	24.8	1.2	90.9	108.5	24.1	157.2	1054.9
平均	9.4	22.4	10.3	11.7	6.7	15.5	8.3	0.6	11.4	13.6	8.0	17.5	11.3
最大	40.1	68.7	88.5	43.3	10.5	74.0	11.5	1.1	27.3	32.5	19.0	47.5	88.5
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	13.0	9.0	13.0	4.0	3.0	8.0	3.0	2.0	8.0	8.0	3.0	9.0	83.0

## 2007年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	5.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	5.8
2	0.0	0.0	6.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.0	0.0	18.5
3	8.2	4.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	32.5	0.0	45.0
4	0.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.1	10.2
5	0.0	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	72.3	73.3
6	1.9	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	55.5	0.0	0.0	57.4
7	0.0	0.0	0.0	0.0	7.0	0.0	0.0	0.0	0.0	0.0	7.8	8.4	23.2
8	2.6	0.0	0.0	0.0	1.7	0.0	0.5	0.0	0.0	0.0	11.8	0.0	16.6
9	11.9	15.3	2.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	29.4
10	0.0	0.3	9.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.5	0.0	11.9
11	1.3	0.5	1.1	44.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	16.0	63.4
12	1.5	66.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	67.6
13	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.1	0.0	5.8	11.9
14	0.6	13.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.0	18.7
15	2.1	41.0	7.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.5	59.8
16	65.5	15.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	80.8
17	5.2	0.0	0.0	0.0	17.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	22.7
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.5	0.0	14.5
20	15.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.6	0.0	21.8
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
22	0.0	7.1	0.0	0.5	62.1	0.0	13.5	0.0	0.0	0.0	0.0	0.0	83.2
23	0.0	0.0	0.0	3.7	0.0	0.0	31.5	0.0	0.0	0.0	25.0	0.0	60.2
24	45.5	0.0	0.0	0.0	0.0	0.0	19.1	0.0	0.0	0.0	0.0	0.0	64.6
25	4.4	0.0	0.0	4.5	0.0	0.0	0.0	0.0	0.0	15.5	0.0	0.0	24.4
26	0.0	0.0	0.0	0.4	0.0	0.0	0.0	0.5	0.0	0.0	0.0	0.0	0.9
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	44.2	44.2
28	63.1	4.1	35.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	102.7
29	7.3	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.3
30	187.3	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.3	0.0	0.0	187.6
31	0.0	****	0.0	****	0.0	****	0.0	0.0	****	18.5	****	0.0	18.5
合計	423.7	176.4	62.6	53.6	88.3	0.0	64.6	0.5	0.0	91.9	112.7	171.8	1246.1
平均	24.9	14.7	8.9	10.7	22.1	0.0	16.1	0.5	0.0	18.4	14.1	19.1	15.0
最大	187.3	66.1	35.5	44.5	62.1	0.0	31.5	0.5	0.0	55.5	32.5	72.3	187.3
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	17.0	12.0	7.0	5.0	4.0	0.0	4.0	1.0	0.0	5.0	8.0	9.0	72.0

## 2008年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	1.9	3.6	0.0	69.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	75.0
2	0.0	0.0	0.2	0.0	0.0	0.0	0.0	0.7	0.0	0.0	8.3	0.0	9.2
3	78.6	0.0	9.0	0.0	0.0	0.0	0.0	0.0	18.3	7.3	0.0	0.0	113.2
4	0.0	0.0	26.2	0.0	0.0	0.0	0.0	0.0	20.2	62.0	0.0	0.0	108.4
5	10.1	0.0	0.5	0.0	0.0	0.0	0.0	0.0	0.0	4.6	0.0	0.0	15.2
6	0.0	0.0	9.0	0.0	0.0	0.0	0.0	0.0	0.0	2.5	7.3	0.0	18.8
7	0.0	0.0	21.1	0.0	0.0	0.0	24.4	10.5	0.0	0.0	0.0	0.0	56.0
8	0.0	0.0	3.7	0.0	0.0	0.5	2.2	0.0	0.0	0.0	0.0	0.0	5.1
9	0.0	11.2	30.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.7	0.0	59.0
10	0.0	0.0	23.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.6	47.1
11	0.0	0.0	0.6	0.0	4.9	0.0	0.0	0.0	0.0	0.0	25.6	2.7	33.8
12	0.0	0.0	0.0	1.8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.8
13	12.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	12.5
14	14.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.4
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5	5.5	0.0	6.0
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
17	0.0	14.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	14.2
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	8.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	9.0	17.0
20	90.3	9.5	2.1	0.0	0.0	0.0	0.0	0.8	0.0	0.0	0.0	0.0	102.7
21	54.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	15.0	69.0
22	4.1	1.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.7	0.0	22.8	29.7
23	3.8	13.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.0	28.0
24	0.0	0.9	0.0	0.0	0.0	0.0	0.0	0.0	9.6	0.0	0.0	0.0	10.5
25	0.0	1.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.2	0.0	4.2
26	12.2	30.0	0.0	0.0	0.0	0.0	0.0	0.7	0.0	0.0	0.0	0.0	42.9
27	0.0	13.0	1.9	5.4	18.4	0.0	0.0	0.0	4.4	0.0	0.0	0.0	43.1
28	14.0	62.2	0.0	0.0	0.0	0.0	0.0	11.5	0.0	0.0	0.0	0.0	87.7
29	0.0	29.2	0.0	5.4	0.0	0.0	16.5	0.0	0.0	35.5	1.5	0.0	88.1
30	0.0	****	0.0	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	0.7	1.9
31	11.0	****	69.5	****	0.0	****	12.2	0.0	****	0.0	****	0.0	92.7
合計	314.9	189.1	197.4	82.1	24.5	0.5	55.3	22.7	49.6	118.5	69.1	89.9	1213.6
平均	24.2	15.8	15.2	20.5	8.2	0.5	13.8	7.6	9.9	14.8	9.9	11.2	12.6
最大	90.3	62.2	69.5	69.5	18.4	0.5	24.4	11.5	20.2	62.0	25.6	23.6	90.3
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	13.0	12.0	13.0	4.0	3.0	1.0	4.0	3.0	5.0	8.0	7.0	8.0	81.0

## 2009年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	29.7	0.0	0.0	0.0	3.0	32.7
2	28.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.9	0.0	0.0	0.0	31.9
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.0	0.0	0.0	0.0	0.0	4.4	0.0	5.7	0.0	0.0	0.0	10.1
5	0.0	0.0	0.0	1.1	0.0	0.0	8.0	0.0	0.0	0.0	3.5	0.0	12.6
6	0.0	0.2	0.0	1.0	0.0	0.0	0.0	0.0	0.0	39.0	0.0	0.0	40.2
7	0.0	24.1	0.0	16.0	0.9	0.0	1.6	0.0	0.0	0.0	7.7	2.0	52.3
8	0.7	0.0	0.0	0.0	0.0	4.0	0.0	0.0	0.0	0.0	16.5	0.0	21.2
9	0.0	3.5	0.0	0.0	0.0	0.0	7.3	0.0	0.0	0.0	0.0	0.0	10.8
10	0.0	2.5	3.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	5.5
11	0.0	103.1	11.5	0.0	0.0	0.0	6.9	0.0	0.0	17.2	0.0	5.3	144.0
12	0.0	0.0	0.5	0.0	13.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.7
13	0.0	0.0	0.0	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.2
14	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
15	11.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.3	0.0	0.0	15.3
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
17	2.5	9.0	5.0	0.0	0.0	0.0	0.0	1.3	0.0	0.0	0.0	0.0	17.8
18	39.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	39.3
19	0.0	3.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.9	0.0	0.0	24.4
20	0.0	0.0	17.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.3
21	0.0	0.3	0.0	0.0	0.0	0.0	3.0	6.6	0.0	0.0	0.0	0.0	9.9
22	0.0	0.0	0.5	0.0	0.0	0.0	32.8	0.0	20.0	0.0	0.0	0.0	53.3
23	0.0	13.0	0.0	0.0	0.0	10.2	4.3	0.0	0.0	0.0	0.0	4.0	31.5
24	0.0	0.0	0.7	12.1	0.0	31.4	0.0	0.0	0.0	9.5	0.0	0.0	53.7
25	58.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	58.1
26	0.0	0.0	40.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.5	50.5
27	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.0	68.0	0.0	0.0	79.0
28	9.3	0.0	0.0	0.0	52.4	0.0	0.0	0.0	0.0	0.0	5.0	0.0	66.7
29	0.0	****	0.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5
30	0.0	****	0.1	0.0	0.0	****	0.0	0.0	0.0	0.0	55.5	7.0	62.6
31	0.0	****	41.5	****	0.0	****	0.0	0.0	****	0.0	****	0.0	41.5
合計	148.9	159.2	120.6	30.2	67.7	45.6	68.3	37.6	40.6	158.9	88.2	31.8	997.6
平均	21.3	17.7	11.0	7.6	16.9	15.2	8.5	12.5	10.2	26.5	17.6	5.3	14.2
最大	58.1	103.1	41.5	16.0	52.4	31.4	32.8	29.7	20.0	68.0	55.5	10.5	103.1
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	7.0	9.0	11.0	4.0	4.0	3.0	8.0	3.0	4.0	6.0	5.0	6.0	70.0

## 2010年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.0	0.0	7.0
2	84.9	0.0	0.0	0.0	3.8	0.0	0.0	0.0	0.0	0.5	0.0	0.0	89.2
3	3.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.0
4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
5	0.0	4.3	0.0	10.6	0.0	0.0	0.0	0.0	0.0	0.0	12.6	0.0	27.5
6	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5
7	3.5	0.0	0.0	0.0	0.4	0.0	24.0	0.0	0.0	0.0	0.0	0.0	27.9
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
9	0.0	4.2	0.0	0.0	0.0	0.0	2.0	0.0	0.0	0.0	0.0	0.0	6.2
10	0.0	40.0	78.0	78.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	196.0
11	0.0	0.5	37.5	37.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	75.5
12	100.9	1.0	0.0	0.0	0.0	0.0	2.1	0.0	0.0	0.0	0.0	37.7	141.7
13	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.7	0.0	0.0	0.0	6.7
14	0.0	20.0	1.6	1.6	0.0	0.0	11.0	0.0	0.0	0.0	0.0	0.0	34.2
15	0.0	0.0	0.0	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5
16	0.0	5.5	0.0	0.0	0.0	0.0	12.5	0.0	0.0	0.0	0.0	0.0	18.0
17	5.5	3.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.6
18	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
19	47.5	0.0	0.0	5.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	52.5
20	0.0	0.5	0.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.0	0.0	2.0
21	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
22	0.0	0.0	0.0	65.0	0.0	0.0	0.0	0.0	0.0	25.0	0.0	0.0	90.0
23	0.0	0.0	65.0	0.0	3.9	0.0	0.0	0.0	0.0	0.0	10.2	0.0	79.1
24	0.0	0.0	0.0	0.0	1.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.5
25	0.0	9.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	25.8	35.3
26	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.0
27	0.0	40.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	90.2	0.0	130.2
28	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.8	0.0	0.0	40.0	41.8
29	0.0	****	1.0	0.0	0.0	0.0	0.0	12.9	6.0	6.2	0.0	0.0	26.1
30	0.0	****	0.0	0.0	1.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.7
31	0.0	****	0.0	****	****	****	0.0	0.0	****	0.0	****	0.0	0.0
合計	249.8	132.6	183.6	199.2	11.3	0.0	51.6	12.9	14.5	31.7	121.0	103.5	1111.7
平均	35.7	11.0	30.6	28.5	2.3	0.0	10.3	12.9	4.8	10.6	24.2	34.5	18.7
最大	100.9	40.0	78.0	78.0	3.9	0.0	24.0	12.9	6.7	25.0	90.2	40.0	100.9
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	7.0	12.0	6.0	7.0	5.0	0.0	5.0	1.0	3.0	3.0	5.0	3.0	57.0

## 2011年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	0.0	0.0	0.0	1.0	0.0	0.0	0.0	1.7	0.0	0.0	0.0	0.0	2.7
2	0.0	0.0	0.0	2.5	0.0	0.0	0.0	0.0	0.0	6.5	0.0	0.0	9.0
3	0.0	0.0	5.7	13.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.7
4	1.5	3.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.0	10.6
5	5.0	23.6	0.0	0.5	0.0	0.0	0.0	0.0	0.0	0.0	38.8	0.0	67.9
6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
7	0.0	49.5	0.0	0.0	0.0	0.1	0.0	0.0	0.0	0.0	0.0	0.0	49.6
8	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.2	0.0	0.0	0.0	18.2
9	0.0	0.0	27.8	0.0	0.0	17.6	0.0	0.0	0.0	0.0	0.0	31.5	76.9
10	3.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.2	0.0	11.7
11	0.0	15.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.2	0.0	0.0	22.8
12	12.0	0.0	0.0	2.5	0.0	8.5	2.7	0.0	0.0	0.0	0.0	31.5	57.2
13	3.5	3.5	8.5	0.0	0.0	0.0	0.0	0.0	0.0	20.0	0.0	0.0	35.5
14	60.0	0.0	0.0	0.2	0.0	0.0	0.0	0.0	0.0	23.5	0.0	0.0	83.7
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.0	17.0
16	60.7	0.0	0.0	0.0	0.0	0.0	8.6	0.0	0.0	0.0	0.0	0.5	69.8
17	0.0	5.4	0.0	0.0	0.0	0.0	0.0	0.0	14.4	0.0	0.0	0.0	19.8
18	0.0	0.0	1.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.1
19	0.0	13.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.4
20	0.0	8.5	0.0	0.0	0.0	0.0	26.2	0.0	0.0	0.0	0.0	0.0	34.7
21	0.0	1.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.5	0.0	4.7
22	0.0	35.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	35.5
23	0.0	30.5	2.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	32.6
24	0.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.5
25	1.3	5.2	0.0	0.0	17.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	23.5
26	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	1.7	0.0	1.7
27	18.1	0.0	14.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	32.3
28	0.0	0.0	6.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	6.3
29	0.0	****	0.0	0.0	0.0	5.2	2.3	0.0	0.0	60.2	0.0	0.0	67.7
30	0.0	****	0.0	****	0.0	****	3.5	0.0	0.0	0.0	0.0	0.0	3.5
31	0.0	****	****	****	****	****	12.9	0.0	****	0.0	****	0.0	12.9
合計	166.1	195.0	65.7	19.7	17.0	31.4	56.2	1.7	32.6	117.4	52.2	86.5	841.5
平均	16.6	16.2	9.4	3.3	17.0	7.8	9.4	1.7	16.3	23.5	13.0	17.3	12.6
最大	60.7	49.5	27.8	13.0	17.0	17.6	26.2	1.7	18.2	60.2	38.8	31.5	60.7
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	10.0	12.0	7.0	6.0	1.0	4.0	6.0	1.0	2.0	5.0	4.0	5.0	63.0


## 2012年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	18.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	18.0
2	0.0	0.5	5.3	0.0	0.0	0.0	0.0	0.0	0.0	25.9	0.0	0.0	31.7
3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
4	0.0	0.3	0.0	0.0	0.0	35.0	0.0	0.0	0.0	0.0	0.0	0.0	35.3
5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
6	12.5	0.0	0.0	0.0	0.0	3.6	3.6	0.0	0.0	0.0	23.5	0.0	43.2
7	0.0	0.0	28.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	39.5	67.5
8	0.0	0.0	0.0	2.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.5
9	0.0	49.1	0.0	14.9	0.0	0.0	0.0	0.0	0.0	14.0	0.0	0.0	78.0
10	17.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	17.0
11	30.0	10.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	40.0
12	1.5	0.0	0.0	0.0	40.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	41.6
13	0.0	0.0	37.2	0.0	41.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	78.7
14	0.0	67.5	0.0	4.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	71.5
15	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
16	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	8.5	0.0	0.0	8.5
17	0.0	0.0	0.0	0.0	0.0	0.7	0.0	0.0	0.0	0.0	0.0	0.0	0.7
18	0.0	0.0	0.0	0.0	13.2	0.0	0.0	42.3	30.1	0.0	0.0	0.0	85.6
19	0.0	0.0	5.5	0.0	0.0	58.4	0.0	0.0	0.0	0.0	90.5	0.0	154.4
20	0.0	0.0	0.0	0.0	0.0	58.6	0.0	0.0	40.1	0.0	0.0	0.0	98.7
21	0.0	13.1	0.0	0.0	5.5	35.0	0.0	0.0	0.0	0.0	0.0	0.0	53.6
22	0.0	0.0	63.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	63.1
23	0.0	5.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	55.5	0.0	60.6
24	0.0	4.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	4.5
25	64.5	3.0	6.5	34.0	0.0	0.0	12.0	0.0	0.0	0.0	0.0	0.0	120.0
26	0.0	64.2	12.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	13.2	89.6
27	0.0	3.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3.5
28	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
29	1.5	1.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	10.0	0.0	12.5
30	0.0	****	0.0	7.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	7.0
31	0.0	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0	****	0.0
合計	145.0	221.8	157.8	62.4	100.3	191.3	15.6	42.3	70.2	48.4	179.5	52.7	1287.3
平均	20.7	18.5	22.5	12.5	25.1	31.9	7.8	42.3	35.1	16.1	44.9	26.4	25.3
最大	64.5	67.5	63.1	34.0	41.5	58.6	12.0	42.3	40.1	25.9	90.5	39.5	90.5
最小	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	7.0	12.0	7.0	5.0	4.0	6.0	2.0	1.0	2.0	3.0	4.0	2.0	55.0

## 2013年

日付	1月	2月	3月	4月	5月	6月	7月	8月	9月	10月	11月	12月	合計
1	25.5	43.9	0.0	0.0	****	55.1	0.0	0.0	0.0	0.0	19.3	0.0	143.8
2	0.0	0.0	0.0	26.5	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	26.5
3	0.0	0.0	8.5	0.0	****	0.0	0.0	0.0	6.0	0.0	0.0	0.0	14.5
4	0.0	0.0	0.0	20.5	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	20.5
5	0.0	0.0	0.0	40.4	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	40.4
6	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
7	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
8	22.5	0.0	0.0	0.0	****	0.0	0.0	0.0	1.5	0.0	0.0	0.0	24.0
9	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
10	0.0	0.0	2.7	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	2.7
11	0.0	28.5	0.0	0.0	****	1.5	0.0	0.0	0.0	0.0	0.0	0.0	30.0
12	0.0	0.0	0.0	32.5	****	0.0	0.0	0.0	5.7	0.0	0.0	13.3	51.5
13	0.0	1.5	39.6	0.0	****	0.0	0.0	0.0	5.3	0.0	0.0	14.2	60.6
14	0.0	0.0	0.0	24.5	****	0.0	0.0	0.0	0.0	6.5	9.3	0.0	40.3
15	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
16	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	13.2	13.2
17	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	30.1	0.0	0.0	30.1
18	0.0	0.0	0.0	0.0	****	12.2	0.0	0.0	0.0	12.2	0.0	0.0	24.4
19	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	4.2	0.0	4.2
20	0.0	8.5	0.0	0.0	****	0.0	14.6	0.0	0.0	0.0	11.4	16.5	51.0
21	0.0	0.0	0.0	0.0	****	4.5	0.0	0.0	0.0	0.0	0.0	0.0	4.5
22	0.0	0.0	0.0	0.0	****	8.0	0.0	0.0	0.0	38.2	0.0	20.2	66.4
23	0.0	0.0	11.2	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	11.2
24	0.0	0.0	9.1	0.0	****	20.7	0.0	0.0	0.0	20.1	0.0	14.8	64.7
25	20.1	6.5	0.0	0.0	****	25.0	0.0	0.0	0.0	0.0	0.0	0.0	51.6
26	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
27	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
28	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
29	0.0	****	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	29.0	0.0	29.0
30	0.0	****	0.0	0.0	****	7.9	0.0	0.0	0.0	1.5	0.0	0.0	9.4
31	0.0	****	0.0	****	****	****	0.0	0.0	****	0.0	****	15.5	15.5
合計	68.1	88.9	71.1	144.4	****	134.9	14.6	0.0	18.5	108.6	73.2	107.7	830.0
平均	22.7	17.8	14.2	28.9	****	16.9	14.6	0.0	4.6	18.1	14.6	15.4	16.8
最大	25.5	43.9	39.6	40.4	****	55.1	14.6	0.0	6.0	38.2	29.0	20.2	55.1
最小	0.0	0.0	0.0	0.0	****	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
個数	3.0	5.0	5.0	5.0	****	8.0	1.0	0.0	4.0	6.0	5.0	7.0	49.0

(2) 流域面積

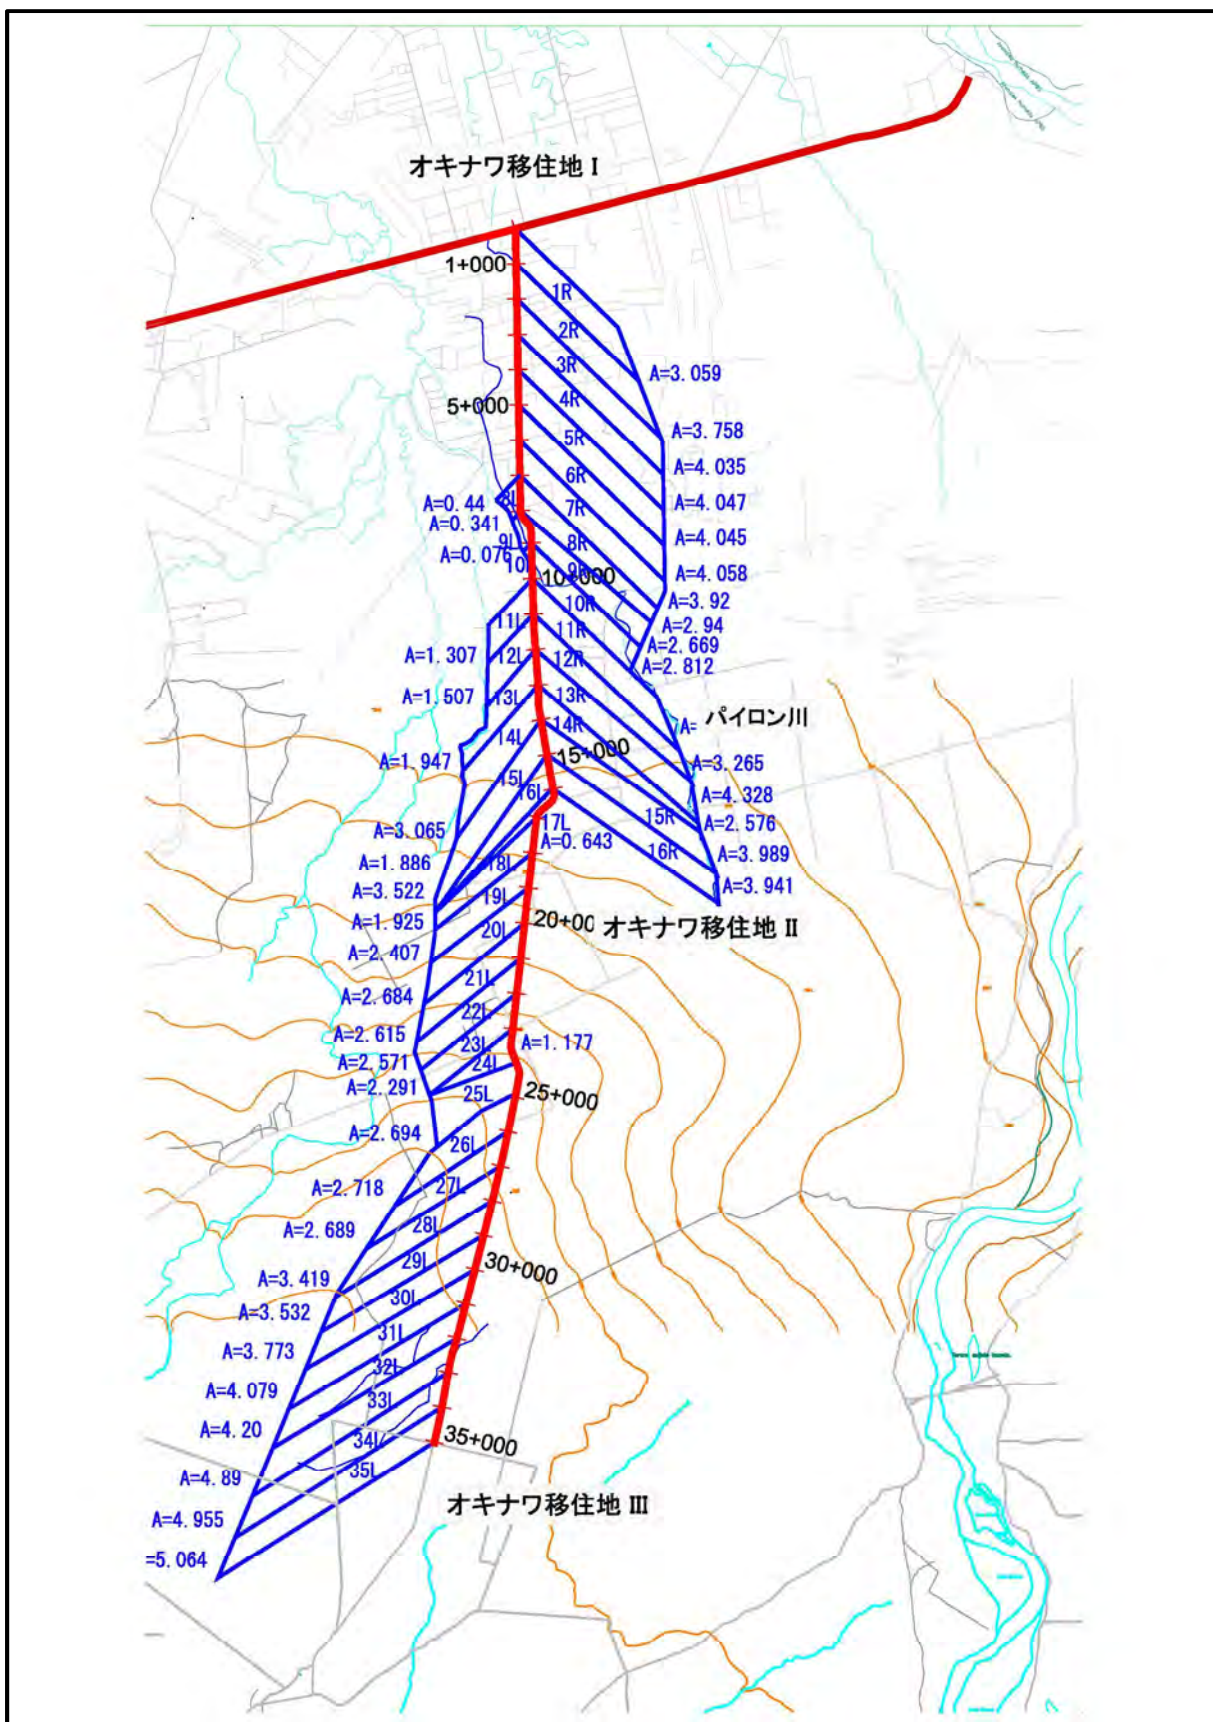

### (3) ガンベル法による降雨量計算

超過確率雨量計算

Gumbel Method (Exteam Value distribution)

(1) 順位 i	(2)		(3) 超過確率 F(x)	(4) x <sup>2</sup>	(5) 極致変量 y
	生起年	雨量 x (mm)			
1	1992	203.5	0.96429	41,412.25	3.3142
2	2007	187.3	0.92857	35,081.29	2.6022
3	2004	144.2	0.89286	20,793.64	2.1775
4	1994	131	0.85714	17,161.00	1.8698
5	1993	120	0.82143	14,400.00	1.6260
6	2000	110.2	0.78571	12,144.04	1.4223
7	2003	108.8	0.75000	11,837.44	1.2459
8	1997	106.1	0.71429	11,257.21	1.0893
9	1996	104.1	0.67857	10,836.81	0.9473
10	2009	103.1	0.64286	10,629.61	0.8168
11	2010	100.9	0.60714	10,180.81	0.6952
12	1987	100.9	0.57143	10,180.81	0.5805
13	1990	100.3	0.53571	10,060.09	0.4713
14	1991	100.2	0.50000	10,040.04	0.3665
15	1989	99.5	0.46429	9,900.25	0.2649
16	2012	90.5	0.42857	8,190.25	0.1657
17	2008	90.3	0.39286	8,154.09	0.0680
18	2006	88.5	0.35714	7,832.25	-0.0292
19	2005	82.2	0.32143	6,756.84	-0.1266
20	1999	77.9	0.28571	6,068.41	-0.2254
21	2001	76.9	0.25000	5,913.61	-0.3266
22	2002	76.6	0.21429	5,867.56	-0.4321
23	1995	64.1	0.17857	4,108.81	-0.5439
24	1998	63.1	0.14286	3,981.61	-0.6657
25	2011	60.7	0.10714	3,684.49	-0.8036
26	2013	55.1	0.07143	3,036.01	-0.9704
27	1988	53.3	0.03571	2,840.89	-1.2037
	Total	2,699.3		302,350.11	
	平均 Σx/N=	99.97	Σx <sup>2</sup> /N=	11198.152	
		$\bar{x}$		$\bar{x}^2$	

$$F(x)=1-j/(N+1)$$

$$S_x = (\bar{x}^2 - (\bar{x})^2)^{0.5} = 34.7009$$

N=27であるから、上表より

$$\bar{y} = 0.5332 \quad S_y = 1.1004$$

よって

$$1/a = S_x/S_y = 31.5348$$

$$x_0 = \bar{x} - (1/a) \bar{y} = 83.156$$

以上より確率雨量の基本式は

$$x = 83.156 + 31.5348 * y$$

確率年Tとyの関係は上表3.6に示されているので、これを上式に代入して以下のように確率雨量xが求まる。

T 回帰年	F(%)	$\bar{y}$	(1/a)*y	x 確率雨量
3	66.7	0.9027	28.467	112
10	90	2.2504	70.965	154
20	95	2.9702	93.665	177
25	96	3.1985	100.865	184
30	96.7	3.3843	106.723	190
40	97.5	3.6763	115.930	199
50	98	3.9019	123.047	<b>206</b>
100	99	4.6002	145.065	228

⇐道路横断排水施設の確率雨量を50回帰年で求める。

標本数Nと $\bar{y}$ 、 $S_y$ の数表

標本数 N	$\bar{y}$	$S_y$
20	0.5236	1.0628
21	0.5252	1.0696
22	0.5268	1.0754
23	0.5283	1.0811
24	0.5296	1.0864
25	0.5309	1.0915
26	0.5320	1.0961
27	0.5332	1.1004
28	0.5343	1.1047
29	0.5353	1.1086
30	0.5362	1.1124

Tに対する極値変量y

確率年 T	1/T= 1-F	極値変量 y
500	0.00200	6.21361
400	0.00250	5.99021
300	0.00333	5.70213
250	0.00400	5.51946
200	0.00500	5.29581
150	0.00667	5.00729
100	0.01000	4.60015
80	0.01250	4.37574
60	0.01667	4.08595
50	0.02000	3.90194
40	0.02500	3.67625
30	0.03333	3.38429
25	0.04000	3.19853
20	0.05000	2.97020
15	0.06667	2.67375
10	0.10000	2.25037
8	0.12500	2.01342
7	0.14286	1.86983
6	0.16667	1.70198
5	0.20000	1.49940
4	0.25000	1.24590
3	0.33333	0.90272
2	0.50000	0.36651

(4) 雨水流出量の計算

Sta.	左	右	流域面積	合計	流路長 (km): L	標高(m)	標高差 (m)	勾配	流速速度 (km/hr): W	算出到達 時間 (hr): Tc	仮定流達 時間 (min)	流達時間 (min)	流達時間 内降雨強 度 (mm/h)	流出係数 : C	雨水 流出量 (m <sup>3</sup> /s)	流下能力(m <sup>3</sup> /s)			確認	
																新規力 ルバー ト	追加 DP800 本 数	追加 DP800		合計
1	0.48	3.06	3.06	3.06	5.54	274.49	2.88	0.0005	0.77	7.19	431	431	19.20	0.1	1.63	4.98	0.00	4.98	OK	
2	2.417	3.758	3.758	23.863	10.84	276.00	6.00	0.0006	0.80	13.55	813	813	12.58	0.1	8.34	21.87	0.00	21.87	OK	
3	2.109	4.035	4.035	20.105	9.91	277.12	4.88	0.0005	0.75	13.26	796	796	12.76	0.1	7.12	0.00	8	7.30	OK	
4	1.772	4.047	4.047	16.07	8.98	277.37	4.63	0.0005	0.77	11.71	703	703	13.86	0.1	6.19	1.66	5	4.57	OK	
5	1.37	4.045	4.045	12.023	8.08	277.42	4.58	0.0006	0.81	9.95	597	597	15.45	0.1	5.16	1.66	4	3.65	OK	
6	1.141	4.058	4.058	7.978	7.20	277.78	4.22	0.0006	0.83	8.69	521	521	16.92	0.1	3.75	10.63	0.00	10.63	OK	
7	0.849	3.92	3.92	3.92	6.36	278.70	3.30	0.0005	0.77	8.27	496	496	17.49	0.1	1.90	0.00	3	2.74	OK	
8	0.44	2.94	3.38	19.001	5.57	279.04	2.96	0.0005	0.78	7.13	428	428	19.29	0.1	10.18	8.24	3	2.74	10.98	OK
9	0.341	2.669	3.01	99.201	18.15	279.63	35.37	0.0019	1.70	10.66	640	640	14.75	0.1	40.65	59.37	0.00	59.37	OK	
10	0.076	2.812	2.888	12.611	17.29	280.37	34.63	0.0020	1.73	9.99	599	599	15.42	0.1	5.40	11.05	0.00	11.05	OK	
11	1.307	3.644	4.951	9.723	16.31	280.96	34.05	0.0021	1.78	9.19	551	551	16.30	0.1	4.40	0.00	5	4.57	4.57	OK
12	1.507	3.265	4.772	4.772	15.33	281.63	33.38	0.0022	1.82	8.42	505	505	17.28	0.1	2.29	3.32	0.00	3.32	OK	
13	1.947	4.328	6.275	44.261	14.36	282.81	32.19	0.0022	1.85	7.75	465	465	18.25	0.1	22.44	14.66	9	8.22	22.88	OK
14	3.065	2.576	5.641	37.986	13.41	284.28	30.72	0.0023	1.88	7.14	428	428	19.29	0.1	20.36	27.12	0.00	27.12	OK	
15	3.522	3.989	7.511	32.345	12.45	284.91	30.09	0.0024	1.94	6.42	385	385	20.70	0.1	18.60	8.24	4	3.65	11.90	OK
16	1.886	3.941	5.827	24.834	11.54	287.80	27.20	0.0024	1.91	6.04	362	362	21.57	0.1	14.88	7.33	9	8.22	15.55	OK
17	0.643	9.424	0.643	19.007	10.64	290.00	25.00	0.0023	1.91	5.59	335	335	22.71	0.1	11.99	0.00	14	12.78	12.78	OK
18	1.925	3.258	1.925	18.364	9.71	291.81	23.19	0.0024	1.92	5.05	303	303	24.29	0.1	12.39	0.00	14	12.78	12.78	OK

### (5) 道路排水施設サイズの計算

側溝および排水管の排水能力は、以下のマンニングの流速等式より求められる通水量の8割を排水施設の可能通水量とした。

$$Q_c = 0.8 \times V \times A$$

$$V = 1/n \times R^{2/3} \times I^{1/2}$$

ここで

Q<sub>c</sub> : 排水施設の可能通水量 (m<sup>3</sup>/sec)

V : 流速 (m/sec)

n : 粗度係数 (コンクリート管 0.013、コンクリート側溝 0.015、石積側溝 0.025)

R : 径深 (m) , R = A/S

I : 流路勾配

A : 排水施設の通水断面積 (m<sup>2</sup>)

S : 潤辺 (m)

#	サイズ	幅 (m)	高さ (m)	潤辺:S (m)	水深:h (m)	断面積:A (m <sup>2</sup> )	流速:v (m/s)	粗度 係数:n	勾配:I	径深:R (m)	通水量:Q <sub>c</sub> (m <sup>3</sup> /s)
PC1	DP800	直径 0.80		1.77	0.64	0.43	2.12	0.013	0.005	0.24	0.91
PC2	DP1000	直径 1.00		2.21	0.80	0.67	2.46	0.013	0.005	0.30	1.65
BC1	2.0×1.0	2.00	1.00	3.60	0.80	1.60	2.75	0.015	0.005	0.44	4.39
BC2	3.0×1.0	3.00	1.00	4.60	0.80	2.40	3.06	0.015	0.005	0.52	7.33
BC3	3.0×1.30	3.00	1.30	5.08	1.04	3.12	3.41	0.015	0.005	0.61	10.63
BC4	2*2.5×1.30	2.50	1.30	4.58	1.04	2.60	3.23	0.015	0.005	0.57	16.80
BC5	1.5×1.5	1.50	1.50	3.90	1.20	1.80	2.82	0.015	0.005	0.46	5.07
BC6	2*2.5×1.5	2.50	1.50	4.90	1.20	3.00	3.40	0.015	0.005	0.61	20.39



(6) 新規道路排水施設の延長及び通水量

測点	既設断面		新規断面		延長(m)		通水流量(m <sup>3</sup> /s)		合計
	Pipe	Box	Pipe	Box	Pipe	Box	Pipe	Box	
Sta. 0+016	1000		1000		18.24		1.66		4.98
Sta. 0+025	1000		1000		18.24		1.66		
Sta. 0+937	800		1000		20.06		1.66		
Sta. 1+121	1200			1.5×1.5		18.61		5.07	21.87
Sta. 1+154		2*1.8×1.4		2*2.5×1.30		17.25		16.80	
Sta. 3+200	1000		1000		17.62		1.66		1.66
Sta. 4+819	800		1000		19.41		1.66		1.66
Sta. 5+026		1.5×1.3		3.0×1.30		18.43		10.63	10.63
Sta. 7+010	800		800		15.94		0.91		8.24
Sta. 7+972		1.6×1.2		3.0×1.0		18.09		7.33	
Sta. 8+012	600		800		18.74		0.91		
Sta. 8+047		1.4×1.6		3.0×1.30		16.97		10.63	59.37
Sta. 8+429		2.0×1.6		3.0×1.30		17.70		10.63	
Sta. 8+664		2*1.8×1.6		2*2.5×1.30		18.51		16.80	
Sta. 8+815		2*2.0×1.6		2*2.5×1.5		16.11		20.40	
Sta. 9+132	1000			1.5×1.5		21.51		5.07	
Sta. 9+223	1500			1.5×1.5		20.83		5.07	11.05
Sta. 9+330	600		800		17.26		0.91		
Sta. 11+742	1000		1000		17.82		1.66		
Sta. 11+935	1000		1000		19.27		1.66		3.32
Sta. 12+330	1200			3.0×1.0		16.88		7.33	14.66
Sta. 12+982	1200			3.0×1.0		17.88		7.33	
Sta. 13+035	800			2.0×1.0		18.95		4.39	27.12
Sta. 13+356	1000			2.0×1.0		19.81		4.39	
Sta. 13+437	1000		1000		16.09		1.66		
Sta. 13+630	1500			3.0×1.30		19.24		10.63	
Sta. 13+782	1000		1000		18.27		1.66		
Sta. 13+894	800			2.0×1.0		18.81		4.39	
Sta. 13+994	800		800		16.35		0.91		
Sta. 14+200	800			3.0×1.0		17.54		7.33	
Sta. 15+261		1.6×1.0		3.0×1.0		15.68		7.33	

### 8-3 流出解析（パイロン川、橋梁）

#### 1) 雨量記録の整理

CETABOL 及び SENAMHI の雨量データを整理し、最終的に SENAMHI のデータを利用して、最大雨量を取り出し水文統計処理の準備を行った。

#### 2) 超過確率の算定

対数正規分布法と Gumbel 法を使って確率雨量の算定を行った。結果を下記に示す。流量計算には、Gumbel 法を用いた。

表 2-2-14 確率日雨量

回帰年	確率日雨量 (mm/日)	
	対数正規分布法	Gumbel 法
10	146	154
20	168	177
25	175	184
30	181	190
40	190	199
50	198	206
100	221	228

出典：調査団

#### 3) 降雨確率年の算定

サンタクルス県の基準より降雨確率年の回帰年 100 年、確率日雨量 228mm/日を採用した。

#### 4) 流域面積の算定

Instituto Geografico Militar (軍地理院)から入手した地形図から流域面積 30.5km<sup>2</sup> を算出した。

#### 5) 流出係数の設定

パイロン川流域周辺は耕地であることから、流出係数は建設省河川砂防基準（案）を参考に 0.45 を採用した。

#### 6) 洪水到達時間の算定

パイロン川流域の標高と流路延長から洪水到達時間を算出した。この結果より洪水到達時間は、表 2-2-15 に示す複数の算定式による結果を比較し、110 分とした。

表 0-15 洪水到達時間

算出方法	等流流速法	土研式	角屋式	Kinematic Wave 式
洪水到達時間 (分)	80	140	110	90

出典：調査団

### 7) 洪水到達時間内の平均雨量の算定

洪水到達時間 110 分の場合の平均降雨強度の計算結果を表 2-2-16 に示す。一般的で安全側の物部式で算出した値を採用した。

表 0-16 到達時間内平均降雨強度

	伊藤式	物部式
到達時間内平均降雨強度 (mm/h)	38.2	52.8

出典：調査団

### 8) 高水位流量の算定

ラショナル式を使って解析洪水流量を算定した。

$$Q_p = 1/3.6 * f_p * r * A = 201 \text{ m}^3/\text{s}$$

$Q_p$ : 洪水ピークの流量 (m<sup>3</sup>/s)


$r$ : 洪水到達時間内平均降雨強度

$f_p$ : 流出係数

$A$ : 流域面積 (km<sup>2</sup>)

### 9) 高水位の算定

上記から得た回帰年 100 年における確率日雨量を用いて算出した流量 201m<sup>3</sup>/s を地形測量から得た河川断面から作成した水位水量曲線に当てはめると H=280.11 となった。

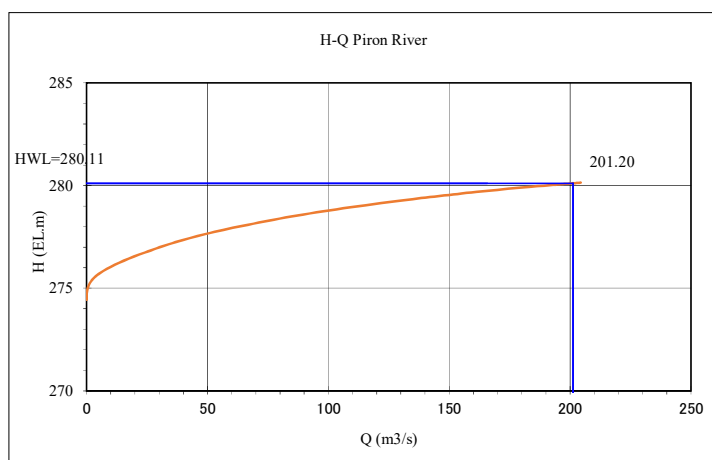

8-4 地質・土質試験結果

CBR試験結果 乾期


N° POLL	N° SAMPLES	PROGRESSIVE	HUMEDAD NATURAL	GRANULOMETRIA			LIMITES DE ATTERBERG			CLASIFICACION CHISTATION AASHTO	CLASIFICACION S.U.S.C.	Proctor	HUMEDAD OPTIMA		OBSERVACIONES		
				4	10	200	L.L.	L.P.	I.P.				% DE CLER. P. 0.1 PENETRATION	95%		100%	
01	01	0+630	19.97%	100.00	99.57	98.60	88.79	26.54%	0.00%	N.P.	A-4 (8)	ML	1.835	15.79%	1.41	2.16	
02	01	1+600	21.90%	100.00	99.92	99.64	97.92	24.93%	0.00%	N.P.	A-4 (8)	ML	1.804	14.37%	0.74	1.43	
03	01	2+600	16.54%	100.00	99.69	98.51	85.11	20.48%	0.00%	N.P.	A-4 (8)	ML	1.920	12.43%	4.03	10.04	
04	01	3+600	18.04%	100.00	100.00	99.77	57.55	0.00%	0.00%	N.P.	A-4 (8)	ML	1.754	13.01%	7.01	15.07	
05	01	4+000	30.26%	100.00	99.85	99.67	97.56	24.48%	0.00%	N.P.	A-4 (8)	ML	1.804	14.37%	2.68	5.48	
06	01	5+600	20.24%	100.00	99.95	99.71	99.15	27.01%	0.00%	N.P.	A-4 (8)	ML	1.817	16.31%	1.36	2.49	
07	01	6+000	24.86%	100.00	100.00	99.95	97.22	0.00%	0.00%	N.P.	A-4 (8)	ML	1.843	12.41%	4.25	11.06	
08	01	7+000	19.35%	100.00	100.00	99.82	85.12	21.13%	0.00%	N.P.	A-4 (8)	ML	1.916	13.14%	7.40	12.32	
09	01	8+000	20.24%	100.00	99.95	99.71	99.15	22.34%	0.00%	N.P.	A-4 (8)	ML	1.832	14.44%	2.05	5.06	
10	01	9+100	22.31%	100.00	99.87	99.62	97.15	40.84%	21.74%	19.10%	A-7-6 (12)	CL	1.742	17.35%	0.86	1.34	
11	01	10+000	12.58%	100.00	100.00	99.67	97.46	49.95%	28.53%	21.41%	A-7-6 (15)	ML	1.726	16.34%	0.77	1.17	
12	01	11+000	12.74%	100.00	99.81	98.50	93.64	56.84%	24.49%	32.35%	A-7-6 (20)	CH	1.754	15.81%	0.59	1.72	
13	01	12+000	15.46%	100.00	100.00	99.53	96.91	61.75%	26.54%	35.21%	A-7-6 (20)	CH	1.608	20.27%	0.92	1.47	
14	01	13+000	7.94%	100.00	99.40	96.20	67.23	35.96%	16.09%	19.88%	A-6 (11)	CL	1.912	14.08%	1.52	2.40	
15	01	14+000	26.50%	100.00	99.92	99.64	97.25	49.93%	25.78%	24.15%	A-7-6 (16)	CL	1.625	22.65%	0.69	1.44	
16	01	15+000	17.21%	100.00	99.41	99.04	71.73	22.11%	11.24%	10.87%	A-6 (8)	CL	2.024	8.03%	2.41	5.22	
17	01	16+000	14.88%	100.00	100.00	99.56	65.69	20.44%	0.00%	N.P.	A-4 (6)	ML	2.060	9.43%	4.57	8.62	
18	01	17+000	13.61%	100.00	100.00	99.32	53.23	0.00%	0.00%	N.P.	A-4 (6)	ML	1.982	8.43%	11.79	26.30	
19	01	18+000	24.10%	100.00	100.00	99.70	93.88	41.22%	21.36%	19.86%	A-7-6 (13)	CL	1.828	15.91%	1.56	2.83	
20	01	19+000	13.17%	100.00	100.00	99.71	45.18	26.85%	0.00%	N.P.	A-4 (3)	SM	1.958	7.67%	8.57	18.73	
21	01	20+000	17.03%	100.00	99.95	98.45	60.63	0.00%	0.00%	N.P.	A-4 (6)	ML	2.057	9.46%	6.40	11.80	
22	01	21+000	18.25%	100.00	100.00	99.68	94.19	35.73%	17.64%	18.09%	A-6 (12)	CL	1.922	12.23%	1.61	3.19	
23	01	22+000	13.49%	100.00	99.95	99.50	61.64	20.04%	0.00%	N.P.	A-4 (6)	ML	2.058	9.31%	10.49	16.38	
24	01	23+000	14.52%	100.00	100.00	99.92	48.04	18.62%	0.00%	N.P.	A-4 (3)	SM	2.013	6.79%	15.07	24.26	
25	01	24+000	13.11%	100.00	100.00	99.58	64.56	18.12%	0.00%	N.P.	A-4 (6)	ML	2.061	9.36%	11.16	17.88	
26	01	25+000	13.01%	100.00	99.97	96.20	67.95	18.02%	0.00%	N.P.	A-4 (7)	ML	2.076	9.07%	9.35	13.09	
27	01	26+000	10.15%	100.00	100.00	99.32	48.04	0.00%	0.00%	N.P.	A-4 (6)	SM	2.046	8.27%	9.90	15.52	
28	01	27+000	20.02%	100.00	100.00	97.30	84.24	38.80%	20.44%	18.36%	A-6 (12)	CL	1.805	14.99%	1.08	2.43	
29	01	28+000	24.77%	100.00	100.00	99.03	96.98	46.79%	22.60%	24.20%	A-7-6 (16)	CL	1.786	15.82%	1.58	2.58	
30	01	29+000	20.11%	100.00	99.89	99.28	90.36	39.23%	18.45%	20.78%	A-6 (13)	CL	1.764	16.78%	1.77	2.74	
31	01	30+000	25.93%	100.00	99.98	98.56	94.51	44.85%	21.22%	23.63%	A-7-6 (15)	CL	1.844	14.77%	1.26	2.04	
32	01	31+000	15.50%	100.00	100.00	99.70	72.40	24.17%	12.18%	11.98%	A-6 (9)	CL	2.073	7.97%	3.33	5.87	
33	01	32+000	16.30%	100.00	100.00	100.00	72.41	25.22%	13.66%	11.55%	A-6 (9)	CL	2.056	9.28%	5.15	10.09	
34	01	33+000	21.14%	100.00	100.00	99.87	96.33	37.31%	18.84%	18.47%	A-6 (12)	CL	1.791	14.61%	1.46	2.08	
35	01	34+000	11.71%	100.00	100.00	98.24	35.50	0.00%	0.00%	N.P.	A-4 (6)	SM	1.864	7.15%	12.47	22.77	




Client: KATAHIRA & Engineers International.

Project: Preparatory Study of the Oknawa I - II and III Road Paving Project  
Location: Municipality of Oknawa I - II, 2<sup>o</sup> Section, Wanans Province, Northern Region of Santa Cruz de la Sierra City

REV: 00  
REPORT: 2104-14  
DATE: 02/09/2014

<b>SUMMARY CBR</b>																	
																	
<b>Client:</b> KATAHIRA & Engineers International. <b>Project:</b> Preparatory Study of the Okinawa I - II and III Road Paving Project <b>Location:</b> Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																	
REV: 00 REPORT: 308-14 DATE: 23/12/2014																	
№ POLL	№ SAMPLES	HUMEDAD NATURAL		GRANULOMETRIA			LIMITES DE ATTERBERG			CLASIFICACION	CLASIFICACION A.A.S.H.T.O	Proctor T-180 MOD. grs/cm <sup>3</sup>	HUMEDAD OPTIMA	% DE C.B.R. P/0.10PENETRATION		OSERVACIONES	
		Nat. Moisture	Moisture	4	10	40	200	L.L	L.P					I.P	95%		100%
01	01	3+100	8.50%	100.00	100.00	99.92	31.81	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.789	12.07%	10.71	14.75	Natural Land
02	01	6+100	9.50%	100.00	100.00	100.00	97.16	18.42%	0.00%	N.P.	A-4 (8)	ML	1.895	12.55%	6.19	8.08	Natural Land
03	01	9+100	9.61%	99.68	99.53	98.90	97.21	42.47%	21.84%	20.63%	A-7-6 (13)	CL	1.828	15.77%	1.10	1.44	Natural Land
04	01	12+000	10.11%	99.62	99.53	98.90	97.04	41.29%	21.09%	20.20%	A-7-6 (13)	CL	1.656	21.40%	0.88	1.24	Natural Land
05	01	15+100	10.80%	100.00	100.00	99.44	67.35	16.43%	0.00%	N.P.	A-4 (7)	ML	1.915	11.66%	10.51	16.81	Natural Land
06	01	18+100	10.61%	100.00	99.90	98.59	85.75	30.95%	16.25%	14.70%	A-6 (10)	CL	1.981	10.76%	1.18	1.42	Natural Land
07	01	21+100	11.60%	100.00	100.00	98.57	87.63	24.74%	13.82%	10.91%	A-6 (9)	CL	1.964	11.86%	4.68	6.11	Natural Land
08	01	24+100	11.60%	99.89	99.68	97.65	39.34	0.00%	0.00%	N.P.	A-4 (0)	SM	1.951	9.37%	18.17	24.56	Natural Land
09	01	27+100	12.60%	100.00	99.71	93.36	68.45	28.54%	15.46%	13.08%	A-6 (8)	CL	1.877	10.35%	0.99	1.33	Natural Land
10	01	30+100	13.51%	84.52	81.65	76.66	61.50	38.55%	20.21%	18.35%	A-6 (9)	CL	1.851	10.85%	0.92	1.20	Natural Land

		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 DATE: 20/09/2014 REPORTE: RP 001/14 PAG: 01 de 01				
<b>CLIENTE / Client:</b> KAYAMIRA & Engineers International. <b>PROYECTO / Project:</b> Preparatory Study of the Okiñawa I - II and III Road Paving Project <b>UBICACIÓN / Location:</b> Municipality of Okiñawa I - II, 2ª Sección, Warnes Province, Northern Region of Santa Cruz de la Sierra City		<b>DCP N°:</b> 01						
<b>TEST DATA</b>								
<b>PROFESIVE:</b> 0-042 X Coordinate: 17°14'09.30"N Y Coordinate: 62°54'08.60"W		not Applicable <b>WATER TABLE:</b> 1.70 m. <b>WEIGHT HAMMER:</b> 8 Kg.						
RECORD FIELD		TEST RESULTS						
DEPTH (m)	VISUAL DESCRIPTION OF THE MATERIAL	Cumulative penetration (mm) B	Penetration Between Readings (mm) C	Factor of Hammer Punches E	DCP Index (mm / Punches) F	CBR % G	AVERAGE CBR %	observations
0.20	Clayey silt with plasticity, dark brown coloration	0 2	50	1	2.50	68.80		
0.40		18 110	60	1	3.33	49.85	49.37	
0.60		15 150	80	1	5.33	29.45		
0.80		1 30	30	1	30.00	4.26		
1.00		3 80	50	1	16.67	8.22	8.42	
1.20		4 150	70	1	17.50	7.78		
1.40		4 60	60	1	15.00	9.25		
1.60		7 140	80	1	11.43	12.54	11.52	
1.80		8 220	90	1	11.25	12.76		
2.00		3 60	60	1	20.00	6.70		
2.20		4 130	70	1	17.50	7.78	7.70	
2.40		5 210	80	1	16.00	8.60		
2.60		5 50	50	1	10.00	14.56		
2.80		9 120	70	1	7.78	19.30	16.93	
3.00		4 40	40	1	10.00	14.56		
3.20		7 110	70	1	10.00	14.56	13.37	
3.40		7 200	90	1	12.86	10.99		
3.60		6 210	80	1	13.33	10.55		
3.80		5 60	60	1	12.00	11.87		
4.00		6 130	70	1	14.00	9.99	10.81	
4.20		6 210	80	1	13.33	10.55		
4.40		5 60	60	1	12.00	11.87		
4.60		5 130	70	1	14.00	9.99	10.81	
4.80		6 210	80	1	13.33	10.55		
5.00		5 60	60	1	12.00	11.87		
5.20		5 130	70	1	14.00	9.99	10.81	
5.40		6 210	80	1	13.33	10.55		
5.60		5 60	60	1	12.00	11.87		
5.80		5 130	70	1	14.00	9.99	10.81	
6.00		6 210	80	1	13.33	10.55		
6.20		5 60	60	1	12.00	11.87		
6.40		5 130	70	1	14.00	9.99	10.81	
6.60		6 210	80	1	13.33	10.55		
6.80		5 60	60	1	12.00	11.87		
7.00		5 130	70	1	14.00	9.99	10.81	
7.20		6 210	80	1	13.33	10.55		
7.40		5 60	60	1	12.00	11.87		
7.60		5 130	70	1	14.00	9.99	10.81	
7.80		6 210	80	1	13.33	10.55		
8.00		5 60	60	1	12.00	11.87		
8.20		5 130	70	1	14.00	9.99	10.81	
8.40		6 210	80	1	13.33	10.55		
8.60		5 60	60	1	12.00	11.87		
8.80		5 130	70	1	14.00	9.99	10.81	
9.00		6 210	80	1	13.33	10.55		
9.20		5 60	60	1	12.00	11.87		
9.40		5 130	70	1	14.00	9.99	10.81	
9.60		6 210	80	1	13.33	10.55		
9.80		5 60	60	1	12.00	11.87		
10.00		5 130	70	1	14.00	9.99	10.81	
10.20		6 210	80	1	13.33	10.55		
10.40		5 60	60	1	12.00	11.87		
10.60		5 130	70	1	14.00	9.99	10.81	
10.80		6 210	80	1	13.33	10.55		
11.00		5 60	60	1	12.00	11.87		
11.20		5 130	70	1	14.00	9.99	10.81	
11.40		6 210	80	1	13.33	10.55		
11.60		5 60	60	1	12.00	11.87		
11.80		5 130	70	1	14.00	9.99	10.81	
12.00		6 210	80	1	13.33	10.55		
12.20		5 60	60	1	12.00	11.87		
12.40		5 130	70	1	14.00	9.99	10.81	
12.60		6 210	80	1	13.33	10.55		
12.80		5 60	60	1	12.00	11.87		
13.00		5 130	70	1	14.00	9.99	10.81	
13.20		6 210	80	1	13.33	10.55		
13.40		5 60	60	1	12.00	11.87		
13.60		5 130	70	1	14.00	9.99	10.81	
13.80		6 210	80	1	13.33	10.55		
14.00		5 60	60	1	12.00	11.87		
14.20		5 130	70	1	14.00	9.99	10.81	
14.40		6 210	80	1	13.33	10.55		
14.60		5 60	60	1	12.00	11.87		
14.80		5 130	70	1	14.00	9.99	10.81	
15.00		6 210	80	1	13.33	10.55		
15.20		5 60	60	1	12.00	11.87		
15.40		5 130	70	1	14.00	9.99	10.81	
15.60		6 210	80	1	13.33	10.55		
15.80		5 60	60	1	12.00	11.87		
16.00		5 130	70	1	14.00	9.99	10.81	
16.20		6 210	80	1	13.33	10.55		
16.40		5 60	60	1	12.00	11.87		
16.60		5 130	70	1	14.00	9.99	10.81	
16.80		6 210	80	1	13.33	10.55		
17.00		5 60	60	1	12.00	11.87		
17.20		5 130	70	1	14.00	9.99	10.81	
17.40		6 210	80	1	13.33	10.55		
17.60		5 60	60	1	12.00	11.87		
17.80		5 130	70	1	14.00	9.99	10.81	
18.00		6 210	80	1	13.33	10.55		
18.20		5 60	60	1	12.00	11.87		
18.40		5 130	70	1	14.00	9.99	10.81	
18.60		6 210	80	1	13.33	10.55		
18.80		5 60	60	1	12.00	11.87		
19.00		5 130	70	1	14.00	9.99	10.81	
19.20		6 210	80	1	13.33	10.55		
19.40		5 60	60	1	12.00	11.87		
19.60		5 130	70	1	14.00	9.99	10.81	
19.80		6 210	80	1	13.33	10.55		
20.00		5 60	60	1	12.00	11.87		
20.20		5 130	70	1	14.00	9.99	10.81	
20.40		6 210	80	1	13.33	10.55		
20.60		5 60	60	1	12.00	11.87		
20.80		5 130	70	1	14.00	9.99	10.81	
21.00		6 210	80	1	13.33	10.55		
21.20		5 60	60	1	12.00	11.87		
21.40		5 130	70	1	14.00	9.99	10.81	
21.60		6 210	80	1	13.33	10.55		
21.80		5 60	60	1	12.00	11.87		
22.00		5 130	70	1	14.00	9.99	10.81	
22.20		6 210	80	1	13.33	10.55		
22.40		5 60	60	1	12.00	11.87		
22.60		5 130	70	1	14.00	9.99	10.81	
22.80		6 210	80	1	13.33	10.55		
23.00		5 60	60	1	12.00	11.87		
23.20		5 130	70	1	14.00	9.99	10.81	
23.40		6 210	80	1	13.33	10.55		
23.60		5 60	60	1	12.00	11.87		
23.80		5 130	70	1	14.00	9.99	10.81	
24.00		6 210	80	1	13.33	10.55		
24.20		5 60	60	1	12.00	11.87		
24.40		5 130	70	1	14.00	9.99	10.81	
24.60		6 210	80	1	13.33	10.55		
24.80		5 60	60	1	12.00	11.87		
25.00		5 130	70	1	14.00	9.99	10.81	
25.20		6 210	80	1	13.33	10.55		
25.40		5 60	60	1	12.00	11.87		
25.60		5 130	70	1	14.00	9.99	10.81	
25.80		6 210	80	1	13.33	10.55		
26.00		5 60	60	1	12.00	11.87		
26.20		5 130	70	1	14.00	9.99	10.81	
26.40		6 210	80	1	13.33	10.55		
26.60		5 60	60	1	12.00	11.87		
26.80		5 130	70	1	14.00	9.99	10.81	
27.00		6 210	80	1	13.33	10.55		
27.20		5 60	60	1	12.00	11.87		
27.40		5 130	70	1	14.00	9.99	10.81	
27.60		6 210	80	1	13.33	10.55		
27.80		5 60	60	1	12.00	11.87		
28.00		5 130	70	1	14.00	9.99	10.81	
28.20		6 210	80	1	13.33	10.55		
28.40		5 60	60	1	12.00	11.87		
28.60		5 130	70	1	14.00	9.99</		

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		NORMA ASTM-D-6951-03		REV: 00	03/09/2014
CLIENT / Client:		KATAYIRA & Engineers International.		PROYECTO / Project:		REPORTE	RP 00
UBICACIÓN / Location:		Municipality of Okinawa I - II, 2 <sup>nd</sup> Section, Warmes Province, Northern Region of Santa Cruz de la Sierra City		UBICACIÓN / Location:		PAG.	01 de 01
PROGRESIVO:		1-045		TEST DATA		DCP N °: 03	
WATER TABLE:		not Applicable		WEIGHT HAMMER:		8 Kg.	
RECORD FIELD		TEST RESULTS		LABORATORY MANAGER		25/08/2014	
VISUAL DESCRIPTION OF THE MATERIAL:		TEST RESULTS		LABORATORY MANAGER		25/08/2014	
DEPTH (m)	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C
0.10	30	1	5.00	1	5.00	31.166	54.82
0.20	40	1	2.50	1	2.50	68.80	64.01
0.30	40	1	2.67	1	2.67	64.01	
0.40	30	1	6.00	1	6.00	25.81	
0.50	30	1	3.00	1	3.00	56.10	56.75
0.60	30	1	2.00	1	2.00	88.34	
0.70	30	1	7.50	1	7.50	20.10	
0.80	40	1	5.71	1	5.71	27.26	23.75
0.90	40	1	6.43	1	6.43	23.89	
1.00	40	1	10.00	1	10.00	14.56	
1.10	50	1	10.00	1	10.00	14.56	
1.20	40	1	10.00	1	10.00	14.56	
1.30	40	1	20.00	1	20.00	6.70	
1.40	40	1	16.67	1	16.67	8.22	7.21
1.50	50	1	12.50	1	12.50	11.34	
1.60	60	1	12.00	1	12.00	11.87	
1.70	60	1	12.00	1	12.00	11.87	
1.80	60	1	15.00	1	15.00	9.25	9.78
1.90	50	1	16.67	1	16.67	8.22	
2.00	50	1	12.50	1	12.50	11.34	
2.10	60	1	14.00	1	14.00	9.99	
2.20	70	1	12.00	1	12.00	11.87	
2.30	70	1	14.00	1	14.00	9.99	
2.40	70	1	14.00	1	14.00	9.99	
2.50	70	1	14.00	1	14.00	9.99	
2.60	70	1	14.00	1	14.00	9.99	
2.70	70	1	14.00	1	14.00	9.99	
2.80	70	1	14.00	1	14.00	9.99	
2.90	70	1	14.00	1	14.00	9.99	
3.00	70	1	14.00	1	14.00	9.99	

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		NORMA ASTM-D-6951-03		REV: 00	03/09/2014
CLIENT / Client:		KATAYIRA & Engineers International.		PROYECTO / Project:		REPORTE	RP 00
UBICACIÓN / Location:		Municipality of Okinawa I - II, 2 <sup>nd</sup> Section, Warmes Province, Northern Region of Santa Cruz de la Sierra City		UBICACIÓN / Location:		PAG.	01 de 01
PROGRESIVO:		1-045		TEST DATA		DCP N °: 04	
WATER TABLE:		not Applicable		WEIGHT HAMMER:		8 Kg.	
RECORD FIELD		TEST RESULTS		LABORATORY MANAGER		23/08/2014	
VISUAL DESCRIPTION OF THE MATERIAL:		TEST RESULTS		LABORATORY MANAGER		23/08/2014	
DEPTH (m)	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C	Factor Of Hit D	Penetration Between Readings (mm) C
0.10	30	1	3.75	1	3.75	43.69	
0.20	30	1	2.73	1	2.73	62.41	69.25
0.30	30	1	1.76	1	1.76	101.63	
0.40	40	1	4.00	1	4.00	40.64	
0.50	40	1	1.74	1	1.74	103.31	82.42
0.60	40	1	1.74	1	1.74	103.31	
0.70	40	1	4.44	1	4.44	36.12	
0.80	50	1	2.38	1	2.38	72.67	67.62
0.90	30	1	1.88	1	1.88	94.96	
1.00	30	1	15.00	1	15.00	9.25	
1.10	40	1	13.33	1	13.33	10.56	9.34
1.20	50	1	16.67	1	16.67	8.22	
1.30	40	1	20.00	1	20.00	6.70	
1.40	40	1	20.00	1	20.00	6.70	
1.50	70	1	23.33	1	23.33	5.64	
1.60	40	1	20.00	1	20.00	6.70	
1.70	40	1	20.00	1	20.00	6.70	
1.80	40	1	20.00	1	20.00	6.70	
1.90	40	1	20.00	1	20.00	6.70	
2.00	40	1	20.00	1	20.00	6.70	
2.10	40	1	20.00	1	20.00	6.70	
2.20	40	1	20.00	1	20.00	6.70	
2.30	40	1	20.00	1	20.00	6.70	
2.40	40	1	20.00	1	20.00	6.70	
2.50	40	1	20.00	1	20.00	6.70	
2.60	40	1	20.00	1	20.00	6.70	
2.70	40	1	20.00	1	20.00	6.70	
2.80	40	1	20.00	1	20.00	6.70	
2.90	40	1	20.00	1	20.00	6.70	
3.00	40	1	20.00	1	20.00	6.70	









PROFESIONISTA:		WATER TABLE:		TEST DATA		TEST RESULTS		WEIGHT HAMMER:																																																																																																																																																
5-015		2.10 m.		17°16'02.30" S 62°54'06.20" W		8 Kg.		8 Kg.																																																																																																																																																
<p><b>CLIENTE / CLIENT:</b> KATAMBA &amp; Engineers International  <b>PROYECTO / PROJECT:</b> Preparatory Study of the Urban 7-1 Road III Road Boring Project  <b>UBICACION / LOCATION:</b> Municipality of Chiminá 7-11, 2° Section, Verano Province, Northern Region of Santa Cruz de la Sierra City</p>																																																																																																																																																								
<p><b>RECORD FIELD</b></p> <table border="1"> <thead> <tr> <th>Visual Description of the Material</th> <th>Number of Blows (A)</th> <th>Cumulative Penetration (mm) (G)</th> <th>Penetration Between Readings (mm) (C)</th> <th>Factor Correction (mm) (D)</th> <th>Factor Correction (mm) (E)</th> <th>Factor Correction (mm) (F)</th> <th>Factor Correction (mm) (G)</th> <th>Factor Correction (mm) (H)</th> <th>Average CBR %</th> <th>Observations</th> </tr> </thead> <tbody> <tr> <td>Limo, in-situ condition firm, medium bedded, dry and light brown coloring.</td> <td>4</td> <td>31</td> <td>30</td> <td>7.50</td> <td>1</td> <td>7.50</td> <td>20.10</td> <td></td> <td>31.90</td> <td>Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two</td> </tr> <tr> <td>Organic silt, in-situ condition firm, medium bedded, dry and greyish coloration.</td> <td>13</td> <td>40</td> <td>40</td> <td>3.08</td> <td>1</td> <td>3.08</td> <td>50.53</td> <td></td> <td>61.91</td> <td></td> </tr> <tr> <td>Organic clayey silt, firm-silt, medium bedded, dry and grey coloring condition.</td> <td>6</td> <td>30</td> <td>30</td> <td>2.50</td> <td>1</td> <td>2.50</td> <td>68.80</td> <td></td> <td>15.24</td> <td></td> </tr> <tr> <td>Clayey silt, in-situ condition firm, medium bedded, partially dry, dark brown with light brown partings.</td> <td>4</td> <td>50</td> <td>50</td> <td>12.50</td> <td>1</td> <td>12.50</td> <td>113.34</td> <td></td> <td>17.31</td> <td></td> </tr> <tr> <td>Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.</td> <td>5</td> <td>100</td> <td>100</td> <td>15.00</td> <td>1</td> <td>15.00</td> <td>92.25</td> <td></td> <td>10.19</td> <td></td> </tr> <tr> <td>Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.</td> <td>4</td> <td>60</td> <td>60</td> <td>15.00</td> <td>1</td> <td>15.00</td> <td>92.25</td> <td></td> <td>9.28</td> <td></td> </tr> <tr> <td>Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.</td> <td>7</td> <td>100</td> <td>100</td> <td>14.28</td> <td>1</td> <td>14.28</td> <td>97.71</td> <td></td> <td>9.30</td> <td></td> </tr> <tr> <td>Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.</td> <td>8</td> <td>200</td> <td>200</td> <td>15.00</td> <td>1</td> <td>15.00</td> <td>92.25</td> <td></td> <td>8.88</td> <td></td> </tr> <tr> <td>Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.</td> <td>9</td> <td>300</td> <td>300</td> <td>11.11</td> <td>1</td> <td>11.11</td> <td>123.94</td> <td></td> <td>12.41</td> <td></td> </tr> <tr> <td>Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.</td> <td>7</td> <td>100</td> <td>100</td> <td>14.28</td> <td>1</td> <td>14.28</td> <td>97.71</td> <td></td> <td>10.46</td> <td></td> </tr> <tr> <td>Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.</td> <td>9</td> <td>200</td> <td>200</td> <td>13.33</td> <td>1</td> <td>13.33</td> <td>103.51</td> <td></td> <td>11.72</td> <td></td> </tr> <tr> <td>Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.</td> <td>11</td> <td>260</td> <td>260</td> <td>12.73</td> <td>1</td> <td>12.73</td> <td>111.21</td> <td></td> <td></td> <td></td> </tr> </tbody> </table>										Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	Factor Correction (mm) (F)	Factor Correction (mm) (G)	Factor Correction (mm) (H)	Average CBR %	Observations	Limo, in-situ condition firm, medium bedded, dry and light brown coloring.	4	31	30	7.50	1	7.50	20.10		31.90	Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two	Organic silt, in-situ condition firm, medium bedded, dry and greyish coloration.	13	40	40	3.08	1	3.08	50.53		61.91		Organic clayey silt, firm-silt, medium bedded, dry and grey coloring condition.	6	30	30	2.50	1	2.50	68.80		15.24		Clayey silt, in-situ condition firm, medium bedded, partially dry, dark brown with light brown partings.	4	50	50	12.50	1	12.50	113.34		17.31		Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.	5	100	100	15.00	1	15.00	92.25		10.19		Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.	4	60	60	15.00	1	15.00	92.25		9.28		Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	7	100	100	14.28	1	14.28	97.71		9.30		Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	8	200	200	15.00	1	15.00	92.25		8.88		Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	9	300	300	11.11	1	11.11	123.94		12.41		Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	7	100	100	14.28	1	14.28	97.71		10.46		Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	9	200	200	13.33	1	13.33	103.51		11.72		Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	11	260	260	12.73	1	12.73	111.21			
Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	Factor Correction (mm) (F)	Factor Correction (mm) (G)	Factor Correction (mm) (H)	Average CBR %	Observations																																																																																																																																														
Limo, in-situ condition firm, medium bedded, dry and light brown coloring.	4	31	30	7.50	1	7.50	20.10		31.90	Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two																																																																																																																																														
Organic silt, in-situ condition firm, medium bedded, dry and greyish coloration.	13	40	40	3.08	1	3.08	50.53		61.91																																																																																																																																															
Organic clayey silt, firm-silt, medium bedded, dry and grey coloring condition.	6	30	30	2.50	1	2.50	68.80		15.24																																																																																																																																															
Clayey silt, in-situ condition firm, medium bedded, partially dry, dark brown with light brown partings.	4	50	50	12.50	1	12.50	113.34		17.31																																																																																																																																															
Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.	5	100	100	15.00	1	15.00	92.25		10.19																																																																																																																																															
Clayey silt, in-situ condition firm, medium bedded, dry and grey coloring condition.	4	60	60	15.00	1	15.00	92.25		9.28																																																																																																																																															
Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	7	100	100	14.28	1	14.28	97.71		9.30																																																																																																																																															
Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	8	200	200	15.00	1	15.00	92.25		8.88																																																																																																																																															
Limo Sandy, in-situ condition firm, medium compaction, saturated state and dark brown coloration.	9	300	300	11.11	1	11.11	123.94		12.41																																																																																																																																															
Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	7	100	100	14.28	1	14.28	97.71		10.46																																																																																																																																															
Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	9	200	200	13.33	1	13.33	103.51		11.72																																																																																																																																															
Limo Clay, in-situ condition firm, medium compaction, saturated state and brown with grey partings.	11	260	260	12.73	1	12.73	111.21																																																																																																																																																	
<p><b>OBSERVATIONS:</b>  A= Number of hammer blows between readings.  B= Average CBR of the first two readings.  C= Uniform cone penetration (mm) between readings.  D= Factor Correction (mm) for the first two readings.  E= Factor Correction (mm) for the first two readings.  F= Factor Correction (mm) for the first two readings.  G= Factor Correction (mm) for the first two readings.  H= Factor Correction (mm) for the first two readings.</p>																																																																																																																																																								
<p>The presence of the Water Table at a depth of 2.10 m was evident, until the end of Geotechnical Study. For the study is considered the month (full) of survey done.</p>																																																																																																																																																								
DATE OF CREATION OF TEST:				30/08/2014		DATE OF CREATION OF TEST:		30/08/2014																																																																																																																																																
CLOSING DATE OF TEST:				30/08/2014		CLOSING DATE OF TEST:		30/08/2014																																																																																																																																																
						LABORATORY MANAGER																																																																																																																																																		

PROFESIONISTA:		WATER TABLE:		TEST DATA		TEST RESULTS		WEIGHT HAMMER:																																																																																																																																																																																																							
5-515		1.50 m.		17°16'18.50" S 62°54'16.00" W		8 Kg.		8 Kg.																																																																																																																																																																																																							
<p><b>CLIENTE / CLIENT:</b> KATAMBA &amp; Engineers International  <b>PROYECTO / PROJECT:</b> Preparatory Study of the Urban 7-1 Road III Road Boring Project  <b>UBICACION / LOCATION:</b> Municipality of Chiminá 7-11, 2° Section, Verano Province, Northern Region of Santa Cruz de la Sierra City</p>																																																																																																																																																																																																															
<p><b>RECORD FIELD</b></p> <table border="1"> <thead> <tr> <th>Visual Description of the Material</th> <th>Number of Blows (A)</th> <th>Cumulative Penetration (mm) (G)</th> <th>Penetration Between Readings (mm) (C)</th> <th>Factor Correction (mm) (D)</th> <th>Factor Correction (mm) (E)</th> <th>Factor Correction (mm) (F)</th> <th>Factor Correction (mm) (G)</th> <th>Factor Correction (mm) (H)</th> <th>Average CBR %</th> <th>Observations</th> </tr> </thead> <tbody> <tr> <td>Filled with Granular Base Layer Material Type</td> <td>22</td> <td>60</td> <td>30</td> <td>1.36</td> <td>1</td> <td>1.36</td> <td>135.66</td> <td></td> <td>68.80</td> <td>Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two</td> </tr> <tr> <td>Limo, in-situ condition firm, compact consistency, dry and dark brown coloration.</td> <td>17</td> <td>80</td> <td>40</td> <td>4.44</td> <td>1</td> <td>4.44</td> <td>36.12</td> <td></td> <td>68.03</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.</td> <td>11</td> <td>110</td> <td>30</td> <td>2.73</td> <td>1</td> <td>2.73</td> <td>62.41</td> <td></td> <td>62.41</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.</td> <td>2</td> <td>40</td> <td>40</td> <td>20.00</td> <td>1</td> <td>20.00</td> <td>6.70</td> <td></td> <td>6.70</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.</td> <td>4</td> <td>100</td> <td>60</td> <td>15.00</td> <td>1</td> <td>15.00</td> <td>92.25</td> <td></td> <td>8.18</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.</td> <td>5</td> <td>180</td> <td>80</td> <td>16.00</td> <td>1</td> <td>16.00</td> <td>8.60</td> <td></td> <td>8.60</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.</td> <td>5</td> <td>60</td> <td>60</td> <td>12.00</td> <td>1</td> <td>12.00</td> <td>118.71</td> <td></td> <td>11.79</td> <td></td> </tr> <tr> <td>Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.</td> <td>6</td> <td>140</td> <td>80</td> <td>13.33</td> <td>1</td> <td>13.33</td> <td>103.51</td> <td></td> <td>12.94</td> <td></td> </tr> <tr> <td>Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.</td> <td>6</td> <td>100</td> <td>100</td> <td>16.67</td> <td>1</td> <td>16.67</td> <td>8.22</td> <td></td> <td>8.22</td> <td></td> </tr> <tr> <td>Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.</td> <td>10</td> <td>200</td> <td>100</td> <td>10.00</td> <td>1</td> <td>10.00</td> <td>14.56</td> <td></td> <td>10.33</td> <td></td> </tr> <tr> <td>Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.</td> <td>6</td> <td>300</td> <td>100</td> <td>16.67</td> <td>1</td> <td>16.67</td> <td>8.22</td> <td></td> <td>8.22</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>3</td> <td>80</td> <td>80</td> <td>26.67</td> <td>1</td> <td>26.67</td> <td>4.86</td> <td></td> <td>4.86</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>3</td> <td>160</td> <td>80</td> <td>26.67</td> <td>1</td> <td>26.67</td> <td>4.86</td> <td></td> <td>4.50</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>3</td> <td>260</td> <td>100</td> <td>33.33</td> <td>1</td> <td>33.33</td> <td>3.78</td> <td></td> <td>3.78</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>4</td> <td>70</td> <td>70</td> <td>17.50</td> <td>1</td> <td>17.50</td> <td>7.78</td> <td></td> <td>7.78</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>6</td> <td>130</td> <td>80</td> <td>13.33</td> <td>1</td> <td>13.33</td> <td>10.35</td> <td></td> <td>9.78</td> <td></td> </tr> <tr> <td>Firm-silt, on average compaction, saturated state and dark brown coloration.</td> <td>7</td> <td>170</td> <td>90</td> <td>12.66</td> <td>1</td> <td>12.66</td> <td>10.99</td> <td></td> <td>10.99</td> <td></td> </tr> </tbody> </table>										Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	Factor Correction (mm) (F)	Factor Correction (mm) (G)	Factor Correction (mm) (H)	Average CBR %	Observations	Filled with Granular Base Layer Material Type	22	60	30	1.36	1	1.36	135.66		68.80	Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two	Limo, in-situ condition firm, compact consistency, dry and dark brown coloration.	17	80	40	4.44	1	4.44	36.12		68.03		Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	11	110	30	2.73	1	2.73	62.41		62.41		Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	2	40	40	20.00	1	20.00	6.70		6.70		Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	4	100	60	15.00	1	15.00	92.25		8.18		Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	5	180	80	16.00	1	16.00	8.60		8.60		Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.	5	60	60	12.00	1	12.00	118.71		11.79		Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.	6	140	80	13.33	1	13.33	103.51		12.94		Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	6	100	100	16.67	1	16.67	8.22		8.22		Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	10	200	100	10.00	1	10.00	14.56		10.33		Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	6	300	100	16.67	1	16.67	8.22		8.22		Firm-silt, on average compaction, saturated state and dark brown coloration.	3	80	80	26.67	1	26.67	4.86		4.86		Firm-silt, on average compaction, saturated state and dark brown coloration.	3	160	80	26.67	1	26.67	4.86		4.50		Firm-silt, on average compaction, saturated state and dark brown coloration.	3	260	100	33.33	1	33.33	3.78		3.78		Firm-silt, on average compaction, saturated state and dark brown coloration.	4	70	70	17.50	1	17.50	7.78		7.78		Firm-silt, on average compaction, saturated state and dark brown coloration.	6	130	80	13.33	1	13.33	10.35		9.78		Firm-silt, on average compaction, saturated state and dark brown coloration.	7	170	90	12.66	1	12.66	10.99		10.99	
Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	Factor Correction (mm) (F)	Factor Correction (mm) (G)	Factor Correction (mm) (H)	Average CBR %	Observations																																																																																																																																																																																																					
Filled with Granular Base Layer Material Type	22	60	30	1.36	1	1.36	135.66		68.80	Due to the characteristics of these soils (Base Layer) the cone penetrometer was dragged during the test, since it would be average, since it would be because the test was conducted on an unsaturated state and the average CBR of the first two																																																																																																																																																																																																					
Limo, in-situ condition firm, compact consistency, dry and dark brown coloration.	17	80	40	4.44	1	4.44	36.12		68.03																																																																																																																																																																																																						
Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	11	110	30	2.73	1	2.73	62.41		62.41																																																																																																																																																																																																						
Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	2	40	40	20.00	1	20.00	6.70		6.70																																																																																																																																																																																																						
Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	4	100	60	15.00	1	15.00	92.25		8.18																																																																																																																																																																																																						
Limo, in-situ condition firm, partially saturated compact consistency, state and dark brown coloration.	5	180	80	16.00	1	16.00	8.60		8.60																																																																																																																																																																																																						
Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.	5	60	60	12.00	1	12.00	118.71		11.79																																																																																																																																																																																																						
Limo, in-situ condition firm, medium bedded, partially saturated state and dark brown with grey partings.	6	140	80	13.33	1	13.33	103.51		12.94																																																																																																																																																																																																						
Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	6	100	100	16.67	1	16.67	8.22		8.22																																																																																																																																																																																																						
Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	10	200	100	10.00	1	10.00	14.56		10.33																																																																																																																																																																																																						
Silty Sand plasticity condition without strong in-situ, on average compaction, saturated state and dark brown coloration.	6	300	100	16.67	1	16.67	8.22		8.22																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	3	80	80	26.67	1	26.67	4.86		4.86																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	3	160	80	26.67	1	26.67	4.86		4.50																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	3	260	100	33.33	1	33.33	3.78		3.78																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	4	70	70	17.50	1	17.50	7.78		7.78																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	6	130	80	13.33	1	13.33	10.35		9.78																																																																																																																																																																																																						
Firm-silt, on average compaction, saturated state and dark brown coloration.	7	170	90	12.66	1	12.66	10.99		10.99																																																																																																																																																																																																						
<p><b>OBSERVATIONS:</b>  A= Number of hammer blows between readings.  B= Average CBR of the first two readings.  C= Uniform cone penetration (mm) between readings.  D= Factor Correction (mm) for the first two readings.  E= Factor Correction (mm) for the first two readings.  F= Factor Correction (mm) for the first two readings.  G= Factor Correction (mm) for the first two readings.  H= Factor Correction (mm) for the first two readings.</p>																																																																																																																																																																																																															
<p>The presence of the Water Table at a depth of 1.50 m was evident, until the end of Geotechnical Study. For the study is considered the month (full) of survey done.</p>																																																																																																																																																																																																															
DATE OF CREATION OF TEST:				27/08/2014		DATE OF CREATION OF TEST:		27/08/2014																																																																																																																																																																																																							
CLOSING DATE OF TEST:				27/08/2014		CLOSING DATE OF TEST:		27/08/2014																																																																																																																																																																																																							
						LABORATORY MANAGER																																																																																																																																																																																																									


		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 Date: 27/08/2014 REPORT: RP 00 PAGE: 01 de 01
		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 Date: 27/08/2014 REPORT: RP 00 PAGE: 01 de 01
<b>CLIENTE / Client:</b> KATAMBA & Engineers International <b>PROYECTO / Project:</b> Preparatory Study of the Urban 7-11 and 111 Road Paving Project <b>UBICACION / Location:</b> Municipality of Chiminá 7-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		<b>DCP N°:</b> 13		REV: 00 Date: 27/08/2014 REPORT: RP 00 PAGE: 01 de 01
<b>PROFESIONISTA:</b> 6-010 X Coordinate: 17°16'24.60"N Y Coordinate: 62°54'05.50"W		<b>WEIGHT HAMMER:</b> 8 Kg.		REV: 00 Date: 27/08/2014 REPORT: RP 00 PAGE: 01 de 01
<b>TEST DATA</b>		<b>TEST DATA</b>		REV: 00 Date: 27/08/2014 REPORT: RP 00 PAGE: 01 de 01

DEPTH (m)	K.M.F. (mm)	VISUAL DESCRIPTION OF THE MATERIAL	TEST RESULTS				AVERAGE CBR %	observations	
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)			Factor Correction (mm) (E)
0.10	0.15	Filled with Granular Base Layer Material Type	18	30	30	1.67	1.67	106.35	Due to the characteristics of these soils (Base Layer) disintegration occurred during calibration. The average area would be 106.35 cm <sup>2</sup> because the test was conducted on unsoaked samples. The average CBR of the first two
0.30	0.45	Limo, in-situ condition firm, compact consistency, dry and dark brown coloration	7	40	40	5.71	5.71	27.26	
0.50	0.90	Firmstiu, on average compactness, partially saturated state and dark brown coloration Sandy Limo condition	3	50	50	16.67	16.67	8.22	
0.70	1.10	Clayey SIL firm condition in-situ, medium consistency, saturated state and dark brown coloration	3	100	50	16.67	16.67	8.22	
0.90	1.30		9	130	40	4.44	4.44	36.12	
1.10	1.50		5	70	70	14.00	14.00	9.09	
1.30	1.70		7	150	80	11.43	11.43	12.54	
1.50	1.90		5	240	90	18.00	18.00	7.54	
1.70	2.10		5	40	80	16.00	16.00	8.60	
1.90	2.30		10	170	50	9.00	9.00	16.38	
2.10	2.50		8	270	100	12.50	12.50	11.34	
2.30	2.70		6	40	60	10.00	10.00	14.56	
2.50	2.90		6	140	80	13.33	13.33	10.55	
2.70	3.10		9	240	100	11.11	11.11	12.94	
2.90	3.30		8	90	90	11.25	11.25	12.76	
3.10	3.50		10	190	100	10.00	10.00	14.56	
3.30	3.70		10	200	100	10.00	10.00	14.56	
3.50	3.90		10	220	100	10.00	10.00	14.56	
3.70	4.10		10	220	90	9.00	9.00	16.39	
3.90	4.30		10	220	90	9.00	9.00	16.39	
4.10	4.50		10	220	90	9.00	9.00	16.39	
4.30	4.70		10	220	90	9.00	9.00	16.39	
4.50	4.90		10	220	90	9.00	9.00	16.39	
4.70	5.10		10	220	90	9.00	9.00	16.39	
4.90	5.30		10	220	90	9.00	9.00	16.39	
5.10	5.50		10	220	90	9.00	9.00	16.39	
5.30	5.70		10	220	90	9.00	9.00	16.39	
5.50	5.90		10	220	90	9.00	9.00	16.39	
5.70	6.10		10	220	90	9.00	9.00	16.39	
5.90	6.30		10	220	90	9.00	9.00	16.39	
6.10	6.50		10	220	90	9.00	9.00	16.39	
6.30	6.70		10	220	90	9.00	9.00	16.39	
6.50	6.90		10	220	90	9.00	9.00	16.39	
6.70	7.10		10	220	90	9.00	9.00	16.39	
6.90	7.30		10	220	90	9.00	9.00	16.39	
7.10	7.50		10	220	90	9.00	9.00	16.39	
7.30	7.70		10	220	90	9.00	9.00	16.39	
7.50	7.90		10	220	90	9.00	9.00	16.39	
7.70	8.10		10	220	90	9.00	9.00	16.39	
7.90	8.30		10	220	90	9.00	9.00	16.39	
8.10	8.50		10	220	90	9.00	9.00	16.39	
8.30	8.70		10	220	90	9.00	9.00	16.39	
8.50	8.90		10	220	90	9.00	9.00	16.39	
8.70	9.10		10	220	90	9.00	9.00	16.39	
8.90	9.30		10	220	90	9.00	9.00	16.39	
9.10	9.50		10	220	90	9.00	9.00	16.39	
9.30	9.70		10	220	90	9.00	9.00	16.39	
9.50	9.90		10	220	90	9.00	9.00	16.39	
9.70	10.10		10	220	90	9.00	9.00	16.39	
9.90	10.30		10	220	90	9.00	9.00	16.39	
10.10	10.50		10	220	90	9.00	9.00	16.39	
10.30	10.70		10	220	90	9.00	9.00	16.39	
10.50	10.90		10	220	90	9.00	9.00	16.39	
10.70	11.10		10	220	90	9.00	9.00	16.39	
10.90	11.30		10	220	90	9.00	9.00	16.39	
11.10	11.50		10	220	90	9.00	9.00	16.39	
11.30	11.70		10	220	90	9.00	9.00	16.39	
11.50	11.90		10	220	90	9.00	9.00	16.39	
11.70	12.10		10	220	90	9.00	9.00	16.39	
11.90	12.30		10	220	90	9.00	9.00	16.39	
12.10	12.50		10	220	90	9.00	9.00	16.39	
12.30	12.70		10	220	90	9.00	9.00	16.39	
12.50	12.90		10	220	90	9.00	9.00	16.39	
12.70	13.10		10	220	90	9.00	9.00	16.39	
12.90	13.30		10	220	90	9.00	9.00	16.39	
13.10	13.50		10	220	90	9.00	9.00	16.39	
13.30	13.70		10	220	90	9.00	9.00	16.39	
13.50	13.90		10	220	90	9.00	9.00	16.39	
13.70	14.10		10	220	90	9.00	9.00	16.39	
13.90	14.30		10	220	90	9.00	9.00	16.39	
14.10	14.50		10	220	90	9.00	9.00	16.39	
14.30	14.70		10	220	90	9.00	9.00	16.39	
14.50	14.90		10	220	90	9.00	9.00	16.39	
14.70	15.10		10	220	90	9.00	9.00	16.39	
14.90	15.30		10	220	90	9.00	9.00	16.39	
15.10	15.50		10	220	90	9.00	9.00	16.39	
15.30	15.70		10	220	90	9.00	9.00	16.39	
15.50	15.90		10	220	90	9.00	9.00	16.39	
15.70	16.10		10	220	90	9.00	9.00	16.39	
15.90	16.30		10	220	90	9.00	9.00	16.39	
16.10	16.50		10	220	90	9.00	9.00	16.39	
16.30	16.70		10	220	90	9.00	9.00	16.39	
16.50	16.90		10	220	90	9.00	9.00	16.39	
16.70	17.10		10	220	90	9.00	9.00	16.39	
16.90	17.30		10	220	90	9.00	9.00	16.39	
17.10	17.50		10	220	90	9.00	9.00	16.39	
17.30	17.70		10	220	90	9.00	9.00	16.39	
17.50	17.90		10	220	90	9.00	9.00	16.39	
17.70	18.10		10	220	90	9.00	9.00	16.39	
17.90	18.30		10	220	90	9.00	9.00	16.39	
18.10	18.50		10	220	90	9.00	9.00	16.39	
18.30	18.70		10	220	90	9.00	9.00	16.39	
18.50	18.90		10	220	90	9.00	9.00	16.39	
18.70	19.10		10	220	90	9.00	9.00	16.39	
18.90	19.30		10	220	90	9.00	9.00	16.39	
19.10	19.50		10	220	90	9.00	9.00	16.39	
19.30	19.70		10	220	90	9.00	9.00	16.39	
19.50	19.90		10	220	90	9.00	9.00	16.39	
19.70	20.10		10	220	90	9.00	9.00	16.39	
19.90	20.30		10	220	90	9.00	9.00	16.39	
20.10	20.50		10	220	90	9.00	9.00	16.39	
20.30	20.70		10	220	90	9.00	9.00	16.39	
20.50	20.90		10	220	90	9.00	9.00	16.39	
20.70	21.10		10	220	90	9.00	9.00	16.39	
20.90	21.30		10	220	90	9.00	9.00	16.39	
21.10	21.50		10	220	90	9.00	9.00	16.39	
21.30	21.70		10	220	90	9.00	9.00	16.39	
21.50	21.90		10	220	90	9.00	9.00	16.39	
21.70	22.10		10	220	90	9.00	9.00	16.39	
21.90	22.30		10	220	90	9.00	9.00	16.39	
22.10	22.50		10	220	90	9.00	9.00	16.39	
22.30	22.70		10	220	90	9.00	9.00	16.39	
22.50	22.90		10	220	90	9.00	9.00	16.39	
22.70	23.10		10	220	90	9.00	9.00	16.39	
22.90	23.30		10	220	90	9.00	9.00	16.39	
23.10	23.50		10	220	90	9.00	9.00	16.39	
23.30	23.70		10	220	90	9.00	9.00	16.39	
23.50	23.90		10	220	90	9.00	9.00	16.39	
23.70	24.10		10	220	90	9.00	9.00	16.39	
23.90	24.30		10	220	90	9.00	9.00	1	



REV.:		27/08/2014		RP 00		01 de 01				
DYNAMIC PENETRATION TESTING (DCP)		NORMA ASTM-D-6951-03		WEIGHT HAMMER:		8 Kg.				
CLIENTE / Client:		KATAMBA & Engineers International		X Coordinate:		1791729,30°S				
PROYECTO / Project:		Preparatory Study of the Urban 1-1 Road III Road Paving Project		Y Coordinate:		62°54'04,30°O				
UBICACION / Location:		Municipality of Chitina 1-1, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City		DCP N°:		17				
TEST DATA										
PROFESOR:		84-000		1791729,30°S		WEIGHT HAMMER:				
WATER TABLE:		1,40 m.		62°54'04,30°O		8 Kg.				
RECORD FIELD										
DEPTH (m)	NO. OF TESTS	DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Pundada) (F)	CBR % (G)	AVERAGE CBR %	observations
0,10	14	Filled with Granular Base Layer Material Type	14	31	30	2,14	1	2,14	81,77	79,60
0,20	14	Clay, in-situ condition firm, compact consistency, dry and dark brown coloration.	14	30	30	2,14	1	2,14	81,77	
0,30	6	Clay, in-situ condition firm, compact consistency, dry and dark brown coloration.	6	40	40	6,67	1	6,67	22,94	
0,40	8	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	8	48	40	5,00	1	5,00	31,66	31,14
0,50	12	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	12	130	50	4,17	1	4,17	38,83	
0,60	13	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	13	50	50	3,85	1	3,85	42,47	
0,70	12	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	12	100	50	4,17	1	4,17	38,83	
0,80	12	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	12	150	50	4,17	1	4,17	38,83	
0,90	5	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	5	50	50	10,00	1	10,00	14,56	
1,00	6	Sandy Lino firm condition in-situ on average compactness, partially saturated state and dark brown coloration.	6	110	60	10,00	1	10,00	14,56	13,89
1,10	7	Clay, in-situ condition firm, medium consistency, saturated state and gray color with light brown patina.	7	150	80	11,43	1	11,43	12,54	
1,20	7	Clay, in-situ condition firm, medium consistency, saturated state and gray color with light brown patina.	7	70	70	10,00	1	10,00	14,56	
1,30	6	Limo Clay, in-situ condition firm, medium consistency, saturated state and light brown coloration.	6	150	80	13,33	1	13,33	10,55	12,04
1,40	7	Limo Clay, in-situ condition firm, medium consistency, saturated state and light brown coloration.	7	240	90	12,86	1	12,86	10,99	
1,50	8	Clay, in-situ condition firm, medium consistency, saturated state, light brown with gray patina.	8	80	80	10,00	1	10,00	14,56	15,17
1,60	8	Clay, in-situ condition firm, medium consistency, saturated state, light brown with gray patina.	8	170	90	9,00	1	9,00	16,38	
1,70	8	Clay, in-situ condition firm, medium consistency, saturated state, light brown with gray patina.	8	250	80	10,00	1	10,00	14,56	
OBSERVATIONS:										
The presence of the Water Table at a depth of 1,40 m was evident, until the end of Geotechnical Study. For the study is considered the month 01/01 of survey done.										
A= Number of hammer blows between readings B= Total number of hammer blows C= Difference between readings (mm) between readings D= Cumulative penetration (mm) between readings E= Factor correction (mm) F= DCP Index (mm / Pundada) G= Correlation between CBR and DCP index.										
DATE OF CREATION OF TEST:				27/08/2014						
CLOSING DATE OF TEST:				27/08/2014						
				LABORATORY MANAGER						

REV.:		20/08/2014		RP 00		01 de 01				
DYNAMIC PENETRATION TESTING (DCP)		NORMA ASTM-D-6951-03		WEIGHT HAMMER:		8 Kg.				
CLIENTE / Client:		KATAMBA & Engineers International		X Coordinate:		1791753,20°S				
PROYECTO / Project:		Preparatory Study of the Urban 1-1 Road III Road Paving Project		Y Coordinate:		62°53'55,80°O				
UBICACION / Location:		Municipality of Chitina 1-1, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City		DCP N°:		18				
TEST DATA										
PROFESOR:		84-500		1791753,20°S		WEIGHT HAMMER:				
WATER TABLE:		1,00 m.		62°53'55,80°O		8 Kg.				
RECORD FIELD										
DEPTH (m)	NO. OF TESTS	DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Pundada) (F)	CBR % (G)	AVERAGE CBR %	observations
0,10	9	Limo, in-situ condition compact, dense consistency, saturated state and dark brown coloration.	9	30	30	3,33	1	3,33	49,85	
0,20	10	Limo, in-situ condition compact, dense consistency, saturated state and dark brown coloration.	10	60	30	3,00	1	3,00	56,10	64,76
0,30	15	Limo, in-situ condition compact, dense consistency, saturated state and dark brown coloration.	15	90	30	2,00	1	2,00	88,34	
0,40	5	Limo, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	5	40	40	8,00	1	8,00	18,70	
0,50	5	Limo, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	5	70	30	6,00	1	6,00	25,81	22,48
0,60	6	Clay loam, in-situ condition firm, medium consistency, partially saturated state and changes to dark brown with light brown patina.	6	110	40	6,67	1	6,67	22,94	
0,70	3	Clay loam, in-situ condition firm, medium consistency, partially saturated state and changes to dark brown with light brown patina.	3	40	40	13,33	1	13,33	10,55	
0,80	4	Clay loam, in-situ condition firm, medium consistency, partially saturated state and changes to dark brown with light brown patina.	4	80	40	10,00	1	10,00	14,56	13,23
0,90	5	Clay loam, in-situ condition firm, medium consistency, partially saturated state and changes to dark brown with light brown patina.	5	130	50	10,00	1	10,00	14,56	
1,00	2	Sandy Lino firm condition in-situ on average compactness, saturated state and dark brown coloration.	2	80	80	40,00	1	40,00	3,08	
1,10	2	Sandy Lino firm condition in-situ on average compactness, saturated state and dark brown coloration.	2	150	70	35,00	1	35,00	3,58	2,59
1,20	1	Sandy Lino firm condition in-situ on average compactness, saturated state and dark brown coloration.	1	250	100	100,00	1	100,00	1,10	
1,30	2	Limo Clay, of weak in-situ condition, soft consistency, saturated state and gray and brown coloring.	2	80	80	45,00	1	45,00	2,70	
1,40	3	Limo Clay, of weak in-situ condition, soft consistency, saturated state and gray and brown coloring.	3	150	100	33,33	1	33,33	3,79	5,94
1,50	8	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	8	250	100	12,50	1	12,50	11,34	
1,60	5	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	5	90	90	10,00	1	10,00	14,56	
1,70	5	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	5	40	40	8,00	1	8,00	18,70	18,73
1,80	6	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	6	130	40	6,67	1	6,67	22,94	
1,90	6	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	6	200	80	10,00	1	10,00	14,56	13,67
2,00	8	Clay, in-situ condition firm, medium consistency, saturated state and reddish coloration.	8	200	80	10,00	1	10,00	14,56	
OBSERVATIONS:										
The presence of the Water Table at a depth of 1,00 m was evident, until the end of Geotechnical Study. For the study is considered the month 01/01 of survey done.										
A= Number of hammer blows between readings B= Total number of hammer blows C= Difference between readings (mm) between readings D= Cumulative penetration (mm) between readings E= Factor correction (mm) F= DCP Index (mm / Pundada) G= Correlation between CBR and DCP index.										
DATE OF CREATION OF TEST:				28/08/2014						
CLOSING DATE OF TEST:				28/08/2014						
				LABORATORY MANAGER						

		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 Date: 20/08/2014 REPORT: RP 00 PAGE: 01 de 01
CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Camino 7-E and III Road Boring Project</b> UBICACION / Location: <b>Municipality of Chimu in T-H, 2° Section, Vicos Pampa, Northern Region of Santa Cruz de la Sierra City</b>		<b>DCP N°:</b> 19		
<b>TEST DATA</b>				
<b>PROGRESIVO:</b> 9+000		X Coordinate: 17°18'25.80" S Y Coordinate: 62°53'53.50" W		<b>WEIGHT HAMMER:</b> 8 Kg.
<b>WATER TABLE:</b> not Applicable				

K.M.T.	MATERIAL	DEPTH (m)	TEST RESULTS					AVERAGE CBR %	OBSERVATIONS
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Puntos) (B)		
0.15	Filled with Granular Base Layer Material Type	30	15	30	2.00	1	2.00	86.34	
0.15	Filled with Granular Base Layer Material Type	30	18	108.36	1.67	1	1.67	108.36	Due to the characteristics of these soils (Base Layer) dropped values are observed, therefore, an average value would be used because the test was not conducted in accordance with the standard and the CBR = 88.34%.
0.90	Clay in-situ condition dense, compact consistency, dry and gray coloring.	40	11	40	3.64	1	3.64	46.22	
0.90	Clay in-situ condition dense, compact consistency, dry and gray coloring.	40	11	40	3.64	1	3.64	46.22	
0.90	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	40	12	120	4.00	1	4.00	48.85	
1.00	Alimo condition in-situ firm, dense, medium bodied, dry and dark brown coloration.	30	4	30	7.50	1	7.50	20.10	
1.00	Alimo condition in-situ firm, dense, medium bodied, dry and dark brown coloration.	40	8	70	4.00	1	5.00	37.66	26.34
1.00	Alimo condition in-situ firm, dense, medium bodied, dry and dark brown coloration.	40	7	110	4.00	1	5.71	27.26	
1.00	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	40	7	40	5.71	1	5.71	27.26	
1.00	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	40	10	120	4.00	1	4.00	40.64	36.18
1.00	Limón, in-situ condition firm, medium bodied, partially dry and yellowish coloration.	50	11	50	4.55	1	4.55	36.22	
1.00	Limón, in-situ condition firm, medium bodied, partially dry and yellowish coloration.	40	10	50	4.00	1	4.00	40.64	36.85
1.00	Limón, in-situ condition firm, medium bodied, partially dry and yellowish coloration.	30	8	120	3.75	1	3.75	45.68	
1.00	Clay, in-situ condition firm, medium bodied, partially dry and light gray color with reddish patinas.	50	18	50	2.78	1	2.78	61.14	
1.00	Clay, in-situ condition firm, medium bodied, partially dry and light gray color with reddish patinas.	40	14	50	2.86	1	2.86	59.25	61.47
1.00	Clay, in-situ condition firm, medium bodied, partially dry and light gray color with reddish patinas.	40	15	130	4.00	1	2.67	64.01	
1.00	Limón, in-situ condition firm, medium bodied, partially dry and brown coloring.	30	9	30	3.33	1	3.33	48.85	
1.00	Limón, in-situ condition firm, medium bodied, partially dry and brown coloring.	40	15	70	2.67	1	2.67	64.01	64.12
1.00	Limón, in-situ condition firm, medium bodied, partially dry and brown coloring.	40	18	110	2.22	1	2.22	76.51	
1.00	Clay, in-situ condition firm, medium bodied, partially dry and gray coloring.	30	9	30	3.33	1	3.33	48.85	
1.00	Clay, in-situ condition firm, medium bodied, partially dry and gray coloring.	40	12	70	3.33	1	3.33	48.85	46.78
1.00	Clay, in-situ condition firm, medium bodied, partially dry and gray coloring.	40	10	110	4.00	1	4.00	40.64	

<b>PROGRESIVO:</b> 9+500		X Coordinate: 17°18'25.80" S Y Coordinate: 62°53'53.50" W		<b>WEIGHT HAMMER:</b> 8 Kg.					
<b>WATER TABLE:</b> not Applicable									
<b>TEST DATA</b>									
<b>RECORD FIELD</b>									
K.M.T.	MATERIAL	DEPTH (m)	TEST RESULTS					AVERAGE CBR %	OBSERVATIONS
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Puntos) (B)		
0.20	Clay in-situ condition dense, compact consistency, dry and gray coloring.	30	16	70	4.00	1	2.50	68.80	64.75
0.20	Clay in-situ condition dense, compact consistency, dry and gray coloring.	30	14	100	3.00	1	2.14	81.77	
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	5	40	8.00	1	8.00	18.70	
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	8	80	4.00	1	5.00	31.66	29.33
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	7	110	3.00	1	4.29	37.62	30.74
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	5	30	6.00	1	6.00	26.81	
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	8	70	4.00	1	5.00	31.66	33.31
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	13	120	5.00	1	3.85	42.47	
0.20	Limón, in-situ condition firm, medium bodied, partially dry and brown with gray patinas.	30	10	40	4.00	1	4.00	40.64	
0.20	Limón, in-situ condition firm, medium bodied, partially dry and brown with gray patinas.	30	13	110	4.00	1	3.08	56.10	50.42
0.20	Clay, in-situ condition firm, medium bodied, partially dry and reddish coloration gray slate.	30	9	40	4.44	1	4.44	36.12	
0.20	Clay, in-situ condition firm, medium bodied, partially dry, reddish and gray coloring.	30	12	80	3.33	1	3.33	48.85	49.46
0.20	Clay, in-situ condition firm, medium bodied, partially dry and reddish coloration gray slate.	30	11	110	3.00	1	2.73	62.41	
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	14	30	2.14	1	2.14	81.77	
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	24	70	4.00	1	5.67	105.35	92.62
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	20	110	2.00	1	2.00	88.34	

<b>PROGRESIVO:</b> 9+500		X Coordinate: 17°18'25.80" S Y Coordinate: 62°53'53.50" W		<b>WEIGHT HAMMER:</b> 8 Kg.					
<b>WATER TABLE:</b> not Applicable									
<b>TEST DATA</b>									
<b>RECORD FIELD</b>									
K.M.T.	MATERIAL	DEPTH (m)	TEST RESULTS					AVERAGE CBR %	OBSERVATIONS
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Puntos) (B)		
0.20	Clay in-situ condition dense, compact consistency, dry and gray coloring.	30	16	70	4.00	1	2.50	68.80	64.75
0.20	Clay in-situ condition dense, compact consistency, dry and gray coloring.	30	14	100	3.00	1	2.14	81.77	
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	5	40	8.00	1	8.00	18.70	
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	8	80	4.00	1	5.00	31.66	29.33
0.20	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	30	7	110	3.00	1	4.29	37.62	30.74
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	5	30	6.00	1	6.00	26.81	
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	8	70	4.00	1	5.00	31.66	33.31
0.20	Clay, in-situ condition firm, medium consistency, saturated state and dark brown coloration.	30	13	120	5.00	1	3.85	42.47	
0.20	Limón, in-situ condition firm, medium bodied, partially dry and brown with gray patinas.	30	10	40	4.00	1	4.00	40.64	
0.20	Limón, in-situ condition firm, medium bodied, partially dry and brown with gray patinas.	30	13	110	4.00	1	3.08	56.10	50.42
0.20	Clay, in-situ condition firm, medium bodied, partially dry and reddish coloration gray slate.	30	9	40	4.44	1	4.44	36.12	
0.20	Clay, in-situ condition firm, medium bodied, partially dry, reddish and gray coloring.	30	12	80	3.33	1	3.33	48.85	49.46
0.20	Clay, in-situ condition firm, medium bodied, partially dry and reddish coloration gray slate.	30	11	110	3.00	1	2.73	62.41	
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	14	30	2.14	1	2.14	81.77	
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	24	70	4.00	1	5.67	105.35	92.62
0.20	Clay, strong in-situ condition, medium consistency, partially dry and reddish coloration gray slate.	30	20	110	2.00	1	2.00	88.34	

A= Number of hammer blows between readings.  
 B= DCP Index (mm / Puntos).  
 C= Penetration between readings (mm).  
 D= Factor Correction.  
 E= Position of the hammer in kg. And "mm" if the hammer is 4.0 kg.  
 F= CBR %.  
 G= Correlation between CBR and DCP Index.

The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the maximum level of survey data.

DATE OF CREATION OF TEST: 28/08/2014  
 CLOSING DATE OF TEST: 28/08/2014  
 LABORATORY MANAGER:

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 20/08/2014 RP 00 01 de 01																																																																																																																																																																																																																																																																																															
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		21																																																																																																																																																																																																																																																																																															
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		21																																																																																																																																																																																																																																																																																															
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		21																																																																																																																																																																																																																																																																																															
<p>10-000</p> <p>not Applicable</p> <p>WEIGHT HAMMER: 8 Kg.</p>																																																																																																																																																																																																																																																																																																			
<p>TEST RESULTS</p> <table border="1"> <thead> <tr> <th>DEPTH (mm)</th> <th>Penetration Between Readings (mm)</th> <th>Penetration (mm)</th> <th>Factor E</th> <th>Factor D</th> <th>Factor C</th> <th>Factor B</th> <th>Factor A</th> <th>Cumulative Penetration (mm)</th> <th>Visual Description of the Material</th> <th>Observations</th> </tr> </thead> <tbody> <tr><td>0.10</td><td>30</td><td>2.00</td><td>1</td><td>2.00</td><td>1</td><td>2.00</td><td>1</td><td>2.00</td><td>Filled with Granular Base Layer Material Type</td><td>88.34</td></tr> <tr><td>0.10</td><td>30</td><td>1.36</td><td>1</td><td>1.36</td><td>1</td><td>1.36</td><td>1</td><td>3.36</td><td>Filled with Granular Base Layer Material Type</td><td>149.54</td></tr> <tr><td>0.10</td><td>30</td><td>1.25</td><td>1</td><td>1.25</td><td>1</td><td>1.25</td><td>1</td><td>4.61</td><td>Filled with Granular Base Layer Material Type</td><td>149.54</td></tr> <tr><td>0.60</td><td>40</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>9.61</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>31.66</td></tr> <tr><td>0.60</td><td>40</td><td>6.67</td><td>1</td><td>6.67</td><td>1</td><td>6.67</td><td>1</td><td>16.28</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>22.94</td></tr> <tr><td>0.60</td><td>30</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>21.28</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>31.66</td></tr> <tr><td>1.20</td><td>40</td><td>4.00</td><td>1</td><td>4.00</td><td>1</td><td>4.00</td><td>1</td><td>25.28</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>40.64</td></tr> <tr><td>1.20</td><td>30</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>27.59</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>75.26</td></tr> <tr><td>1.20</td><td>30</td><td>2.00</td><td>1</td><td>2.00</td><td>1</td><td>2.00</td><td>1</td><td>29.59</td><td>Clay in-situ condition dense, compact consistency, dry and light gray coloring.</td><td>88.34</td></tr> <tr><td>1.80</td><td>30</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>34.59</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>31.66</td></tr> <tr><td>1.80</td><td>30</td><td>6.67</td><td>1</td><td>6.67</td><td>1</td><td>6.67</td><td>1</td><td>41.26</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>22.94</td></tr> <tr><td>1.80</td><td>30</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>44.59</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>49.85</td></tr> <tr><td>2.40</td><td>40</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>50.59</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>31.66</td></tr> <tr><td>2.40</td><td>40</td><td>2.22</td><td>1</td><td>2.22</td><td>1</td><td>2.22</td><td>1</td><td>52.81</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>78.51</td></tr> <tr><td>2.40</td><td>40</td><td>2.86</td><td>1</td><td>2.86</td><td>1</td><td>2.86</td><td>1</td><td>55.67</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>59.25</td></tr> <tr><td>2.40</td><td>30</td><td>1.88</td><td>1</td><td>1.88</td><td>1</td><td>1.88</td><td>1</td><td>57.55</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>94.96</td></tr> <tr><td>2.40</td><td>30</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>60.05</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>74.34</td></tr> <tr><td>2.40</td><td>40</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>63.38</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>68.80</td></tr> <tr><td>2.40</td><td>40</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>66.05</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>49.85</td></tr> <tr><td>2.40</td><td>30</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>68.36</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>64.01</td></tr> <tr><td>2.40</td><td>30</td><td>2.73</td><td>1</td><td>2.73</td><td>1</td><td>2.73</td><td>1</td><td>71.09</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>75.26</td></tr> <tr><td>2.40</td><td>40</td><td>2.11</td><td>1</td><td>2.11</td><td>1</td><td>2.11</td><td>1</td><td>73.20</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>63.04</td></tr> <tr><td>2.40</td><td>40</td><td>2.11</td><td>1</td><td>2.11</td><td>1</td><td>2.11</td><td>1</td><td>75.31</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>68.80</td></tr> <tr><td>2.40</td><td>40</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>77.98</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>63.04</td></tr> <tr><td>2.40</td><td>40</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>2.67</td><td>1</td><td>80.65</td><td>Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.</td><td>68.80</td></tr> </tbody> </table>						DEPTH (mm)	Penetration Between Readings (mm)	Penetration (mm)	Factor E	Factor D	Factor C	Factor B	Factor A	Cumulative Penetration (mm)	Visual Description of the Material	Observations	0.10	30	2.00	1	2.00	1	2.00	1	2.00	Filled with Granular Base Layer Material Type	88.34	0.10	30	1.36	1	1.36	1	1.36	1	3.36	Filled with Granular Base Layer Material Type	149.54	0.10	30	1.25	1	1.25	1	1.25	1	4.61	Filled with Granular Base Layer Material Type	149.54	0.60	40	5.00	1	5.00	1	5.00	1	9.61	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	31.66	0.60	40	6.67	1	6.67	1	6.67	1	16.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	22.94	0.60	30	5.00	1	5.00	1	5.00	1	21.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	31.66	1.20	40	4.00	1	4.00	1	4.00	1	25.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	40.64	1.20	30	2.31	1	2.31	1	2.31	1	27.59	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	75.26	1.20	30	2.00	1	2.00	1	2.00	1	29.59	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	88.34	1.80	30	5.00	1	5.00	1	5.00	1	34.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	31.66	1.80	30	6.67	1	6.67	1	6.67	1	41.26	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	22.94	1.80	30	3.33	1	3.33	1	3.33	1	44.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	49.85	2.40	40	5.00	1	5.00	1	5.00	1	50.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	31.66	2.40	40	2.22	1	2.22	1	2.22	1	52.81	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	78.51	2.40	40	2.86	1	2.86	1	2.86	1	55.67	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	59.25	2.40	30	1.88	1	1.88	1	1.88	1	57.55	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	94.96	2.40	30	2.50	1	2.50	1	2.50	1	60.05	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	74.34	2.40	40	3.33	1	3.33	1	3.33	1	63.38	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80	2.40	40	2.67	1	2.67	1	2.67	1	66.05	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	49.85	2.40	30	2.31	1	2.31	1	2.31	1	68.36	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	64.01	2.40	30	2.73	1	2.73	1	2.73	1	71.09	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	75.26	2.40	40	2.11	1	2.11	1	2.11	1	73.20	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	63.04	2.40	40	2.11	1	2.11	1	2.11	1	75.31	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80	2.40	40	2.67	1	2.67	1	2.67	1	77.98	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	63.04	2.40	40	2.67	1	2.67	1	2.67	1	80.65	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80
DEPTH (mm)	Penetration Between Readings (mm)	Penetration (mm)	Factor E	Factor D	Factor C	Factor B	Factor A	Cumulative Penetration (mm)	Visual Description of the Material	Observations																																																																																																																																																																																																																																																																																									
0.10	30	2.00	1	2.00	1	2.00	1	2.00	Filled with Granular Base Layer Material Type	88.34																																																																																																																																																																																																																																																																																									
0.10	30	1.36	1	1.36	1	1.36	1	3.36	Filled with Granular Base Layer Material Type	149.54																																																																																																																																																																																																																																																																																									
0.10	30	1.25	1	1.25	1	1.25	1	4.61	Filled with Granular Base Layer Material Type	149.54																																																																																																																																																																																																																																																																																									
0.60	40	5.00	1	5.00	1	5.00	1	9.61	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	31.66																																																																																																																																																																																																																																																																																									
0.60	40	6.67	1	6.67	1	6.67	1	16.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	22.94																																																																																																																																																																																																																																																																																									
0.60	30	5.00	1	5.00	1	5.00	1	21.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	31.66																																																																																																																																																																																																																																																																																									
1.20	40	4.00	1	4.00	1	4.00	1	25.28	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	40.64																																																																																																																																																																																																																																																																																									
1.20	30	2.31	1	2.31	1	2.31	1	27.59	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	75.26																																																																																																																																																																																																																																																																																									
1.20	30	2.00	1	2.00	1	2.00	1	29.59	Clay in-situ condition dense, compact consistency, dry and light gray coloring.	88.34																																																																																																																																																																																																																																																																																									
1.80	30	5.00	1	5.00	1	5.00	1	34.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	31.66																																																																																																																																																																																																																																																																																									
1.80	30	6.67	1	6.67	1	6.67	1	41.26	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	22.94																																																																																																																																																																																																																																																																																									
1.80	30	3.33	1	3.33	1	3.33	1	44.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	49.85																																																																																																																																																																																																																																																																																									
2.40	40	5.00	1	5.00	1	5.00	1	50.59	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	31.66																																																																																																																																																																																																																																																																																									
2.40	40	2.22	1	2.22	1	2.22	1	52.81	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	78.51																																																																																																																																																																																																																																																																																									
2.40	40	2.86	1	2.86	1	2.86	1	55.67	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	59.25																																																																																																																																																																																																																																																																																									
2.40	30	1.88	1	1.88	1	1.88	1	57.55	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	94.96																																																																																																																																																																																																																																																																																									
2.40	30	2.50	1	2.50	1	2.50	1	60.05	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	74.34																																																																																																																																																																																																																																																																																									
2.40	40	3.33	1	3.33	1	3.33	1	63.38	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80																																																																																																																																																																																																																																																																																									
2.40	40	2.67	1	2.67	1	2.67	1	66.05	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	49.85																																																																																																																																																																																																																																																																																									
2.40	30	2.31	1	2.31	1	2.31	1	68.36	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	64.01																																																																																																																																																																																																																																																																																									
2.40	30	2.73	1	2.73	1	2.73	1	71.09	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	75.26																																																																																																																																																																																																																																																																																									
2.40	40	2.11	1	2.11	1	2.11	1	73.20	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	63.04																																																																																																																																																																																																																																																																																									
2.40	40	2.11	1	2.11	1	2.11	1	75.31	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80																																																																																																																																																																																																																																																																																									
2.40	40	2.67	1	2.67	1	2.67	1	77.98	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	63.04																																																																																																																																																																																																																																																																																									
2.40	40	2.67	1	2.67	1	2.67	1	80.65	Clay in-situ condition firm, medium bodied, partially saturated and light gray coloring.	68.80																																																																																																																																																																																																																																																																																									
<p>CONCLUSIONS</p> <p>The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the amount of water service data.</p>																																																																																																																																																																																																																																																																																																			
DATE OF CREATION OF TEST:		28/08/2014		LABORATORY MANAGER																																																																																																																																																																																																																																																																																															

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 20/08/2014 RP 00 01 de 01																																																																																																																																																																																																																																																																																				
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		22																																																																																																																																																																																																																																																																																				
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		22																																																																																																																																																																																																																																																																																				
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		22																																																																																																																																																																																																																																																																																				
<p>10-500</p> <p>not Applicable</p> <p>WEIGHT HAMMER: 8 Kg.</p>																																																																																																																																																																																																																																																																																								
<p>TEST RESULTS</p> <table border="1"> <thead> <tr> <th>DEPTH (mm)</th> <th>Penetration Between Readings (mm)</th> <th>Penetration (mm)</th> <th>Factor E</th> <th>Factor D</th> <th>Factor C</th> <th>Factor B</th> <th>Factor A</th> <th>Cumulative Penetration (mm)</th> <th>Visual Description of the Material</th> <th>Observations</th> </tr> </thead> <tbody> <tr><td>0.10</td><td>30</td><td>1.25</td><td>1</td><td>1.25</td><td>1</td><td>1.25</td><td>1</td><td>1.25</td><td>Filled with Granular Base Layer Material Type</td><td>149.54</td></tr> <tr><td>0.10</td><td>30</td><td>1.15</td><td>1</td><td>1.15</td><td>1</td><td>1.15</td><td>1</td><td>2.40</td><td>Filled with Granular Base Layer Material Type</td><td>149.54</td></tr> <tr><td>0.10</td><td>30</td><td>1.36</td><td>1</td><td>1.36</td><td>1</td><td>1.36</td><td>1</td><td>3.76</td><td>Filled with Granular Base Layer Material Type</td><td>149.54</td></tr> <tr><td>0.50</td><td>40</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>7.40</td><td>Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.</td><td>45.22</td></tr> <tr><td>0.50</td><td>30</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>10.73</td><td>Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.</td><td>49.85</td></tr> <tr><td>0.50</td><td>40</td><td>2.86</td><td>1</td><td>2.86</td><td>1</td><td>2.86</td><td>1</td><td>13.59</td><td>Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.</td><td>51.44</td></tr> <tr><td>1.00</td><td>40</td><td>4.44</td><td>1</td><td>4.44</td><td>1</td><td>4.44</td><td>1</td><td>18.03</td><td>Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.</td><td>36.12</td></tr> <tr><td>1.00</td><td>30</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>23.03</td><td>Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.</td><td>31.66</td></tr> <tr><td>1.00</td><td>30</td><td>4.55</td><td>1</td><td>4.55</td><td>1</td><td>4.55</td><td>1</td><td>27.58</td><td>Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.</td><td>34.30</td></tr> <tr><td>1.60</td><td>40</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>31.22</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>45.22</td></tr> <tr><td>1.60</td><td>30</td><td>3.00</td><td>1</td><td>3.00</td><td>1</td><td>3.00</td><td>1</td><td>34.22</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>56.10</td></tr> <tr><td>1.60</td><td>30</td><td>2.73</td><td>1</td><td>2.73</td><td>1</td><td>2.73</td><td>1</td><td>36.95</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>64.58</td></tr> <tr><td>1.60</td><td>30</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>3.33</td><td>1</td><td>40.28</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>49.85</td></tr> <tr><td>1.60</td><td>30</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>2.31</td><td>1</td><td>42.59</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>75.26</td></tr> <tr><td>1.60</td><td>30</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>45.09</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>68.80</td></tr> <tr><td>2.20</td><td>40</td><td>4.44</td><td>1</td><td>4.44</td><td>1</td><td>4.44</td><td>1</td><td>49.53</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>36.12</td></tr> <tr><td>2.20</td><td>30</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>53.28</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>48.54</td></tr> <tr><td>2.20</td><td>30</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>2.50</td><td>1</td><td>55.78</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>68.80</td></tr> <tr><td>2.20</td><td>40</td><td>4.17</td><td>1</td><td>4.17</td><td>1</td><td>4.17</td><td>1</td><td>60.95</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>42.17</td></tr> <tr><td>2.20</td><td>40</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>3.64</td><td>1</td><td>64.59</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>49.85</td></tr> <tr><td>2.20</td><td>40</td><td>3.85</td><td>1</td><td>3.85</td><td>1</td><td>3.85</td><td>1</td><td>68.44</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>42.17</td></tr> <tr><td>2.80</td><td>40</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>5.00</td><td>1</td><td>73.44</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>31.66</td></tr> <tr><td>2.80</td><td>40</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>77.19</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>48.54</td></tr> <tr><td>2.80</td><td>40</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>3.75</td><td>1</td><td>80.94</td><td>Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.</td><td>39.68</td></tr> </tbody> </table>						DEPTH (mm)	Penetration Between Readings (mm)	Penetration (mm)	Factor E	Factor D	Factor C	Factor B	Factor A	Cumulative Penetration (mm)	Visual Description of the Material	Observations	0.10	30	1.25	1	1.25	1	1.25	1	1.25	Filled with Granular Base Layer Material Type	149.54	0.10	30	1.15	1	1.15	1	1.15	1	2.40	Filled with Granular Base Layer Material Type	149.54	0.10	30	1.36	1	1.36	1	1.36	1	3.76	Filled with Granular Base Layer Material Type	149.54	0.50	40	3.64	1	3.64	1	3.64	1	7.40	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	45.22	0.50	30	3.33	1	3.33	1	3.33	1	10.73	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	49.85	0.50	40	2.86	1	2.86	1	2.86	1	13.59	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	51.44	1.00	40	4.44	1	4.44	1	4.44	1	18.03	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	36.12	1.00	30	5.00	1	5.00	1	5.00	1	23.03	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	31.66	1.00	30	4.55	1	4.55	1	4.55	1	27.58	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	34.30	1.60	40	3.64	1	3.64	1	3.64	1	31.22	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	45.22	1.60	30	3.00	1	3.00	1	3.00	1	34.22	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	56.10	1.60	30	2.73	1	2.73	1	2.73	1	36.95	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	64.58	1.60	30	3.33	1	3.33	1	3.33	1	40.28	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	49.85	1.60	30	2.31	1	2.31	1	2.31	1	42.59	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	75.26	1.60	30	2.50	1	2.50	1	2.50	1	45.09	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	68.80	2.20	40	4.44	1	4.44	1	4.44	1	49.53	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	36.12	2.20	30	3.75	1	3.75	1	3.75	1	53.28	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	48.54	2.20	30	2.50	1	2.50	1	2.50	1	55.78	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	68.80	2.20	40	4.17	1	4.17	1	4.17	1	60.95	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	42.17	2.20	40	3.64	1	3.64	1	3.64	1	64.59	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	49.85	2.20	40	3.85	1	3.85	1	3.85	1	68.44	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	42.17	2.80	40	5.00	1	5.00	1	5.00	1	73.44	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	31.66	2.80	40	3.75	1	3.75	1	3.75	1	77.19	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	48.54	2.80	40	3.75	1	3.75	1	3.75	1	80.94	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	39.68
DEPTH (mm)	Penetration Between Readings (mm)	Penetration (mm)	Factor E	Factor D	Factor C	Factor B	Factor A	Cumulative Penetration (mm)	Visual Description of the Material	Observations																																																																																																																																																																																																																																																																														
0.10	30	1.25	1	1.25	1	1.25	1	1.25	Filled with Granular Base Layer Material Type	149.54																																																																																																																																																																																																																																																																														
0.10	30	1.15	1	1.15	1	1.15	1	2.40	Filled with Granular Base Layer Material Type	149.54																																																																																																																																																																																																																																																																														
0.10	30	1.36	1	1.36	1	1.36	1	3.76	Filled with Granular Base Layer Material Type	149.54																																																																																																																																																																																																																																																																														
0.50	40	3.64	1	3.64	1	3.64	1	7.40	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	45.22																																																																																																																																																																																																																																																																														
0.50	30	3.33	1	3.33	1	3.33	1	10.73	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	49.85																																																																																																																																																																																																																																																																														
0.50	40	2.86	1	2.86	1	2.86	1	13.59	Clay in-situ condition dense, compact consistency, dryness and reddish coloration gray patina.	51.44																																																																																																																																																																																																																																																																														
1.00	40	4.44	1	4.44	1	4.44	1	18.03	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	36.12																																																																																																																																																																																																																																																																														
1.00	30	5.00	1	5.00	1	5.00	1	23.03	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	31.66																																																																																																																																																																																																																																																																														
1.00	30	4.55	1	4.55	1	4.55	1	27.58	Clay in-situ condition dense, compact consistency, dry and light brown and gray coloring.	34.30																																																																																																																																																																																																																																																																														
1.60	40	3.64	1	3.64	1	3.64	1	31.22	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	45.22																																																																																																																																																																																																																																																																														
1.60	30	3.00	1	3.00	1	3.00	1	34.22	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	56.10																																																																																																																																																																																																																																																																														
1.60	30	2.73	1	2.73	1	2.73	1	36.95	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	64.58																																																																																																																																																																																																																																																																														
1.60	30	3.33	1	3.33	1	3.33	1	40.28	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	49.85																																																																																																																																																																																																																																																																														
1.60	30	2.31	1	2.31	1	2.31	1	42.59	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	75.26																																																																																																																																																																																																																																																																														
1.60	30	2.50	1	2.50	1	2.50	1	45.09	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	68.80																																																																																																																																																																																																																																																																														
2.20	40	4.44	1	4.44	1	4.44	1	49.53	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	36.12																																																																																																																																																																																																																																																																														
2.20	30	3.75	1	3.75	1	3.75	1	53.28	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	48.54																																																																																																																																																																																																																																																																														
2.20	30	2.50	1	2.50	1	2.50	1	55.78	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	68.80																																																																																																																																																																																																																																																																														
2.20	40	4.17	1	4.17	1	4.17	1	60.95	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	42.17																																																																																																																																																																																																																																																																														
2.20	40	3.64	1	3.64	1	3.64	1	64.59	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	49.85																																																																																																																																																																																																																																																																														
2.20	40	3.85	1	3.85	1	3.85	1	68.44	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	42.17																																																																																																																																																																																																																																																																														
2.80	40	5.00	1	5.00	1	5.00	1	73.44	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	31.66																																																																																																																																																																																																																																																																														
2.80	40	3.75	1	3.75	1	3.75	1	77.19	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	48.54																																																																																																																																																																																																																																																																														
2.80	40	3.75	1	3.75	1	3.75	1	80.94	Firm clay in-situ condition, medium bodied, dry and brown and gray coloring.	39.68																																																																																																																																																																																																																																																																														
<p>CONCLUSIONS</p> <p>The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the amount of water service data.</p>																																																																																																																																																																																																																																																																																								
DATE OF CREATION OF TEST:		28/08/2014		LABORATORY MANAGER																																																																																																																																																																																																																																																																																				





PROYECTOS:		11+990		X Coordinate: 179194620" S		WEIGHT HAMMER: 8 Kg.					
WATER TABLE:		not Applicable		not Applicable		not Applicable					
RECORD FIELD		TEST RESULTS		TEST RESULTS		TEST RESULTS					
DEPTH (m)	DEPTH (ft)	Number of Blows (A)	Cumulative Penetration (mm) G	Penetration Between Readings (mm) C	Factor Correction (mm) D	Factor Correction (mm) E	Factor Correction (mm) F	Factor Correction (mm) G	AVERAGE CBR %	observations	
0.10	0.33	26	31	30	1.07	1	1.07	1.07	177.72	(For the test item Due to the Base Layer (Base Layer) CBR values are discarded since they would be inconsistent. This is concluded on an isolated hammer stone.	
0.60	1.97	11	40	40	5.00	1	5.00	31.66	46.43		
1.10	3.61	11	110	30	2.73	1	2.73	62.41			
1.60	5.25	8	40	40	5.00	1	5.00	31.66	42.24		
2.10	6.89	18	90	40	3.33	1	3.33	49.85	72.04		
2.60	8.53	35	130	40	3.64	1	3.64	45.22			
3.10	10.17	28	40	40	2.50	1	2.50	68.80			
3.60	11.81	31	40	40	2.22	1	2.22	78.51			
4.10	13.45	35	110	30	0.83	1	0.83	235.50			
4.60	15.09	40	30	30	1.25	1	1.25	149.54			
5.10	16.73	31	30	40	1.29	1	1.29	144.32	154.83		
5.60	18.37	35	130	40	1.11	1	1.11	170.63			
6.10	19.99	19	30	30	1.58	1	1.58	115.11			
6.60	21.63	22	60	30	1.36	1	1.36	135.66	131.12		
7.10	23.27	22	30	30	1.30	1	1.30	142.58			
<b>OBSERVATIONS:</b>											
The presence of the Water Table was not evidenced until the end of Consolidated Study. For the study is considered the maximum level was not conducted.											
A= Number of hammer blows between readings. B= Cumulative penetration (mm) between readings. C= Penetration between readings (mm). D= Factor correction (mm) for the hammer is 8 Kg. And "m" if the hammer is 4 Kg. E= Factor correction (mm) for the hammer is 4 Kg. And "m" if the hammer is 8 Kg. F= Correlation between CBR and DCP data. G= Correlation between CBR and DCP data.											
DATE OF CREATION OF TEST: 29/08/2014								CLOSING DATE OF TEST: 29/08/2014		LABORATORY MANAGER	

PROYECTOS:		12+485		X Coordinate: 1772010230" S		WEIGHT HAMMER: 8 Kg.					
WATER TABLE:		not Applicable		not Applicable		not Applicable					
RECORD FIELD		TEST RESULTS		TEST RESULTS		TEST RESULTS					
DEPTH (m)	DEPTH (ft)	Number of Blows (A)	Cumulative Penetration (mm) G	Penetration Between Readings (mm) C	Factor Correction (mm) D	Factor Correction (mm) E	Factor Correction (mm) F	Factor Correction (mm) G	AVERAGE CBR %	observations	
0.10	0.33	22	30	30	1.30	1	1.30	142.58	142.58	(For the test item Due to the Base Layer (Base Layer) CBR values are discarded since they would be inconsistent. This is concluded on an isolated hammer stone.	
0.60	1.97	5	40	40	8.00	1	8.00	18.70	23.02		
1.10	3.61	4	70	40	10.00	1	10.00	14.56	14.56		
1.60	5.25	4	110	40	10.00	1	10.00	14.56			
2.10	6.89	4	40	40	10.00	1	10.00	14.56			
2.60	8.53	3	80	40	13.33	1	13.33	10.55	13.23		
3.10	10.17	4	120	40	10.00	1	10.00	14.56			
3.60	11.81	2	30	30	15.00	1	15.00	9.25	9.25		
4.10	13.45	2	70	40	20.00	1	20.00	6.70	8.40		
4.60	15.09	2	100	30	15.00	1	15.00	9.25			
5.10	16.73	6	40	40	6.67	1	6.67	22.94			
5.60	18.37	6	80	40	6.67	1	6.67	22.94	21.98		
6.10	19.99	4	110	30	7.50	1	7.50	20.10			
6.60	21.63	4	40	40	10.00	1	10.00	14.56			
7.10	23.27	8	80	40	5.00	1	5.00	31.66	38.21		
7.60	24.91	11	110	30	2.73	1	2.73	62.41			
<b>OBSERVATIONS:</b>											
The presence of the Water Table was not evidenced until the end of Consolidated Study. For the study is considered the maximum level was not conducted.											
A= Number of hammer blows between readings. B= Cumulative penetration (mm) between readings. C= Penetration between readings (mm). D= Factor correction (mm) for the hammer is 8 Kg. And "m" if the hammer is 4 Kg. E= Factor correction (mm) for the hammer is 4 Kg. And "m" if the hammer is 8 Kg. F= Correlation between CBR and DCP data. G= Correlation between CBR and DCP data.											
DATE OF CREATION OF TEST: 29/08/2014								CLOSING DATE OF TEST: 29/08/2014		LABORATORY MANAGER	





REV.		REV.	
DATE	BY	DATE	BY
20/09/2014	00	20/09/2014	00
RP 00		RP 00	
01 de 01		01 de 01	

<b>DYNAMIC PENETRATION TESTING (DCP)</b>		<b>DYNAMIC PENETRATION TESTING (DCP)</b>	
NORMA ASTM-D-6951-03		NORMA ASTM-D-6951-03	
CLIENTE / Client: KATAMBA & Engineers International PREPARADO / Project: Preparatory Study of the Camino 7-E and 111 Road Boring Project UBICACION / Location: Municipality of Chitina in 7-E, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City		CLIENTE / Client: KATAMBA & Engineers International PREPARADO / Project: Preparatory Study of the Camino 7-E and 111 Road Boring Project UBICACION / Location: Municipality of Chitina in 7-E, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City	
<b>TEST DATA</b>		<b>TEST DATA</b>	
PROGRESIVO: 14+970 X Coordinate: 1721122.40" S Y Coordinate: 6275339.00" O WEIGHT HAMMER: 8 Kg.		PROGRESIVO: 15+465 X Coordinate: 172138.40" S Y Coordinate: 62753336.40" O WEIGHT HAMMER: 8 Kg.	
WATER TABLE: not applicable		WATER TABLE: not applicable	
RECORD FIELD		RECORD FIELD	
DEPTH (m)	DEPTH (ft)	DEPTH (m)	DEPTH (ft)
0.15	0.49	0.10	0.30
0.40	1.31	0.40	1.31
0.90	2.95	0.90	2.95
1.40	4.59	1.30	4.27
1.90	6.23	1.90	6.23
2.30	7.54	2.30	7.54
2.80	9.19	2.70	8.87
3.30	10.83	3.30	10.83
3.80	12.47	3.80	12.47
4.30	14.11	4.30	14.11
4.80	15.75	4.80	15.75
5.30	17.39	5.30	17.39
5.80	19.03	5.80	19.03
6.30	20.67	6.30	20.67
6.80	22.31	6.80	22.31
7.30	23.95	7.30	23.95
7.80	25.59	7.80	25.59
8.30	27.23	8.30	27.23
8.80	28.87	8.80	28.87
9.30	30.51	9.30	30.51
9.80	32.15	9.80	32.15
10.30	33.79	10.30	33.79
10.80	35.43	10.80	35.43
11.30	37.07	11.30	37.07
11.80	38.71	11.80	38.71
12.30	40.35	12.30	40.35
12.80	41.99	12.80	41.99
13.30	43.63	13.30	43.63
13.80	45.27	13.80	45.27
14.30	46.91	14.30	46.91
14.80	48.55	14.80	48.55
15.30	50.19	15.30	50.19
15.80	51.83	15.80	51.83
16.30	53.47	16.30	53.47
16.80	55.11	16.80	55.11
17.30	56.75	17.30	56.75
17.80	58.39	17.80	58.39
18.30	60.03	18.30	60.03
18.80	61.67	18.80	61.67
19.30	63.31	19.30	63.31
19.80	64.95	19.80	64.95
20.30	66.59	20.30	66.59
20.80	68.23	20.80	68.23
21.30	69.87	21.30	69.87
21.80	71.51	21.80	71.51
22.30	73.15	22.30	73.15
22.80	74.79	22.80	74.79
23.30	76.43	23.30	76.43
23.80	78.07	23.80	78.07
24.30	79.71	24.30	79.71
24.80	81.35	24.80	81.35
25.30	82.99	25.30	82.99
25.80	84.63	25.80	84.63
26.30	86.27	26.30	86.27
26.80	87.91	26.80	87.91
27.30	89.55	27.30	89.55
27.80	91.19	27.80	91.19
28.30	92.83	28.30	92.83
28.80	94.47	28.80	94.47
29.30	96.11	29.30	96.11
29.80	97.75	29.80	97.75
30.30	99.39	30.30	99.39
30.80	101.03	30.80	101.03
31.30	102.67	31.30	102.67
31.80	104.31	31.80	104.31
32.30	105.95	32.30	105.95
32.80	107.59	32.80	107.59
33.30	109.23	33.30	109.23
33.80	110.87	33.80	110.87
34.30	112.51	34.30	112.51
34.80	114.15	34.80	114.15
35.30	115.79	35.30	115.79
35.80	117.43	35.80	117.43
36.30	119.07	36.30	119.07
36.80	120.71	36.80	120.71
37.30	122.35	37.30	122.35
37.80	123.99	37.80	123.99
38.30	125.63	38.30	125.63
38.80	127.27	38.80	127.27
39.30	128.91	39.30	128.91
39.80	130.55	39.80	130.55
40.30	132.19	40.30	132.19
40.80	133.83	40.80	133.83
41.30	135.47	41.30	135.47
41.80	137.11	41.80	137.11
42.30	138.75	42.30	138.75
42.80	140.39	42.80	140.39
43.30	142.03	43.30	142.03
43.80	143.67	43.80	143.67
44.30	145.31	44.30	145.31
44.80	146.95	44.80	146.95
45.30	148.59	45.30	148.59
45.80	150.23	45.80	150.23
46.30	151.87	46.30	151.87
46.80	153.51	46.80	153.51
47.30	155.15	47.30	155.15
47.80	156.79	47.80	156.79
48.30	158.43	48.30	158.43
48.80	160.07	48.80	160.07
49.30	161.71	49.30	161.71
49.80	163.35	49.80	163.35
50.30	164.99	50.30	164.99
50.80	166.63	50.80	166.63
51.30	168.27	51.30	168.27
51.80	169.91	51.80	169.91
52.30	171.55	52.30	171.55
52.80	173.19	52.80	173.19
53.30	174.83	53.30	174.83
53.80	176.47	53.80	176.47
54.30	178.11	54.30	178.11
54.80	179.75	54.80	179.75
55.30	181.39	55.30	181.39
55.80	183.03	55.80	183.03
56.30	184.67	56.30	184.67
56.80	186.31	56.80	186.31
57.30	187.95	57.30	187.95
57.80	189.59	57.80	189.59
58.30	191.23	58.30	191.23
58.80	192.87	58.80	192.87
59.30	194.51	59.30	194.51
59.80	196.15	59.80	196.15
60.30	197.79	60.30	197.79
60.80	199.43	60.80	199.43
61.30	201.07	61.30	201.07
61.80	202.71	61.80	202.71
62.30	204.35	62.30	204.35
62.80	205.99	62.80	205.99
63.30	207.63	63.30	207.63
63.80	209.27	63.80	209.27
64.30	210.91	64.30	210.91
64.80	212.55	64.80	212.55
65.30	214.19	65.30	214.19
65.80	215.83	65.80	215.83
66.30	217.47	66.30	217.47
66.80	219.11	66.80	219.11
67.30	220.75	67.30	220.75
67.80	222.39	67.80	222.39
68.30	224.03	68.30	224.03
68.80	225.67	68.80	225.67
69.30	227.31	69.30	227.31
69.80	228.95	69.80	228.95
70.30	230.59	70.30	230.59
70.80	232.23	70.80	232.23
71.30	233.87	71.30	233.87
71.80	235.51	71.80	235.51
72.30	237.15	72.30	237.15
72.80	238.79	72.80	238.79
73.30	240.43	73.30	240.43
73.80	242.07	73.80	242.07
74.30	243.71	74.30	243.71
74.80	245.35	74.80	245.35
75.30	246.99	75.30	246.99
75.80	248.63	75.80	248.63
76.30	250.27	76.30	250.27
76.80	251.91	76.80	251.91
77.30	253.55	77.30	253.55
77.80	255.19	77.80	255.19
78.30	256.83	78.30	256.83
78.80	258.47	78.80	258.47
79.30	260.11	79.30	260.11
79.80	261.75	79.80	261.75
80.30	263.39	80.30	263.39
80.80	265.03	80.80	265.03
81.30	266.67	81.30	266.67
81.80	268.31	81.80	268.31
82.30	269.95	82.30	269.95
82.80	271.59	82.80	271.59
83.30	273.23	83.30	273.23
83.80	274.87	83.80	274.87
84.30	276.51	84.30	276.51
84.80	278.15	84.80	278.15
85.30	279.79	85.30	279.79
85.80	281.43	85.80	281.43
86.30	283.07	86.30	283.07
86.80	284.71	86.80	284.71
87.30	286.35	87.30	286.35
87.80	287.99	87.80	287.99
88.30	289.63	88.30	289.63
88.80	291.27	88.80	291.27
89.30	292.91	89.30	292.91
89.80	294.55	89.80	294.55
90.30	296.19	90.30	296.19
90.80	297.83	90.80	297.83
91.30	299.47	91.30	299.47
91.80	301.11	91.80	301.11
92.30	302.75	92.30	302.75
92.80	304.39	92.80	304.39
93.30	306.03	93.30	306.03
93.80	307.67	93.80	307.67
94.30	309.31	94.30	309.31
94.80	310.95	94.80	310.95
95.30	312.59	95.30	312.59
95.80	314.23	95.80	314.23
96.30	315.87	96.30	315.87
96.80	317.51	96.80	317.51
97.30	319.15	97.30	319.15
97.80	320.79	97.80	320.79
98.30	322.43	98.30	322.43
98.80	324.07	98.80	324.07
99.30	325.71	99.30	325.71
99.80	327.35	99.80	327.35
100.30	328.99	100.30	328.99
100.80	330.63	100.80	330.63
101.30	332.27	101.30	332.27
101.80	333.91	101.80	333.91
102.30	335.55	102.30	335.55
102.80	337.19	102.80	337.19
103.30	338.83	103.30	338.83
103.80	340.47	103.80	340.47
104.30	342.11	104.30	342.11
104.80	343.75	104.80	343.75
105.30	345.39	105.30	345.39
105.80	347.03	105.80	347.03
106.30	348.67	106.30	348.67
106.80	350.31	106.80	350.31
107.30	351.95	107.30	351.95
107.80	353.59	107.80	353.59
108.30	355.23	108.30	355.23
108.80	356.87	108.80	356.87

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01						
CLIENTE / CLIENT: PROYECTO / PROJECT: UBICACION / LOCATION:		KATAMBA & Engineers International Preparatory Study of the Urban T-1 Road III Road Paving Project Municipality of Chiriquí - T-1, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		NORMA ASTM-D-6951-03						
PROFESIONISTA: 15-4980		172115430°S 62°53'33.30°O		00 2008/2014 RP 00 01 de 01						
WATER TABLE:		not applicable		WEIGHT HAMMER: 8 Kg.						
TEST DATA		X Coordinate: 172115430°S Y Coordinate: 62°53'33.30°O		DIRECCION: 8 Kg.						
RECORD FIELD		TEST RESULTS		OBSERVATIONS						
DEPTH (m)	DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor E (mm) (D)	Factor F (mm) (E)	DCP Index (mm / Pundada) (F)	CBR % (G)	AVERAGE CBR %	observations
0.10	Filled with Granular Base Layer Material Type	10	30	30	3.00	1	3.00	56.10	56.12	(For the second point) of these soils (Base Layer) disregard CBR on average, since that would be inconsistent with the results of the test with conductance on an isolated balance stone.
0.40	Silty Sand condition in-situ Firm, dense compaction of dry and gray coloring.	9	40	33	40.65	1	40.65	14.56	14.56	
0.40	Clayey Sand weak condition in-situ, soft consistency, partially dry and light gray coloring.	11	50	30	2.73	1	2.73	65.41	65.41	
0.90	Clayey Sand weak condition in-situ, soft consistency, partially dry and light gray coloring.	42	50	50	1.19	1	1.19	157.94	172.70	
1.00	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	40	100	50	1.25	1	1.25	149.54	172.70	
1.20	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	44	140	40	0.91	1	0.91	213.63	213.63	
1.40	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	4	40	40	10.00	1	10.00	14.56	14.56	
1.60	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	3	40	40	13.33	1	13.33	10.55	11.89	
1.80	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	3	120	40	13.33	1	13.33	10.55	11.89	
2.00	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	4	200	60	15.00	1	15.00	9.25	9.25	
2.20	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	2	40	40	20.00	1	20.00	6.70	6.70	
2.40	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	3	60	40	13.33	1	13.33	10.55	9.53	
2.60	Clayey Sand weak condition in-situ, soft consistency, partially dry and reddish brown coloration.	4	130	50	12.50	1	12.50	11.34	11.34	
2.80	Silty Sand Firm condition in-situ, on average compaction, partially saturated state and reddish brown coloration.	8	60	60	7.50	1	7.50	20.10	20.10	
3.00	Silty Sand Firm condition in-situ, on average compaction, partially saturated state and reddish brown coloration.	13	120	60	4.82	1	4.82	34.62	28.85	
3.20	Silty Sand Firm condition in-situ, on average compaction, partially saturated state and reddish brown coloration.	10	180	60	6.00	1	6.00	25.81	25.81	
3.40	Limo weak in-situ condition, soft consistency, saturated state and light brown coloring.	2	30	30	15.00	1	15.00	9.25	9.25	
3.60	Limo weak in-situ condition, soft consistency, saturated state and light brown coloring.	2	70	40	20.00	1	20.00	6.70	8.83	
3.80	Limo weak in-situ condition, soft consistency, saturated state and light brown coloring.	3	110	40	13.33	1	13.33	10.55	10.55	
4.00	Weak clay in-situ condition, soft consistency, saturated state, light brown with presence of clasts.	5	70	70	14.00	1	14.00	9.99	9.99	
4.20	Weak clay in-situ condition, soft consistency, saturated state, light brown with presence of clasts.	7	140	70	10.00	1	10.00	14.56	13.04	
4.40	Weak clay in-situ condition, soft consistency, saturated state, light brown with presence of clasts.	7	210	70	10.00	1	10.00	14.56	14.56	
OBSERVATIONS:		The presence of the Water Table was not considered in the end of Geotechnical Study. For the study, it was considered the mouth 0.00 level survey done. Hanging water of 2.30 m was evident, to 2.70 m.		Number of hammer blows between readings (A) C = Cumulative penetration (mm) (B) between readings E = Penetration in the hammer in a kg. And "m" in the hammer is 4.9 Kg. F = Factor between CBR and DCP index. G = Correlation between CBR and DCP index.						
DATE OF CREATION OF TEST: 02/09/2014		CLOSING DATE OF TEST: 02/09/2014		LABORATORY MANAGER						


CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01						
CLIENTE / CLIENT: PROYECTO / PROJECT: UBICACION / LOCATION:		KATAMBA & Engineers International Preparatory Study of the Urban T-1 Road III Road Paving Project Municipality of Chiriquí - T-1, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		NORMA ASTM-D-6951-03						
PROFESIONISTA: 16-5905		172210930°S 62°53'38.30°O		00 2008/2014 RP 00 01 de 01						
WATER TABLE:		1.50 m.		WEIGHT HAMMER: 8 Kg.						
TEST DATA		X Coordinate: 172210930°S Y Coordinate: 62°53'38.30°O		DIRECCION: 8 Kg.						
RECORD FIELD		TEST RESULTS		OBSERVATIONS						
DEPTH (m)	DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor E (mm) (D)	Factor F (mm) (E)	DCP Index (mm / Pundada) (F)	CBR % (G)	AVERAGE CBR %	observations
0.10	Silty sand with gravel presence of isolated, in-situ condition compact, dense compaction of dry, light brown in color	16	30	30	3.13	1	3.13	53.59	59.41	
0.40	Silty sand, compacted in-situ condition, dense compaction of dry and gray coloring.	18	140	40	2.22	1	2.22	78.51	78.51	
0.60	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	20	50	50	2.50	1	2.50	68.80	68.80	
0.80	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	22	100	50	2.27	1	2.27	76.55	76.25	
1.00	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	19	140	40	2.11	1	2.11	83.41	83.41	
1.20	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	6	50	50	8.33	1	8.33	17.88	17.88	
1.40	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	4	90	40	10.00	1	10.00	14.56	17.51	
1.60	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	4	120	30	7.50	1	7.50	20.10	20.10	
1.80	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	3	30	30	10.00	1	10.00	14.56	14.56	
2.00	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	3	60	30	10.00	1	10.00	14.56	14.56	
2.20	Silty sand, firm-situ, on average compaction, partially dry and gray coloring condition.	4	100	40	10.00	1	10.00	14.56	14.56	
2.40	Silty sand, firm-situ, on average compaction, saturated state and dark brown coloring condition.	1	60	60	60.00	1	60.00	1.99	1.99	
2.60	Silty sand, firm-situ, on average compaction, saturated state and dark brown coloring condition.	3	120	60	20.00	1	20.00	6.70	4.63	
2.80	Silty sand, firm-situ, on average compaction, saturated state and dark brown coloring condition.	2	170	50	25.00	1	25.00	5.22	5.22	
3.00	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	5	60	60	12.00	1	12.00	11.87	11.87	
3.20	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	6	120	60	10.00	1	10.00	14.56	13.67	
3.40	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	6	180	60	10.00	1	10.00	14.56	14.56	
3.60	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	6	70	70	11.67	1	11.67	12.26	12.26	
3.80	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	7	140	70	10.00	1	10.00	14.56	13.79	
4.00	Silty sand, firm-situ, on average compaction, saturated state and reddish brown coloring condition.	7	210	70	10.00	1	10.00	14.56	14.56	
OBSERVATIONS:		The presence of the Water Table was not considered in the end of Geotechnical Study. For the study, it was considered the mouth 0.00 level survey done.		Number of hammer blows between readings (A) C = Cumulative penetration (mm) (B) between readings E = Penetration in the hammer in a kg. And "m" in the hammer is 4.9 Kg. F = Factor between CBR and DCP index. G = Correlation between CBR and DCP index.						
DATE OF CREATION OF TEST: 02/09/2014		CLOSING DATE OF TEST: 02/09/2014		LABORATORY MANAGER						



CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) NORMA ASTM-D-4951-03		REV. 00 2009/2014 RP 00 01 de 01					
CLIENTE / CLIENT: KATAMBA & Engineers International Preparatory Study of the Alignment 1 - Road III Road Driving Project Municipality of Chiriquí - 1-11-2 Section, Verano District, Northern Region of San José de Sierra City		PROYECTO / PROJECT: UBACACION / LOCATION:		DCP Nº: 37					
PROGRESIVO: 18-015		COORDENADAS: X Coordinate: 1722754.50' S Y Coordinate: 625352.80' W		WEIGHT HAMMER: 8 Kg.					
WATER TABLE: 2.60 m.		TEST RESULTS		OBSERVATIONS					
DEPTH (m)	RECORDED FIELD VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (mm) A	Cumulative penetration (mm) G	Penetration between readings (mm) C	Penetration (mm) D	DCP Index (mm / Pours) E	CBR % G	AVERAGE CBR %	observations
0.15	Clay with presence of isolated dark spots and reddish coloration.	12	31	40	333	1	3.33	48.86	66.81
0.30	Lime Clay, in-situ condition Firm, medium soft consistency, partially dry and reddish coloration.	5	50	50	10.00	1	10.00	14.56	
0.40	Lime Clay, in-situ condition Firm, medium soft consistency, partially dry and reddish coloration.	6	140	40	6.67	1	6.67	22.94	
0.50	Lime Clay, in-situ condition Firm, medium soft consistency, partially dry and reddish coloration containing small clasts.	8	30	50	6.25	1	6.25	24.66	
0.60	Lime Clay, in-situ condition Firm, medium soft consistency, partially dry and reddish coloration containing small clasts.	9	100	50	5.56	1	5.56	20.13	31.14
0.70	Lime Clay, in-situ condition Firm, medium soft consistency, partially dry and reddish coloration containing small clasts.	10	140	40	4.00	1	4.00	40.64	
0.80	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	3	70	70	23.33	1	23.33	5.64	
0.90	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	4	130	60	15.00	1	15.00	9.25	8.40
1.00	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	4	180	50	15.00	1	15.00	9.25	
1.10	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	3	60	60	20.00	1	20.00	6.70	
1.20	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	3	120	60	20.00	1	20.00	6.70	7.55
1.30	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	4	180	60	15.00	1	15.00	9.25	
1.40	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	10	60	60	6.00	1	6.00	23.81	
1.50	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	15	120	60	4.00	1	4.00	40.64	30.75
1.60	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	10	180	60	6.00	1	6.00	23.81	
1.70	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	5	40	40	8.00	1	8.00	18.70	
1.80	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	5	90	50	10.00	1	10.00	14.56	16.86
1.90	Clayey sand, Firm condition in-situ, medium soft consistency, partially dry and reddish coloration.	7	150	60	8.57	1	8.57	17.31	
OBSERVATIONS: The presence of the Water Table at a depth of 2.60 m was evident, until the end of Geotechnical Study. For the study is considered the month 09th level survey date.		DATE OF CREATION OF TEST: 04/09/2014		CLOSING DATE OF TEST: 04/09/2014		LABORATORY MANAGER			


CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) NORMA ASTM-D-4951-03		REV. 00 2009/2014 RP 00 01 de 01					
CLIENTE / CLIENT: KATAMBA & Engineers International Preparatory Study of the Alignment 1 - Road III Road Driving Project Municipality of Chiriquí - 1-11-2 Section, Verano District, Northern Region of San José de Sierra City		PROYECTO / PROJECT: UBACACION / LOCATION:		DCP Nº: 38					
PROGRESIVO: 18-016		COORDENADAS: X Coordinate: 1722799.87' S Y Coordinate: 625354.97' W		WEIGHT HAMMER: 8 Kg.					
WATER TABLE: not Applicable		TEST RESULTS		OBSERVATIONS					
DEPTH (m)	RECORDED FIELD VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (mm) A	Cumulative penetration (mm) G	Penetration between readings (mm) C	Penetration (mm) D	DCP Index (mm / Pours) E	CBR % G	AVERAGE CBR %	observations
0.15	Lime Sand, in-situ condition Firm, medium soft consistency, saturated state and dark brown coloration.	11	70	40	92	3.04	3.04	43.22	
0.30	Lime Sand, in-situ condition Firm, medium soft consistency, saturated state and dark brown coloration.	9	90	30	3.33	1	3.33	49.05	44.23
0.45	Lime Sand, in-situ condition Firm, medium soft consistency, saturated state and dark brown coloration.	7	100	30	4.29	1	4.29	37.62	
0.60	Sandy loam, partially in-situ Firm, medium soft consistency, saturated state and dark brown coloration.	1	30	30	30.00	1	30.00	1.28	
0.75	Sandy loam, partially in-situ Firm, medium soft consistency, saturated state and dark brown coloration.	6	90	30	30.00	1	30.00	1.28	3.86
0.90	Sandy loam, partially in-situ Firm, medium soft consistency, saturated state and dark brown coloration.	1	100	40	40.00	1	40.00	3.28	
1.05	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	1	50	50	50.00	1	50.00	2.40	
1.20	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	1	100	50	50.00	1	50.00	2.40	3.34
1.35	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	2	150	50	25.00	1	25.00	3.22	
1.50	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	3	60	60	20.00	1	20.00	4.86	
1.65	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	3	100	60	20.00	1	20.00	4.86	5.47
1.80	Silty Clay, in-situ condition Firm, medium soft consistency, partially saturated state and brown.	4	200	60	20.00	1	20.00	4.70	
1.95	Silty loam, partially in-situ Firm, medium soft consistency, saturated state and light brown coloration.	3	100	100	33.33	1	33.33	3.22	6.26
2.10	Silty loam, partially in-situ Firm, medium soft consistency, saturated state and light brown coloration.	7	300	100	14.29	1	14.29	3.77	
2.25	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	3	100	100	33.33	1	33.33	3.76	
2.40	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	5	200	100	20.00	1	20.00	4.70	6.23
2.55	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	6	300	100	16.67	1	16.67	3.22	
2.70	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	2	100	100	50.00	1	50.00	3.40	
2.85	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	4	200	100	25.00	1	25.00	3.22	4.77
3.00	Lime Clay, in-situ condition Firm, medium soft consistency, saturated state and light brown coloration.	5	300	100	20.00	1	20.00	4.70	
OBSERVATIONS: The presence of the Water Table at a depth of 2.60 m was evident, until the end of Geotechnical Study. For the study is considered the month 09th level survey date.		DATE OF CREATION OF TEST: 04/09/2014		CLOSING DATE OF TEST: 04/09/2014		LABORATORY MANAGER			




 <b>CLIENTE / Client:</b> KATARIKA & Engineers International. <b>PROYECTO / Project:</b> Preparatory Study of the Oblique 1 - 1st and III Road Paving Project. <b>UBICACION / Location:</b> Municipality of Oblique 1 - 1st, 2° Section, Warner Province, Northern Region of Saint Cruz de la Sierra City.		<b>DYNAMIC PENETRATION TESTING (DPT)</b> NORMAS ASTM D 1585-03		REV. 00 20/09/2014 RP 00 01.001		
<b>PROYECTO:</b> 80455 <b>WATER TABLE:</b> not Applicable <b>TEST DATA:</b>		<b>TEST RESULTS:</b>		8 Kg. observations		
<b>RECORD HEAD</b> <b>VSUAL DESCRIPTION OF THE MATERIAL:</b>		<b>TEST RESULTS:</b>		8 Kg. observations		
DEPTH (m)	VSUAL DESCRIPTION OF THE MATERIAL	Number of Tests	Penetration Reading (mm)	Penetration Reading (mm)	AVERAGE DPT (mm)	AVG. DPT (mm)
31	Filled with Granular Base Layer	3	30	10.00	10.00	10.00
32		6	60	5.00	5.00	5.00
33		7	100	4.0	5.71	5.71
34	Sandy clay, in-situ condition compact medium consist of dense, medium brown coloring.	3	50	16.67	16.67	16.67
35		3	100	50	16.67	16.67
36		3	150	50	16.67	16.67
37	Silty Clay, partially in-situ firm, partially saturated state and reddish brown coloration.	3	100	33.33	33.33	33.33
38		3	200	33.33	33.33	33.33
39		4	300	25.00	25.00	25.00
40						
41						
42						
43						
44						
45						
46						
47						
48						
49						
50						
51						
52						
53						
54						
55						
56						
57						
58						
59						
60						
61						
62						
63						
64						
65						
66						
67						
68						
69						
70						
71						
72						
73						
74						
75						
76						
77						
78						
79						
80						
81						
82						
83						
84						
85						
86						
87						
88						
89						
90						
91						
92						
93						
94						
95						
96						
97						
98						
99						
100						
101						
102						
103						
104						
105						
106						
107						
108						
109						
110						
111						
112						
113						
114						
115						
116						
117						
118						
119						
120						
121						
122						
123						
124						
125						
126						
127						
128						
129						
130						
131						
132						
133						
134						
135						
136						
137						
138						
139						
140						
141						
142						
143						
144						
145						
146						
147						
148						
149						
150						
151						
152						
153						
154						
155						
156						
157						
158						
159						
160						
161						
162						
163						
164						
165						
166						
167						
168						
169						
170						
171						
172						
173						
174						
175						
176						
177						
178						
179						
180						
181						
182						
183						
184						
185						
186						
187						
188						
189						
190						
191						
192						
193						
194						
195						
196						
197						
198						
199						
200						
201						
202						
203						
204						
205						
206						
207						
208						
209						
210						
211						
212						
213						
214						
215						
216						
217						
218						
219						
220						
221						
222						
223						
224						
225						
226						
227						
228						
229						
230						
231						
232						
233						
234						
235						
236						
237						
238						
239						
240						
241						
242						
243						
244						
245						
246						
247						
248						
249						
250						
251						
252						
253						
254						
255						
256						
257						
258						
259						
260						
261						
262						
263						
264						
265						
266						
267						
268						
269						
270						
271						
272						
273						
274						
275						
276						
277						
278						
279						
280						
281						
282						
283						
284						

K.M.T. (m)		RECORD FIELD		TEST RESULTS		WEIGHT HAMMER: 8 Kg.			
no	RELATIVE HUMIDITY (%)	Visual Description of the Material	Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Between Readings (mm) (E)	DPF Index (Punches) (F)	AVERAGE CBR %	observations
0.10		Silty sand of medium grain, in-situ condition compact, dense compaction of dry and dark brown coloration.	5	31	30	6.00	1	26.81	40.14
0.20		Silty fine-grained sand, in-situ condition compact, dense compaction of dry and dark brown coloration.	50	40	40	0.80	1	246.91	
0.40		Silty fine-grained sand, in-situ condition compact, dense compaction of dry and dark brown coloration.	54	40	0.74	1	0.74	283.70	287.68
0.60		Silty fine-grained sand, in-situ condition compact, dense compaction of dry and dark brown coloration.	51	110	30	0.59	1	347.86	
0.80		Silty fine-grained sand, in-situ condition compact, dense compaction of dry and dark brown coloration.	12	40	40	3.33	1	48.82	
1.00		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	15	30	50	3.33	1	49.85	43.79
1.20		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	12	150	60	5.00	1	31.66	
1.40		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	8	60	60	7.50	1	20.10	
1.60		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	12	120	60	5.00	1	31.66	25.88
1.70		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	30	160	60	6.00	1	25.81	
1.80		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	6	40	60	10.00	1	14.56	
1.90		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	5	110	50	10.00	1	14.56	14.56
2.00		Silty sand of medium grain, in-situ condition, average compaction, partially dry and reddish brown coloration.	6	170	60	10.00	1	14.56	
2.10		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	6	30	50	8.33	1	17.86	
2.20		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	5	30	40	8.00	1	18.70	21.57
2.30		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	9	140	50	5.56	1	14.56	26.13
2.40		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	5	40	40	8.00	1	18.70	
2.50		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	6	140	50	8.33	1	17.86	18.14
2.60		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	6	140	50	8.33	1	17.86	
2.70		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	6	40	60	10.00	1	14.56	14.56
2.80		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	6	120	60	10.00	1	14.56	16.79
2.90		Silty sand, firm-situ, on average compaction, saturated state condition and reddish brown coloration.	7	170	50	7.14	1	21.23	
<b>OBSERVATIONS:</b>									
<p>The presence of the Water Table at a depth of 1.80 m was evident, until the end of Geotechnical Study. For the study is considered the month 0/00 level of survey done.</p> <p>At: Number of hammer blows between readings          B: Penetration measured after each series of blows          C: Penetration between readings (mm) (between readings)          D: Note C between A and E          E: Note D between A and F          F: Note D Note E          G: Comparison between CBR and DPF Index.</p>									

K.M.T. (m)		RECORD FIELD		TEST RESULTS		WEIGHT HAMMER: 8 Kg.			
no	RELATIVE HUMIDITY (%)	Visual Description of the Material	Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Between Readings (mm) (E)	DPF Index (Punches) (F)	AVERAGE CBR %	observations
0.10		Filled with Granular Base Layer	6	30	30	5.00	1	31.66	
0.20		Silty sand, firm-situ, dense compaction of dry reddish brown coloration and condition.	9	50	50	5.56	1	26.13	
0.40		Silty sand, firm-situ, dense compaction of dry reddish brown coloration and condition.	8	100	50	6.25	1	24.68	22.45
0.60		Silty sand, firm-situ, dense compaction of dry reddish brown coloration and condition.	5	150	50	10.00	1	14.56	
0.80		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	4	60	60	15.00	1	9.25	
1.00		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	2	120	60	30.00	1	4.26	5.05
1.20		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	1	150	70	70.00	1	1.65	
1.30		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.							
1.40		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	6	80	80	13.33	1	13.33	10.55
1.50		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	5	160	80	16.00	1	8.60	8.34
1.60		Silty Sand, in-situ condition firm, compact loose, partially saturated state and reddish coloration.	4	250	90	22.50	1	22.50	5.87
1.70		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	4	60	60	15.00	1	9.25	
1.80		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	3	120	60	20.00	1	6.70	7.20
1.90		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	3	180	70	23.33	1	23.33	5.84
2.00		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	6	50	50	8.33	1	8.33	17.88
2.10		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	6	110	60	10.00	1	14.56	14.14
2.20		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	5	180	70	14.00	1	14.00	9.99
2.30		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	8	100	100	12.50	1	12.50	11.34
2.40		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	8	200	100	12.50	1	12.50	11.34
2.50		Silty Sand, firm condition in-situ, on average compaction, saturated state and reddish coloration.	8	300	100	12.50	1	12.50	11.34
<b>OBSERVATIONS:</b>									
<p>The presence of the Water Table at a depth of 1.20 m was evident, until the end of Geotechnical Study. For the study is considered the month 0/00 level of survey done.</p> <p>At: Number of hammer blows between readings          B: Penetration measured after each series of blows          C: Penetration between readings (mm) (between readings)          D: Note C between A and E          E: Note D between A and F          F: Note D Note E          G: Comparison between CBR and DPF Index.</p>									

		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 Date: 20/09/2014 REPORT: RP 00 PAGE: 01 de 01							
CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Camino 7-H and 11 Road Boring Project</b> UBICACION / Location: <b>Municipality of Chama 1-11, 2-Section, Varona Province, Northern Region of Santa Cruz de la Sierra City</b>		<b>DCP N°:</b> 43									
<b>TEST DATA</b>											
<b>PROFESIONISTA:</b> 20-4110 X Coordinate: 1724102.30°S Y Coordinate: 62°54'00.60°O		<b>WEIGHT HAMMER:</b> 8 Kg.									
<b>WATER TABLE:</b> 3.00 m.											
<b>RECORD FIELD</b>											
K.M.T.	NO. DE BARRIL	DESCRIPCIÓN VISUAL DEL MATERIAL	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	DCP Index (mm/100blows) (F)	CBR %	AVERAGE CBR %	Observations
0.00	01	Clayey silty, firm-situ, dense compactness, partially dry and light gray coloring condition.	15	31	30	2.00	1	2.00	96.34	97.22	
0.00	02		16	61	30	1.88	1	1.88	94.96		
0.00	03		18	91	30	1.67	1	1.67	108.35		
0.00	04		32	121	30	1.25	1	1.25	149.54		
0.00	05		37	158	37	1.08	1	1.08	175.95	95.30	
0.00	06		21	179	40	1.80	1	1.80	95.30		
0.00	07		7	186	60	8.57	1	8.57	17.31		
0.00	08		5	190	40	12.00	1	12.00	11.87	12.81	
0.00	09		4	194	60	15.00	1	15.00	9.25		
0.00	10		3	197	40	13.33	1	13.33	10.55	9.77	
0.00	11		3	200	50	16.67	1	16.67	8.22		
0.00	12		5	205	60	12.00	1	12.00	11.87		
0.00	13		4	209	60	15.00	1	15.00	9.25	12.81	
0.00	14		7	216	60	8.57	1	8.57	17.31		
0.00	15		7	223	50	12.86	1	12.86	10.99		
0.00	16		14	237	50	6.43	1	6.43	20.89	19.59	
0.00	17		14	251	50	6.43	1	6.43	20.89		
0.00	18		6	257	60	13.33	1	13.33	10.55	11.48	
0.00	19		7	264	60	11.43	1	11.43	12.54		
0.00	20		4	268	50	12.50	1	12.50	11.34		
<b>OBSERVATIONS:</b>											
The presence of the Water Table at a depth of 3.00 m was evident, until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.											
A= Number of blows between readings B= Penetration measurement after series of blows C= Net C between A and B D= Net C between A and B E= Net C between A and B F= Net C between A and B G= Correlation between CBR and DCP index											
DATE OF CREATION OF TEST: 04/09/2014 CLOSING DATE OF TEST: 04/09/2014										LABORATORY MANAGER	

		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		REV: 00 Date: 20/09/2014 REPORT: RP 00 PAGE: 01 de 01							
CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Camino 7-H and 11 Road Boring Project</b> UBICACION / Location: <b>Municipality of Chama 1-11, 2-Section, Varona Province, Northern Region of Santa Cruz de la Sierra City</b>		<b>DCP N°:</b> 44									
<b>TEST DATA</b>											
<b>PROFESIONISTA:</b> 20-610 X Coordinate: 1724118.40°S Y Coordinate: 62°54'02.70°O		<b>WEIGHT HAMMER:</b> 8 Kg.									
<b>WATER TABLE:</b> 2.80 m.											
<b>RECORD FIELD</b>											
K.M.T.	NO. DE BARRIL	DESCRIPCIÓN VISUAL DEL MATERIAL	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	Factor Correction (mm) (E)	DCP Index (mm/100blows) (F)	CBR %	AVERAGE CBR %	Observations
0.00	01	Silty sand, firm-situ, dense compactness of dry and gray coloring condition.	34	30	30	0.88	1	0.88	220.89	237.99	
0.00	02		39	60	30	0.77	1	0.77	257.98		
0.00	03		36	90	30	0.83	1	0.83	235.50		
0.00	04		52	120	30	0.96	1	0.96	200.02		
0.00	05		63	150	30	0.79	1	0.79	243.72	241.58	
0.00	06		69	180	30	0.72	1	0.72	275.40		
0.00	07		5	185	50	10.00	1	10.00	14.56		
0.00	08		6	191	50	8.33	1	8.33	17.86	15.66	
0.00	09		4	195	40	10.00	1	10.00	14.56		
0.00	10		15	210	60	4.00	1	4.00	46.64		
0.00	11		16	216	60	3.75	1	3.75	49.69	44.73	
0.00	12		18	224	60	3.33	1	3.33	49.85		
0.00	13		10	230	50	5.00	1	5.00	31.66		
0.00	14		13	243	50	3.85	1	3.85	42.47	33.79	
0.00	15		7	250	40	5.71	1	5.71	27.28		
0.00	16		5	255	60	12.00	1	12.00	11.87		
0.00	17		5	260	60	12.00	1	12.00	11.87	12.77	
0.00	18		6	266	60	10.00	1	10.00	14.56		
0.00	19		4	270	60	15.00	1	15.00	9.25		
0.00	20		3	273	60	20.00	1	20.00	6.70	8.18	
0.00	21		5	278	80	16.00	1	16.00	8.60		
0.00	22		4	282	40	10.00	1	10.00	14.56		
0.00	23		5	287	50	10.00	1	10.00	14.56	15.48	
0.00	24		7	294	60	8.57	1	8.57	17.31		
<b>OBSERVATIONS:</b>											
The presence of the Water Table at a depth of 2.80 m was evident, until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.											
A= Number of blows between readings B= Penetration measurement after series of blows C= Net C between A and B D= Net C between A and B E= Net C between A and B F= Net C between A and B G= Correlation between CBR and DCP index											
DATE OF CREATION OF TEST: 04/09/2014 CLOSING DATE OF TEST: 04/09/2014										LABORATORY MANAGER	



	<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03	REV: 00 Date: 20/08/2014 REPORT: RP 00 PAGE: 01 de 01
		CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Urban 7-1 Road III Road Paving Project</b> UBICACION / Location: <b>Municipality of Chitara 7-1, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City</b>
<b>TEST DATA</b>		DCP N°: <b>48</b>

PROYECTIVO: <b>22-400</b> not Applicable	X Coordinate: <b>172522.70°N</b> Y Coordinate: <b>625410.20°W</b>	WEIGHT HAMMER: <b>8 Kg.</b>
---	--	-----------------------------

K.M.T.	METER	RECORDER FIELD	TEST RESULTS										AVERAGE CBR %	observations
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Penetration CBR (mm) (D)	Factor E	DCP Index (mm / Pound) (E)	Factor F	CBR % (G)				
0.15		Silty Sand condition in-situ firm, dense consistency of dry and light gray coloring.	42	40	40	0.95	1	0.95	202.78	1	0.95	202.78	251.71	
0.30			40	100	30	0.75	1	0.75	264.99	1	0.75	264.99		
0.45			10	50	50	5.00	1	5.00	31.66	1	5.00	31.66		
0.60			12	100	50	4.17	1	4.17	38.83	1	4.17	38.83		
0.75			18	150	50	2.78	1	2.78	61.14	1	2.78	61.14		
0.90														
1.05			9	50	50	5.56	1	5.56	28.13	1	5.56	28.13		
1.20			9	100	50	5.56	1	5.56	28.13	1	5.56	28.13		
1.35			5	140	40	8.00	1	8.00	18.70	1	8.00	18.70		
1.50			4	40	40	10.00	1	10.00	14.56	1	10.00	14.56		
1.65			4	80	40	8.00	1	8.00	18.70	1	8.00	18.70		
1.80			7	130	50	7.14	1	7.14	21.23	1	7.14	21.23		
1.95														
2.10			9	70	70	7.78	1	7.78	19.30	1	7.78	19.30		
2.25			7	140	70	10.00	1	10.00	14.56	1	10.00	14.56		
2.40			6	200	60	10.00	1	10.00	14.56	1	10.00	14.56		
2.55			6	40	40	6.67	1	6.67	22.94	1	6.67	22.94		
2.70			5	50	50	10.00	1	10.00	14.56	1	10.00	14.56		
2.85			7	150	60	8.57	1	8.57	17.31	1	8.57	17.31		
3.00			4	60	60	15.00	1	15.00	9.25	1	15.00	9.25		
3.15			3	120	60	20.00	1	20.00	6.70	1	20.00	6.70		
3.30			4	150	70	17.50	1	17.50	7.78	1	17.50	7.78		
3.45			7	50	50	7.14	1	7.14	21.23	1	7.14	21.23		
3.60			7	100	50	7.14	1	7.14	21.23	1	7.14	21.23		
3.75			7	150	50	7.14	1	7.14	21.23	1	7.14	21.23		


<b>OBSERVATIONS</b> The color of the Water Table was not obtained until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey done. Hanging water of 2.50 m was evident to 2.90 m.	DATE OF CREATION OF TEST: <b>05/09/2014</b> CLOSING DATE OF TEST: <b>05/09/2014</b>	LABORATORY MANAGER:
---	--	---------------------


	<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03	REV: 00 Date: 20/08/2014 REPORT: RP 00 PAGE: 01 de 01
		CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Urban 7-1 Road III Road Paving Project</b> UBICACION / Location: <b>Municipality of Chitara 7-1, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City</b>
<b>TEST DATA</b>		DCP N°: <b>47</b>

PROYECTIVO: <b>22-400</b> not Applicable	X Coordinate: <b>172526.60°N</b> Y Coordinate: <b>625410.10°W</b>	WEIGHT HAMMER: <b>8 Kg.</b>
---	--	-----------------------------

K.M.T.	METER	RECORDER FIELD	TEST RESULTS										AVERAGE CBR %	observations
			Number of Blows (A)	Cumulative penetration (mm) (G)	Penetration Between Readings (mm) (C)	Penetration CBR (mm) (D)	Factor E	DCP Index (mm / Pound) (E)	Factor F	CBR % (G)				
0.10		Filled with Gravel Base Layer	23	31	30	1.30	1	1.30	142.86	1	1.30	142.86	121.92	
0.25			26	100	30	1.54	1	1.54	116.91	1	1.54	116.91		
0.40			37	40	40	1.08	1	1.08	173.99	1	1.08	173.99		
0.55			27	80	40	1.48	1	1.48	123.63	1	1.48	123.63	73.64	
0.70			17	120	40	2.25	1	2.25	70.64	1	2.25	70.64		
0.85														
1.00			7	50	50	7.14	1	7.14	21.23	1	7.14	21.23		
1.15			6	100	50	8.33	1	8.33	17.86	1	8.33	17.86		
1.30			5	140	40	8.00	1	8.00	18.70	1	8.00	18.70		
1.45														
1.60			5	40	40	8.00	1	8.00	18.70	1	8.00	18.70		
1.75			5	80	40	8.00	1	8.00	18.70	1	8.00	18.70		
1.90			4	120	40	10.00	1	10.00	14.56	1	10.00	14.56		
2.05			9	70	70	7.78	1	7.78	19.30	1	7.78	19.30		
2.20			7	140	70	10.00	1	10.00	14.56	1	10.00	14.56	9.99	
2.35			5	210	70	14.00	1	14.00	9.99	1	14.00	9.99		
2.50														
2.65			8	60	60	7.50	1	7.50	20.10	1	7.50	20.10		
2.80			6	120	60	10.00	1	10.00	14.56	1	10.00	14.56		
2.95			6	180	60	10.00	1	10.00	14.56	1	10.00	14.56		
3.10														
3.25			9	70	70	7.78	1	7.78	19.30	1	7.78	19.30		
3.40			9	130	60	6.67	1	6.67	22.94	1	6.67	22.94		
3.55			9	200	70	7.78	1	7.78	19.30	1	7.78	19.30		
3.70														
3.85			8	60	60	7.50	1	7.50	20.10	1	7.50	20.10		
4.00			9	120	60	6.67	1	6.67	22.94	1	6.67	22.94	21.23	
4.15			7	170	50	7.14	1	7.14	21.23	1	7.14	21.23		

<b>OBSERVATIONS</b> The presence of the Water Table was not obtained until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey done.	DATE OF CREATION OF TEST: <b>05/09/2014</b> CLOSING DATE OF TEST: <b>05/09/2014</b>	LABORATORY MANAGER:
---	--	---------------------

REV. 00 2008/2014 RP 00 01 de 01		DYNAMIC PENETRATION TESTING (DCP) NORMA ASTM-D-6951-03		REV. 00 2008/2014 RP 00 01 de 01					
 CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Camino 7 - 8 and 11 Road Paving Project</b> UBICACION / Location: <b>Municipality of Chiminá 7-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City</b>		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		00 2008/2014 RP 00 01 de 01					
<b>PROFESIONISTA:</b> 23+100 <b>WATER TABLE:</b> not applicable <b>WEIGHT HAMMER:</b> 8 Kg.		<b>TEST DATA</b> X Coordinate: 172523830" S Y Coordinate: 62541190" W		<b>PROFESIONISTA:</b> 50 <b>WATER TABLE:</b> 2.60 m. <b>WEIGHT HAMMER:</b> 8 Kg.					
RECORD FIELD		TEST RESULTS		OBSERVATIONS:					
K.M. (m)	Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	DCP Index (mm/30 blows) (E)	Factor Correction (mm/30 blows) (F)	AVERAGE CBR %	Observations
0.00	Filled with Gravel base Layer	36	30	30	0.83	1	0.83	295.50	(For the first item) Due to the characteristics of this material, the CBR values are disregarded. CBR values greater than 100% on average, since the test was conducted on an isolated laboratory plate.
0.15	Silty Sand condition in-situ firm, dense compaction of dry and gray coloring.	4	40	40	10.00	1	10.00	14.56	
0.40	Firm-situ, medium bedded, partially dry and light gray color with brown patinas condition.	3	100	30	10.00	1	10.00	14.56	
0.90	Limo Clay.	7	60	60	8.57	1	8.57	17.31	
1.00	Firm-situ, soft consistency to medium partially dry and reddish brown coloration Silty Clay	7	110	50	7.14	1	7.14	21.23	
1.20	Firm-situ, soft consistency to medium partially dry and reddish brown coloration Silty Clay	6	150	40	8.33	1	8.33	17.66	
1.40	Firm-situ, soft consistency to medium partially dry and reddish brown coloration Silty Clay	6	40	40	6.67	1	6.67	25.94	
1.70	Firm-situ, medium bedded, partially dry and light brown with small presence of clayey silty clay sand dunes.	6	80	40	6.67	1	6.67	25.94	
2.00	Firm-situ, medium bedded, partially dry and light brown with small presence of clayey silty clay sand dunes.	9	120	40	6.67	1	6.67	25.94	
2.20	Firm-situ, medium bedded, partially dry and light brown with small presence of clayey silty clay sand dunes.	8	180	60	7.50	1	7.50	20.10	
2.40	Firm-situ, medium bedded, partially dry and light brown with small presence of clayey silty clay sand dunes.	7	40	40	5.71	1	5.71	27.26	
3.00	Clayey Sand weak condition in-situ, soft consistency, partially saturated state and reddish coloration	4	20	20	17.50	1	17.50	7.78	
		3	140	70	23.33	1	23.33	5.64	
		3	210	70	23.33	1	23.33	5.64	
OBSERVATIONS:		DATE OF CREATION OF TEST:		CLOSING DATE OF TEST:					
The presence of the Water Table at a depth of 2.60 m was not considered for the study. It is considered the month 0.00 level survey date.		05/09/2014		05/09/2014					
LABORATORY MANAGER		LABORATORY MANAGER		LABORATORY MANAGER					



REV. 00 2008/2014 RP 00 01 de 01		DYNAMIC PENETRATION TESTING (DCP) NORMA ASTM-D-6951-03		REV. 00 2008/2014 RP 00 01 de 01					
 CLIENTE / Client: <b>KATAMBA &amp; Engineers International</b> PROYECTO / Project: <b>Preparatory Study of the Camino 7 - 8 and 11 Road Paving Project</b> UBICACION / Location: <b>Municipality of Chiminá 7-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City</b>		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03		00 2008/2014 RP 00 01 de 01					
<b>PROFESIONISTA:</b> 23+595 <b>WATER TABLE:</b> 2.60 m. <b>WEIGHT HAMMER:</b> 8 Kg.		<b>TEST DATA</b> X Coordinate: 172525410" S Y Coordinate: 62541290" W		<b>PROFESIONISTA:</b> 50 <b>WATER TABLE:</b> 2.60 m. <b>WEIGHT HAMMER:</b> 8 Kg.					
RECORD FIELD		TEST RESULTS		OBSERVATIONS:					
K.M. (m)	Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (G)	Penetration Between Readings (mm) (C)	Factor Correction (mm) (D)	DCP Index (mm/30 blows) (E)	Factor Correction (mm/30 blows) (F)	AVERAGE CBR %	Observations
0.10	Silty sand with gravel isolated presence of strong in-situ condition, dense compaction of dry and gray coloring.	24	70	30	1.25	1	1.25	148.54	(For the 8 at point) Given the characteristics of this material, the CBR values are disregarded. CBR values greater than 100% on average, since the test was conducted on an isolated laboratory plate.
0.40	Silty sand, firm-situ, dense compaction of dry and dark brown coloration condition.	8	100	30	6.25	1	6.25	24.66	
0.90	Silty sand, firm-situ, dense compaction of dry and gray coloring condition.	12	130	40	3.33	1	3.33	49.95	
1.30	Silty sand, firm-situ, dense compaction of dry and gray coloring condition.	13	150	50	3.85	1	3.85	42.47	
1.50	Silty sand, firm-situ, dense compaction of dry and gray coloring condition.	12	40	40	3.33	1	3.33	49.95	
1.80	Silty sand, firm-situ, dense compaction of dry and gray coloring condition.	14	80	40	2.86	1	2.86	59.25	
2.00	Silty sand, firm-situ, dense compaction of dry and gray coloring condition.	18	140	60	3.33	1	3.33	49.95	
2.20	Clayey sand, in-situ condition firm, medium bedded, partially dry and reddish brown coloration.	4	50	50	12.50	1	12.50	11.34	
2.40	Clayey sand, in-situ condition firm, medium bedded, partially dry and reddish brown coloration.	3	100	50	16.67	1	16.67	8.22	
2.60	Clayey sand, in-situ condition firm, medium bedded, partially saturated state and reddish coloration.	2	140	40	20.00	1	20.00	6.70	
2.80	Clayey sand, in-situ condition firm, medium bedded, partially saturated state and reddish coloration.	5	60	60	12.00	1	12.00	11.87	
3.00	Clayey sand, in-situ condition firm, medium bedded, partially saturated state and reddish coloration.	4	180	60	15.00	1	15.00	9.25	
3.20	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	7	70	70	10.00	1	10.00	14.56	
3.40	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	5	140	70	14.00	1	14.00	9.99	
3.60	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	3	200	60	20.00	1	20.00	6.70	
3.80	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	7	180	60	8.57	1	8.57	17.31	
3.90	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	6	60	60	10.00	1	10.00	14.56	
4.00	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	3	120	60	20.00	1	20.00	6.70	
4.20	Limo Silty, in-situ condition firm, soft compaction, partially saturated state and light brown coloring.	7	180	60	8.57	1	8.57	17.31	
OBSERVATIONS:		DATE OF CREATION OF TEST:		CLOSING DATE OF TEST:					
The presence of the Water Table at a depth of 2.60 m was not considered for the study. It is considered the month 0.00 level survey date.		05/09/2014		05/09/2014					
LABORATORY MANAGER		LABORATORY MANAGER		LABORATORY MANAGER					



CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01							
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		00							
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		RP 00							
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		01 de 01							
<p><b>PROGRESIVO:</b> 24+100 <b>TEST DATA</b> X Coordinate: 1723610.20°S Y Coordinate: 62°54'06.90°O <b>WEIGHT HAMMER:</b> 8 Kg.</p> <p><b>WATER TABLE:</b> 2.20 m. <b>RECORD FIELD</b></p>											
DEPTH (m)	NO. OF TESTS	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Pounds) (F)	Factor Correction (E)	CBR % (G)	AVERAGE CBR %	observations
0.00	15	Filled with Gravel Base Layer	31	31	2.00	1	2.00	1	86.34	86.34	(For the first three points) of this type of soil (Silty Sand and Base Layer) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted on an isolated surface stone of compacted CBR of 89.34 was adopted at the first point, 69.8 in the third point.
0.10	23	Material Type	30	61	1.30	1	1.30	1	142.98	142.98	
0.20	29		30	91	1.03	1	1.03	1	184.85	184.85	
0.30	21	Silty sand, firm-situ, dense compaction of dry and dark brown coloring condition.	40	131	1.30	1	1.30	1	93.30	93.30	
0.40	26		40	171	1.54	1	1.54	1	118.57	118.57	
0.50	41		40	211	0.88	1	0.88	1	197.38	197.38	
0.60	8		20	231	2.50	1	2.50	1	68.80	68.80	
0.70	33	Silty sand, firm to dense compaction of dry and brown with presence of clay condition.	40	271	0.61	1	0.61	1	336.42	336.42	
0.80	48		30	301	0.83	1	0.83	1	323.02	323.02	
0.90	8	Limo Sandy with plasticity condition in-situ firm, medium compact, partially dry and reddish brown coloration.	30	331	3.75	1	3.75	1	43.69	43.69	
1.00	8		30	361	3.75	1	3.75	1	43.69	43.69	
1.10	7		30	391	4.29	1	4.29	1	37.62	37.62	
1.20	5		40	431	8.00	1	8.00	1	18.70	18.70	
1.30	5		40	471	8.00	1	8.00	1	18.70	18.70	
1.40	5		40	511	8.00	1	8.00	1	18.70	18.70	
1.50	4		40	551	10.00	1	10.00	1	14.56	14.56	
1.60	4		40	591	10.00	1	10.00	1	14.56	14.56	
1.70	7		40	631	5.71	1	5.71	1	27.26	27.26	
1.80	7		40	671	5.71	1	5.71	1	27.26	27.26	
1.90	7		40	711	5.71	1	5.71	1	27.26	27.26	
2.00	3		40	751	13.33	1	13.33	1	10.56	10.56	
2.10	4		40	791	10.00	1	10.00	1	14.56	14.56	
2.20	5		40	831	8.00	1	8.00	1	18.70	18.70	
<p><b>OBSERVATIONS:</b></p> <p>The presence of the Water Table at a depth of 2.20 m was evident, until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.</p> <p>A = Number of blows taken between readings  B = Penetration measured after even series of blows  C = Penetration between readings (from 0.30m mark)  D = Total penetration (from 0.30m mark)  E = Factor Correction  F = DCP Index  G = Correlation between CBR and DCP index</p>											
DATE OF CREATION OF TEST:				09/09/2014				LABORATORY MANAGER			
CLOSING DATE OF TEST:				09/09/2014				LABORATORY MANAGER			


CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01							
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		00							
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		RP 00							
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		01 de 01							
<p><b>PROGRESIVO:</b> 24+615 <b>TEST DATA</b> X Coordinate: 1723626.60°S Y Coordinate: 62°54'07.10°O <b>WEIGHT HAMMER:</b> 8 Kg.</p> <p><b>WATER TABLE:</b> 2.70 m. <b>RECORD FIELD</b></p>											
DEPTH (m)	NO. OF TESTS	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm / Pounds) (F)	Factor Correction (E)	CBR % (G)	AVERAGE CBR %	observations
0.00	25	Filled with Gravel Base Layer	30	30	1.20	1	1.20	1	156.54	156.54	(For the first two points) of this type of soil (Silty Sand and Base Layer) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted on an isolated consolidated dry ground.
0.10	32	Material Type	30	60	0.84	1	0.84	1	200.39	200.39	
0.20	40		30	90	0.75	1	0.75	1	264.99	264.99	
0.30	20	Silty sand, firm-situ, dense compaction of dry and dark brown coloring condition.	20	110	1.00	1	1.00	1	192.00	192.00	
0.40	28		40	150	0.71	1	0.71	1	273.88	273.88	
0.50	35		60	210	0.57	1	0.57	1	395.34	395.34	
0.60	5		20	230	4.00	1	4.00	1	40.64	40.64	
0.70	5		40	270	4.00	1	4.00	1	40.64	40.64	
0.80	3		30	300	10.00	1	10.00	1	14.56	14.56	
0.90	6		30	330	5.00	1	5.00	1	31.66	31.66	
1.00	6		30	360	5.00	1	5.00	1	31.66	31.66	
1.10	5		30	390	6.00	1	6.00	1	26.81	26.81	
1.20	5		60	450	5.00	1	5.00	1	31.66	31.66	
1.30	5		100	550	8.00	1	8.00	1	18.70	18.70	
1.40	4		40	590	10.00	1	10.00	1	14.56	14.56	
1.50	5		80	670	8.00	1	8.00	1	18.70	18.70	
1.60	5		120	790	8.00	1	8.00	1	18.70	18.70	
1.70	5		40	830	8.00	1	8.00	1	18.70	18.70	
1.80	5		40	870	8.00	1	8.00	1	18.70	18.70	
1.90	5		40	910	8.00	1	8.00	1	18.70	18.70	
2.00	5		40	950	8.00	1	8.00	1	18.70	18.70	
<p><b>OBSERVATIONS:</b></p> <p>The presence of the Water Table at a depth of 2.70 m was evident, until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.</p> <p>A = Number of blows taken between readings  B = Penetration measured after even series of blows  C = Penetration between readings (from 0.30m mark)  D = Total penetration (from 0.30m mark)  E = Factor Correction  F = DCP Index  G = Correlation between CBR and DCP index</p>											
DATE OF CREATION OF TEST:				09/09/2014				LABORATORY MANAGER			
CLOSING DATE OF TEST:				09/09/2014				LABORATORY MANAGER			






PROYECTOS:		WATER TABLE:		TEST RESULTS:		WEIGHT HAMMER:						
28+110		1.80 m.		1.7271440°S		8 Kg.						
COORDENADAS:		COORDENADAS:		COORDENADAS:		COORDENADAS:						
X: 62°54'16.70"O		Y: 17°27'14.00"S		X: 62°54'20.40"O		Y: 17°27'30.30"S						
				<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03						
<b>CLIENTE / CLIENT:</b> KATAMBA & Engineers International <b>PROYECTO / PROJECT:</b> Preparatory Study of the Camino 1-1 and 111 Road Boring Project <b>UBICACION / LOCATION:</b> Municipality of Chiminá 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		<b>CLIENTE / CLIENT:</b> KATAMBA & Engineers International <b>PROYECTO / PROJECT:</b> Preparatory Study of the Camino 1-1 and 111 Road Boring Project <b>UBICACION / LOCATION:</b> Municipality of Chiminá 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		<b>PROGRESIVO:</b> 2008/2014 RP 00 01 de 01		<b>PROGRESIVO:</b> 2008/2014 RP 00 01 de 01						
<b>TEST DATA</b>		<b>TEST DATA</b>		<b>TEST DATA</b>		<b>TEST DATA</b>						
DEPTH (m)	WATER TABLE (m)	RECORD FIELD	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DPT Index (mm/Point) (B)	Factor Correction (E)	CBR %	AVERAGE CBR %	observations
0.05		Filled with Granular Base Layer Material Type		15	20	1.33	1	1.33	1	153.17	153.17	(For the first item) Due to the characteristics of the material, the use of the Standard Penetration Test (SPT) and Bore Log (SBL) is not recommended. Disregard CBR values as average, since that would be inconsistent data. This test was conducted on an isolated hammer stone or consolidated, dry ground.
0.20		Silty sand, firm, dense compaction, saturated state and brown coloration.		19	40	2.31	1	2.31	1	76.26	76.26	
0.40		Silty fine-grained sand, firm in-situ, loose to medium, partially dry and dark brown coloration.		17	60	3.00	1	3.00	1	101.63	84.05	
1.00		Silty sand, firm, in-situ, average compaction, partially saturated state and reddish brown coloration.		13	90	2.31	1	2.31	1	76.26	76.26	
1.20				3	30	10.00	1	10.00	1	14.56	14.56	
1.40				3	40	10.00	1	10.00	1	14.56	14.56	
1.60				5	50	10.00	1	10.00	1	14.56	12.15	
1.80				4	140	12.50	1	12.50	1	11.34	11.34	
2.00				3	40	13.33	1	13.33	1	10.55	10.55	
2.20				5	50	10.00	1	10.00	1	14.56	14.56	
2.40				4	140	12.50	1	12.50	1	11.34	11.34	
2.60				4	50	12.50	1	12.50	1	11.34	11.34	
2.80				5	100	10.00	1	10.00	1	14.56	13.49	
3.00				5	150	10.00	1	10.00	1	14.56	14.56	
3.20				2	50	25.00	1	25.00	1	5.22	5.22	
3.40				2	100	25.00	1	25.00	1	5.22	7.26	
3.60				4	150	12.50	1	12.50	1	11.34	11.34	
3.80				6	50	8.33	1	8.33	1	17.66	17.66	
4.00				5	100	10.00	1	10.00	1	14.56	15.66	
4.20				5	150	10.00	1	10.00	1	14.56	14.56	
<b>OBSERVATIONS:</b> The presence of the Water Table at a depth of 1.80 m was not evident, until the end of the Cone Penetration Test. For the work it is considered the month 0.00 to end of survey date.												
<b>CONCLUSION:</b> The presence of the Water Table at a depth of 1.80 m was not evident, until the end of the Cone Penetration Test. For the work it is considered the month 0.00 to end of survey date.												
<b>DATE OF CREATION OF TEST:</b> 06/09/2014										<b>CLOSING DATE OF TEST:</b> 06/09/2014		<b>LABORATORY MANAGER</b>

PROYECTOS:		WATER TABLE:		TEST RESULTS:		WEIGHT HAMMER:						
28+610		2.50 m.		1.7273030°S		8 Kg.						
COORDENADAS:		COORDENADAS:		COORDENADAS:		COORDENADAS:						
X: 62°54'16.70"O		Y: 17°27'14.00"S		X: 62°54'20.40"O		Y: 17°27'30.30"S						
				<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03		<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-4951-03						
<b>CLIENTE / CLIENT:</b> KATAMBA & Engineers International <b>PROYECTO / PROJECT:</b> Preparatory Study of the Camino 1-1 and 111 Road Boring Project <b>UBICACION / LOCATION:</b> Municipality of Chiminá 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		<b>CLIENTE / CLIENT:</b> KATAMBA & Engineers International <b>PROYECTO / PROJECT:</b> Preparatory Study of the Camino 1-1 and 111 Road Boring Project <b>UBICACION / LOCATION:</b> Municipality of Chiminá 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		<b>PROGRESIVO:</b> 2008/2014 RP 00 01 de 01		<b>PROGRESIVO:</b> 2008/2014 RP 00 01 de 01						
<b>TEST DATA</b>		<b>TEST DATA</b>		<b>TEST DATA</b>		<b>TEST DATA</b>						
DEPTH (m)	WATER TABLE (m)	RECORD FIELD	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DPT Index (mm/Point) (B)	Factor Correction (E)	CBR %	AVERAGE CBR %	observations
0.05		Filled with Granular Base Layer Material Type		47	40	0.43	1	0.43	1	493.62	524.45	(For the first three points) Due to the characteristics of the material, the use of the Standard Penetration Test (SPT) and Bore Log (SBL) is not recommended. Disregard CBR values as average, since that would be inconsistent data. This test was conducted on an isolated hammer stone or consolidated, dry ground.
0.20		Silty fine-grained sand, firm in-situ, dense compaction, saturated state and dark brown coloration.		25	60	3.00	1	3.00	1	156.54	156.54	
0.40		Silty sand, firm, in-situ, average compaction, partially saturated state and reddish brown coloration.		13	60	2.00	1	2.00	1	118.51	118.51	
0.60				5	90	6.00	1	6.00	1	25.81	25.81	
0.80				5	30	6.00	1	6.00	1	25.81	25.81	
1.00				3	50	16.67	1	16.67	1	8.22	8.22	
1.20				2	100	25.00	1	25.00	1	5.22	7.22	
1.40				6	200	16.67	1	16.67	1	8.22	8.22	
1.60				4	100	25.00	1	25.00	1	5.22	5.22	
1.80				5	200	20.00	1	20.00	1	6.70	6.21	
2.00				5	300	20.00	1	20.00	1	6.70	6.70	
2.20												
2.40				6	90	15.00	1	15.00	1	15.00	9.25	
2.60				4	190	100	1	25.00	1	25.00	5.22	
2.80				8	290	100	1	12.50	1	12.50	11.34	
3.00												
<b>OBSERVATIONS:</b> The presence of the Water Table at a depth of 2.50 m was not evident, until the end of the Cone Penetration Test. For the work it is considered the month 0.00 to end of survey date.												
<b>CONCLUSION:</b> The presence of the Water Table at a depth of 2.50 m was not evident, until the end of the Cone Penetration Test. For the work it is considered the month 0.00 to end of survey date.												
<b>DATE OF CREATION OF TEST:</b> 09/09/2014										<b>CLOSING DATE OF TEST:</b> 09/09/2014		<b>LABORATORY MANAGER</b>

 <b>CLIENTE / Client:</b> KATAMBA & Engineers International <b>PROYECTO / Project:</b> Preparatory Study of the Extension of Highway 11 Road Boring Project <b>UBICACION / Location:</b> Municipality of Chitara 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City	<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03	REV: 00 Date: 20/09/2014 REPORT: RP 00 PAGE: 01 de 01
		<b>DCP N°:</b> 58

K.M.T.	PROFUNDIDAD (m)	TIPO DE MATERIAL	RECARGO FIELD	TEST RESULTS							WEIGHT HAMMER: 8 Kg.	OBSERVATIONS
				Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm/100blows) (F)	CBR % (G)	AVERAGE CBR %		
0.05	20	Filled with Granular Base Layer	Material Type	35	20	20	0.57	1	0.57	359.34	348.28	(For the first item) Due to the characteristics of this material, the test was not conducted on an isolated consolidated dry ground.
0.10	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		39	40	20	0.51	1	0.51	405.64		
0.15	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		28	60	20	0.71	1	0.71	279.88		
0.20	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		5	30	30	6.00	1	6.00	25.81	29.71	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
0.25	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		6	50	30	5.00	1	5.00	31.66		
0.30	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		6	30	30	5.00	1	5.00	31.66		
0.35	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		8	70	40	5.00	1	5.00	31.66	33.14	
0.40	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		9	110	40	4.44	1	4.44	36.12		
0.45	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		10	40	40	4.00	1	4.00	40.64		
0.50	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		9	80	40	4.44	1	4.44	36.12	37.63	
0.55	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.		9	120	40	4.44	1	4.44	36.12		
0.60	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.65	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.70	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.75	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.80	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.85	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.90	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
0.95	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.00	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.05	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.10	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.15	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.20	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.25	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.30	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.35	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.40	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.45	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.50	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.55	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.60	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.65	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.70	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.75	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.80	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.85	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.90	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
1.95	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.00	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.05	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.10	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.15	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.20	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.25	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.30	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.35	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.40	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.45	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.50	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.55	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.60	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.65	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.70	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.75	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.80	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.85	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.90	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
2.95	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										
3.00	30	Clay, in-situ condition firm, dense consistency, dry and dark brown with reddish brown patina and red.										

<b>CONSIDERACIONES:</b>		No. - Number of blows between readings. DCP - Penetration measurement after each series of blows. D - Distance between A and B between readings. E - Height of the hammer as Kg. And "H" if the hammer is 4.5 Kg. F - Factor to correct the hammer as Kg. And "H" if the hammer is 4.5 Kg. G - Correction between CBR and DCP index.
The presence of the Water Table was not evidenced, until the end of Geotechnical Study. For the study, it is considered the maximum 0.00 level survey datum.		DATE OF CREATION OF TEST: 10/09/2014 CLOSING DATE OF TEST: 10/09/2014 LABORATORY MANAGER:

 <b>CLIENTE / Client:</b> KATAMBA & Engineers International <b>PROYECTO / Project:</b> Preparatory Study of the Extension of Highway 11 Road Boring Project <b>UBICACION / Location:</b> Municipality of Chitara 1-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City	<b>DYNAMIC PENETRATION TESTING (DCP)</b> NORMA ASTM-D-6951-03	REV: 00 Date: 20/09/2014 REPORT: RP 00 PAGE: 01 de 01
		<b>DCP N°:</b> 57

K.M.T.	PROFUNDIDAD (m)	TIPO DE MATERIAL	RECARGO FIELD	TEST RESULTS							WEIGHT HAMMER: 8 Kg.	OBSERVATIONS
				Number of Blows (A)	Cumulative penetration (mm) (D)	Penetration Between Readings (mm) (C)	Factor Correction (E)	DCP Index (mm/100blows) (F)	CBR % (G)	AVERAGE CBR %		
0.05	30	Filled with Granular Base Layer	Material Type	23	30	30	1.30	1	1.30	142.89	192.54	(For the first three points) Given the characteristics of this material, the test was not conducted on an isolated consolidated dry ground.
0.10	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		38	60	30	0.79	1	0.79	250.20		
0.15	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		29	90	30	1.03	1	1.03	194.85		
0.20	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		12	30	30	2.50	1	2.50	68.80	68.80	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
0.25	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		25	60	30	1.20	1	1.20	156.54		
0.30	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		41	90	30	0.73	1	0.73	272.42		
0.35	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.										
0.40	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		13	30	30	2.31	1	2.31	75.26	75.26	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
0.45	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		25	70	40	1.80	1	1.80	113.42		
0.50	30	Clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		41	110	40	0.88	1	0.88	197.39		
0.55	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.										
0.60	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		19	40	40	2.11	1	2.11	65.41	65.41	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
0.65	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		19	60	40	2.11	1	2.11	65.41	93.41	
0.70	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		25	120	40	1.60	1	1.60	113.42		
0.75	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.										
0.80	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		33	40	40	1.21	1	1.21	154.79		
0.85	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		22	80	40	1.82	1	1.82	92.29	93.31	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
0.90	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		20	120	40	2.00	1	2.00	85.34		
0.95	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.										
1.00	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		2	50	50	25.00	1	25.00	5.22	5.22	greater than 100% on average, since that would be because the test was conducted on an isolated consolidated dry ground.
1.05	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		2	100	50	25.00	1	25.00	5.22	5.22	
1.10	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		2	150	50	25.00	1	25.00	5.22		
1.15	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		2	50	50	25.00	1	25.00	5.22		
1.20	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		3	100	50	16.67	1	16.67	8.22	7.22	
1.25	30	Sandy clay, in-situ condition firm, dense consistency, dryness and reddish brown with dark gray patina.		3	150	50	16.67	1	16.67	8.22		

<b>CONSIDERACIONES:</b>		No. - Number of blows between readings. DCP - Penetration measurement after each series of blows. D - Distance between A and B between readings. E - Height of the hammer as Kg. And "H" if the hammer is 4.5 Kg. F - Factor to correct the hammer as Kg. And "H" if the hammer is 4.5 Kg. G - Correction between CBR and DCP index.
The presence of the Water Table was not evidenced, until the end of Geotechnical Study. For the study, it is considered the maximum 0.00 level survey datum.		DATE OF CREATION OF TEST: 10/09/2014 CLOSING DATE OF TEST: 10/09/2014 LABORATORY MANAGER:

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01						
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		FORMET PAGE						
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		FORMET PAGE						
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		FORMET PAGE						
PROFESIONISTA:		NORMA ASTM-D-6951-03		FORMET PAGE						
WATER TABLE:		NORMA ASTM-D-6951-03		FORMET PAGE						
RECORD FIELD:		NORMA ASTM-D-6951-03		FORMET PAGE						
VISUAL DESCRIPTION OF THE MATERIAL:		NORMA ASTM-D-6951-03		FORMET PAGE						
TEST RESULTS:		NORMA ASTM-D-6951-03		FORMET PAGE						
OBSERVATIONS:		NORMA ASTM-D-6951-03		FORMET PAGE						
0.10	0.10	21	20	0.95	1	0.95	292.78	257.95		
0.20	0.20	27	40	0.74	1	0.74	268.70	257.95		
0.30	0.30	30	60	0.67	1	0.67	302.36	31.66		
0.40	0.40	6	30	5.00	1	5.00	31.66	34.63		
0.50	0.50	9	70	4.44	1	4.44	363.12	363.12		
0.60	0.60	9	110	4.44	1	4.44	363.12	363.12		
0.70	0.70	15	40	2.67	1	2.67	64.01	64.01		
0.80	0.80	17	80	2.35	1	2.35	73.64	68.82		
0.90	0.90	16	120	2.50	1	2.50	68.80	68.80		
1.00	1.00									
1.10	1.10	19	50	2.63	1	2.63	64.96	64.96		
1.20	1.20	16	100	3.13	1	3.13	53.98	52.48		
1.30	1.30	12	150	4.17	1	4.17	38.83	38.83		
1.40	1.40	6	50	8.33	1	8.33	17.86	17.86		
1.50	1.50	6	100	8.33	1	8.33	17.86	17.86		
1.60	1.60	6	150	8.33	1	8.33	17.86	17.86		
1.70	1.70	4	40	10.00	1	10.00	14.56	16.76		
1.80	1.80	6	50	8.33	1	8.33	17.86	17.86		
1.90	1.90	6	100	8.33	1	8.33	17.86	17.86		
2.00	2.00	9	50	5.56	1	5.56	26.13	24.71		
2.10	2.10	9	100	5.56	1	5.56	26.13	24.71		
2.20	2.20	12	200	8.33	1	8.33	17.86	17.86		

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01						
CLIENTE / CLIENT:		NORMA ASTM-D-6951-03		FORMET PAGE						
PROYECTO / PROJECT:		NORMA ASTM-D-6951-03		FORMET PAGE						
UBICACION / LOCATION:		NORMA ASTM-D-6951-03		FORMET PAGE						
PROFESIONISTA:		NORMA ASTM-D-6951-03		FORMET PAGE						
WATER TABLE:		NORMA ASTM-D-6951-03		FORMET PAGE						
RECORD FIELD:		NORMA ASTM-D-6951-03		FORMET PAGE						
VISUAL DESCRIPTION OF THE MATERIAL:		NORMA ASTM-D-6951-03		FORMET PAGE						
TEST RESULTS:		NORMA ASTM-D-6951-03		FORMET PAGE						
OBSERVATIONS:		NORMA ASTM-D-6951-03		FORMET PAGE						
0.10	0.10	31	20	0.85	1	0.85	313.87	218.52		
0.20	0.20	15	40	1.33	1	1.33	138.11	202.79		
0.30	0.30	21	60	0.95	1	0.95	202.79	202.79		
0.40	0.40	12	40	3.33	1	3.33	49.85	48.31		
0.50	0.50	11	80	3.64	1	3.64	45.22	48.31		
0.60	0.60	12	120	3.33	1	3.33	49.85	49.85		
0.70	0.70	15	40	2.67	1	2.67	64.01	64.01		
0.80	0.80	17	80	2.35	1	2.35	73.64	67.53		
0.90	0.90	19	130	2.63	1	2.63	64.96	64.96		
1.00	1.00									
1.10	1.10	17	40	2.35	1	2.35	73.64	73.64		
1.20	1.20	18	80	2.22	1	2.22	79.51	76.23		
1.30	1.30	22	130	2.27	1	2.27	76.55	76.55		
1.40	1.40									
1.50	1.50	19	50	2.63	1	2.63	64.96	64.96		
1.60	1.60	22	100	2.27	1	2.27	76.55	68.83		
1.70	1.70	19	150	2.63	1	2.63	64.96	64.96		
1.80	1.80									
1.90	1.90	5	40	8.00	1	8.00	18.70	18.70		
2.00	2.00	6	50	8.33	1	8.33	17.86	18.14		
2.10	2.10	6	140	50	8.33	1	17.86	17.86		
2.20	2.20									

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01			
CLIENTE / CLIENT: KATAMBA & Engineers International		NORMA ASTM-D-4951-03		PROJECT / PROYECTO: Preparatory Study of the Urban 7-11 and 111 Road Paving Project			
UBICACION / LOCATION: Municipality of Chiminá 7-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		DCP N°: 61					
PROFESIONISTA: 28+100		TEST DATA		DATE OF CREATION OF TEST: 10/09/2014			
WATER TABLE: not applicable		WEIGHT HAMMER: 8 Kg.		LABORATORY MANAGER			
COORDINATES: X: 62°54'40.10" W Y: 7°28'49.00" S		TEST RESULTS		LABORATORY MANAGER			
RECORD FIELD		TEST RESULTS		LABORATORY MANAGER			
DEPTH (m)	DESCRIPTION OF THE MATERIAL	Cumulative penetration (mm) D	Penetration between readings (mm) C	Factor Correction (mm) E	DCP Index (mm/Pushes) G	AVERAGE CBR %	observations
0.00	Filled with Granular Base Layer	39	30	0.77	1	257.98	
0.00		23	20	0.87	1	224.53	239.20
0.00		24	20	0.83	1	233.50	
0.30		9	40	4.44	1	4.44	30.12
0.30	Clay, in-situ condition firm, dense consistency, dry and reddish brown with reddish patinas.	9	40	4.44	1	4.44	30.12
0.30		11	40	3.64	1	3.64	45.22
0.30		12	40	3.33	1	3.33	49.85
0.30		15	50	3.33	1	3.33	49.85
0.30		16	50	3.73	1	3.73	53.98
0.30		17	50	7.14	1	7.14	21.23
0.30		7	100	7.14	1	7.14	21.23
0.30		7	150	7.14	1	7.14	21.23
0.30		6	50	8.33	1	8.33	17.86
0.30		6	100	8.33	1	8.33	17.86
0.30		6	150	8.33	1	8.33	17.86
0.30		2	50	25.00	1	25.00	5.22
0.30		4	150	25.00	1	25.00	5.22
0.30		4	250	25.00	1	25.00	5.22
3.00		5	280	100.00	1	20.00	6.70
OBSERVATIONS: The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.		LABORATORY MANAGER		LABORATORY MANAGER			

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01			
CLIENTE / CLIENT: KATAMBA & Engineers International		NORMA ASTM-D-4951-03		PROJECT / PROYECTO: Preparatory Study of the Urban 7-11 and 111 Road Paving Project			
UBICACION / LOCATION: Municipality of Chiminá 7-11, 2° Section, Veraguas Province, Northern Region of Santa Cruz de la Sierra City		DCP N°: 62					
PROFESIONISTA: 29+600		TEST DATA		DATE OF CREATION OF TEST: 10/09/2014			
WATER TABLE: 2.70 m.		WEIGHT HAMMER: 8 Kg.		LABORATORY MANAGER			
COORDINATES: X: 62°54'44.60" W Y: 7°29'04.70" S		TEST RESULTS		LABORATORY MANAGER			
RECORD FIELD		TEST RESULTS		LABORATORY MANAGER			
DEPTH (m)	DESCRIPTION OF THE MATERIAL	Cumulative penetration (mm) D	Penetration between readings (mm) C	Factor Correction (mm) E	DCP Index (mm/Pushes) G	AVERAGE CBR %	observations
0.00	Filled with Granular Base Layer	21	20	0.95	1	0.95	202.79
0.00		27	60	0.74	1	0.74	269.70
0.00		6	30	5.00	1	5.00	31.66
0.00	Clay, in-situ condition firm, medium bedded, dry and dark brown with reddish patinas.	6	30	5.00	1	5.00	31.66
0.00		5	50	6.00	1	6.00	25.81
0.00		4	50	12.50	1	12.50	11.34
0.00		3	100	16.67	1	16.67	8.22
0.00		2	150	25.00	1	25.00	5.22
0.00		3	50	16.67	1	16.67	8.22
0.00		4	100	12.50	1	12.50	11.34
0.00		4	150	12.50	1	12.50	11.34
0.00		6	80	13.33	1	13.33	10.55
0.00		10	180	10.00	1	10.00	14.56
0.00		12	280	8.33	1	8.33	17.86
0.00		5	80	16.00	1	16.00	8.60
0.00		10	180	10.00	1	10.00	14.56
0.00		10	280	10.00	1	10.00	14.56
0.00		3	80	26.67	1	26.67	4.86
0.00		4	180	25.00	1	25.00	5.22
0.00		5	280	100.00	1	20.00	6.70
OBSERVATIONS: The presence of the Water Table at a depth of 2.70 m was evident, until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey date.		LABORATORY MANAGER		LABORATORY MANAGER			

K.M.T. (m)		30+100		172920.40°N		62°54'48.70"O		WEIGHT HAMMER: 8 Kg.	
WATER TABLE:		not Applicable		TEST RESULTS		TEST RESULTS		WEIGHT HAMMER: 8 Kg.	
4	1.00	0.05	30	250	1	2.50	68.80	68.80	
3	1.00	0.05	30	130	1	1.30	142.98		
2	1.00	0.05	30	130	1	1.30	142.98		
1	1.00	0.05	40	687	1	6.87	22.94		
0	1.00	0.05	40	4.00	1	4.00	40.84	36.27	
0	1.00	0.05	40	3.64	1	3.64	45.22		
0	1.00	0.05	50	8.33	1	8.33	17.86		
0	1.00	0.05	100	6.25	1	6.25	26.66	20.13	
0	1.00	0.05	150	8.33	1	8.33	17.86		
0	1.00	0.05	50	8.33	1	8.33	17.86		
0	1.00	0.05	150	6.67	1	6.67	22.94	18.00	
0	1.00	0.05	250	9.09	1	9.09	16.21		
0	1.00	0.05	100	10.00	1	10.00	14.56		
0	1.00	0.05	200	9.09	1	9.09	16.21	16.21	
0	1.00	0.05	300	8.33	1	8.33	17.86		
0	1.00	0.05	70	17.50	1	17.50	7.78		
0	1.00	0.05	130	7.69	1	7.69	19.54	20.85	
0	1.00	0.05	270	4.55	1	4.55	35.22		
<b>OBSERVATIONS:</b>									
<p>The presence of the Water Table at a depth of 2.30 m was evident, until the end of Geotechnical Study. For the study is considered the month 10/01 level of survey dome.</p> <p>As: Number of blows between readings          B<sub>1</sub>: Penetration measurement after each series of blows          D<sub>1</sub>: Note G (between A) blow (between B) between readings          E: Note D (between A) blow (between B) between readings          F: Note D (between A) blow (between B) between readings          G: Correlation between CBR and DCP index.</p>									
DATE OF CREATION OF TEST:		11/09/2014		DATE OF CREATION OF TEST:		11/09/2014		LABORATORY MANAGER	

K.M.T. (m)		30+595		1729236.10°N		62°54'43.10"O		WEIGHT HAMMER: 8 Kg.	
WATER TABLE:		not Applicable		TEST RESULTS		TEST RESULTS		WEIGHT HAMMER: 8 Kg.	
4	1.00	0.05	20	4.00	1	4.00	40.84		
3	1.00	0.05	40	2.22	1	2.22	78.51	75.83	
2	1.00	0.05	20	1.67	1	1.67	108.39		
1	1.00	0.05	50	12.50	1	12.50	11.34		
0	1.00	0.05	4	100	50	12.50	12.50	11.34	12.42
0	1.00	0.05	5	150	50	10.00	10.00	14.56	
0	1.00	0.05	3	50	50	16.67	16.67	8.22	
0	1.00	0.05	5	100	50	10.00	10.00	14.56	12.45
0	1.00	0.05	5	150	50	10.00	10.00	14.56	
0	1.00	0.05	10	100	100	10.00	10.00	14.56	15.11
0	1.00	0.05	20	200	100	10.00	10.00	14.56	
0	1.00	0.05	11	300	100	9.09	9.09	16.21	
0	1.00	0.05	6	60	60	10.00	10.00	14.56	
0	1.00	0.05	9	160	100	11.11	11.11	12.94	13.48
0	1.00	0.05	9	260	100	11.11	11.11	12.94	
0	1.00	0.05	5	100	100	20.00	20.00	6.70	7.21
0	1.00	0.05	5	200	100	20.00	20.00	6.70	
0	1.00	0.05	6	300	100	16.67	16.67	8.22	
<b>OBSERVATIONS:</b>									
<p>The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 10/01 level survey dome. Presence of Water hanging 1.50 m to 2.40 m.</p> <p>As: Number of blows between readings          B<sub>1</sub>: Penetration measurement after each series of blows          D<sub>1</sub>: Note G (between A) blow (between B) between readings          E: Note D (between A) blow (between B) between readings          F: Note D (between A) blow (between B) between readings          G: Correlation between CBR and DCP index.</p>									
DATE OF CREATION OF TEST:		11/09/2014		DATE OF CREATION OF TEST:		11/09/2014		LABORATORY MANAGER	

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV: 00 Date: 20/08/2014 RP 00 Page: 01 de 01					
CLIENTE / Client: KATAMBA & Engineers International		NORMA ASTM-D-6951-03		PROJECT: Preparatory Study of the Urban 7-11 and 111 Road Paving Project					
UBICACION / Location: Municipality of Chama 7-11, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City		DCP N°: 65		DATE: 20/08/2014					
PROFESIONISTA: 314-090		X Coordinate: 1729151.807°S		WEIGHT HAMMER: 8 Kg.					
WATER TABLE: not Applicable		Y Coordinate: 62°54'57.20"O		TEST RESULTS:					
RECORD FIELD		TEST RESULTS		WEIGHT HAMMER: 8 Kg.					
DEPTH (m)	NO. OF TESTS	Cumulative penetration (mm) G	Penetration between Readings (mm) C	Factor Correction (mm) D	Factor Correction (mm) E	DCP Index (mm / Pounds) F	CBR % G	AVERAGE CBR %	observations
VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:	
0.10	7	20	2.86	1	2.86	59.25	73.79		(For the first item) Due to the characteristics of this material, the average CBR values are greater than 100%, on this occasion, the test was not included in the report because the test was conducted on an isolated area. Average CBR of 73.79 was adopted.
0.10	18	40	2.00	1.11	1.11	170.63			
0.40	17	50	50	2.84	1	2.84	57.35		
0.40	15	100	50	3.33	1	3.33	40.85		
0.40	12	150	50	4.17	1	4.17	30.83		
0.80	3	50	50	16.67	1	16.67	8.22		
0.80	3	100	50	16.67	1	16.67	8.22	9.26	
0.80	4	150	50	12.50	1	12.50	11.34		
1.70	5	100	100	20.00	1	20.00	6.70		
1.70	6	200	100	16.67	1	16.67	8.22	7.71	
2.20	6	300	100	16.67	1	16.67	8.22		
2.20	5	40	60	12.00	1	12.00	11.87		
2.20	8	160	100	12.50	1	12.50	11.34	11.52	
2.20	8	260	100	12.50	1	12.50	11.34		
2.70	9	50	50	5.56	1	5.56	26.13		
2.70	13	100	50	3.85	1	3.85	42.47	37.69	
3.00	13	150	50	3.85	1	3.85	42.47		

**OBSERVATIONS:**  
 The presence of the Water Table was not considered until the month 0/00 level survey date.

A= Number of tests between readings  
 B= Penetration measurement after seven series of blows  
 C= Net C between A and B (blow on markings)  
 D= Net C between A and B (blow on markings)  
 E= Net C between A and B (blow on markings)  
 F= Net C between A and B (blow on markings)  
 G= Correction between CBR and DCP index

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV: 00 Date: 20/08/2014 RP 00 Page: 01 de 01					
CLIENTE / Client: KATAMBA & Engineers International		NORMA ASTM-D-6951-03		PROJECT: Preparatory Study of the Urban 7-11 and 111 Road Paving Project					
UBICACION / Location: Municipality of Chama 7-11, 2° Section, Varadero Province, Northern Region of Santa Cruz de la Sierra City		DCP N°: 66		DATE: 20/08/2014					
PROFESIONISTA: 314-585		X Coordinate: 1723072.307°S		WEIGHT HAMMER: 8 Kg.					
WATER TABLE: not Applicable		Y Coordinate: 62°55'01.40"O		TEST RESULTS:					
RECORD FIELD		TEST RESULTS		WEIGHT HAMMER: 8 Kg.					
DEPTH (m)	NO. OF TESTS	Cumulative penetration (mm) G	Penetration between Readings (mm) C	Factor Correction (mm) D	Factor Correction (mm) E	DCP Index (mm / Pounds) F	CBR % G	AVERAGE CBR %	observations
VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:		VISUAL DESCRIPTION OF THE MATERIAL:	
0.10	20	20	20	1.00	1	1.00	192.00		(For the first item) Due to the characteristics of this material, the average CBR values are greater than 100%, on this occasion, the test was not included in the report because the test was conducted on an isolated area. Average CBR of 202.84 was adopted.
0.10	23	40	20	0.87	1	0.87	224.53	202.84	
0.10	20	60	20	1.00	1	1.00	192.00		
0.40	7	50	50	7.14	1	7.14	21.23		
0.40	10	100	50	5.00	1	5.00	31.66	30.57	
0.40	12	150	50	4.17	1	4.17	38.83		
0.80	10	100	100	10.00	1	10.00	14.56		
0.80	11	200	100	9.09	1	9.09	16.21	15.86	
0.80	11	300	100	9.09	1	9.09	16.21		
1.80	6	50	50	8.33	1	8.33	17.86		
1.80	9	150	100	11.11	1	11.11	12.94	14.56	
1.80	9	250	100	11.11	1	11.11	12.94		
2.40	3	80	80	26.67	1	26.67	4.86		
2.40	5	180	100	20.00	1	20.00	6.70	6.99	
2.40	6	280	100	16.67	1	16.67	8.22		

**OBSERVATIONS:**  
 The presence of the Water Table was not considered until the month 0/00 level survey date.

A= Number of tests between readings  
 B= Penetration measurement after seven series of blows  
 C= Net C between A and B (blow on markings)  
 D= Net C between A and B (blow on markings)  
 E= Net C between A and B (blow on markings)  
 F= Net C between A and B (blow on markings)  
 G= Correction between CBR and DCP index

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01				
CLIENTE / CLIENT:		PROYECTO / PROJECT:		UBICACION / LOCATION:				
KATAMBA & Engineers International		Preparatory Study of the Camino 1-1 and 11 Road Paving Project		Municipality of Chimalá 1-11, 2° Section, Verme Province, Northern Region of Santa Cruz de la Sierra City				
32-480		1730123.10°S		62°58'05.40°W				
not Applicable		WEIGHT HAMMER:		8 Kg.				
TEST DATA		TEST RESULTS		OBSERVATIONS				
DEPTH (m)	COEFFICIENT OF VARIATION (%)	Cumulative penetration (mm) D	Penetration between Readings C	Factor E	Factor F	Factor G	AVERAGE CBR %	observations
0.10	0.12	30	2.00	1	2.00	86.34	97.22	
0.20	0.12	60	1.88	1	1.88	94.96		
0.30	0.12	90	1.67	1	1.67	108.35		
0.40	0.12	120	2.50	1	2.50	68.80		
0.50	0.12	150	2.22	1	2.22	76.51		
0.60	0.12	180	2.22	1	2.22	76.51		
0.70	0.12	210	2.22	1	2.22	76.51		
0.80	0.12	240	2.22	1	2.22	76.51		
0.90	0.12	270	2.22	1	2.22	76.51		
1.00	0.12	300	2.22	1	2.22	76.51		
1.10	0.12	330	2.22	1	2.22	76.51		
1.20	0.12	360	2.22	1	2.22	76.51		
1.30	0.12	390	2.22	1	2.22	76.51		
1.40	0.12	420	2.22	1	2.22	76.51		
1.50	0.12	450	2.22	1	2.22	76.51		
1.60	0.12	480	2.22	1	2.22	76.51		
1.70	0.12	510	2.22	1	2.22	76.51		
1.80	0.12	540	2.22	1	2.22	76.51		
1.90	0.12	570	2.22	1	2.22	76.51		
2.00	0.12	600	2.22	1	2.22	76.51		
2.10	0.12	630	2.22	1	2.22	76.51		
2.20	0.12	660	2.22	1	2.22	76.51		
2.30	0.12	690	2.22	1	2.22	76.51		
2.40	0.12	720	2.22	1	2.22	76.51		
2.50	0.12	750	2.22	1	2.22	76.51		
2.60	0.12	780	2.22	1	2.22	76.51		
2.70	0.12	810	2.22	1	2.22	76.51		
2.80	0.12	840	2.22	1	2.22	76.51		
2.90	0.12	870	2.22	1	2.22	76.51		
3.00	0.12	900	2.22	1	2.22	76.51		

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV. 00 2008/2014 RP 00 01 de 01				
CLIENTE / CLIENT:		PROYECTO / PROJECT:		UBICACION / LOCATION:				
KATAMBA & Engineers International		Preparatory Study of the Camino 1-1 and 11 Road Paving Project		Municipality of Chimalá 1-11, 2° Section, Verme Province, Northern Region of Santa Cruz de la Sierra City				
32-490		1730138.70°S		62°55'10.80°W				
not Applicable		WEIGHT HAMMER:		8 Kg.				
TEST DATA		TEST RESULTS		OBSERVATIONS				
DEPTH (m)	COEFFICIENT OF VARIATION (%)	Cumulative penetration (mm) D	Penetration between Readings C	Factor E	Factor F	Factor G	AVERAGE CBR %	observations
0.10	0.12	30	1.00	1	1.00	192.00	192.00	
0.20	0.12	60	1.00	1	1.00	192.00	192.00	
0.30	0.12	90	1.00	1	1.00	192.00	192.00	
0.40	0.12	120	3.75	1	3.75	43.69	67.87	
0.50	0.12	150	1.88	1	1.88	94.96		
0.60	0.12	180	2.63	1	2.63	64.96		
0.70	0.12	210	2.63	1	2.63	64.96		
0.80	0.12	240	2.63	1	2.63	64.96		
0.90	0.12	270	2.63	1	2.63	64.96		
1.00	0.12	300	2.63	1	2.63	64.96		
1.10	0.12	330	2.63	1	2.63	64.96		
1.20	0.12	360	2.63	1	2.63	64.96		
1.30	0.12	390	2.63	1	2.63	64.96		
1.40	0.12	420	2.63	1	2.63	64.96		
1.50	0.12	450	2.63	1	2.63	64.96		
1.60	0.12	480	2.63	1	2.63	64.96		
1.70	0.12	510	2.63	1	2.63	64.96		
1.80	0.12	540	2.63	1	2.63	64.96		
1.90	0.12	570	2.63	1	2.63	64.96		
2.00	0.12	600	2.63	1	2.63	64.96		
2.10	0.12	630	2.63	1	2.63	64.96		
2.20	0.12	660	2.63	1	2.63	64.96		
2.30	0.12	690	2.63	1	2.63	64.96		
2.40	0.12	720	2.63	1	2.63	64.96		
2.50	0.12	750	2.63	1	2.63	64.96		
2.60	0.12	780	2.63	1	2.63	64.96		
2.70	0.12	810	2.63	1	2.63	64.96		
2.80	0.12	840	2.63	1	2.63	64.96		
2.90	0.12	870	2.63	1	2.63	64.96		
3.00	0.12	900	2.63	1	2.63	64.96		








CAEM ISO		DYNAMIC PENETRATION TESTING (DCP)		REV: 00 2009/2014 RP 00 REVISIT PAGE 01 de 01		
CLIENT / Client: PROYECTO / Project: UBICACION / Location:		KUTAMBA & Engineers International Preparatory Study of the Highway 7 - Road 111 Road Boring Project Municipality of Chitima 1 - H-1, 2 - Xetam, Yuma Province, Northern Region of Santa Cruz de Sierra City		NORMA ASTM-D-4951-03		
PROFESIONISTA / Professional: 35+100		COORDINADAS / Coordinates: X Coordinate: 173189487.8 Y Coordinate: 6275827.2670		DERECHO / Right: 8 Kg.		
WATER TABLE: not applicable		WEIGHT HAMMER: 8 Kg.				
<b>TEST DATA</b>						
<b>TEST RESULTS</b>						
DEPTH (m)	NO. OF BLOWS	CUMULATIVE PENETRATION (mm)	AV. PENETRATION (mm)	DCP INDEX (mm/Blow)	AV. CBR %	OBSERVATIONS
0.15	7	31	30	4.29	37.62	
	9	41	33	3.33	48.85	
	19	100	40	2.11	53.41	
0.30	20	40	40	2.00	86.34	
	25	60	40	1.60	113.42	
	29	120	40	1.38	133.65	
0.45	5	40	40	8.00	18.70	
	7	60	40	5.71	27.26	25.87
	8	120	40	5.00	31.66	
1.40	4	50	50	12.50	11.34	
	5	100	50	10.00	14.56	14.59
	6	150	50	8.33	17.86	
2.20	5	50	50	10.00	14.56	
	5	100	50	10.00	14.56	15.66
	6	150	50	8.33	17.86	
2.70	5	50	50	10.00	14.56	
	6	100	50	8.33	17.86	16.76
3.00	6	150	50	8.33	17.86	
<b>OBSERVATIONS</b>						
<p>Number of blows between readings</p> <p>Penetration measured after seven series of blows</p> <p>Notes: A - Normal Penetration Test (ASTM D-4951)</p> <p>Note C - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note D - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note E - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note F - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note G - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note H - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note I - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note J - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note K - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note L - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note M - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note N - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note O - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note P - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note Q - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note R - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note S - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note T - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note U - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note V - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note W - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note X - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note Y - Dynamic Penetration Test (ASTM D-4951)</p> <p>Note Z - Dynamic Penetration Test (ASTM D-4951)</p>						
DATE OF CREATION OF TEST: 19/09/2014		LABORATORY MANAGER: LABORATORY MANAGER				
CLOSING DATE OF TEST: 19/09/2014						
<p>The presence of the Water Table was not indicated until the end of Geotechnical Study. For the study is considered the month 0.00 level of survey done.</p>						

DCP試驗結果 (兩期)

CAEM ISO Client: KACMIRA & Engineers International Project: Preparatory Study for the Highway Alignment L- II and III Location: Municipality of Okanosa One, 2nd Section of the Province of Okanosa, Santa Cruz Department		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 BY: EDC/PS: 002-14 PAGE: 02 de 35			
CLIENT / Cliente: KACMIRA & Ingenieros Internacionales PROYECTO / Project: Preparatory Study for the Highway Alignment L- II and III UBICACIÓN / Location: Municipality of Okanosa One, 2nd Section of the Province of Okanosa, Santa Cruz Department		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 BY: EDC/PS: 002-14 PAGE: 02 de 35			
PROGRESSIVE: 2 + 020		COORDINATE: 17°14'28.17"S 62°54'18.12"W		SIDE: Not Applicable		TYPE OF MATERIAL: Not Applicable			
WATER TABLE: 1.60 mts.		COORDINATE: 17°14'28.17"S 62°54'18.12"W		TYPE OF MATERIAL: Not Applicable		WEIGHT OF HAMMER: 8 Kg.			
REGISTERS FIELD		TEST DATA		TEST RESULTS		OBSERVATIONS			
SL. No.	DEPTH (m)	Number of Blows (A)	Penetration (mm) (B)	Penetration (mm) (C)	Penetration (mm) (D)	DCP Index (mm) (E)	CHRS (%) (F)	AVRAGE CBR (%) (G)	Observation
1	0.00	12	30	30	2.50	2.50	88.80	86.26	Due to characteristics of these soils (Bancos) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted in a homogeneous mass of stone. Adapt CBR = 86.26%
2	0.30	15	60	30	2.00	2.00	88.34		
3	0.60	17	90	30	1.76	1.76	101.63		
4	0.90	12	30	30	2.50	2.50	89.80		
5	1.20	14	60	30	2.14	2.14	81.77		
6	1.50	15	100	40	2.67	2.67	64.01		
7	1.80	6	40	40	6.67	6.67	22.94		
8	2.10	7	90	50	7.14	7.14	21.23		
9	2.40	7	140	50	7.14	7.14	21.23		
10	2.70	5	50	50	10.00	10.00	14.56		
11	3.00	6	100	50	8.33	8.33	17.86		
12	3.30	6	150	50	8.33	8.33	17.86		
13	3.60	5	70	70	14.00	14.00	9.99		
14	3.90	6	140	70	11.67	11.67	12.26		
15	4.20	7	210	70	10.00	10.00	14.56		
16	4.50	5	70	70	14.00	14.00	9.99		
17	4.80	6	140	70	11.67	11.67	12.26		
18	5.10	5	60	60	12.00	12.00	11.87		
19	5.40	5	120	60	12.00	12.00	11.87		
20	5.70	6	180	60	10.00	10.00	14.56		

At: Number of hammer blows between readings  
 B: Penetration accumulated after an average of three readings  
 C: Penetration accumulated after an average of five readings  
 D: New Correction Factor  
 E: Note to Table A  
 F: Note to Table E  
 G: Correction between CBR and DCP Index


DATE OF CREATION OF TEST: 11/02/2015  
 DATE OF CONCLUSION OF TEST: 11/02/2015  
 HEAD OF LABORATORY



CAEM ISO Client: KACMIRA & Engineers International Project: Preparatory Study for the Highway Alignment L- II and III Location: Municipality of Okanosa One, 2nd Section of the Province of Okanosa, Santa Cruz Department		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 BY: EDC/PS: 002-14 PAGE: 01 de 35			
CLIENT / Cliente: KACMIRA & Ingenieros Internacionales PROYECTO / Project: Preparatory Study for the Highway Alignment L- II and III UBICACIÓN / Location: Municipality of Okanosa One, 2nd Section of the Province of Okanosa, Santa Cruz Department		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 BY: EDC/PS: 002-14 PAGE: 01 de 35			
PROGRESSIVE: 1 + 020		COORDINATE: 17°14'52.27"S 62°54'18.24"W		SIDE: Not Applicable		TYPE OF MATERIAL: Not Applicable			
WATER TABLE: 0.00 mts.		COORDINATE: 17°14'52.27"S 62°54'18.24"W		SIDE: Not Applicable		WEIGHT OF HAMMER: 8 Kg.			
REGISTERS FIELD		TEST DATA		TEST RESULTS		OBSERVATIONS			
SL. No.	DEPTH (m)	Number of Blows (A)	Penetration (mm) (B)	Penetration (mm) (C)	Penetration (mm) (D)	DCP Index (mm) (E)	CHRS (%) (F)	AVRAGE CBR (%) (G)	Observation
1	0.00	12	30	30	2.50	2.50	88.80	81.84	Due to characteristics of these soils (Bancos) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted in a homogeneous mass of stone. Adapt CBR = 81.84%
2	0.30	14	60	30	2.14	2.14	84.96		
3	0.60	16	90	30	1.88	1.88	94.96		
4	0.90	11	30	30	2.75	2.75	62.41		
5	1.20	15	30	40	2.67	2.67	64.01		
6	1.50	16	110	40	2.50	2.50	68.80		
7	1.80	6	40	40	6.67	6.67	22.94		
8	2.10	7	90	50	7.14	7.14	21.23		
9	2.40	8	150	60	7.50	7.50	20.10		
10	2.70	7	60	60	8.57	8.57	17.31		
11	3.00	7	120	60	8.57	8.57	17.31		
12	3.30	8	180	60	7.50	7.50	20.10		
13	3.60	2	30	30	15.00	15.00	9.25		
14	3.90	3	70	40	20.00	20.00	6.70		
15	4.20	3	120	50	16.67	16.67	8.22		
16	4.50	3	40	40	13.33	13.33	10.55		
17	4.80	3	80	40	13.33	13.33	10.55		
18	5.10	4	130	50	12.50	12.50	11.34		
19	5.40	3	50	50	16.67	16.67	8.22		
20	5.70	4	100	50	12.50	12.50	11.34		
21	6.00	5	150	50	10.00	10.00	14.56		

At: Number of hammer blows between readings  
 B: Penetration accumulated after an average of three readings  
 C: Penetration accumulated after an average of five readings  
 D: New Correction Factor  
 E: Note to Table A  
 F: Note to Table E  
 G: Correction between CBR and DCP Index

DATE OF CREATION OF TEST: 11/02/2015  
 DATE OF CONCLUSION OF TEST: 11/02/2015  
 HEAD OF LABORATORY



CAEM ISO		DYNAMIC PENETRATION TESTING (DPT) ASTM-D-6951-03		NORMA		REV: 00			
CLIENTE / Client:		PROYECTO / Project:		UBICACIÓN / Location:		DATE: 14/02/2015			
KATAMBA & Engenieros Internacionales		Preparatory Study Paving Project Highway Obispo L - II and III		Municipalidad Obispo Oros, 2nd Section of the Province Iquitos Warras, Santa Cruz Department		REPORT: EDCDPS-002-14			
PROGRESIVA:		COORDINADA:		SIDE:		PAG: 03 de 35			
3 + 020		17°14'57.36"S		Not Applicable		DCP N°: 03			
WATER TABLE:		TYPE OF MATERIAL:		WEIGHT OF HAMMER:		00			
2.00 mts.		1.50 mts.		8 Kg.		14/02/2015			
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS		14/02/2015			
STATION	DEPTH (m)	DESCRIPTION	Number of Blows (A)	Compaction penetration (B) (mm)	Percentage of Hits (C) (%)	Number of Hammer E (F)	Penetration (G) (mm)	AVERAGE CBR %	Observations
100	0.30	Artificial fill, consisting of silty sand with no plasticity gravel, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	10	30	3.00	1	3.00	56.10	77.59
100	0.60	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	15	60	2.00	1	2.00	88.34	
100	0.70	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	8	30	3.75	1	3.75	49.69	Due to the characteristics of these soils (homogeneity, consistency, plasticity, etc.) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted on an isolated subbase stone. Adopt CBR = 77.59%.
100	1.00	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	11	90	3.00	1	2.73	62.41	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	8	40	5.00	1	5.00	31.66	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	8	80	4.00	1	5.00	31.66	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	11	120	4.00	1	3.64	45.22	
100	1.00	Limo Clay, in-situ condition weak, partially saturated soft consistency, saturated state and geological interpretation alluvial fan	5	70	14.00	1	14.00	9.99	
100	1.00	Limo Clay, in-situ condition weak, partially saturated soft consistency, saturated state and geological interpretation alluvial fan	5	140	7.00	1	14.00	9.99	11.52
100	1.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	7	210	10.00	1	10.00	14.56	
100	2.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	2	50	25.00	1	25.00	5.22	
100	2.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	3	110	20.00	1	20.00	6.70	7.06
100	2.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	4	170	15.00	1	15.00	9.25	
100	2.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	7	80	11.43	1	11.43	12.54	13.22
100	2.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	7	160	11.43	1	11.43	12.54	
100	2.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	8	240	10.00	1	10.00	14.56	
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	10	60	6.00	1	6.00	25.81	
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	12	120	6.00	1	5.00	31.66	30.70
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	13	180	6.00	1	4.62	34.62	

CAEM ISO		DYNAMIC PENETRATION TESTING (DPT) ASTM-D-6951-03		NORMA		REV: 00			
CLIENTE / Client:		PROYECTO / Project:		UBICACIÓN / Location:		DATE: 14/02/2015			
KATAMBA & Engenieros Internacionales		Preparatory Study Paving Project Highway Obispo L - II and III		Municipalidad Obispo Oros, 2nd Section of the Province Iquitos Warras, Santa Cruz Department		REPORT: EDCDPS-002-14			
PROGRESIVA:		COORDINADA:		SIDE:		PAG: 04 de 35			
4 + 000		17°18'29.90"S		Not Applicable		DCP N°: 04			
WATER TABLE:		TYPE OF MATERIAL:		WEIGHT OF HAMMER:		00			
2.00 mts.		1.50 mts.		8 Kg.		14/02/2015			
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS		14/02/2015			
STATION	DEPTH (m)	DESCRIPTION	Number of Blows (A)	Compaction penetration (B) (mm)	Percentage of Hits (C) (%)	Number of Hammer E (F)	Penetration (G) (mm)	AVERAGE CBR %	Observations
100	0.30	Artificial fill, consisting of silty sand with no plasticity gravel, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	10	30	3.00	1	3.00	56.10	77.59
100	0.60	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	15	60	2.00	1	2.00	88.34	
100	0.70	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan	8	30	3.75	1	3.75	49.69	Due to the characteristics of these soils (homogeneity, consistency, plasticity, etc.) greater than 100% on average, since that would be inconsistent data. This is because the test was conducted on an isolated subbase stone. Adopt CBR = 77.59%.
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	11	90	3.00	1	2.73	62.41	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	8	40	5.00	1	5.00	31.66	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	8	80	4.00	1	5.00	31.66	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	11	120	4.00	1	3.64	45.22	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	5	70	14.00	1	14.00	9.99	
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	5	140	7.00	1	14.00	9.99	11.52
100	1.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially saturated state and geological interpretation alluvial fan	7	210	10.00	1	10.00	14.56	
100	2.00	Limo Clay, in-situ condition weak, partially saturated soft consistency, saturated state and geological interpretation alluvial fan	2	50	25.00	1	25.00	5.22	
100	2.00	Limo Clay, in-situ condition weak, partially saturated soft consistency, saturated state and geological interpretation alluvial fan	3	110	20.00	1	20.00	6.70	7.06
100	2.00	Limo Clay, in-situ condition weak, partially saturated soft consistency, saturated state and geological interpretation alluvial fan	4	170	15.00	1	15.00	9.25	
100	2.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	7	80	11.43	1	11.43	12.54	13.22
100	2.00	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan	7	160	11.43	1	11.43	12.54	
100	2.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	8	240	10.00	1	10.00	14.56	
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	10	60	6.00	1	6.00	25.81	
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	12	120	6.00	1	5.00	31.66	30.70
100	3.00	Limo Clay, in-situ condition firm, medium consistency, saturated state and geological interpretation alluvial fan	13	180	6.00	1	4.62	34.62	

CAEM ISO  
**DYNAMIC PENETRATION TESTING (DPP)**  
 ASTM-D-6951-03

CLIENT / Client: **KAYAMIRA & Engenharia Internacional**  
 PROYECTO / Project: **Preparatory Study For the Project Highway Okonawa I - II and III**  
 UBICACIÓN / Location: **Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department**

REV: 00  
 DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 05 de 35

**NORMA**

DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 05 de 35

**DYNAMIC PENETRATION TESTING (DPP)**  
 ASTM-D-6951-03

CLIENT / Client: **KAYAMIRA & Engenharia Internacional**  
 PROYECTO / Project: **Preparatory Study For the Project Highway Okonawa I - II and III**  
 UBICACIÓN / Location: **Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department**

REV: 00  
 DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 06 de 35

**NORMA**

DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 06 de 35

**TEST DATA**

PROGRESSIVE: **6 + 000**

COORDINATE: **62°54'31"O**

WATER TABLE: **0.90 mts.**

TYPE OF MATERIAL: **Not Applicable**

WEIGHT OF HAMMER: **8 Kg.**

Elev. (m)	Elev. (ft)	DEPTH BY WIND (m)	REGISTERS FIELD		TEST RESULTS										OBSERVATIONS
			Number of Blows (A)	Complete penetration (B) (mm)	Penetration Between Readings (C) (mm)	Percentage of Hits (E) (%)	Blow Index (F) (mm/F)	CBR % (G)	AVERAGE CBR % (H)	Observations					
1.00	3.28	0.30	15	30	30	2.00	1	2.00	38.24	38.24	86.18		Due to the characteristics of these soils (heterogeneity, loose compactness and medium to dark brown geological interpretation alluvial fan)		
1.10	3.61	0.30	13	60	30	2.31	1	2.31	52.26	52.26					
1.20	3.94	0.30	16	90	30	1.88	1	1.88	94.96	94.96		Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan			
1.30	4.27	0.30	5	30	30	6.00	1	6.00	25.81	25.81	35.77				
1.40	4.60	0.30	6	60	30	5.00	1	5.00	31.66	31.66		Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan			
1.50	4.93	0.30	9	90	30	3.33	1	3.33	49.83	49.83					
1.60	5.26	0.30	2	40	40	20.00	1	20.00	6.70	6.70		Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan			
1.70	5.59	0.30	3	90	30	16.67	1	16.67	8.22	8.22	7.77				
1.80	5.92	N.F.	3	140	50	16.67	1	16.67	8.22	8.22		Arcas Limosa without plasticity condition in-situ loose, loose compactness, saturated state and geological interpretation alluvial fan			
1.90	6.25	1.20	6	80	80	13.33	1	13.33	10.93	10.93	11.88				
2.00	6.58	1.60	7	160	80	11.43	1	11.43	12.51	12.51		Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan			
2.10	6.91	2.00	4	60	60	15.00	1	15.00	9.25	9.25	12.81				
2.20	7.24	2.30	5	120	60	12.00	1	12.00	11.87	11.87		Limo Clay, weak condition to sign in-situ, soft consistency to medium saturated state and geological interpretation alluvial fan			
2.30	7.57	2.70	7	180	60	8.57	1	8.57	17.31	17.31	13.40				
2.40	7.90	3.00	6	90	90	15.00	1	15.00	9.25	9.25		Limo Clay, weak condition to sign in-situ, soft consistency to medium saturated state and geological interpretation alluvial fan			
2.50	8.23	3.40	9	180	90	10.00	1	10.00	14.58	14.58					
2.60	8.56	3.80	10	270	90	9.00	1	9.00	16.39	16.39		Limo Clay, weak condition to sign in-situ, soft consistency to medium saturated state and geological interpretation alluvial fan			
2.70	8.89	4.20	8	240	80	14.56	1	14.56	11.24	11.24					

**OBSERVATIONS:**

The presence of the water table was evident at a depth of 0.90 mts., until the end of Geotechnical Study. For the study are considered level 0.00 mts. the height of the wellhead.

DATE OF CREATION OF TEST: 04/02/2015  
 DATE OF CONCLUSION OF TEST: 04/02/2015

HEAD OF LABORATORY

CAEM ISO  
**DYNAMIC PENETRATION TESTING (DPP)**  
 ASTM-D-6951-03

CLIENT / Client: **KAYAMIRA & Engenharia Internacional**  
 PROYECTO / Project: **Preparatory Study For the Project Highway Okonawa I - II and III**  
 UBICACIÓN / Location: **Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department**

REV: 00  
 DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 05 de 35

**NORMA**

DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 05 de 35

**DYNAMIC PENETRATION TESTING (DPP)**  
 ASTM-D-6951-03

CLIENT / Client: **KAYAMIRA & Engenharia Internacional**  
 PROYECTO / Project: **Preparatory Study For the Project Highway Okonawa I - II and III**  
 UBICACIÓN / Location: **Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department**

REV: 00  
 DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 06 de 35

**NORMA**

DATE: 14/02/2015  
 REPORT: EGDCTS-002-14  
 PAGE: 06 de 35

**TEST DATA**

PROGRESSIVE: **5 + 000**

COORDINATE: **62°54'34"O**

WATER TABLE: **2.60 mts.**

TYPE OF MATERIAL: **Not Applicable**

WEIGHT OF HAMMER: **8 Kg.**

Elev. (m)	Elev. (ft)	DEPTH BY WIND (m)	REGISTERS FIELD		TEST RESULTS										OBSERVATIONS
			Number of Blows (A)	Complete penetration (B) (mm)	Penetration Between Readings (C) (mm)	Percentage of Hits (E) (%)	Blow Index (F) (mm/F)	CBR % (G)	AVERAGE CBR % (H)	Observations					
1.00	3.28	0.30	6	30	30	5.00	1	5.00	31.66	31.66	43.81	Artificial fill, consisting of silt and sand with plasticity given to the mixture of different percentages of these soils (heterogeneity, loose compactness and medium to dark brown geological interpretation alluvial fan)			
1.10	3.61	0.30	10	90	30	3.00	1	3.00	56.10	56.10					
1.20	3.94	0.30	13	60	30	2.31	1	2.31	75.26	75.26	75.44	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially dry and geological interpretation alluvial fan			
1.30	4.27	0.30	16	90	30	1.88	1	1.88	94.96	94.96					
1.40	4.60	0.30	2	30	30	15.00	1	15.00	9.25	9.25	7.58	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially dry and geological interpretation alluvial fan			
1.50	4.93	0.30	1	90	30	30.00	1	30.00	4.26	4.26	6.74				
1.60	5.26	1.40	2	40	40	20.00	1	20.00	6.70	6.70		Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan			
1.70	5.59	1.80	1	70	30	30.00	1	30.00	4.26	4.26					
1.80	5.92	2.20	2	100	30	15.00	1	15.00	9.25	9.25		Clayey silt with presence of clasts in minimum percentage related, light flimsy-silt, partially dry soft consistency, state and brownish geological interpretation alluvial fan status			
1.90	6.25	2.60	3	50	50	16.67	1	16.67	8.22	8.22	7.22				
2.00	6.58	3.00	3	150	50	16.67	1	16.67	8.22	8.22		Weak silt, soft consistency, partially dry and light brown with gray patina geological interpretation alluvial fan			
2.10	6.91	3.40	2	40	40	20.00	1	20.00	6.70	6.70	7.21				
2.20	7.24	3.80	3	130	50	16.67	1	16.67	8.22	8.22		Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state, light brown with gray patina geological interpretation alluvial fan			
2.30	7.57	4.20	1	50	50	50.00	1	50.00	2.40	2.40	2.40				
2.40	7.90	4.60	1	100	50	50.00	1	50.00	2.40	2.40		Limo Clay, weak condition in-situ in dependence of clasts in light brown with reddish brown patina, interpreting geological interpretation alluvial fan			
2.50	8.23	5.00	6	80	80	13.33	1	13.33	10.55	10.55	11.24				
2.60	8.56	5.40	5	160	60	16.00	1	16.00	8.60	8.60		Limo Clay, weak condition to sign in-situ, soft consistency to medium saturated state and geological interpretation alluvial fan			
2.70	8.89	5.80	8	240	80	14.56	1	14.56	11.24	11.24					

**OBSERVATIONS:**

The presence of the water table was evident at a depth of 2.60 mts., until the end of Geotechnical Study. For the study are considered level 0.00 mts. the height of the wellhead.

DATE OF CREATION OF TEST: 04/02/2015  
 DATE OF CONCLUSION OF TEST: 04/02/2015

HEAD OF LABORATORY

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 REPORT: EGD/CTS-002-14 PAGE: 07 de 35			
CLIENTE / Cliente: KAVAMIRA & Engenharia Internacional		PROYECTO / Project: Preparation Study Forcing Project Highway Okonawa I - II and III		UBICACIÓN / Location: Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		DPP Nº: 07			
PROGRESIVA: 7 + 020		COORDINADA: 17°17'49"S 62°54'5,88"O		SÍDE: Not Applicable		TYPE OF MATERIAL: Not Applicable			
WATER TABLE: 2.30 mts.		WEIGHT OF HAMMER: 8 Kg.		TEST RESULTS		OBSERVATIONS:			
REGISTER FIELD		VISUAL DESCRIPTION OF THE MATERIAL		TEST RESULTS		OBSERVATIONS			
TY	HT (mm)	Number of Blows (A)	Compaction preparation (mm)	Penetration (B) (mm)	Penetration of Hits (C) (mm)	Penetration of Hits (D) (mm)	Penetration of Hits (E) (mm)	AVRAGE CBR %	Observations
1	0.80	11	30	30	2.73	1	2.73	62.41	Artificial fill, consisting of dry sand with no plasticity gravel condition, compacted and medium to dark brown geological interpretation alluvial fan
2	0.30	12	60	30	2.50	1	2.50	68.80	Artificial fill, consisting of dry sand with no plasticity gravel condition, compacted and medium to dark brown geological interpretation alluvial fan
3	0.70	5	30	30	6.00	1	6.00	25.51	Limo with mixtures of very fine sand, weak condition to dry in-situ, soft consistency, partially dry and brown coloration geological interpretation alluvial fan
4	0.70	8	70	40	5.00	1	5.00	31.66	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
5	1.20	11	110	40	3.64	1	3.64	45.22	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
6	1.20	12	40	40	3.33	1	3.33	49.85	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
7	1.20	12	90	50	4.17	1	4.17	38.83	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
8	1.80	4	40	40	10.00	1	10.00	14.56	Areña Limosa without plasticity, condition loose in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan
9	1.80	4	100	60	15.00	1	15.00	9.25	Areña Limosa without plasticity, condition loose in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan
10	1.80	6	160	60	10.00	1	10.00	14.56	Areña Limosa without plasticity, condition loose in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan
11	2.30	11	250	90	8.18	1	8.18	18.24	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
12	2.30	8	80	80	10.00	1	10.00	14.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
13	N.P.	10	160	80	8.00	1	8.00	18.70	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
14	2.60	6	130	70	11.67	1	11.67	12.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
15	2.60	6	190	70	11.67	1	11.67	12.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
16	3.00	5	70	70	14.00	1	14.00	9.99	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan
17	3.00	8	140	70	8.75	1	8.75	16.51	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan
18	3.00	8	210	70	8.75	1	8.75	16.51	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan

OBSERVATIONS:  
 A- Number of hammer blows between readings  
 B- Penetration accumulated after each series of blows  
 C- Penetration accumulated after each series of blows  
 D- Near to between A and B  
 E- Near to between A and B  
 F- Near to between A and B  
 G- Combination between CBR and DCP values

CAEM ISO	DATE OF CREATION OF TEST: 11/02/2015	HEAD OF LABORATORY
CAEM ISO	DATE OF CONCLUSION OF TEST: 11/02/2015	HEAD OF LABORATORY

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00 DATE: 14/02/2015 REPORT: EGD/CTS-002-14 PAGE: 08 de 35			
CLIENTE / Cliente: KAVAMIRA & Engenharia Internacional		PROYECTO / Project: Preparation Study Forcing Project Highway Okonawa I - II and III		UBICACIÓN / Location: Municipality Okonawa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		DPP Nº: 08			
PROGRESIVA: 8 + 020		COORDINADA: 17°17'40.83"S 62°54'4.29"O		SÍDE: Not Applicable		TYPE OF MATERIAL: Not Applicable			
WATER TABLE: 1.60 mts.		WEIGHT OF HAMMER: 8 Kg.		TEST RESULTS		OBSERVATIONS:			
REGISTER FIELD		VISUAL DESCRIPTION OF THE MATERIAL		TEST RESULTS		OBSERVATIONS			
TY	HT (mm)	Number of Blows (A)	Compaction preparation (mm)	Penetration (B) (mm)	Penetration of Hits (C) (mm)	Penetration of Hits (D) (mm)	Penetration of Hits (E) (mm)	AVRAGE CBR %	Observations
1	0.80	11	30	30	2.73	1	2.73	62.41	Artificial fill, consisting of dry sand with no plasticity gravel condition, compacted and medium to dark brown geological interpretation alluvial fan
2	0.30	13	60	30	2.31	1	2.31	75.34	Artificial fill, consisting of dry sand with no plasticity gravel condition, compacted and medium to dark brown geological interpretation alluvial fan
3	0.70	15	90	30	2.00	1	2.00	83.34	Artificial fill, consisting of dry sand with no plasticity gravel condition, compacted and medium to dark brown geological interpretation alluvial fan
4	0.80	4	40	40	10.00	1	10.00	14.56	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
5	0.80	7	80	40	5.71	1	5.71	27.26	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
6	1.20	12	120	40	3.33	1	3.33	49.85	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
7	1.20	11	50	50	4.55	1	4.55	38.22	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
8	1.20	13	100	50	3.85	1	3.85	42.47	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
9	1.20	14	150	50	3.57	1	3.57	46.13	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
10	1.60	6	70	70	11.67	1	11.67	12.56	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
11	1.60	6	140	70	11.67	1	11.67	12.56	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
12	N.P.	7	210	70	10.00	1	10.00	14.56	Limo with mixtures of very fine sand, strong in-situ condition, medium consistency, partially dry and brown coloration geological interpretation alluvial fan
13	1.90	5	60	60	12.00	1	12.00	11.87	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
14	1.90	6	130	70	11.67	1	11.67	12.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
15	2.20	7	200	70	10.00	1	10.00	14.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
16	2.60	4	70	70	17.50	1	17.50	7.26	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
17	2.60	7	140	70	10.00	1	10.00	14.56	Limo Clay, in-situ condition weak, soft consistency, saturated state and geological interpretation alluvial fan
18	3.00	7	70	70	10.00	1	10.00	14.56	Limo with mixtures of very fine sand, strong in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan
19	3.00	8	150	80	10.00	1	10.00	14.56	Limo with mixtures of very fine sand, strong in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan
20	3.00	8	230	80	10.00	1	10.00	14.56	Limo with mixtures of very fine sand, strong in-situ condition, soft consistency, saturated state and geological interpretation alluvial fan

OBSERVATIONS:  
 A- Number of hammer blows between readings  
 B- Penetration accumulated after each series of blows  
 C- Penetration accumulated after each series of blows  
 D- Near to between A and B  
 E- Near to between A and B  
 F- Near to between A and B  
 G- Combination between CBR and DCP values

CAEM ISO	DATE OF CREATION OF TEST: 11/02/2015	HEAD OF LABORATORY
CAEM ISO	DATE OF CONCLUSION OF TEST: 11/02/2015	HEAD OF LABORATORY

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00	
CLIENTE / Client:		KATAMIRA & Engenieros Internacionales		PROYECTO / Project:		DATE: 14/02/2015	
UBICACIÓN / Location:		Municipalidad Obisipo Oros, 2nd Section of the Province Iquitos Warras, Santa Cruz Department		FORMA: EDCDTS-002-14		REPORT: 10.48.35	
PROGRESIVO:		9 + 020		DPP No.: 09		PAG: 09 de 35	
TEST DATA		COORDINATED:		SIDE:		Not Applicable	
WATER TABLE:		17°18'9.72"S		TYPE OF MATERIAL:		Not Applicable	
REGISTERED FIELD		62°53'53.87"O		WEIGHT OF HAMMER:		8 Kg.	
VISUAL DESCRIPTION OF THE MATERIAL:		0.00 mts.		TEST RESULTS		Observations	
TYPE	DEPTH (m)	Number of Blows (A)	Compactive penetration (B) (mm)	Penetration of Hammer (E) (mm)	Penetration of Hammer (F) (mm)	AVRAGE CIR (%)	Observations
1.00	0.00	11	30	2.73	1	62.41	
1.00	0.30	15	60	2.00	1	88.34	Due to the characteristics of the test, the CIR values are greater than 100%. This is because the test was conducted on an isolated fibrous stone. Adapt CIR = 81.90%
1.00	0.70	12	120	4.0	1	49.85	
1.00	0.00	5	30	6.00	1	25.81	
1.00	0.00	7	110	5.71	1	27.26	
1.00	1.00	8	40	5.00	1	31.66	
1.00	1.30	9	80	4.44	1	36.12	
1.00	1.60	10	120	4.00	1	40.64	
1.00	2.00	9	40	4.44	1	36.12	
1.00	2.30	10	120	4.00	1	40.64	
1.00	2.60	9	30	3.00	1	56.10	
1.00	3.00	12	60	2.50	1	68.80	
1.00	3.30	14	100	2.86	1	59.25	
1.00	3.60	10	30	2.50	1	68.80	
1.00	3.90	11	90	2.73	1	62.41	
1.00	4.20	9	30	3.00	1	56.10	
1.00	4.50	10	60	3.00	1	56.10	
1.00	4.80	10	100	4.00	1	40.64	

Number of blowers between readings  
 A: Penetration accumulated after each series of blows  
 B: Penetration accumulated after each series of blows  
 C: Penetration accumulated after each series of blows  
 D: Penetration accumulated after each series of blows  
 E: Penetration accumulated after each series of blows  
 F: Penetration accumulated after each series of blows  
 G: Penetration accumulated after each series of blows

CAEM ISO	DATE OF CREATION OF TEST: 11/02/2015	HEAD OF LABORATORY
CAEM ISO	DATE OF CONCLUSION OF TEST: 11/02/2015	HEAD OF LABORATORY

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00	
CLIENTE / Client:		KATAMIRA & Engenieros Internacionales		PROYECTO / Project:		DATE: 14/02/2015	
UBICACIÓN / Location:		Municipalidad Obisipo Oros, 2nd Section of the Province Iquitos Warras, Santa Cruz Department		FORMA: EDCDTS-002-14		REPORT: 10.48.35	
PROGRESIVO:		10 + 020		DPP No.: 10		PAG: 10 de 35	
TEST DATA		COORDINATED:		SIDE:		Not Applicable	
WATER TABLE:		17°18'42.77"S		TYPE OF MATERIAL:		Not Applicable	
REGISTERED FIELD		62°53'52.94"O		WEIGHT OF HAMMER:		8 Kg.	
VISUAL DESCRIPTION OF THE MATERIAL:		0.00 mts.		TEST RESULTS		Observations	
TYPE	DEPTH (m)	Number of Blows (A)	Compactive penetration (B) (mm)	Penetration of Hammer (E) (mm)	Penetration of Hammer (F) (mm)	AVRAGE CIR (%)	Observations
1.00	0.00	13	30	2.31	1	73.20	
1.00	0.30	15	60	2.00	1	88.34	
1.00	0.60	14	90	2.14	1	81.77	
1.00	0.90	5	30	6.00	1	25.81	
1.00	1.20	7	70	5.71	1	27.26	
1.00	1.50	8	110	5.00	1	31.66	
1.00	1.80	12	30	2.50	1	68.80	
1.00	2.10	15	70	2.67	1	64.01	
1.00	2.40	15	110	2.67	1	64.01	
1.00	2.70	8	40	5.00	1	31.66	
1.00	3.00	8	80	4.00	1	40.64	
1.00	3.30	10	120	4.00	1	40.64	
1.00	3.60	10	30	3.00	1	56.10	
1.00	3.90	12	60	2.50	1	68.80	
1.00	4.20	14	90	2.14	1	81.77	
1.00	4.50	12	30	2.50	1	68.80	
1.00	4.80	12	60	2.50	1	68.80	
1.00	5.10	14	90	2.14	1	81.77	
1.00	5.40	14	30	2.14	1	81.77	
1.00	5.70	15	70	2.67	1	64.01	
1.00	6.00	15	110	2.67	1	64.01	


Number of blowers between readings  
 A: Penetration accumulated after each series of blows  
 B: Penetration accumulated after each series of blows  
 C: Penetration accumulated after each series of blows  
 D: Penetration accumulated after each series of blows  
 E: Penetration accumulated after each series of blows  
 F: Penetration accumulated after each series of blows  
 G: Penetration accumulated after each series of blows


CAEM ISO	DATE OF CREATION OF TEST: 11/02/2015	HEAD OF LABORATORY
CAEM ISO	DATE OF CONCLUSION OF TEST: 11/02/2015	HEAD OF LABORATORY

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00					
CLIENTE / Client: KATAMIRA & Engenieros Internacionales		PROYECTO / Project: Preparatory Study Paving Project Highway Obanosa I - II and III		UBICACIÓN / Location: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		DATE: 14/02/2015					
PROYECTO / Project: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		UBICACIÓN / Location:		DPP No.: 11		REPORT: EGDPCS-002-14					
PROYECTO / Project: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		UBICACIÓN / Location:		DPP No.: 11		PAGE: 11 de 35					
<b>TEST DATA</b>											
<b>PROGRESSIVE:</b> 11 + 000		<b>COORDINATED:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINATE X:</b> 17°19'14.13"S		<b>WEIGHT OF HAMMER:</b> 8 Kg.		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINATE Y:</b> 62°53'51.94"O		<b>WEIGHT OF HAMMER:</b> 8 Kg.		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>REGISTER FIELD</b>											
DEPTH (m)	TYPE OF SOIL	Visual Description of the Material	Number of Blows (A)	Compaction (B) (%)	Penetration (C) (mm)	Preparation of Hils (D) (mm)	Preparation of Hils (E) (mm)	Preparation of Hils (F) (mm)	Preparation of Hils (G) (mm)	AVERAGE CBR (%)	Observations
0.00	Artificial fill, consisting of clay and with no plasticity given, loose, loose to medium brown color, compactness and geological interpretation alluvial-fan		8	30	30	3.75	1	3.75	49.89	49.89	
0.30			8	60	30	3.75	1	3.75	49.89	49.89	
0.60			10	90	30	3.00	1	3.00	56.10		
0.90			9	40	40	4.44	1	4.44	36.12		
1.20			10	80	40	4.00	1	4.00	40.64	39.14	
1.50			10	120	40	4.00	1	4.00	40.64		
1.80			10	50	50	5.00	1	5.00	31.66	34.05	
2.10			10	100	50	5.00	1	5.00	31.66		
2.40			12	150	50	4.17	1	4.17	38.83		
2.70			12	60	60	5.00	1	5.00	31.66		
3.00			12	120	60	5.00	1	5.00	31.66	33.64	
3.30			14	180	60	4.29	1	4.29	37.62		
3.60			14	50	50	3.57	1	3.57	46.14		
3.90			14	100	50	3.57	1	3.57	46.14	48.63	
4.20			16	150	50	3.13	1	3.13	53.59		
4.50			4	70	70	17.50	1	17.50	7.78		
4.80			5	140	70	14.00	1	14.00	9.99	10.78	
5.10			7	210	70	10.00	1	10.00	14.56		
5.40			3	60	60	20.00	1	20.00	6.70		
5.70			4	120	60	15.00	1	15.00	9.25	9.27	
6.00			5	180	60	12.00	1	12.00	11.87		
<b>OBSERVATIONS:</b>											
The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 0.00 level survey done.											
A= Number of hammer blows between readings B= Penetration accumulated after each series of blows C= Penetration accumulated after each series of blows D= Soil Consistency E= Soil Consistency F= Soil Consistency G= Comparison between CBR and DCP rate											
CAEM ISO		DATE OF CREATION OF TEST: 19/12/2014		HEAD OF LABORATORY:							
CAEM ISO		DATE OF CONCLUSION OF TEST: 19/12/2014		HEAD OF LABORATORY:							

CAEM ISO		DYNAMIC PENETRATION TESTING (DPP) ASTM-D-6951-03		NORMA		REV: 00					
CLIENTE / Client: KATAMIRA & Engenieros Internacionales		PROYECTO / Project: Preparatory Study Paving Project Highway Obanosa I - II and III		UBICACIÓN / Location: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		DATE: 14/02/2015					
PROYECTO / Project: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		UBICACIÓN / Location:		DPP No.: 12		REPORT: EGDPCS-002-14					
PROYECTO / Project: Municipality Obanosa One, 2nd Section of the Province Iguaçu, Paraná, Santa Cruz Department		UBICACIÓN / Location:		DPP No.: 12		PAGE: 12 de 35					
<b>TEST DATA</b>											
<b>PROGRESSIVE:</b> 12 + 000		<b>COORDINATED:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINATE X:</b> 17°19'46.64"S		<b>WEIGHT OF HAMMER:</b> 8 Kg.		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINATE Y:</b> 62°53'49.99"O		<b>WEIGHT OF HAMMER:</b> 8 Kg.		<b>TYPE OF MATERIAL:</b> Not Applicable					
<b>REGISTER FIELD</b>											
DEPTH (m)	TYPE OF SOIL	Visual Description of the Material	Number of Blows (A)	Compaction (B) (%)	Penetration (C) (mm)	Preparation of Hils (D) (mm)	Preparation of Hils (E) (mm)	Preparation of Hils (F) (mm)	Preparation of Hils (G) (mm)	AVERAGE CBR (%)	Observations
0.00	Artificial fill, consisting of clay and with no plasticity given, loose, loose to medium brown color, compactness and geological interpretation alluvial-fan		20	30	30	1.50	1	1.50	131.92	138.04	(For the first point) Because of the shape of the blow (the compact) disengaged CBR values greater than 100% on average, since that would be inconsistent with the results of the assay was performed on an isolated heavier state.
0.30			22	60	30	1.36	1	1.36	135.66		
0.60			25	90	30	1.20	1	1.20	156.54		
0.90			8	40	40	5.00	1	5.00	31.66		
1.20			13	80	40	3.08	1	3.08	54.83	48.48	
1.50			14	120	40	2.86	1	2.86	59.25		
1.80			10	40	40	4.00	1	4.00	40.64		
2.10			11	80	40	3.64	1	3.64	43.22	43.70	
2.40			11	120	40	3.64	1	3.64	43.22		
2.70			12	30	30	2.50	1	2.50	68.80		
3.00			15	60	30	2.00	1	2.00	98.32	76.93	
3.30			17	100	40	2.35	1	2.35	73.64		
3.60			22	30	30	1.36	1	1.36	135.66		
3.90			26	60	30	1.15	1	1.15	163.57	63.74	(For points 5, 6 and 7), Due to uncertainty of disengaged CBR values greater than 100% on average, since that would be inconsistent with the results of the assay was performed on an isolated heavier state.
4.20			30	90	30	1.00	1	1.00	192.00		
4.50			20	30	30	1.50	1	1.50	121.92		
4.80			23	60	30	1.30	1	1.30	142.24	142.69	
5.10			26	90	30	1.15	1	1.15	163.57		
5.40			16	60	30	1.88	1	1.88	94.96		
5.70			20	60	30	1.50	1	1.50	121.92	124.47	
6.00			25	90	30	1.20	1	1.20	156.54		
<b>OBSERVATIONS:</b>											
The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 0.00 level survey done.											
A= Number of hammer blows between readings B= Penetration accumulated after each series of blows C= Penetration accumulated after each series of blows D= Soil Consistency E= Soil Consistency F= Soil Consistency G= Comparison between CBR and DCP rate											
CAEM ISO		DATE OF CREATION OF TEST: 11/02/2015		HEAD OF LABORATORY:							
CAEM ISO		DATE OF CONCLUSION OF TEST: 11/02/2015		HEAD OF LABORATORY:							



		<b>DYNAMIC PENETRATION TESTING (DPT)</b> <b>ASTM-D-6951-03</b>		<b>NORMA</b>		REV: 00 DATE: 14/02/2015 REPORT: EDCDPS-002-14 PAG: 13 de 35			
<b>CLIENTE / Client:</b> <b>PROYECTO / Project:</b> <b>UBICACIÓN / Location:</b>		<b>CAETAMA &amp; Engenharia Internacional</b> <b>Preparatory Study Proving Project Highway Okonawa I - II and III</b> <b>Municipality Okonawa One, 2nd Section of the Province Iguaçu Warras, Santa Cruz Department</b>		<b>NORMA</b>		REV: 00 DATE: 14/02/2015 REPORT: EDCDPS-002-14 PAG: 13 de 35			
<b>PROGRESIVA:</b> 13 + 000		<b>COORDINADA:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable <b>WEIGHT OF HAMMER:</b> 8 Kg.			
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINADA:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable <b>WEIGHT OF HAMMER:</b> 8 Kg.			
<b>REGISTERS FIELD</b>		<b>TEST RESULTS</b>		<b>TEST RESULTS</b>		<b>TEST RESULTS</b>			
ELEVATION (m)	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Compaction preparation (B) (mm)	Penetration (C) (mm)	Penetration (D) (mm)	Number of Blows (E)	CUR % (G)	AVIRAGE CUR % (H)	Observations
0.00	Artificial fill, consisting of silty sand with no plasticity gravel mixtures of different measures. Scaled Type strong in-situ condition, medium brown color compactness and geogical interpretation alluvial fan	9	30	30	3.33	1	3.33	49.83	(For the first Point) Due to the characteristics of the material, the average CUR values greater than 100% on average, since that would be inconsistent data. This is because the test was conducted on an isolated in-situ stone
0.30	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	11	90	30	2.73	1	2.73	62.41	
0.60	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	30	30	6.00	1	6.00	25.81	
0.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	3	40	40	13.33	1	13.33	10.55	
1.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	90	50	10.00	1	10.00	14.56	
1.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	140	50	8.33	1	8.33	17.86	
1.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	30	30	5.00	1	5.00	31.66	
2.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	60	30	5.00	1	5.00	31.66	
2.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	100	40	5.71	1	5.71	27.26	
2.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	30	30	7.50	1	7.50	20.10	
3.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	60	30	6.00	1	6.00	25.81	
3.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	90	30	5.00	1	5.00	31.66	
3.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	50	50	12.50	1	12.50	11.34	
4.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	100	50	12.50	1	12.50	11.34	
4.60	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	150	50	10.00	1	10.00	14.56	
5.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	30	30	5.00	1	5.00	31.66	
5.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	70	40	5.71	1	5.71	27.26	
5.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	110	40	5.71	1	5.71	27.26	
6.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	100	40	8.00	1	8.00	18.70	
6.60	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	60	30	6.00	1	6.00	25.81	
7.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	100	40	8.00	1	8.00	18.70	
7.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	2	30	30	15.00	1	15.00	9.23	
7.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	60	30	7.50	1	7.50	20.10	
8.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	100	40	8.00	1	8.00	18.70	
<b>OBSERVATIONS:</b> A= Number of blows between readings B= Penetration accumulated after each series of blows C= Penetration accumulated after each series of blows D= Near to between A Axis E= Near to between A Axis F= Near to between A Axis G= Consistency between CUR and DPT tests									
<b>The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 0.00 level survey done.</b>		<b>CAEM ISO</b>		<b>CAEM ISO</b>		DATE OF CREATION OF TEST: 11/02/2015 DATE OF CONCLUSION OF TEST: 11/02/2015		<b>HEAD OF LABORATORY</b>	

		<b>DYNAMIC PENETRATION TESTING (DPT)</b> <b>ASTM-D-6951-03</b>		<b>NORMA</b>		REV: 00 DATE: 14/02/2015 REPORT: EDCDPS-002-14 PAG: 14 de 35			
<b>CLIENTE / Client:</b> <b>PROYECTO / Project:</b> <b>UBICACIÓN / Location:</b>		<b>CAETAMA &amp; Engenharia Internacional</b> <b>Preparatory Study Proving Project Highway Okonawa I - II and III</b> <b>Municipality Okonawa One, 2nd Section of the Province Iguaçu Warras, Santa Cruz Department</b>		<b>NORMA</b>		REV: 00 DATE: 14/02/2015 REPORT: EDCDPS-002-14 PAG: 14 de 35			
<b>PROGRESIVA:</b> 14 + 000		<b>COORDINADA:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable <b>WEIGHT OF HAMMER:</b> 8 Kg.			
<b>WATER TABLE:</b> 0.00 mts.		<b>COORDINADA:</b>		<b>SIDE:</b> Not Applicable		<b>TYPE OF MATERIAL:</b> Not Applicable <b>WEIGHT OF HAMMER:</b> 8 Kg.			
<b>REGISTERS FIELD</b>		<b>TEST RESULTS</b>		<b>TEST RESULTS</b>		<b>TEST RESULTS</b>			
ELEVATION (m)	VISUAL DESCRIPTION OF THE MATERIAL	Number of Blows (A)	Compaction preparation (B) (mm)	Penetration (C) (mm)	Penetration (D) (mm)	Number of Blows (E)	CUR % (G)	AVIRAGE CUR % (H)	Observations
0.00	Artificial fill, consisting of silty sand with no plasticity gravel mixtures of different measures. Scaled Type strong in-situ condition, medium brown color compactness and geogical interpretation alluvial fan	27	30	30	1.11	1	1.11	170.63	(For the first point) Because of the characteristics of these soils (Bancop) in regard to the average CUR values greater than 100%, on average, since that would be inconsistent data. This is because the test was conducted on an isolated in-situ stone
0.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	30	30	4.29	1	4.29	37.62	
0.70	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	8	130	30	3.75	1	3.75	43.69	
1.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	30	30	3.75	1	3.75	43.69	
1.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	100	40	5.71	1	5.71	27.26	
1.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	6	60	30	3.75	1	3.75	43.69	
2.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	8	140	40	5.00	1	5.00	31.66	
2.60	Clay of low plasticity, firm-situ, medium bodied, dry and brown coloration geogical interpretation alluvial fan status	10	40	40	4.00	1	4.00	30.62	
3.00	Clay of low plasticity, firm-situ, medium bodied, dry and brown coloration geogical interpretation alluvial fan status	10	80	40	4.00	1	4.00	30.62	
3.40	Clay of low plasticity, firm-situ, medium bodied, dry and brown coloration geogical interpretation alluvial fan status	10	120	40	4.00	1	4.00	30.62	
3.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	30	30	6.00	1	6.00	25.81	
4.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	7	110	40	5.71	1	5.71	27.26	
4.60	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	30	30	6.00	1	6.00	25.81	
5.00	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	60	30	6.00	1	6.00	25.81	
5.40	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	100	40	8.00	1	8.00	18.70	
5.80	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	2	30	30	15.00	1	15.00	9.23	
6.20	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	4	60	30	7.50	1	7.50	20.10	
6.60	Low plasticity clay, in-situ condition weak, partially dry soft consistency, state and browning geogical interpretation alluvial fan	5	100	40	8.00	1	8.00	18.70	
<b>OBSERVATIONS:</b> A= Number of blows between readings B= Penetration accumulated after each series of blows C= Penetration accumulated after each series of blows D= Near to between A Axis E= Near to between A Axis F= Near to between A Axis G= Consistency between CUR and DPT tests									
<b>The presence of the Water Table was not evidenced until the end of Geotechnical Study. For the study is considered the month 0.00 level survey done.</b>		<b>CAEM ISO</b>		<b>CAEM ISO</b>		DATE OF CREATION OF TEST: 11/02/2015 DATE OF CONCLUSION OF TEST: 11/02/2015		<b>HEAD OF LABORATORY</b>	





CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00				
CLIENTE / Client: KATIMBA & Engineers International		PROJECTO / Project: Preliminary Study Paving Project Highway Okinawa I - Ham III		UBICACION / Location: Municipio Okinawa One, 2nd Section of the Province Reg de Warms, Santa Cruz Department		DATE: 14/02/2015				
COORDINATED: 20 + 000		SIDE: Not Applicable		TYPE OF MATERIAL: Not Applicable		REF: EGDCTS-002-14				
WATER TABLE: 2.90 mts.		WEIGHT OF HAMMER: 8 Kg.		TEST RESULTS		PAGE: 20 de 35				
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS						
DEPTH (m)	DEPTH (ft)	Number of Blows (A)	Cumulative Penetration (mm) (B)	Penetration Between Readings (mm) (C)	Penetration Between Readings (mm) (D)	Factor of Hammer (E)	CBR (%) (F)	CBR (%) (G)	AVIAGE CBR (%) (H)	Observations
0.00	0.00	12	30	30	2.50	1	2.50	68.30	104.27	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	18	60	30	1.67	1	1.67	108.35		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	22	90	30	1.36	1	1.36	135.66		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	12	30	30	2.50	1	2.50	68.30		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	16	60	30	1.88	1	1.88	54.96		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	19	90	30	1.58	1	1.58	115.11		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	5	60	60	12.00	1	12.00	11.87		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	6	120	70	11.67	1	11.67	12.26		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	200	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	4	60	60	15.00	1	15.00	9.25		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	4	120	60	15.00	1	15.00	9.25		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	5	190	70	14.00	1	14.00	9.99		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	6	70	70	11.67	1	11.67	12.26		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	140	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	210	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	5	40	40	8.00	1	8.00	16.30		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	6	90	50	8.33	1	8.33	17.86		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	6	140	50	8.33	1	8.33	17.86		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	4	70	70	17.50	1	17.50	7.74		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	6	140	70	11.67	1	11.67	12.26		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	210	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00				
CLIENTE / Client: KATIMBA & Engineers International		PROJECTO / Project: Preliminary Study Paving Project Highway Okinawa I - Ham III		UBICACION / Location: Municipio Okinawa One, 2nd Section of the Province Reg de Warms, Santa Cruz Department		DATE: 14/02/2015				
COORDINATED: 19 + 000		SIDE: Not Applicable		TYPE OF MATERIAL: Not Applicable		REF: EGDCTS-002-14				
WATER TABLE: 2.00 mts.		WEIGHT OF HAMMER: 8 Kg.		TEST RESULTS		PAGE: 19 de 35				
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS						
DEPTH (m)	DEPTH (ft)	Number of Blows (A)	Cumulative Penetration (mm) (B)	Penetration Between Readings (mm) (C)	Penetration Between Readings (mm) (D)	Factor of Hammer (E)	CBR (%) (F)	CBR (%) (G)	AVIAGE CBR (%) (H)	Observations
0.00	0.00	7	30	30	4.29	1	4.29	37.62	41.67	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	60	30	3.75	1	3.75	43.69		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	90	30	3.75	1	3.75	43.69		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	25	30	30	1.20	1	1.20	156.64		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	33	60	30	0.91	1	0.91	213.63	201.89	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	36	90	30	0.83	1	0.83	235.50		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	30	30	4.29	1	4.29	37.62	41.67	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	60	30	3.75	1	3.75	43.69		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	90	30	3.75	1	3.75	43.69		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	30	30	7.14	1	7.14	21.23		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	100	30	6.25	1	6.25	24.66	23.51	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	150	30	6.25	1	6.25	24.66		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	70	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	140	70	10.00	1	10.00	14.56	14.56	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	210	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	50	50	7.14	1	7.14	21.23		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	100	50	7.14	1	7.14	21.23	22.37	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	150	50	6.25	1	6.25	24.66		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	60	60	8.57	1	8.57	17.31		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	120	60	8.57	1	8.57	17.31	18.24	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	180	60	7.50	1	7.50	20.10		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	7	70	70	10.00	1	10.00	14.56		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	140	70	8.75	1	8.75	16.91	16.13	(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.
0.00	0.00	8	210	70	8.75	1	8.75	16.91		(F or the second point) of the soil (Disregard CBR values greater than 100% on and the consistent data. This is because the test was conducted on an isolated in-situ state.



CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00	DATE: 14/02/2015	EGDCFS: 002-14	Page: 23 de 35
CLIENTE / Client: KATMIRA & Engineers International		PROYECTO / Project: Preparatory Study Paving Project Highway Okinawa I - Ham III		UBICACION / Location: Municipality Okinawa One, 2nd Section of the Province Regue & Warnes, Santa Cruz Department		DCP No.: 23			
PROGRESSIVE: 23 + 010		COORDINATED: 17°25'36.01" S		SIDE: Not Applicable		Not Applicable			
WATER TABLE: 0.00 mts.		TYPE OF MATERIAL: 0.00 mts.		WEIGHT OF HAMMER: 8 Kg.					
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS					
DEPTH (m)	WATER TABLE (m)	Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (B)	Penetration Between Readings (mm) (D)	Factor of Hammer (F) (E)	CBR <sub>10</sub> (%) (G)	CBR <sub>15</sub> (%) (H)	Observations
0.00	0.00	Artificial fill, consisting of clay soil with no plasticity (very low plasticity) and mixtures of different materials. Second type (single) in-situ conditions, loose brown color, compactness and geological interpretation alluvial fan.	29	30	30	1.03	184.85	208.89	(For the first point) Due to the characteristics of this type of soil, the CBR values are greater than 100%, since it would be inconsistent data. This is because the tests were conducted on an isolated in-hubers stone.
0.00	0.00	Areca Limosa without plasticity, firm condition in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan.	3	40	40	13.33	10.55	14.61	
0.00	0.00	Areca Limosa with low plasticity, firm condition in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan.	5	120	40	8.00	18.20		
0.00	0.00	Limo Clay, in-situ condition weak, partially dry soft consistency, state and brown coloration geological interpretation alluvial fan.	4	30	30	7.50	20.10	19.63	
0.00	0.00	Clayey sand, loose in-situ condition, loose compactness, partially dry and brown coloration geological interpretation alluvial fan.	4	60	30	7.50	20.10	21.54	
0.00	0.00	Clayey sand, loose in-situ condition, loose compactness, partially dry and dark brown coloration geological interpretation alluvial fan.	5	100	40	8.00	18.70	22.06	
0.00	0.00	Limo Clay, in-situ condition weak, partially dry soft consistency, state and dark brown coloration geological interpretation alluvial fan.	5	90	30	6.00	25.81		
0.00	0.00	Limo Clay, in-situ condition weak, partially dry soft consistency, state and brown coloration geological interpretation alluvial fan.	4	30	30	7.50	20.10	22.00	
0.00	0.00	Limo Clay, in-situ condition weak, partially dry soft consistency, state and brown coloration geological interpretation alluvial fan.	4	60	30	7.50	20.10	25.81	
0.00	0.00	Clayey sand, loose in-situ condition, loose compactness, partially dry and dark brown coloration geological interpretation alluvial fan.	3	70	70	23.33	5.64	6.98	
0.00	0.00	Clayey sand, loose in-situ condition, loose compactness, partially dry and dark brown coloration geological interpretation alluvial fan.	4	150	80	20.00	6.70	8.60	
OBSERVATIONS:		The presence of the Water Table was not evidenced until the end of Geotechnical Study. The study is considered the month 0.00 level survey done.							
CAEM ISO		DATE OF CREATION OF TEST: 11/02/2015		HEAD OF LABORATORY: 11/02/2015					

CAEM ISO		DYNAMIC PENETRATION TESTING (DCP) ASTM-D-6951-03		NORMA		REV: 00	DATE: 14/02/2015	EGDCFS: 002-14	Page: 24 de 35
CLIENTE / Client: KATMIRA & Engineers International		PROYECTO / Project: Preparatory Study Paving Project Highway Okinawa I - Ham III		UBICACION / Location: Municipality Okinawa One, 2nd Section of the Province Regue & Warnes, Santa Cruz Department		DCP No.: 24			
PROGRESSIVE: 24 + 000		COORDINATED: 17°26'7.28" S		SIDE: Not Applicable		Not Applicable			
WATER TABLE: 2.90 mts.		TYPE OF MATERIAL: 2.90 mts.		WEIGHT OF HAMMER: 8 Kg.					
REGISTERS FIELD		TEST RESULTS		OBSERVATIONS					
DEPTH (m)	WATER TABLE (m)	Visual Description of the Material	Number of Blows (A)	Cumulative Penetration (mm) (B)	Penetration Between Readings (mm) (D)	Factor of Hammer (F) (E)	CBR <sub>10</sub> (%) (G)	CBR <sub>15</sub> (%) (H)	Observations
0.00	0.00	Artificial fill, consisting of clay soil with no plasticity (very low plasticity) and mixtures of different materials. Second type (single) in-situ conditions, loose brown color, compactness and geological interpretation alluvial fan.	10	30	30	3.00	56.10	88.72	(For the first three points) Due to the characteristics of this type of soil, the CBR values are greater than 100%, since it would be inconsistent data. This is because the tests were conducted on an isolated in-hubers stone or consolidated dry ground.
0.00	0.00	Areca Limosa without plasticity, firm condition in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan.	10	30	30	3.00	56.10	93.19	
0.00	0.00	Areca Limosa with low plasticity, firm condition in-situ, on average compactness, partially dry and brown coloration geological interpretation alluvial fan.	12	30	30	2.50	68.80		
0.00	0.00	Limo with mixtures of very fine sand, strong in-situ soft consistency, state and brown coloration geological interpretation alluvial fan.	12	60	30	2.50	68.80	68.80	
0.00	0.00	Limo with mixtures of very fine sand, strong in-situ soft consistency, state and brown coloration geological interpretation alluvial fan.	11	80	40	3.64	3.64	42.17	
0.00	0.00	Limo with mixtures of very fine sand, clear frail condition in-situ, soft consistency, partially dry and brown coloration geological interpretation alluvial fan.	6	50	50	8.33	17.86	18.43	
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, partially dry and brown coloration geological interpretation alluvial fan.	7	110	60	8.57	17.31		
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	8	170	60	7.50	20.10		
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	4	50	50	12.50	11.33	15.69	
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	6	100	50	8.33	17.86		
0.00	0.00	Clay of low plasticity, firm-situ, medium consistency, partially saturated state and reddish brown coloration geological interpretation alluvial fan.	10	60	60	6.00	25.81	27.75	
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	11	120	60	5.45	28.72		
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	5	60	60	12.00	11.87	14.58	
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	6	120	60	10.00	14.58		
0.00	0.00	Limo with mixtures of very fine sand, weak in-situ condition, soft consistency, saturated state and reddish brown coloration geological interpretation alluvial fan.	7	180	60	8.57	17.31		
OBSERVATIONS:		The presence of the Water Table was evident at a depth of 2.90 mts. The study is considered the month 0.00 level survey done.							
CAEM ISO		DATE OF CREATION OF TEST: 11/02/2015		HEAD OF LABORATORY: 11/02/2015					















CAEM ISO LABORATORIO DE INVESTIGACIONES Y ENSAYOS		DYNAMIC PENETRATION TESTING (DPT) ASTM-D-6951-03		NORMA		REV: 00 REV: 14/02/2015 ECCDPS-002-14 Pag: 35 de 35			
CLIENTE / Client: YAMABA & Engenheiros Internacionais		PROJECTO / Project: Proprietary Study Paving Project Highway Okavango I - Ham III		DYNAMIC PENETRATION TESTING (DPT) ASTM-D-6951-03		DPT No.: 35			
UBICACION / Location: Municipality Okavango One - 2nd Section of the Province of Epangeo Warreco, Santa Cruz Department		COORDINATE: 35 + 000		TYPE OF MATERIAL: SIDE: Not Applicable		Not Applicable			
PROGRESSIVE: 35 + 000		COORDINATE: 733155,70'S		TYPE OF MATERIAL: SIDE: Not Applicable		Not Applicable			
WATER TABLE: 0,00 mts.		COORDINATE: 62°52'26,47" O		TYPE OF MATERIAL: SIDE: Not Applicable		Not Applicable			
REGISTERS FIELD									
DEPTH (m)	FREQ. OF VIBRATION (Hz)	VISUAL DESCRIPTION OF THE MATERIAL		TEST RESULTS					
		Number of Blows (A)	Cumulative Penetration (mm) (B)	Penetration Between Readings (mm) (C)	Penetration of Hammer (mm) (D)	Penetration of Hammer (mm) (E)	Penetration of Hammer (mm) (F)	AVG. CBR (%)	Observations
0,00	0,30	9	30	30	3,33	1	3,33	49,85	
		11	60	30	2,73	1	2,73	62,41	(For the second point) Due to the characteristics of the materials used, the test was conducted on an isolated laboratory site or consolidated, dry ground.
		10	90	30	3,00	1	3,00	56,10	
		12	30	30	2,50	1	2,50	68,50	
		16	60	30	1,88	1	1,88	94,56	
		20	100	40	2,00	1	2,00	88,34	
1,00									
		6	40	40	6,67	1	6,67	22,94	
		6	80	40	6,67	1	6,67	22,94	24,38
		7	120	40	5,71	1	5,71	27,26	
1,50									
		5	50	50	10,00	1	10,00	14,56	
		6	110	60	10,00	1	10,00	14,56	15,48
		7	170	60	8,57	1	8,57	17,31	
2,00									
		6	50	50	8,33	1	8,33	17,26	
		5	100	50	10,00	1	10,00	14,56	16,76
		6	150	50	8,33	1	8,33	17,26	
2,50									
		6	50	50	8,33	1	8,33	17,26	
		6	100	50	8,33	1	8,33	17,26	17,86
		6	150	50	8,33	1	8,33	17,26	
3,00									
OBSERVATIONS:									
The presence of the Water Table was not evidenced until the end of Geotechnical Study. For this step, it is considered the month 0,00 level survey date.									
CAEM ISO		DATE OF CREATION OF TEST:		13/02/2015		HEAD OF LABORATORY			
CAEM ISO		DATE OF CONCLUSION OF TEST:		13/02/2015		HEAD OF LABORATORY			


材料試験結果


P


														REV: 00				
														REPORT: 308-14				
														DATE: 20/01/2015				
<b>Client:</b> KATAHIRA & Engineers International. <b>Project:</b> Preparatory Study of the Okinawa I - II and III Road Paving Project <b>Location:</b> Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progresivas Progressive	HUMEDAD NATURAL	GRANULOMETRIA				LIMITES DE ATTERBERG			CLASIFICACION A.A.S.H.T.O.	CLASIFICACION S.U.S.C.	Proctor T-180 MOD grs/cm <sup>3</sup>	HUMEDAD OPTIMA	% DE C.B.R. P/ 0.10 PENETRATION			OSERVACIONES
			Nat. Moisture	4	10	40	200	L.L.	L.P.	I.P.				Opt. Moisture	95%	100%		
01	01	BANCO 1	6.68%	100.00	99.91	99.31	55.15	0.00%	0.00%	N.P.	A-4 (0)	ML	2.097	7.75%	24.48	34.99		Material Natural
02	02	BANCO 1	3.56%	100.00	99.91	99.50	55.76	0.00%	0.00%	N.P.	A-4 (0)	ML	2.099	7.75%	25.64	36.94		Material Natural
03	01	BANCO 1	3.22%	100.00	99.69	98.51	51.45	0.00%	0.00%	N.P.	A-4 (0)	ML	2.029	8.79%	34.74	47.27		Mezcla con Cal al 4%
04	02	BANCO 1	3.07%	100.00	99.95	97.79	56.43	0.00%	0.00%	N.P.	A-4 (0)	ML	2.043	8.70%	37.65	48.78		Mezcla con Cal al 4%
05	01	BANCO 1	2.83%	100.00	99.79	99.13	54.51	0.00%	0.00%	N.P.	A-4 (0)	ML	2.016	8.62%	45.94	57.27		Mezcla con Cal al 6%
06	02	BANCO 1	2.72%	100.00	99.88	99.33	55.81	0.00%	0.00%	N.P.	A-4 (0)	ML	2.035	8.51%	41.22	55.88		Mezcla con Cal al 6%
07	01	BANCO 1	2.73%	100.00	99.88	98.94	58.77	0.00%	0.00%	N.P.	A-4 (0)	ML	2.009	8.69%	40.56	49.29		Mezcla con Cal al 8%
08	02	BANCO 1	2.72%	100.00	99.75	99.27	58.40	0.00%	0.00%	N.P.	A-4 (0)	ML	2.010	8.46%	34.12	46.82		Mezcla con Cal al 8%
09	01	BANCO 1	3.28%	100.00	99.78	99.35	56.38	0.00%	0.00%	N.P.	A-4 (0)	ML	2.102	8.60%	74.77	92.81		Mezcla con Cemento al 4%
10	02	BANCO 1	2.89%	100.00	99.90	99.39	56.85	0.00%	0.00%	N.P.	A-4 (0)	ML	2.098	8.47%	66.73	90.20		Mezcla con Cemento al 4%
11	01	BANCO 1	2.87%	100.00	99.95	99.34	56.08	0.00%	0.00%	N.P.	A-4 (0)	ML	2.057	8.66%	70.36	92.30		Mezcla con Cemento al 6%
12	02	BANCO 1	3.26%	100.00	99.90	99.90	56.43	0.00%	0.00%	N.P.	A-4 (0)	ML	2.065	8.86%	69.89	90.54		Mezcla con Cemento al 6%
13	01	BANCO 1	4.14%	100.00	99.84	99.41	59.56	0.00%	0.00%	N.P.	A-4 (0)	ML	2.104	9.54%	57.88	80.63		Mezcla con Cemento al 8%
14	02	BANCO 1	2.70%	100.00	99.88	99.38	57.52	0.00%	0.00%	N.P.	A-4 (0)	ML	2.123	9.73%	67.83	83.08		Mezcla con Cemento al 8%


P

														REV: 00				
														REPORT: 308-14				
														DATE: 14/01/2015				
<b>Client:</b> KATAHIRA & Engineers International. <b>Project:</b> Preparatory Study of the Okinawa I - II and III Road Paving Project <b>Location:</b> Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progresivas Progressive	HUMEDAD NATURAL	GRANULOMETRIA				LIMITES DE ATTERBERG			CLASIFICACION A.A.S.H.T.O.	CLASIFICACION S.U.S.C.	Proctor T-180 MOD grs/cm <sup>3</sup>	HUMEDAD OPTIMA	% DE C.B.R. P/ 0.10 PENETRATION			OSERVACIONES
			Nat. Moisture	4	10	40	200	L.L.	L.P.	I.P.				Opt. Moisture	95%	100%		
01	01	BANCO 2	4.97%	100.00	100.00	99.45	38.17	0.00%	0.00%	N.P.	A-4 (0)	SM	1.941	9.46%	18.86	25.45		Material Natural
02	02	BANCO 2	4.80%	100.00	100.00	99.67	38.60	0.00%	0.00%	N.P.	A-4 (0)	SM	1.977	8.60%	21.07	26.42		Material Natural
03	01	BANCO 2	4.93%	100.00	99.69	98.51	41.54	0.00%	0.00%	N.P.	A-4 (0)	SM	1.982	8.44%	29.73	39.17		Mezcla con Cal al 4%
04	02	BANCO 2	4.56%	100.00	100.00	99.64	41.79	0.00%	0.00%	N.P.	A-4 (0)	SM	1.975	8.38%	26.98	36.15		Mezcla con Cal al 4%
05	01	BANCO 2	4.32%	100.00	100.00	99.46	41.65	0.00%	0.00%	N.P.	A-4 (0)	SM	1.968	8.36%	38.52	50.14		Mezcla con Cal al 6%
06	02	BANCO 2	5.14%	100.00	100.00	99.16	40.26	0.00%	0.00%	N.P.	A-4 (0)	SM	1.933	8.36%	34.69	47.12		Mezcla con Cal al 6%
07	01	BANCO 2	4.73%	100.00	100.00	99.63	70.52	0.00%	0.00%	N.P.	A-4 (0)	SM	1.953	7.76%	29.37	38.99		Mezcla con Cal al 8%
08	02	BANCO 2	4.07%	100.00	100.00	98.22	38.92	0.00%	0.00%	N.P.	A-4 (0)	SM	1.964	7.48%	27.72	35.50		Mezcla con Cal al 8%
09	01	BANCO 2	4.75%	100.00	100.00	98.90	39.69	0.00%	0.00%	N.P.	A-4 (0)	SM	2.068	8.70%	38.86	52.58		Mezcla con Cemento al 4%
10	02	BANCO 2	5.33%	100.00	100.00	99.24	39.21	0.00%	0.00%	N.P.	A-4 (0)	SM	2.018	7.96%	37.61	48.57		Mezcla con Cemento al 4%
11	01	BANCO 2	4.95%	100.00	100.00	95.88	39.77	0.00%	0.00%	N.P.	A-4 (0)	SM	2.065	8.86%	48.00	65.07		Mezcla con Cemento al 6%
12	02	BANCO 2	4.43%	100.00	100.00	98.52	40.98	0.00%	0.00%	N.P.	A-4 (0)	SM	2.034	9.02%	43.11	58.85		Mezcla con Cemento al 6%
13	01	BANCO 2	5.08%	100.00	100.00	99.29	39.37	0.00%	0.00%	N.P.	A-4 (0)	SM	2.062	8.78%	62.86	79.42		Mezcla con Cemento al 8%
14	02	BANCO 2	4.02%	100.00	100.00	99.33	40.27	0.00%	0.00%	N.P.	A-4 (0)	SM	2.042	8.53%	51.40	70.73		Mezcla con Cemento al 8%

														REV: 00 REPORT: 308-14 DATE: 26/01/2015				
Client: KATAHIRA & Engineers International.      Project: Preparatory Study of the Okinawa I - II and III Road Paving Project Location: Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progressivas	HUMEDAD NATURAL	GRANULOMETRIA				LIMITES DE ATTERBERG			CLASIFICACION A.A.S.H.T.O.	CLASIFICACION S.U.S.C.	Proctor T-180 MOD. grs/cm3	HUMEDAD OPTIMA	% DE C B R P/ 0.10° PENETRATION			OSERVACIONES
				Grading				L.L.	L.P.	I.P.					Moisture			
		Progressive	Moisture	4	10	40	200											Observations
01	01	BANCO 3	5.39%	100.00	100.00	99.33	26.58	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.985	9.47%	22.48	32.71		Material Natural
02	02	BANCO 3	5.04%	100.00	100.00	99.40	24.02	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.974	9.13%	23.62	32.19		Material Natural
03	01	BANCO 3	1.25%	100.00	99.69	98.51	27.04	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.012	8.86%	22.49	33.70		Mezcla con Cal al 4%
04	02	BANCO 3	1.11%	100.00	100.00	99.39	27.46	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.021	8.57%	23.97	32.70		Mezcla con Cal al 4%
05	01	BANCO 3	1.10%	100.00	99.96	99.34	30.19	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.049	8.62%	32.32	39.79		Mezcla con Cal al 6%
06	02	BANCO 3	1.14%	100.00	99.91	99.35	30.66	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.058	8.51%	31.91	38.48		Mezcla con Cal al 6%
07	01	BANCO 3	2.02%	100.00	100.00	99.39	30.96	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.038	8.69%	24.36	33.15		Mezcla con Cal al 8%
08	02	BANCO 3	2.29%	100.00	100.00	99.38	29.98	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.045	8.55%	23.72	32.30		Mezcla con Cal al 8%
09	01	BANCO 3	1.53%	100.00	99.80	99.06	26.51	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.966	9.39%	44.12	56.86		Mezcla con Cemento al 4%
10	02	BANCO 3	2.05%	100.00	100.00	99.13	32.61	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.975	9.42%	46.88	53.94		Mezcla con Cemento al 4%
11	01	BANCO 3	1.15%	100.00	100.00	99.34	30.93	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.981	8.97%	47.20	62.99		Mezcla con Cemento al 6%
12	02	BANCO 3	1.33%	100.00	100.00	98.93	30.73	0.00%	0.00%	N.P.	A-2-4 (0)	SM	1.975	9.14%	53.84	65.42		Mezcla con Cemento al 6%
13	01	BANCO 3	1.21%	100.00	100.00	99.30	33.15	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.041	8.99%	57.62	73.02		Mezcla con Cemento al 8%
14	02	BANCO 3	1.19%	100.00	100.00	99.30	33.30	0.00%	0.00%	N.P.	A-2-4 (0)	SM	2.031	9.03%	59.60	74.88		Mezcla con Cemento al 8%

														REV: 00 REPORT: 308-14 DATE: 08/01/2015				
Client: KATAHIRA & Engineers International.      Project: Preparatory Study of the Okinawa I - II and III Road Paving Project Location: Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progressivas	HUMEDAD NATURAL	GRANULOMETRIA				LIMITES DE ATTERBERG			CLASIFICACION A.A.S.H.T.O.	CLASIFICACION S.U.S.C.	Proctor T-180 MOD. grs/cm3	HUMEDAD OPTIMA	% DE C B R P/ 0.10° PENETRATION			OSERVACIONES
				Grading				L.L.	L.P.	I.P.					Moisture			
		Progressive	Moisture	4	10	40	200											Observations
01	01	1+000	11.19%	100.00	100.00	99.38	97.03	21.75%	0.00%	N.P.	A-4 (8)	ML	1.876	13.16%	1.34	2.66		Material Natural
02	02	1+000	11.20%	100.00	100.00	99.14	96.82	21.51%	0.00%	N.P.	A-4 (8)	ML	1.886	13.00%	1.32	2.49		Material Natural
03	01	1+000	12.16%	100.00	99.69	98.51	96.74	28.98%	0.00%	N.P.	A-4 (8)	ML	1.847	14.74%	14.08	26.48		Mezcla con Cal al 4%
04	02	1+000	12.56%	100.00	99.95	99.22	97.18	28.43%	0.00%	N.P.	A-4 (8)	ML	1.848	14.53%	13.86	26.16		Mezcla con Cal al 4%
05	01	1+000	13.84%	100.00	99.93	99.21	96.35	29.15%	0.00%	N.P.	A-4 (8)	ML	1.825	15.77%	17.46	32.31		Mezcla con Cal al 6%
06	02	1+000	12.91%	100.00	99.84	99.23	96.30	29.81%	0.00%	N.P.	A-4 (8)	ML	1.817	14.71%	16.75	31.80		Mezcla con Cal al 6%
07	01	1+000	11.74%	100.00	99.90	99.06	95.72	29.95%	0.00%	N.P.	A-4 (8)	ML	1.796	15.94%	18.89	35.21		Mezcla con Cal al 8%
08	02	1+000	11.45%	100.00	99.59	98.04	95.52	31.04%	0.00%	N.P.	A-4 (8)	ML	1.795	16.08%	18.41	33.21		Mezcla con Cal al 8%
09	01	1+000	14.35%	100.00	99.86	99.37	97.09	25.12%	0.00%	N.P.	A-4 (8)	ML	1.783	15.62%	19.82	30.36		Mezcla con Cemento al 4%
10	02	1+000	14.65%	100.00	99.92	99.25	96.61	24.27%	0.00%	N.P.	A-4 (8)	ML	1.784	14.96%	21.39	31.73		Mezcla con Cemento al 4%
11	01	1+000	13.85%	100.00	99.89	99.33	96.96	25.31%	0.00%	N.P.	A-4 (8)	ML	1.801	15.82%	22.83	36.59		Mezcla con Cemento al 6%
12	02	1+000	14.44%	100.00	99.90	99.34	96.92	25.89%	0.00%	N.P.	A-4 (8)	ML	1.781	16.28%	20.30	35.38		Mezcla con Cemento al 6%
13	01	1+000	14.51%	100.00	99.95	99.02	96.37	25.99%	0.00%	N.P.	A-4 (8)	ML	1.800	15.35%	29.24	41.24		Mezcla con Cemento al 8%
14	02	1+000	13.99%	100.00	99.88	99.28	97.28	24.76%	0.00%	N.P.	A-4 (8)	ML	1.802	15.28%	29.15	41.32		Mezcla con Cemento al 8%

															REV: 00 REPORT: 308-14 DATE: 08/01/2015			
<b>Client:</b> KATAHIRA & Engineers International. <b>Project:</b> Preparatory Study of the Okinawa I - II and III Road Paving Project <b>Location:</b> Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progresivas Progressive	HUMEDAD NATURAL	GRANULOMETRIA Grading				LIMITES DE ATTERBERG Atterberg Limits			CLASIFICACION Classification A.A.S.H.T.O.	CLASIFICACION Classification S.U.S.C.	Proctor T-180 MOD. grs/cm3	HUMEDAD OPTIMA	% DE C.B.R. P 0.10*PENETRATION			OSERVACIONES Observations
			Moisture	4	10	40	200	L.L.	L.P.	I.P.				Moisture	95%	100%		
01	01	11+200	7.05%	100.00	99.77	98.81	93.21	49.94%	24.53%	25.41%	A-7-6 (17)	CL	1.783	17.35%	0.97	1.96		Material Natural
02	02	11+200	10.24%	100.00	99.54	98.67	93.22	48.88%	23.86%	25.02%	A-7-6 (16)	CL	1.724	17.48%	1.36	1.95		Material Natural
03	01	11+200	9.54%	100.00	99.95	99.17	93.97	48.24%	0.00%	N.P.	A-5 (10)	ML	1.752	19.06%	5.67	9.76		Mezcla con Cal al 4%
04	02	11+200	9.53%	100.00	99.88	99.26	93.72	47.24%	0.00%	N.P.	A-5 (10)	ML	1.755	18.97%	5.83	9.62		Mezcla con Cal al 4%
05	01	11+200	16.33%	100.00	99.95	98.98	93.33	45.82%	0.00%	N.P.	A-5 (10)	ML	1.739	20.02%	8.63	14.46		Mezcla con Cal al 6%
06	02	11+200	16.86%	100.00	99.89	99.07	93.83	45.36%	0.00%	N.P.	A-5 (10)	ML	1.738	19.49%	7.13	13.05		Mezcla con Cal al 6%
07	01	11+200	8.57%	100.00	99.84	98.97	93.88	42.74%	0.00%	N.P.	A-5 (9)	ML	1.725	19.25%	9.32	18.01		Mezcla con Cal al 8%
08	02	11+200	8.31%	100.00	99.88	98.62	93.83	42.33%	0.00%	N.P.	A-5 (9)	ML	1.729	19.35%	9.79	19.17		Mezcla con Cal al 8%
09	01	11+200	9.92%	100.00	99.94	99.02	93.71	36.64%	19.58%	17.06%	A-6 (11)	CL	1.752	17.50%	4.26	6.47		Mezcla con Cemento al 4%
10	02	11+200	9.73%	100.00	99.78	98.97	93.58	37.38%	20.48%	16.90%	A-6 (11)	CL	1.750	17.43%	3.97	6.06		Mezcla con Cemento al 4%
11	01	11+200	9.64%	100.00	99.86	99.02	93.54	35.76%	22.47%	13.29%	A-6 (10)	CL	1.750	16.75%	7.35	10.03		Mezcla con Cemento al 6%
12	02	11+200	9.96%	100.00	99.93	99.34	94.86	34.50%	21.50%	13.00%	A-6 (10)	CL	1.754	16.41%	7.00	10.04		Mezcla con Cemento al 6%
13	01	11+200	9.12%	100.00	99.85	99.09	93.92	39.41%	24.21%	15.20%	A-6 (11)	CL	1.750	16.93%	9.83	16.00		Mezcla con Cemento al 8%
14	02	11+200	9.03%	100.00	99.89	99.03	94.18	39.79%	24.21%	15.58%	A-6 (11)	CL	1.759	17.15%	10.72	17.03		Mezcla con Cemento al 8%

															REV: 00 REPORT: 308-14 DATE: 17/01/2015			
<b>Client:</b> KATAHIRA & Engineers International. <b>Project:</b> Preparatory Study of the Okinawa I - II and III Road Paving Project <b>Location:</b> Municipality of Okinawa I - II, 2° Section, Warnes Province, Northern Region of Santa Cruz de la Sierra City																		
N° POLL	N° SAMPLES	Progresivas Progressive	HUMEDAD NATURAL	GRANULOMETRIA Grading				LIMITES DE ATTERBERG Atterberg Limits			CLASIFICACION Classification A.A.S.H.T.O.	CLASIFICACION Classification S.U.S.C.	Proctor T-180 MOD. grs/cm3	HUMEDAD OPTIMA	% DE C.B.R. P 0.10*PENETRATION			OSERVACIONES Observations
			Moisture	4	10	40	200	L.L.	L.P.	I.P.				Moisture	95%	100%		
01	01	28+000	11.35%	100.00	99.86	98.26	93.31	50.79%	24.91%	25.89%	A-7-6 (17)	CH	1.734	15.40%	1.23	1.62		Material Natural
02	01	28+000	11.19%	100.00	100.00	99.38	97.03	47.50%	23.79%	23.71%	A-7-6 (15)	CL	1.749	15.60%	0.94	1.20		Material Natural
03	01	28+000	10.47%	100.00	99.69	98.51	94.61	36.38%	0.00%	N.P.	A-4 (8)	ML	1.748	16.66%	3.02	3.76		Mezcla con Cal al 4%
04	02	28+000	10.83%	100.00	99.83	98.88	95.92	29.56%	0.00%	N.P.	A-4 (8)	ML	1.757	17.22%	3.09	3.88		Mezcla con Cal al 4%
05	01	28+000	9.81%	100.00	99.90	98.97	94.48	34.66%	0.00%	N.P.	A-4 (8)	ML	1.719	16.37%	4.53	6.04		Mezcla con Cal al 6%
06	02	28+000	13.10%	100.00	99.81	98.84	95.16	37.30%	0.00%	N.P.	A-4 (8)	ML	1.721	17.42%	4.13	5.68		Mezcla con Cal al 6%
07	01	28+000	10.08%	100.00	99.80	98.76	94.25	30.15%	0.00%	N.P.	A-4 (8)	ML	1.720	15.90%	5.83	7.86		Mezcla con Cal al 8%
08	02	28+000	10.81%	100.00	99.92	99.30	94.37	30.92%	0.00%	N.P.	A-4 (8)	ML	1.731	15.76%	5.65	7.46		Mezcla con Cal al 8%
09	01	28+100	10.86%	100.00	99.93	98.80	93.84	46.06%	24.54%	21.52%	A-7-6 (14)	CL	1.797	17.99%	6.26	8.04		Mezcla con Cemento al 4%
10	02	28+000	14.65%	100.00	99.92	99.25	96.61	45.93%	24.45%	21.48%	A-7-6 (14)	CL	1.792	17.53%	6.34	8.07		Mezcla con Cemento al 4%
11	01	28+000	10.02%	100.00	99.85	99.38	97.16	46.77%	25.56%	21.21%	A-7-6 (14)	CL	1.802	17.08%	7.02	9.37		Mezcla con Cemento al 6%
12	02	28+000	11.95%	100.00	99.93	98.91	95.24	42.88%	24.57%	18.31%	A-7-6 (12)	CL	1.807	17.49%	6.01	7.64		Mezcla con Cemento al 6%
13	01	28+000	11.32%	100.00	99.93	98.72	93.68	41.75%	24.36%	17.39%	A-7-6 (12)	CL	1.792	18.89%	11.66	14.72		Mezcla con Cemento al 8%
14	02	28+000	10.18%	100.00	99.84	98.71	94.73	38.16%	22.82%	15.34%	A-6 (11)	CL	1.752	18.58%	11.46	14.01		Mezcla con Cemento al 8%